



**UNIVERSITI PUTRA MALAYSIA**

**THERMAL DIFFUSIVITY of SMALL VOLUME LIQUIDS USING A  
CONVERGING THERMAL WAVE TECHNIQUE**

**SEPIDEH SOLTANINEJAD**

**FS 2013 28**



**THERMAL DIFFUSIVITY OF SMALL VOLUME LIQUIDS USING A  
CONVERGING THERMAL WAVE TECHNIQUE**

**By**

**SEPIDEH SOLTANINEJAD**

**Thesis submitted to the School of Graduates Studies, Universiti Putra Malaysia, in  
Fulfillment of the Requirement for the Degree of Doctor of Philosophy**

**May 2013**


## **COPYRIGHT**

All material contained within the thesis, including without limitation text, logos, icons, photographs, and all other artwork, is copyright material of Universiti Putra Malaysia unless otherwise stated. Use may be made of any material contained within the thesis for non-commercial purposes from the copyright holder. Commercial use of material may only be made with the express, prior, written permission of Universiti Putra Malaysia.

Copyright© Universiti Putra Malaysia



## DEDICATION

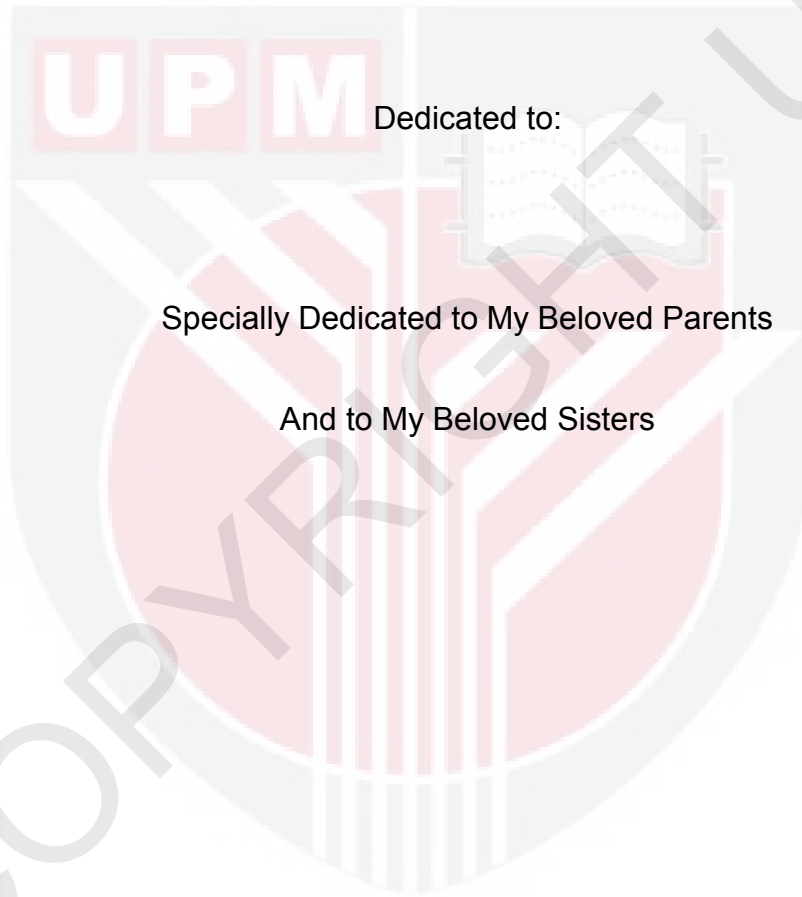

Dedicated to:

Specially Dedicated to My Beloved Parents

And to My Beloved Sisters



Abstract of thesis presented to the Senate of Universiti Putra Malaysia in fulfillment of the requirement for the degree of Doctor of Philosophy

**THERMAL DIFFUSIVITY OF SMALL VOLUME LIQUIDS USING A  
CONVERGING THERMAL WAVE TECHNIQUE**

By

**SEPIDEH SOLTANINEJAD**

**May 2013**

**Chairman: Mohd Maarof H.A. Moxin, PhD**

**Faculty: Science**

Thermal diffusivity of transparent and large volume liquids has been measured accurately by using pump-probe techniques like thermal lens and hot wire. Therefore, this technique would be rendered useless in the case of opaque and small volume liquids. The probe beam would have very weak transmission in the opaque liquids while small volume liquids would not give an appreciable beam deflection to measure. Since there is always a limited amount of precious liquids for evaluation, it is crucial to have a measuring technique dedicated for small volume transparent and opaque liquids.

Such a technique was designed and developed based on a conventional photoflash technique but with an elaborate sample container, which was a small crucible with a thin copper foil base of diameter 10 mm. The liquid filled up about 1 mm height in the crucible during measurement. Thermal waves were induced into the liquid by irradiating the bottom of the container with a camera flash. The heat was generated at the copper base bottom surface subsequent to the radiation absorption before being defused through the base and liquid sample. The temporal temperature of the sample was measured by placing a thermocouple at an appropriate distance in the liquid. The thermal diffusivity was determined by fitting the theoretical temperature to the experimental data.

The theoretical temperature was developed based on the hypothesis that the temperature at the point of detection is a product of heat diffusion in the axial and radial directions that depends on the thickness and thermal properties of the bilayer of solid and liquid as well as on the method of heat generation and detection.

The whole set up was calibrated by using distilled water. The thermal diffusivity of the distilled water was  $1.442 \times 10^{-7} \text{ m}^2\text{s}^{-1}$  which was obtained by fitting the theoretical temperature to the experimental data with R-square value of greater than 0.99. Other work has reported values in the range of  $(1.440 - 1.447) \times 10^{-7} \text{ m}^2\text{s}^{-1}$ .

The technique has been used to measure thermal diffusivity of nano-fluids of zinc sulfide, silver, gold and copper nanoparticles suspension in water, and palm oil biodiesel blends. The metal nano-fluids were prepared by using laser ablation while ZnS nano fluid was prepared by using microwave method.

The thermal diffusivity of the silver nano-fluids at room temperature increased in the range of  $(1.68 - 1.87) \times 10^{-7} \text{ m}^2\text{s}^{-1}$  with volume fraction concentration in the range of 0.10 mg/L to 4.168 mg/L closely matching the results obtained by using thermal lens. The same trend of thermal diffusivity increase with concentration of nanoparticles was also found in the other nano-fluids.

The thermal diffusivity of palm-oil-biodiesel blends of B10, B20, B30, B70, and B80 was found in the range of  $(1.32 - 0.8) \times 10^{-7} \text{ m}^2\text{s}^{-1}$ . Addition of more than 20% biodiesel had no drastic effect in lowering the thermal diffusivity that might help in reducing the fuel volatility due to the increase of the blend flash point.

Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia  
sebagai memenuhi keperluan untuk ijazah Doktor Falsafah

**PENGUKURAN KEMERESAPAN TERMA BAGI CECAIR ISIPADU KECIL  
DENGAN MENGGUNAKAN TEKNIK BARU GELOMBANG TERMA  
MENUMPU**

Oleh

**SEPIDEH SOLTANINEJAD**

**Mei 2013**

**Pengerusi: Prof. Mohd Maarof H.A Moxin, PhD**

**Fakulti: Sains**

Tahap kemeresapan terma bagi cecair telus dan berkapasiti besar telah diukur dengan tepat menggunakan teknik 'pump-probe' seperti kanta terma dan dawai panas. Oleh yang sedemikian, teknik ini tidak memberikan apa-apa kesan dalam kes cecair berkapasiti kecil dan legap. Sinaran alat penguji akan menghasilkan transmisi yang sangat lemah dalam cecair legap manakala cecair berkapasiti kecil tidak akan memberikan pesongan sinaran yang cukup untuk diukur. Oleh kerana hanya ada jumlah terhad bagi cecair berharga untuk penilaian, adalah amat penting untuk mempunyai satu teknik pengukuran yang didedikasikan hanya untuk cecair berkapasiti kecil dan legap.



Teknik ini telah direka dan dibangunkan berdasarkan kepada teknik konvensional photoflash tetapi dengan bekas sampel yang teliti iaitu satu pijar kecil dilengkapi dengan tapak kerajang tembaga nipis berdiameter 10 mm. Cecair berkenaan akan diisi sebanyak 1 mm tinggi dalam pijar tersebut semasa proses pengukuran. Gelombang terma diresapkan kepada cecair berkenaan dengan mendedahkan bahagian bawah bekas kepada flash kamera. Haba dijanakan pada tapak tembaga bahagian bawah selepas penyerapan radiasi sebelum disebarluaskan menerusi tapak dan cecair sampel. Suhu semasa sampel telah diukur dengan meletakkan thermocouple pada jarak yang bersesuaian di dalam cecair tersebut. Tahap pemerapasan terma telah ditentukan dengan membandingkan suhu teori kepada data eksperimen.

Suhu teori telah dibangunkan berdasarkan kepada hipotesis dimana suhu pada titik pengesanan adalah satu produk penyebaran haba dalam arah paksi dan jejari yang bergantung kepada ketebalan dan sifat haba dua lapisan pepejal dan cecair serta ke atas kaedah pengesanan dan penjanaan haba.

Seluruh system pengukuran ini telah ditentukur dengan menggunakan air suling. Tahap pemerapasan terma bagi air suling adalah  $1.442 \times 10^{-7} \text{ m}^2\text{s}^{-1}$ , yang mana telah diperolehi dengan memadankan suhu teori kepada data eksperimen dengan nilai R-square lebih besar daripada 0.99. Kajian-kajian lain telah melaporkan nilai-nilai di antara julat  $(1.440 - 1.447) \times 10^{-7} \text{ m}^2\text{s}^{-1}$ .

Teknik ini telah digunakan untuk mengukur tahap pemeerasapan terma bagi nanofluids daripada zink sulfida, perak, emas, dan nanopartikel tembaga terapung dalam air dan juga campuran biodiesel minyak sawit. Nanofluid-nanofluid daripada logam telah disediakan dengan menggunakan proses ablasi laser manakala ZnS nanofluids disediakan dengan menggunakan kaedah gelombang mikro.

Tahap pemeerasapan terma bagi nanofluid-nanofluid perak pada suhu bilik telah meningkat dalam julat  $(1.68 - 1.87) \times 10^{-7} \text{ m}^2\text{s}^{-1}$  dengan jumlah kepekatan dalam julat antara 0.10 mg/L kepada 4.168 mg/L menghampiri hasil yang telah diperolehi dengan menggunakan kanta terma. Trend peningkatan yang sama bagi tahap pemeerasapan haba dengan pecahan nanopartikel juga telah ditemui dalam nanofluid-nanofluid yang lain.

Tahap pemeerasapan terma bagi campuran biodiesel minyak sawit B10, B20, B30, B70, dan B80 telah ditemui dalam julat  $(1.32 - 0.8) \times 10^{-7} \text{ m}^2\text{s}^{-1}$ . Penambahan lebih daripada 20% biodiesel tidak memberikan kesan yang drastik dalam menurunkan tahap pemeerasapan terma yang mungkin dapat menolong dalam mengurangkan tahap kemeruapan minyak yang disebabkan kepada peningkatan titik flash campuran .

## ACKNOWLEDGEMENTS

The realization of this work was only possible due to the several people's collaboration, to which I desire to express my gratefulness. First and foremost I offer my great pleasure to acknowledge my supervisor, Prof. Dr. Mohd. Maarof H.A. Moxsin, who has supported me throughout my thesis. His support and encouragement were without a doubt crucial to fulfill this thesis. I would like to express my sincere gratitude to my co-supervisors, Prof. Dr. W. Mahmood Mat Yunus and Prof. Dr. Azmi Zakaria for their useful advice and help during the period of my study.

I would like to thank all the staff in physics department, UPM for their co-operation given to me throughout my work especially Mr. Mohd. Shahril Husin for his help as co-worker and lab mate. My sincere thanks go to all my friends especially Dr. Monir noroozi for all her support and kindness. I am also grateful to Dr. Mohammad Gholizadeh for his advice and helpful Guidance to make this work possible. I also must express my appreciation to my friend Dr. Neda Saeipour for her enthusiasm and encouragement.

My most special gratitude goes to my parents for the motivation demonstrated along this arduous course and my sisters with their families who have supported me throughout this research, without their encouragement, understanding and support it would have been impossible for me to finish this work.

This thesis was submitted to the Senate of Universiti Putra Malaysia and has been accepted as fulfillment of the requirement for the degree of Doctor of Philosophy. The members of Supervisory committee were as follows:

**Mohd Maarof H.A. Moxsin, PhD**

Professor  
Faculty of Science  
Universiti Putra Malaysia  
(Chairman)

**W. Mahmood Mat Yunus, PhD**

Professor  
Faculty of Science  
Universiti Putra Malaysia  
(Member)

**Azmi Zakaria, PhD**

Professor  
Faculty of Science  
Universiti Putra Malaysia  
(Member)

---


**BUJANG BIN KIM HUAT, PhD**

Professor and Dean  
School of Graduate Studies  
Universiti Putra Malaysia

Date: 2 AUGUST 2013

## DECLARATION

I declare that the thesis is my original work except for quotations and citations which have been duly acknowledged. I also declare that it has not been previously, and is not concurrently, submitted for any other degree at Universiti Putra Malaysia or at any other institutions.

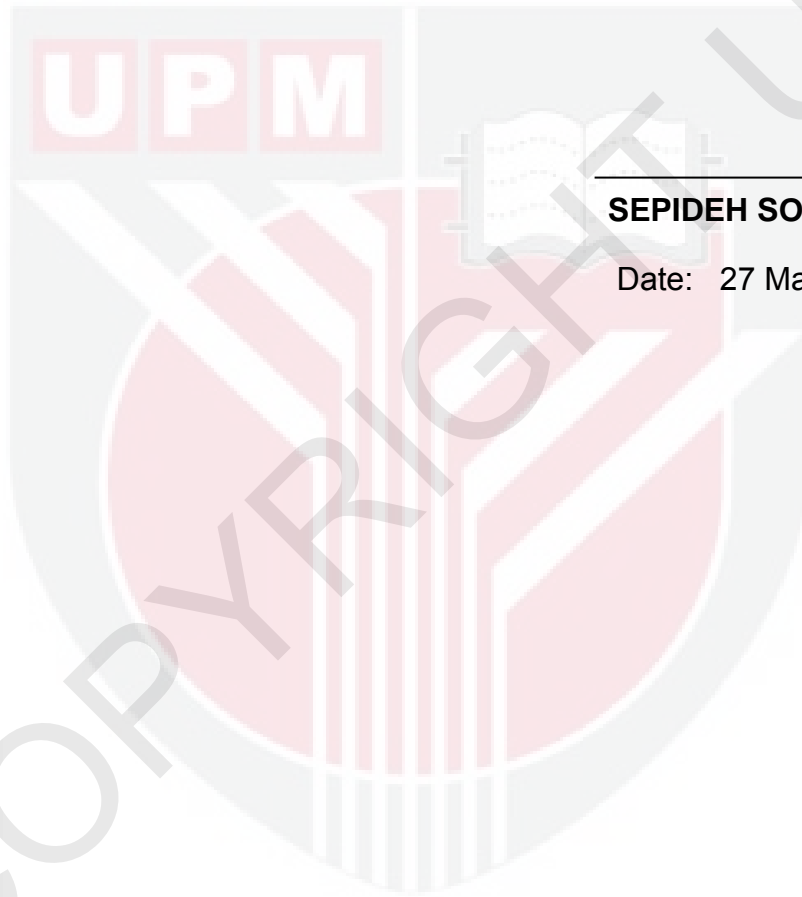

---

**SEPIDEH SOLTANINEJAD**

Date: 27 May 2013

## TABLE OF CONTENTS

	<b>Page</b>
<b>ABSTRACT</b>	ii
<b>ABSTRAK</b>	v
<b>ACKNOWLEDGEMENTS</b>	viii
<b>APPROVAL</b>	ix
<b>DECLARATION</b>	xi
<b>LIST OF TABLES</b>	xvi
<b>LIST OF FIGURES</b>	xvii
<b>LIST OF ABBREVIATIONS</b>	xxi
<b>CHAPTER</b>	
<b>1 INTRODUCTION</b>	
1.1 Introduction	1
1.2 Background and Motivation	1
1.3 Research Problem	3
1.4 Significance of the Study	5
1.5 Objective of the Study	5
1.6 Organization of the Thesis	6
<b>2 LITERATURE REVIEW</b>	7
2.1 Introduction	7
2.2 Thermal Diffusivity in Liquids	8
2.3 Photo-Thermal Technique Application In Liquids	10
2.3.1 Advantages of Photo-Thermal Technique for Measuring Thermal Diffusivity in Fluids	11
2.3.2 Photo-Thermal Methods for Measurement of Thermal Diffusivity of Liquids	13

2.4	Other Techniques for Determining Thermal Diffusivity in Liquids	16
2.5	Thermal Properties of Nano-fluids	26
2.6	The Materials and Synthesis Types Used for Measuring Thermal Diffusivity	27
2.6.1	Nonlinear liquids Materials and Metal Nanoparticles in Fluids	27
2.6.2	Synthesis of Nanoparticles	28
2.7	Effects of Beam Focusing	31
2.7.1	Source of Signal	31
2.8	Signal Detector	32
2.8.1	Direct Detection Methods	33
2.8.2	Indirect Detection Methods	34
2.9	Background of Thermal Wave Expression Theory	35
2.9.1	Axial Measurement	35
2.9.2	Radial Measurement	36
2.9.3	Converging Thermal Wave (CTW) Measurement	39
2.9.4	Parameter Estimation in Converging Thermal Wave (CTW) Application	43
<b>3</b>	<b>THEORY</b>	<b>44</b>
3.1	Introduction	44
3.2	Converging of a Large Number of a Concentric Heat Rings	46
3.3	Axial Heat Flow in Bilayers Sample	49
3.4	Theoretical Temperature in the Liquid Layer	56

<b>4</b>	<b>METHODOLOGY</b>	<b>58</b>
4.1	Introduction	58
4.2	Photo Flash Technique	58
4.2.1	Reduction of Noise	60
4.3	Liquid Sample Holder	61
4.4	Sample Preparation and Characterization	62
4.4.1	Nano-fluids	62
4.4.2	Zinc-sulfide	64
4.4.3	Palm Oil Biodiesel Blend	66
<b>5</b>	<b>RESULTS AND DISCUSSION</b>	<b>67</b>
5.1	Theoretical Model Simulation	67
5.2	Calibration Measurement	70
5.3	Silver Nano fluids of Ag-NPs in Distilled Water	72
5.3.1	Characterization	72
5.3.2	Thermal Diffusivity	75
5.4	Copper Nano fluids of Cu-NPs in distilled water	80
5.4.1	Characterization	80
5.4.2	Thermal Diffusivity	83
5.5	Gold Nano fluids	88
5.5.1	Characterization	88
5.5.2	Thermal Diffusivity	91
5.6	Zinc sulfide Nano fluids	96
5.6.1	Characterization	96
5.6.2	Thermal Diffusivity	98
5.7	Palm Oil Biodiesel Blend	102



<b>6</b>	<b>CONCLUSION AND FUTURE DIRECTION</b>	107
6.1	Conclusion	107
6.2	Future Work	108
<b>REFERENCES</b>		109
<b>BIODATA OF STUDENT</b>		116
<b>LIST OF PUBLICATIONS</b>		117

