



UNIVERSITI PUTRA MALAYSIA

OPTICAL, PHYSICAL AND STRUCTURAL PROPERTIES OF ZINC-BOROTELLURITE GLASS DOPED WITH SAMARIUM OXIDE AND SAMARIUM OXIDE NANOPARTICLES

HAJER SAAD SALEH ABUZZILIA

FS 2015 12



OPTICAL, PHYSICAL AND STRUCTURAL PROPERTIES OF ZINC-BOROTELLURITE GLASS DOPED WITH SAMARIUM OXIDE AND SAMARIUM OXIDE NANOPARTICLES

By

HAJER SAAD SALEH ABUZZILIA

This is Submitted to the School of Graduate Studies, Universiti Putra Malaysia, in Fulfilment of the Requirements for the Degree of Master of Science

July 2015

COPYRIGHT

All material contained within the thesis, including without limitation text, logos, icons, photographs and all other artwork, is copyright material of Universiti Putra Malaysia unless otherwise stated. Use may be made of any material contained within the thesis for non-commercial purposes from the copyright holder. Commercial use of material may only be made with the express, prior, written permission of Universiti Putra Malaysia.

Copyright © Universiti Putra Malaysia



DEDICATION

Always, there have been some hard circumstances during my life which were relieved by love, patient, blessing, encouragement and sacrifice. To evince my feeling, I would like to dedicate my dissertation work to my darling husband for his love and patient, my lovely children for making my life complete, my precious sisters for their blessing, my gentle brothers for their encouragement. And to my devoted parents which nothing can express my gratitude toward their love, patient, blessing, encouragement, sacrifice and all supports.



Abstract of thesis presented to the senate of Universiti Putra Malaysia, in
Fulfilment of the requirements for the degree of Master of Science

**OPTICAL, PHYSICAL AND STRUCTURAL PROPERTIES OF ZINC-
BOROTELLURITE GLASS DOPED WITH SAMARIUM OXIDE AND
SAMARIUM OXIDE NANOPARTICLES**

By

HAJER SAAD SALEH ABUZZILIA

July 2015

Chairman: Assoc. Prof. Halimah Mohamed Kamari, PhD.

Faculty: Science

Tellurite glasses are very promising materials for laser and non-linear applications in optics, due to some of their important characteristic features, such as high refractive index, low phonon maxima and low melting point. Addition of small amount of TeO_2 into borate glass network enhance glass quality with an improvement in transparency and refractive index. Addition of ZnO into borotellurite glass network produce low rates of crystallization and increase glass forming ability. When other metals oxides are added in tellurite glass system, it can enhance the optical and physical behaviour. It is known that there is only a few reasearch on samarium and samarium nanoparticles doped tellurite glass system. Samarium oxide has high potential for optical applications. Meanwhile, samarium nanoparticles affect the optical properties of the glass system which is due to their smaller size of particles. For this research, two series of zinc-borotellurite glass: Samarium oxide and Samarium oxide nanoparticles doped zinc-borotellurite glass were successfully synthesized using a conventional melt-quenching method. XRD results for both Samarium oxide and Samarium oxide nanoparticles doped zinc-borotellurite glass show that the glasses are in amorphous phase. The physical and optical properties measurements were investigated for both series of zinc-borotellurite glass system.

In case of Samarium doped zinc-borotellurite glass system, the density of glass samples was in the range of $3.693\text{--}4.285\text{ kg/m}^3$ and was found to be increased with an increasing content of samarium which is due to the formation of non-bridging oxygen. The molar volume of these glasses was in the range of $31.689\text{--}30\ 057\text{ m}^3/\text{mol}$ and it was increased which is due to the large value of ionic radii and bond length of Sm_2O_3 compared to TeO_2 and increasing in oxygen packing density which results the structure becomes more compact. The non-

linear trend of refractive index 1.871-2.005 and polarizability $5.716-5.981 \times 10^{-24} \text{cm}^3$ are due to the substitution of ZnO oxides which acts as a modifier and former at certain values of mol %. The FTIR analysis consists of several bands which indicate the characteristic of Te-O and B-O vibrational groups. The optical absorption spectra of these glasses revealed that fundamental absorption edge shifts to longer wavelength as the content of Sm_2O_3 increases. The decreasing value of the band gap energy from 2.780 eV to 2.528 eV is due to the increasing number of non-bridging oxygen. The value of Urbach energy was in the range 0.689-0.660 eV and it was found to be increased with increasing content of samarium. This is due to the increasing number of TeO_4 pyramids as the content of Sm_2O_3 oxide increases. The presence of TeO_4 pyramids results the structure to become less stable.

In case of Samarium nanoparticles doped zinc-borotellurite glass system, the density of the prepared glass samples was found in the range 3.644-4.080 kg/m^3 and it was to be increased with an increase content of samarium nanoparticles which is due to the low solubility of samarium nanoparticles. The value of molar volume of these glasses was in the range 32.515-31.570 m^3/mol and it was found to be decreased with increasing content of samarium nanoparticles because of the dual nature of zinc oxide. The range of refractive index of these glasses are 2.056-2.051 and it was decreased to 0.02 mol% of Sm_2O_3 NPs which is due to the restriction movement of the electrons with respect to their small size of particles. The increasing trend of refractive index at 5% of samarium nanoparticles is due to the increasing number of non-bridging oxygen. The presence of Sm_2O_3 nanoparticles was confirmed by using TEM technique with the average size of 22.5 nm. The FTIR spectra revealed the shifting and new absorption peak in the presence of nanoparticles. The absorption edge is found to be shifted to longer wavelength. The decreasing value of the band gap energy from 2.956 eV to 2.980 eV is due to the broadening of the valence band or multivalence structures in the presence of Sm electrons. The value of Urbach energy is 0.361-0.354 eV and it was found to be increased with increasing concentration of samarium nanoparticles. It is known that materials which possess large value of Urbach energy have higher tendency to convert the weak bonds into defects.

Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia
sebagai memenuhi keperluan untuk Ijazah Master Sains

SIFAT OPTIK, FIZIKAL DAN STRUKTUR KACA ZINK-BOROTELURIT DOP DENGAN SAMARIUM OKSIDA DAN NANOPARTIKEL SAMARIUM OKSIDA

Oleh

HAJER SAAD SALEH ABUZZILIA

July 2015

Pengerusi: Prof. Madya. Halimah Mohamed Kamari, PhD

Fakulti: Sains

Kaca telurit adalah bahan yang sangat berpotensi untuk aplikasi laser dan optik tidak linear, disebabkan oleh sebahagian ciri-ciri yang penting padanya seperti indeks biasan yang tinggi, tenaga fonon yang rendah dan takat lebur yang rendah. Penambahan kadar jumlah TeO_2 yang rendah ke dalam sistem kaca borat meningkatkan kualiti kaca dengan penambahbaikan di dalam transparensi dan indeks biasan. Penambahan ZnO ke dalam sistem kaca boro-telurit menghasilkan kadar penghabluran yang rendah dan meningkatkan kebolehan pembentukan kaca. Apabila logam oksida yang lain di masukkan ke dalam sistem kaca telurit, ianya boleh meningkatkan sifat optik dan fizikal. Telah diketahui bahawa hanya sedikit sahaja kajian mengenai samarium dan samarium nanopartikel terdop sistem kaca zink-borotellurit. Samarium oksida memiliki potensi yang tinggi untuk aplikasi optik. Manakala, samarium nanopartikel memberi kesan kepada sifat optik sistem kaca zink-borotellurit yang disebabkan oleh saiz partikel yang kecil. Bagi kajian ini, dua siri kaca zink-borotelurit telah berjaya disintesis dengan menggunakan kaedah lebur lindap. Keputusan XRD untuk kedua-dua samarium dan samarium nanopartikel terdop kaca zink-borotelurit menunjukkan bahawa kaca tersebut adalah di dalam fasa amorfus. Pengukuran sifat fizikal dan optik telah dikaji untuk kedua-dua sistem kaca zink-borotelurit.

Bagi sistem kaca samarium dop zink-borotelurit, ketumpatan sampel kaca di dalam julat $3.693\text{--}4.285 \text{ kg/m}^3$ di dapati meningkat dengan penambahan kandungan samarium yang disebabkan oleh pembentukan bukan penyambung oksigen. Isipadu molar bagi kesemua kaca di dalam julat $1.689\text{--}30.057 \text{ m}^3/\text{mol}$ telah meningkat disebabkan oleh nilai jejari ionik yang besar dan stuktur panjang ikatan Sm_2O_3 berbanding TeO_2 dan peningkatan tumpat kepadatan oksigen yang menghasilkan struktur yang lebih padat. Corak indeks biasan $1.871\text{--}2.005$

yang tidak linear dan kebolehan berkutub $5.716\text{--}5.981 \times 10^{-24} \text{ cm}^3$ adalah disebabkan oleh penggantian ZnO oksida yang bertindak sebagai pengubah dan pembentuk pada nilai mol% yang tertentu. Analisa FTIR merangkumi beberapa jalur yang menunjukkan ciri-ciri Te-O dan B-O kumpulan bergetar. Spektra penyerapan optik pada kaca-kaca ini menunjukkan bahawa pinggir asas penyerapan beralih kepada gelombang yang lebih tinggi apabila kandungan Sm_2O_3 bertambah. Penurunan nilai jurang jalur tenaga dari 2.780 eV ke 2.528 eV adalah disebabkan oleh peningkatan nilai bukan penyambung oksigen. Nilai tenaga Urbach adalah di dalam julat 0.689-0.660 eV telah didapati bertambah dengan penambahan kandungan samarium. Ini disebabkan oleh peningkatan jumlah piramid TeO_4 apabila kandungan Sm_2O_3 bertambah. Kehadiran piramid TeO_4 menyebabkan struktur menjadi tidak stabil.

Bagi sistem kaca samarium nanopartikle dop zink-borotelurit, ketumpatan telah didapati ditemui di dalam julat 3.644-4.080 kg/m^3 dan menunjukkan bertambah dengan penambahan kandungan samarium nanopartikel disebabkan oleh kelarutan samarium nanopartikel yang rendah. Isipadu molar bagi kaca-kaca adalah di dalam julat kadar 32.515-31.570 m^3/mol dan telah didapati berkurang dengan penambahan kandungan samarium nanopartikel yang disebabkan oleh sifat semula jadi pendua bagi zink oksida. Indeks biasan bagi kesemua kaca-kaca adalah di dalam julat 2.056-2.051 dan telah menunjukkan berkurangan sehingga 0.02 mol% Sm_2O_3 nanopartikel. Corak peningkatan bagi indeks biasan pada 5% samarium nanopartikle adalah disebabkan oleh peningkatan nilai bukan penyambung oksigen. Kehadiran Sm_2O_3 nanopartikel telah dipastikan dengan menggunakan teknik TEM dengan saiz purata 22.5 nm. Spektra FITR telah menunjukkan peralihan dan puncak penyerapan yang baru di dalam kehadiran nanopartikel. Pinggir penyerapan telah didapati beralih kepada gelombang yang lebih panjang. Penurunan nilai jurang jalur tenaga dari 2.956 eV ke 2.980 eV adalah disebabkan oleh pelebaran jalur valens atau struktur berbilang valens di dalam kehadiran elektron Sm^{3+} . Nilai tenaga Urbach adalah 0.361-0.354 eV dan telah didapati bertambah dengan penambahan kepekatan samarium nanopartikel. Telah diketahui bahawa bahan yang memiliki jumlah tenaga Urbach yang besar memiliki potensi yang tinggi untuk menukarkan ikatan yang lemah kepada kecacatan.

AKNOWLEDGMENTS

"First of all, praise to the Almighty ALLAH Subhanahu WA Taala for giving me strength, guidance and patient to complete this work. May blessing and peace be upon Prophet Mohammed SallaAllahu Alaihi Wasilla, who was sent for mercy to the world".

I would like to express my sincere gratitude to my supervisor, Associate Professor Dr. Halimah Mohamed Kamari, for her supervision, helpful discussions and encouragement during this research. I also would like to thank the member of my supervisory committee Professor Dr. Azmi Zakari.

I also would like to give special acknowledgements to all staff in physics department, UPM, for their Co-operation given to me throughout my work.

Now I have the pleasant opportunity to express my gratitude to the members of the laboratory Azlan, Azuraida and Hasnie for their help is highly appreciated and kind friendship.

I offer my deepest appreciation to my father. He was the one who motivated and encouraged me to study physics.

I do appreciate my brothers and sisters for their encouragement and support.

I wish to thank my self-giving parents, although my words cannot express my appreciation toward their sacrifices. Truthfully I would have not been able to reach any of my successes without them.

Last but not least, I wish to appreciate to my dear husband who has done more than his share in my life since I met him. He is the one who makes the life easier and happier for me. My greatest appreciate goes to my lovely children for making my life complete and happy. Without them, the journey to completion of the thesis will not be lovely endeavour. It is to them that I dedicate this work, my sincere appreciation and love for you all.

This thesis was submitted to the Senate of Universiti Putra Malaysia and has been accepted as fulfilment of the requirements for the degree of Master of Science. The members of the supervisory Committee were as follows:

Halimah Mohamed Kamari, PhD

Associate professor
Faculty of Science
Universiti Putra Malaysia
(Chairman)

Azmi Zakaria

Professor
Faculty of Science
Universiti Putra Malaysia
(Members)

BUJANG KIM HUAT, PhD
Professor and Dean
School of Graduate Studies
Universiti Putra Malaysia

Date: 13/07/2015

Declaration by Members of Supervisory Committee

This is to confirm that:

- the research conducted and the writing of this thesis was under our supervision;
- supervision responsibilities as stated in the Universiti Putra Malaysia (Graduate Studies) Rules 2003 (Revision 2012-2013) are adhered to.

Signature:

Name of Chairman of Supervisory Committee: Associate professor. Halimah Mohamed Kamari, PhD

Signature:

Name of Member of Supervisory Committee: Professor. Azmi Zakaria, PhD

TABLE OF CONTENTS

	Page
ABSTRACT	i
ABTRAK	iii
AKNOWLEDGEMENTS	v
APPROVAL	vi
DECLARATION	viii
LIST OF TABLES	xii
LIST OF FIGURES	xiii
LIST OF ABBREVIATIONS	xv
 CHAPTER	
 1 INTRODUCTION	
1.1 Overview	1
1.2 Problem statement	6
1.3 Objective of research	6
1.4 Thesis outline	6
 2 LITRATURE REVIEW	
2.1 Introduction	7
2.2 Zinc borotellurite	7
2.3 Samarium doping glass system	10
2.4 Samarium nanoparticles doping in glass system	13
 3 THEORY	
3.1 X-Ray diffraction (XRD)	19
3.2 Transmission Electron Microscope (TEM) principle	20
3.3 Fourier transform infrared spectroscopy (FTIR)	20
3.4 Refractive index, polarization and molar refraction	21
3.5 Optical absorption	22
3.6 Optical band gap and Urbach equation	23
3.7 UV-visible absorption spectroscopy	24
 4 METHODOLOGY	
4.1 Introduction	26
4.2 Glass sample preparation method	26
4.3 Characterization	30
4.3.1 Density and molar volume	30
4.3.2 Refractive index	31
4.3.3 UV-Vis spectroscopy	32
4.3.4 Fourier transform infrared spectroscopy (FTIR)	33

4.3.5	X-ray diffraction measurement	34
4.3.6	Transmission Electron Microscope (TEM) and morphology study.	35
4.4	Error of the experiment	36
5	RESULTS AND DESSCUSSION	
5.1	Introduction	37
5.2	Samarium doped tellurite glass	37
5.2.1	Molar volume and density	37
5.2.2	X-ray diffraction (XRD)	41
5.2.3	Fourier transform infrared spectroscopy (FTIR)	43
5.2.4	Refractive index (n), molar refraction (R_M) and polarizability (α_e)	47
5.2.5	Optical absorption	52
5.2.6	Optical band gap	54
5.2.7	Urbach energy	60
5.3	Samarium nanoparticles doped tellurite glass	63
5.3.1	Molar volume and density	63
5.3.2	X-ray diffraction (XRD) and Transmission Electron Microscope (TEM)	66
5.3.3	Fourier transform infrared spectroscopy (FTIR)	69
5.3.4	Refractive index (n), molar refraction (R_M) and polarizability (α_e)	73
5.3.5	Optical absorption	78
5.3.6	Optical band gap	80
5.3.7	Urbach energy	86
5.4	Comparative analysis of samarium and samarium nanoparticles doped tellurite glass	89
5.4.1	Physical properties	89
5.4.2	Optical properties	89
6	CONCLUSION AND FUTURE RESEARCH	
6.1	Conclusion	99
6.2	Future research	101
	REFERENCES	102
	BIODATA OF STUDENT	109
	LIST OF PUBLICATIONS	110

LIST OF TABLES

Table		Page
2.1	Current status of important physical properties of various glass system	16
5.1	Density and molar volume of samarium doped zinc borotellurite glass system	40
5.2	Assignment of infrared transmission bands of samarium doped glass sample	45
5.3	Refractive index, molar refraction and polarizability of samarium doped zinc borotellurite glass system	48
5.4	Indirect optical band gap (E_{opt}^1), Direct optical band gap (E_{opt}^2) and Urbach energy (ΔE) of samarium doped glass samples	55
5.5	Density and molar volume of samarium nanoparticles doped zinc borotellurite glass system	64
5.6	Assignment of infrared transmission bands of Nano samarium doped glass sample	71
5.7	Refractive index, molar refraction and polarizability of NPs samarium doped zinc borotellurite glass system	74
5.8	Indirect optical band gap (E_{opt}^1), Direct optical band gap (E_{opt}^2) and Urbach energy (ΔE) of Nano samarium doped glass samples	81

LIST OF FIGURES

Figure		Page
1.1	The most widely used glasses are silicate glasses, formed from silica, SiO_2 . Silica consists of a 3D network of tetrahedral where every corner oxygen atom is shared with the adjacent tetrahedron. This SiO_2 tetrahedral unit is also incorporated into chains and sheets (clays), forming different ceramics.	2
1.2	Glass with added sodium as a network modifier.	3
1.3	Glass with added titanium as an intermediate.	3
3.1	Show the reflection of X-ray from two planes of atoms in a solid	19
3.2	The flows from the interferograms corrected and send to computer for calculations and provide the spectrum of the unknown materials.	21
3.3	Schematic diagram for principle of UV- Visible spectroscopy and steps of spectra data collection	25
4.1	Schematic diagram of glass making process for both samarium oxide samarium oxide nanoparticles doped zinc-borotellurite glass samples.	29
4.2	EL X-02C High Precision Ellipsometer	31
4.3	The UV-1650 PC SHAMSDZU Spectrophotometer	32
4.4	Perkin Elmer Spectrum 100 Optical FT-IR Spectrometer	33
4.5	X-ray Diffractometer	34
4.6	TEM system model Hitachi H 7100 at Institute of Bioscience-UPM.	35
5.1	Variation of density and molar volume with Sm_2O_3 mol% doped zinc borotellurite glass system.	39
5.2	XRD patterns with different concentration of samarium doped glass samples	42
5.3	FTIR spectra of zinc oxide, boron oxide, tellurite oxide, samarium oxide and $\{[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]\}_{0.7} [\text{ZnO}]_{0.3}\}_{1-x} \{\text{Sm}_2\text{O}_3\}_x$ glass system	46
5.4	Variation of refractive index vs Sm_2O_3 mol%	49
5.5	Variation of polarizability vs Sm_2O_3 mol%	50
5.6	Variation of molar refraction vs Sm_2O_3 mol%	51
5.7	Optical absorbance spectra for samarium doped glasses $\{[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]\}_{0.7} [\text{ZnO}]_{0.3}\}_{1-x} \{\text{Sm}_2\text{O}_3\}_x$	53
5.8	Plot of $(\alpha\hbar\omega)^2$ against photon energy $\hbar\omega$ of samarium doped glass samples for direct band gap measurement	56
5.9	Plot of $(\alpha\hbar\omega)^{1/2}$ against photon energy $\hbar\omega$ of samarium doped glass samples for indirect band gap measurement	57
5.10	Variation of indirect optical band gap with glass composition for indirect transition for samarium doped glass samples	58
5.11	Variation of direct optical band gap with glass composition for direct transition for samarium doped glass samples	59

5.12	Variation of $\ln(\alpha)$ with photon energy $\hbar\omega$ (eV) for different Sm_2O_3 mol%.	61
5.13	Variation of Urbach energy (ΔE) vs Sm_2O_3 mol%.	62
5.14	Variation of density and molar volume with (NPs Sm_2O_3 mol %) samarium nanoparticles doped zinc borotellurite glass system	65
5.15	XRD patterns with different concentration of Nano samarium doped glass samples	67
5.16	TEM image of Sm_2O_3 NPs doped zinc-borotellurite glass	68
5.17	FTIR spectra of zinc oxide, boron oxide, tellurite oxide, samarium NPs oxide and $\{[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.7}[\text{ZnO}]_{0.3}\}_{1-x}\{\text{NPs Sm}_2\text{O}_3\}_x$ glass system	72
5.18	Variation of refractive index vs Nano Sm_2O_3 mol%	75
5.19	Variation of polarizability vs NPs Sm_2O_3 mol%	76
5.20	Variation of molar refraction vs NPs Sm_2O_3 mol%	77
5.21	Optical absorbance spectra for Nano samarium doped glasses $\{[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.7}[\text{ZnO}]_{0.3}\}_{1-x}\{\text{Ns Sm}_2\text{O}_3\}_x$	79
5.22	Plot of $(\alpha\hbar\omega)^2$ against photon energy $\hbar\omega$ of Nano samarium doped glass samples for direct band gap measurement	82
5.23	Plot of $(\alpha\hbar\omega)^{1/2}$ against photon energy $\hbar\omega$ of Nano samarium doped glass samples for indirect band gap measurement	83
5.24	Variation of indirect optical band gap with glass composition for indirect transition for Nano samarium doped glass samples	84
5.25	Variation of direct optical band gap with glass composition for direct transition for Nano samarium doped glass samples	85
5.26	Variation of $\ln(\alpha)$ with photon energy $\hbar\omega$ (eV) for different NPs Sm_2O_3 mol%.	87
5.27	Variation of Urbach energy (ΔE) vs NPs Sm_2O_3 mol%.	88
5.28	Variation of density with Sm_2O_3 mol% and Sm_2O_3 nanoparticles mol% doped zinc borotellurite glass system	91
5.29	Variation of molar volume with Sm_2O_3 mol% and Sm_2O_3 nanoparticles mol% doped zinc borotellurite glass system	92
5.30	Variation of molar refraction with Sm_2O_3 mol% and Sm_2O_3 nanoparticles mol% doped zinc borotellurite glass system	93
5.31	Variation of Refractive index with Sm_2O_3 mol% and Sm_2O_3 nanoparticles mol% doped zinc borotellurite glass system	94
5.32	Variation of polarazability with Sm_2O_3 mol% and Sm_2O_3 nanoparticles mol% doped zinc borotellurite glass system	95
5.33	Variation of Direct band gab with Sm_2O_3 mol% and Sm_2O_3 nanoparticles mol% doped zinc borotellurite glass system	96
5.34	Variation of Indirect band gab with Sm_2O_3 mol% and Sm_2O_3 nanoparticles mol% doped zinc borotellurite glass system	97
5.35	Variation of Urbach energy with Sm_2O_3 mol% and Sm_2O_3 nanoparticles mol% doped zinc borotellurite glass system	98

LIST OF ABBREVIATIONS

TeO_2	Tellurite oxide	-
B_2O_3	Boron oxide	-
ZnO	Zinc oxide	-
Sm_2O_3	Samarium oxide	-
Sm_2O_3	Samarium oxide nanoparticles	-
NPs		
NBO	Non-bridging oxygen	-
BO	Bridging oxygen	-
XRD	X-ray diffraction	-
FTIR	Fourier transform infrared	-
d	Interplanar distance	m
θ	Scattering angle	°
λ	Wavelength	m
n	Refractive index	-
θ_i	Angle of incidence	°
θ_r	Angle of refraction for a beam of light	°
α_e	Polarizability	cm^3
V_m	Molar volume	m^3/mol
N	Avogadro number	-
ρ_{sample}	Density of sample	g/cm^3
M	Molecular weight of the material	-
R_M	Molar refraction	cm^3
α	Absorption coefficient	cm^{-1}
dI	Fraction absorption of light	eV
dx	Thickness	m
T	Transmission	%
A	Absorbance	-
I	Intensity of light back of the flow cell is defined as reference light	-
I_0	Intensity of light which pass through the flow cell	-
$\hbar\omega$	Energy of the incident photon	eV
\hbar	Plank constant	-
E_{opt}	Optical band gap energy	eV
B	A constant	-
ΔE	Band tail of the electron stated	eV
ρ_L	Density of distill water	$1.0 \text{ g}/\text{m}^3$
M_{air}	Mass in air	g
M_{water}	Mass in distill water	g

CHAPTER 1

INTRODUCTION

1.1 Overview

Glasses have distinctive properties as compared to other matters. It is high in hardness and strength but transparent at room temperature. At the same time glasses have excellent resistance to corrosiveness. Glass has a significant impact in the research field as it has various potential and applications in engineering, technology as well as day to day applications. In other words, it is worthwhile to do research based on the properties of glass in order to explore and unveil the potential of glass applications. There are many advantages in using glassy materials such as the absence of grain boundaries, the ability in continuous variable composition which perfectly making them prominent in optical applications.

The types of glass that is considered the oldest in history are based on chemical compound silica (silica dioxide), the main component in sand. Glass is the common term used to describe the material that is usually used as window glass and bottles.

Most silica-free glass like fluoride glasses, aluminosilicates, borate glasses, phosphate glasses, and glasses may contain physico-chemical properties that make it suitable for usage in fiber optics and various specific technical applications.

The three types of oxide glasses are network intermediates, formers, and modifiers. Network intermediates like zirconium, aluminium, beryllium, titanium, magnesium, zinc play the role of network formers and modifiers, based on the composition of the glass. Network formers like boron, silicon and germanium produce an extremely cross-linked chemical bonds network. Modifiers like calcium, lithium, lead, sodium, potassium generally exist as ions modifying the arrangement of the network. They are compensated by adjacent non-bridging oxygen atoms which were bound by one covalent bond to the glass network and holding one negative charge to compensate for the positive ion. Some elements can perform numerous roles. For example, lead can act both as a network former (Pb^{4+} replacing Si^{4+}), or as a modifier.

The non-bridging oxygen reduces the number of strong bonds relatively in the material and disrupts the glass network system. The viscidness of the melt decreases and lowers the melting temperature.

Glasses are a unique range of ceramic materials defined principally by their atomic structure. Glasses do not display the ordered crystalline structure of most other ceramics but instead have a highly disordered amorphous structure. This gives them very diverse properties to other crystalline ceramics. The most widely utilised glasses are silicate glasses, formed from silica, SiO_2 . Silica consists of a 3D network of tetrahedral where every corner oxygen atom is shared with the adjacent tetrahedron. This SiO_2 tetrahedral unit is also incorporated into chains and sheets (clays), forming diverse ceramics as shown in Figure 1.1.

Pure silica can be made to exist as a glass, and is called fused silica. A glass is a material that has hardened and become rigid without crystallising, making it amorphous. Silicate glasses are the most widely used glasses. All of the most important glasses are based on silica SiO_2 . Two glasses of special interest are soda-lime glass, used in bottles and windows, with composition $70\text{SiO}_2.10\text{CaO}.15\text{Na}_2\text{O}$, and borosilicate glass, used in chemical glassware and cooking, with composition $80\text{SiO}_2.15\text{B}_2\text{O}_3.5\text{Na}_2\text{O}$.

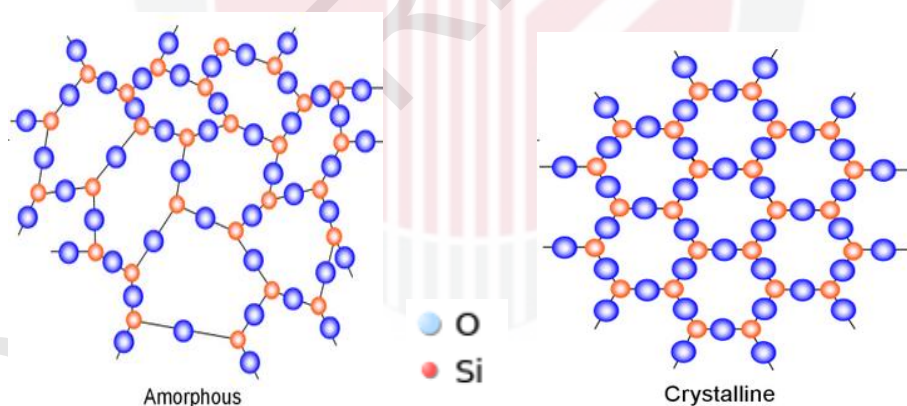


Figure 1.1: The most widely used glasses are silicate glasses, formed from silica, SiO_2 . Silica consists of a 3D network of tetrahedral where every corner oxygen atom is shared with the adjacent tetrahedron. This SiO_2 tetrahedral unit is also incorporated into chains and sheets (clays), forming different ceramics.

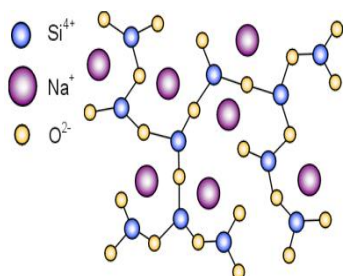


Figure 1.2: Glass with added sodium as a network modifier.

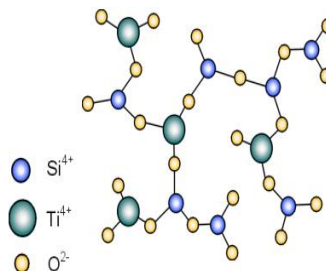


Figure 1.3: Glass with added titanium as an intermediate.

The ability of an oxide to form a glass upon cooling, i.e. an amorphous structure, depends on the structural relationship between the oxygen atoms and the cations of the oxide compound. In order to achieve a glass structure the oxide cations will bind with the oxygen atoms to form a tetrahedral network.

Certain other oxides can be added to substitute for Si atoms in the tetrahedral structure. These oxides become part of the network and act as a stabiliser as exposed in Figure 1.2 and Figure 1.3.

Tellurite based glasses are a fascinating system to study as the glass phase can be moulded over a huge range of concentration in addition to its exceptional properties. Tellurite glass have been researched on for more than 150 years. However TeO_2 glasses of purities exceeding 98.5 mol% have been made recently. (El-Mallawany, 1998).

Tellurite glass used in electric, optical, electronic industries and other areas are vast due to their good physical properties. Tellurite glasses have been used broadly for laser as well as non-linear applications in optics. They have some excellent features which are required in the optical application such as low phonon maxima, high refractive index allowing infrared radiation at high levels conducted and thus applicable as materials for optical devices and lasers or photochromic glasses, as well as low melting point. The non-appearance of hygroscopic properties restricts phosphate and borate glasses application. Furthermore, they own high density and low transformed temperature (El-

Mallawany, 1998). In glass formation process, TeO_2 needs a modifier to enhance the glass formation process easily. In other word, TeO_2 is a conditional glass former. The glass formation process on two glass formers such as Tellurite glass has been a focus of interest from both practical and academic perspective whereby the technical applications and microscopic mechanism are studied for research and industrial undertakings. In addition, researchers are also optimistic on the possibility on new structural formation and discovery in glass research which potentially brings more breakthroughs in glass technology.

Borate oxide is commonly used to solidify the glass and strengthen the glass quality with better reflective index, amelioration in transparency and even rare earth ion solubility and hardness. The formation of borate matrix that consists of BO_3 triangles and BO_4 tetrahedra create stable borate groups form for instance diborate, triborate and tetraborate.

Heavy metal oxides in borate glasses require specific care owing to the glass' applications like laser hosts, lamp phosphors and other photonic devices. Alkaline earth borate glasses contain heavy metal oxides display rare-earth ions good solubility. TeO_2 glasses give fascinating non-linear optical properties, good chemical durability, and low melting point. Alkaline earth oxides increase glass forming ability whereas heavy metal oxides intensify the optical properties' ability of the second harmonic generation. Glass formation ability are the region, stability, chemical durability of the glass forming oxide materials like B_2O_3 , SiO_2 , GeO_2 , P_2O_5 , As_2O_3 etc, can be boosted with the addition of metal oxides such as ZnO , TeO_2 , PbO , Bi_2O_3 etc, which are called conditional glass modifiers.

Zinc oxide or zinc white is the white hexagonal crystal or white powder. It is odourless, has a better taste and non-water soluble. ZnO tolerates high heat and conductivity. The low coefficient of expansion is advantage in ceramic body (Porter, 1991). Moreover, ZnO is an n-type semiconductor with band gap energy of approximately 3.2 eV (Pearton et al., 2003). It shows both photoconductivity and photocatalytic activity (Liu et al., 2001) as a vital semiconductor material, ZnO is applied in catalysis (King and Nix, 1996), rubber and paint industries, ceramics bodies, fertilizers and in cosmetics (Porter, 1991). The addition of zinc oxide in glass formation process is important to decrease the melting point, reduce the rate of crystallization and finally increase the glass forming ability. Past studies have proven that the zinc oxide can decrease the optical energy gap and thus increase the refractive index.

However, the physical properties of glasses might exhibit discontinuous changes when structural changes of cation happens after the addition of zinc oxide as it able to fill up the network forming and modify the position in borate network glasses. Depending on the application, this property is a functional property.

In year 2013, Sailaja et al. published that Samarium (Sm), one of the rare earth ions can be utilised as a dopant in various crystal hosts. Besides, Samarium (Sm) is also used as glass hosts for intense emissions in the visible region. Samarium especially the reddish orange emission region from Sm-doped materials is prominently used in laser applications since it has properties such as strong luminescence intensity, large emission cross section and high quantum efficiency. In addition, Samarium is used widely in fluorescence applications for its $^4G_{5/2}$ level that is high in quantum efficiency.

At the same time, samarium oxide (Sm_2O_3) is widely used in electrical and optical application and has greatly contributed in lasers, neutron capture, masers, magnets, thermoelectric devices productions. More attention is paid to the nano size samarium oxide compared to the micron size samarium oxide because of the nano size effects that give rise to better interfacial influence, quantum and tunnelling effects. Nanoparticles are known to have unique quantum nature which modifies the materials properties. Nowadays, nanotechnology research has focused on enhancing the properties of materials. It is strongly essential to lengthen the research on doped-glass nanoparticles to acquire exceptional photonic devices properties. The nanomaterials exceptional organization has opened up a new dimension for development of nanotechnology applications. The nano size particles have been known to give important effect on semiconductor due to their dependency on size particles.

Due to its vast application and functions Rare Earth doped materials have the market value driven motivation to develop photonic system for even more applications. Samarium oxide could be one of the best choices from the various lanthanide groups in these photonic materials studies. The trivalent electron in Samarium has the exact properties needed for the fiber amplifier applications. However, there is no recent research reported to the best of our knowledge on Sm_2O_3 nanoparticles doped tellurite glass system. Thus, this is a motivation to conduct a study on this potential system in samarium nanoparticles doped Tellurite glasses.

1.2 Problem statement

Rare earth doped glasses have successfully gathered much attention in research and development due to their potentials in optical area. It is well known that rare earth materials have excellent potential in optical switches as well as optical communications. There are extensive research on erbium doped tellurite glass since it has good optical properties. Meanwhile, samarium oxide is an excellent materials for optical applications especially to enhance the properties of optical switches and communications. There is only a few research have been conducted for samarium oxide doped tellurite glass system. Moreover, the interest of nanoparticles to improve the optical properties of tellurite glass is in high demand. Hence, it is important to investigate the optical properties of samarium and samarium nanoparticles doped tellurite glass system.

1.3 Objective of research

The aims of this study are:

- a. To fabricate the quaternary composition glass: $\{[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.7}[\text{ZnO}]_{0.3}\}_{1-x}\{\text{Sm}_2\text{O}_3\}_x$ where : $x= 0, 0.005, 0.01, 0.02, 0.03, 0.04, 0.05$, and $\{[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.7}[\text{ZnO}]_{0.3}\}_{1-x}\{\text{Sm}_2\text{O}_3 \text{ NPs}\}_x$, where: $x=0.005, 0.01, 0.02, 0.03, 0.04, 0.05$.
- b. To determine the structural and optical properties of Samarium and Samarium nanoparticles doped zinc borotellurite.

1.4 Thesis outline

This thesis paper consists of six chapters whereby chapter one is the introduction to glasses and material background, followed by problem statement, definition of scope and objective of research. Second chapter reinstated literature review of the study where important findings and properties that are published by past researchers are discussed and related to this study. Third chapter explains further on the background of the glass properties including the theory of structural, physical and optical properties measurements. Fourth chapter discusses the methodology of the study whereby the procedure of glass sample preparation methods and related tools used for the synthesis and characterization of glasses are reported. Fifth chapter interprets the results obtained and further discussion on the parameter of physical properties, structure properties and optical properties of the study. Lastly, sixth chapter summarizes the conclusion of the study and suggestions for future work.

REFERENCES

- Aboud. H, Wagiran. H and Hossain. I, "Effect of co-doped SnO₂ nanoparticles on the optical properties of Cu-doped lithium potassium borate glass," *Journal of materials letters*, 2012; 85: 21-24.
- Abay. B, Güder. H.S, Efeoğlu. H and Yoğurtçu. Y.K, "Urbach–Martienssen tails in Er-doped and undoped n-type InSe," *Physica B: Condensed Matter* 1998; 254:148-155.
- Abdel-Baki. M, El-Diasty. F and Wahab. F. A. A, "Optical characterization of xTi₂O-(60-x) SiO₂-40Na₂O glasses: II. Absorption edge, Fermi level, electronic polarizability and optical basicity," *Optical Communications* 2006; 261: 65-70.
- Abdel-Hameed. S. A. M, Marzouk. M. A and Abdel-Ghany. A.E, "Magnetic properties of nanoparticles glass-ceramic rich with copper ions," *Journal of Non- Crystalline Solids* 2011; 357: 3888–3896.
- Agarwal. A, Seth. V. P, Sanghi. S, Gahlot. P. S and Goyal. D. R, "Optical band gap studies and estimation of two photon absorption coefficient in alkali bismuth borate glasses," *Radiation Effects & Defects in Solids* 2003; 158: 793-801.
- Ahlawat. N, Sanghi. S and Agarwal. A, "Effect of Li₂O on structure and optical properties of lithium bismosilicate glasses," *Journal of Alloys and Compounds* 2009; 480: 516-520.
- Alivisatos A. P, *Semiconductor Clusters, Nanocrystals and Quantum Dots*," Science 1996; 271: 933-937.
- Aw. S. A, Tan. H. S and Ong. C. K, "optical absorption measurements of band-gap shrinking in moderately and heavily doped silicon," *J. Phys.: Condens. Matter* 1991; 3: 8213-8223.
- Azlan. M. N, Halimah. M. K, Shafinas. S. Z and Daud. W. M, "Effect of erbium nanoparticles on optical properties of zinc borotellurite glass system," *Journal of Nanomaterials* 2013; 2013: 1-8.
- Davis. E. A and Mott. N. F, "Conduction in Non-Crystalline Systems V," *Philosophical Magazine* 1970; 22: 903-922.
- Damas. P, Coelho. J, Hungerford. G, and Hussain. N. S, "Structural studies of lithium boro tellurite glasses doped with praseodymium and samarium oxides," *Materials Research Bulletin* 2012; 47: 3489–3494.
- Demir. M. M, "PMMA/zinc oxide nanocomposites prepared by in situ bulk polymerisation, *Macromol*," *Rapid Commun* 2006; 27: 763-770.
- Dimitrov. V and Sakka. S, "Electronic oxide polarizability and optical basicity of simple oxides. I," *Journal of Applied Physics* 1996; 79: 1736.

- Dousti M. R, Ghoshal S.K, Amjad R, Sahar M.R, Fakhra N, Arifin. R "structural and optical study of samarium doped lead zinc phosphate glasses," *Optics Communications* 2013; 300: 204–209.
- Eraiah. B, Sudha. G and Bhat, "Optical properties of samarium doped zinc-phosphate glasses," *Journal of Physics and Chemistry of Solids* 2007; 68: 581–585.
- Eraiah. B, "Optical properties of samarium doped zinc-tellurite glasses," *Journal of Indian Academy of Sciences* 2006; 29: 375–378.
- Eraiah. B, "Optical properties of lead-tellurite glasses doped with samarium trioxide," *Indian Academy of Sciences* 2010; 33: 391-394.
- El-Mallawany. R, "The optical properties of tellurite glasses," *Journal of Applied Physics* 1992; 72:1774.
- El-Mallawany. R, *Tellurite Glasses Handbook, Physical Properties and Data*, CRC Press, USA, 2002.
- El- Mallawamy. R. A, "Theoretical and experimental IR spectra of binary rare earth tellurite glasses-1," *Infrared Phys* 1989; 29: 781-785.
- El-Mallawany. R, "Review Tellurite glasses Part 1. Elastic properties", *Materials Chemistry and Physics* 1998; 53: 93-120.
- Ellingson. R. J, Beard. M. C, Johnson. J. C, Yu. P, Micic. O. I, Nozik. A. J, Shabaev. A and Efros. A. L, "Highly efficient multiple exciton generation in colloidal PbSe and PbS quantum dots," *Nano Lett* 2005; 5: 865-71.
- El-Zaidia. M, Ammar. A and El-Mallawamy, "IR spectra, ESR spectra and density of TeO₂-WO₃ and TeO₂-ZnCl₂ Glasses," *Physica status soli (a)* 1985; 91: 637.
- Elisa M, Sava B.A, Vasiliu I.C, Monteiro R.C.C, Veiga J.P, Ghervase L, Feraru I, Iordanescu R, "optical and structural characterization of samarium and europium-doped phosphate glasses," *Journal of Non-Crystalline Solids* 2013; 369: 55–60.
- Farouk. M, Samir. A and Metawe. F, "Optical absorption and structural studies of bismuth borate glasses containing Er³⁺ ions," *Journal of non-crystalline solids* 2013; 371: 14-21.
- Ganguly. M, Bhat. M. H and Rao. K. J, "Lithium ion transport in Li₂SO₄-Li₂O-B₂O₃ glasses," *Phys. Chem. Glasses* 1999; 40: 297-304.
- Gautam. C. R and Yadav. A. K, "Synthesis and Optical Investigations on (Ba, Sr) TiO₃ Borosilicate Glasses Doped with La₂O₃," *Optics and Photonics Journal* 2013; 3: 1-7.
- Greenwood. G. W, The growth of dispersed precipitates in solutions. *Acta metallurgica* 1956; 4.

- Gupta. P and Ramrakhiani. M, "Influence of the particle size on the optical properties of CdSe nanoparticles," *The Open Nanoscience Journal* 2009; 3: 15–19.
- Halimah. M. K, Daud. W. M and Sidek. H. A. A, "Optical properties of borotellurite glasses," *Journal of Applied Sciences* 2005; 2340: 1546-9239.
- Halimah.M. K, Daud. W. M, Sidek. H. A. A and Zaidan. A. W, "Optical properties of ternary tellurite glasses," *Materials Science- Poland* 2010; 28:173-180.
- Halimah M.K., Daud W.M., Sidek H.A.A., Zainal A.S., Zainul A.H. and Jumiah H, "Structural analysis of borotellurite glass," *American Journal of Applied Sciences* 2007; 4: 323-327.
- Hsu. S, "Separation Sciences Research and Product Development," Mallinckrodt Baker Division, Mallinckrodt, Inc".
- Jlassi. I, Elhouichet. H and Ferid, M, "Thermal and optical properties of tellurite glasses doped erbium," *Journal of Materials Science* 2011; 46: 806–812.
- Joseph. C. M, Binu. P.R and Shreekrishnakumar. K, "preparation and physical properties of CuPc- substituted borat glass," *Materials Letters* 2001; 50: 251-253.
- Kaur. A, Khanna. A, Pesquera. C, Gonzá lez. F and Sathe. V, "Preparation and characterization of lead and zinc tellurite glasses," *Journal of Non-Crystalline Solids* 2010; 356: 864–872.
- Khattak. G. D and Tabet. N, "Structural properties of glasses in the series $(\text{SrO})_x(\text{V}_2\text{O}_5)_{1-x}$, $(\text{SrO})_{0.5-y}(\text{B}_2\text{O}_3)_y(\text{V}_2\text{O}_5)_{0.5}$ and $(\text{SrO})_{0.2}(\text{B}_2\text{O}_3)_z(\text{V}_2\text{O}_5)_{0.8-z}$," *Physical Review. B* 2005; 72: 104203-14.
- King and Nix, "Airborne scanning spectrometer for remote sensing of cloud, aerosol, water vapor and surface properties", *J. Atmos. Ocean. Tech* 1996; 13: 777–794.
- Konijnendijk. W. L and Stevels. J. M, "The structure of borate glasses studied by Raman scattering," *J. Non-Cryst. Solids* 1975; 18: 307–331.
- Linsebigler. A, Lu. G, Yatus. J.T and Jr, "Photooxidation of CH_3Cl on TiO_2 (110): A Mechanism Not Involving H_2O ," *J. Phys. Chem* 1995; 99: 7626–7631.
- Liu HX, Cartegni L, Zhang MQ, Krainer AR. "A mechanism for exon skipping caused by nonsense or missense mutations in BRCA1 and other genes", *Nat Genet.* 2001; 27: 55–58.
- Lucacel. R. C and Ardelean. I, "Comparative structural investigation of B_2O_3 - MO - CuO glasses (MO= TeO_2 or As_2O_3) by FTIR & Raman spectroscopies," *J. Optoelectronics & advanced meterials* 2006; 8: 1124-1128.
- Mahraz. Z. A. S. M, Sahar. M. R, and Goshal. S. K, "Concentration dependent luminescence quenching of Er^{3+} -doped zinc boro-tellurite glass," *Journal of Luminescence* 2013; 144: 139–145.

- Maheshvaran. K, Veeran. P and Marimuthu. K, "structural and optical studies on Eu^{3+} doped borotellurite glasses," *Journal of solid state sciences* 2013; 17:54-62.
- Maheshvarana. K, Linganna. K and Marimuthuan. K, "Composition dependent structural and optical properties of Sm^{3+} doped boro-tellurite glasses," *Journal of Luminescence* 2011; 131: 2746-2753.
- Manal A, Fouad, E "studied the role of oxygen on the optical properties of borate glass doped with ZnO ," *Journal of Solid State Chemistry* 2011; 184: 2762–2769.
- Mott. N. F and Davis. E. A "Electronic Processes in Non-Crystalline Materials", *Oxford University Press* 2012; 590.
- Murugavel. S and Roling. B, "Ion transport mechanism in borate glasses: Influence of network structure on non-Arrhenius conductivity," *Physical Review B* 2007; 76: 180202-5.
- Neov. S, Kozhukharov. V, Gerasimova. I and Sidzhimov. B, "A model for structural recombination in tellurite glasses," *Journal of physics C: Solid state Physics* 1979; 12: 2475.
- Pavani. P. G, Sadhana. K and Mouli. V. C, "Optical, physical and structural studies of boro-zinc tellurite glasses", *Journal of Physica B* 2011; 406; 6-7: 1242-1247.
- Pascuta. P, Pop. L, Rada. S, Bosca. M and Culea. E, "The local structure of bismuth borate glasses doped with europium ions evidenced by FT-IR spectroscopy," *J. Mater. Sci. : Mater. Electron* 2008; 19: 424–428.
- Pankove, "Optical Processes in Semiconductors," *Dover Books on Physics* 1976.
- Pedreira. W. R, Queiroz. C.A, Abrao. A, Rocha. S.M, Vasconcellos. M.E, Boaventura. G.R and Pimentel. M.M, "Enrichment of yttrium from rare earth concentrate by ammonium carbonate leaching and peroxide precipitation," *Journal of Alloys and Compounds - J alloys compounds* 2006; 418: pp. 200-203.
- Pearnton. S. J., Abernathy. C. R, Norton. D.P, Hebard. A.F, Park. Y.D, Boatner. L.A, Budai. J.D," Advances in wide bandgap materials for semiconductor spintronics", *Materials Science and Engineering R* 2003; 40: 137–168.
- Porter. M. E,"Towards a dynamic theory of strategy", *Strategic Management Journal* 1991; 12: pp. 95–117.
- Prakash. G. V, Rao. D. N and Bhatnagar. A.K, "Linear optical properties of niobium-based tellurite glasses," *Solid state commun* 2001; 119: 39-44.
- Rao. S. L. S, Ramadevudu. G, Shareefuddin. M, Abdul Hameed, Chary. M.N and Rao. M .L, "Optical properties of alkaline earth borate glasses," *International Journal of Engineering, Science and Technology* 2012; 4: 25-35.

- Rada. S, Culea. M and Culea. E, "Structure of TeO_2 - B_2O_3 glasses inferred from infrared spectroscopy and DFT calculations," *Journal of Non-Crystalline Solids* 2008; 354: 5491–5495.
- Rajendran. V, Palanivelu. N and Chaudhuri. B. K, "Characterisation of semiconducting V_2O_5 - Bi_2O_3 - TeO_2 glasses through ultrasonic measurements," *Journal of Noncrystalline Solids* 2003; 320: 195-209.
- Rawson. H, "Properties and applications of glass," *Amster-dam-Elsevier Scientific Pub* 1980; 3: 318.
- Raddy. M. R, Kumar. V. R and Veeraiah. N, "Effect of Chromium impurity on dielectric relaxation effects of ZnF_2 - PbO - TeO_2 glasses," *Indian Journal of Pure and Applied Physics* 1995; 33: 48.
- Rada, E. Culeva, Rus. V, Pica. M, Culea. M, "The local structure of gadolinium vanado-tellurite glasses," *Journal of Materials Science* 2008; 43: 3713-3716.
- Rada. S, Dehelean. A and Culea. E, "FTIR and UV-Vis spectroscopy investigations on the structure of the europium-lead-tellurite glasses," *Journal of non-crystalline solids* 2011; 357: 3070-3073.
- Reza. M. D, Sahar. M. R and Ghosal. S. K, "Effect of AgCl on spectroscopic properties of erbium doped zinc tellurite glass," *Journal of molecular structure* 2013; 1035: 6-12.
- Reddy .K. M, Manorama. S. V and Reddy. A. R, "Bandgap studies on anatase titanium dioxide nanoparticles," *Materials Chemistry and Physics* 2002; 78: 239–245.
- Rokhlin. L. L, "Dependence of the rare earth metal solubility on solid magnesium on its atomic number," *Journal of Phase Equilibria* 1998; 19: 142-145.
- Roychowdury. A, Satya .P. P, Sanjay .K, Dipankar .D, "Effect of magnetite nanoparticles on the properties of Zinc Sulfide in fluorescent-magnetic $\text{Fe}_3\text{O}_4/\text{ZnS}$ nano-composites," *Powder Technology* 2014; 254: 583–590.
- Saddeek. Y. B and Gaafar. M. S, "Physical and structural properties of some bismuth borate glasses," *Journal of materials chemistry and physics* 2009; 115: 280-286.
- Sailaja. S, Raju. C. N and Reddy. C. A, "Optical properties of Sm^{3+} -doped cadmium bismuth borate glasses," *Journal of Molecular Structure* 2013; 1038: 29–34.
- Sanghi. S, Sindhu. S, Agarwal. A and Seth. V. P, "Physical, optical and electrical properties of calcium bismuth borate glasses," *Radiations Effects & Defects* 2004; 159: 369-379.
- Saddeek. Y.B and Latif L.A.E, "Effect of TeO_2 on the elastic moduli of sodium borate glasses," *Physica B: Condensed Matter* 2004; 348: 475–484.

- Selvi. S, Marimuthu. K, Muralidharan. G "Structural and luminescence behaviour of Sm^{3+} ions doped lead boro-telluro-phosphate glasses," *Journal of Luminescence* 2015; 159: 207–218.
- Singh. D, Singh. G, Manupriya, Mohan. S, Arora. M and Sharma. G, "Optical and structural properties of $\text{ZnO-PbOB}_2\text{O}_3$ and $\text{ZnO-PbO-B}_2\text{O}_3\text{-SiO}_2$ glasses," *J. of Phys: Condens. Matter* 2008; 20: 075228.
- Sidek. H. A. A, Chow. S.P, Talib. Z.A and Halim. S.A, "Formation and elastic behavior of lead magnesium chlorophosphate glasses," *Turk. J. Phys* 2004; 28: 65-71.
- Sidek. H. A. A, Rosmawati. S, Talib. Z. A, Halimah. M. K and Daud. W. M, "Synthesis and Optical Properties of ZnO-TeO_2 Glass System," *American Journal of Applied Sciences* 2009; 8: 1489-1494.
- Sidek. H. A. A, El-Mallawany. R, Krishnaswamy H, and Shaharuddin R, "Effect of AlF_3 reduction and concurrent ZnO addition on the elastic properties of Tellurite based glasses," *Advances in Condensed Matter Physics* 2014, ; 2014: 7.
- Singh. R.K, Srinivasan. A, "Magnetic properties of glass-ceramics containing nanocrystalline zinc-ferrite," *Journal of Magnetism and Magnetic Materials* 2011; 323: 330–333.
- Subhadra. M, Kistaiah. P, "Effect of Bi_2O_3 content on physical and optical properties of $15\text{Li}_2\text{O}_3\text{-}15\text{K}_2\text{O-xBi}_2\text{O}_3\text{-(65-x) B}_2\text{O}_3\text{: }5\text{V}_2\text{O}_5$ glass system," *Physica B: of Condensed Matter* 2011; 406: 1501–1505.
- Tauc. J, "Absorption edge and internal electric fields in amorphous semiconductors," *Materials Research Bulletin* 1970; 5: 721–729.
- Tauc. J "Amorphous and liquid semiconductors," The University of Michigan 1974; 441.
- Wang. Y., Dai. S and Chen. F, "Physical properties and optical band gap of new tellurite glasses within the $\text{TeO}_2\text{-Nb}_2\text{O}_5\text{-Bi}_2\text{O}_3$ system," *Journal of materials, chemistry and physics* 2009; 113: 407-411.
- Widanarto. W, Sahar. M.R., Ghoshal. S.K, Arifin. R, Rohani. M.S, Hamzah. K and Jandra. M, "Natural Fe_3O_4 nanoparticles embedded zin-tellurite glasses: Polarizability and optical properties," *Materials Chemistry and Physics* 2013; 138: 174-178.
- Widanarto. W., Sahar. M .R, Ghoshal. S. K, Arifin. R, Rohani. M. S and Hamzah. K, "Effect of natural Fe_3O_4 nanoparticles on structural and optical properties of Er^{3+} doped tellurite glass," *Journal of Magnetism and Magnetic Materials* 2013; 326: 123–128.
- Whiffen D. H and Anne Cunningham, "Absolute signs of dipole moment derivatives in carbonyl sulphide", *J. Chem. Soc. D*1971; 16: 981-982.

- Yousef. E, Hotzel. M and Russel. C, "Effect of ZnO and Bi₂O₃ addition on linear and non-linear optical properties of tellurite glasses," *J. Non-Cryst. Solids* 2007; 353: 333-338.
- Yousef. B, Daghestani. D, Heidar. E "Demographic and Anatomical Survey of Colorectal Polyps in an Iranian Population", *Asian Pacific Journal of Cancer Prevention* 2005; 6: 537-540.
- Yousef. E and Al-Qaisi. B, "UV spectroscopy, refractive indices and elastic properties of the (76 – x) TeO₂.9P₂O₅.15ZnO.xLiNbO₃.xLiNbO₃ glass," *Journal of solid state sciences* 2013; 19: 6-11
- Yusoff N.M, Sahar M.R "Effect of silver nanoparticles incorporated with samarium-doped magnesium tellurite glasses," *Physica. B* 2015; 456: 191–196.
- Yu. H, "A General Low-Temperature Route for Large-Scale Fabrication of Highly Oriented ZnO Nanorod/Nanotube arrays," *J. Am. Chem. Soc.* 2005; 127: 2378-2379.
- Zarifah. N.A, Halimah. M. K, Hashim. M, Azmi. B. Z and Daud. W. M, "Magnetic Behaviour of (Fe₂O₃) x (TeO₂)_{1-x} Glass System Due to Iron Oxide," *Chalcogenide Letters* 2010; 7: 565 – 571.
- Zhu. W, Xu. L, Mab. J, Yang. R and Chen. Y, "Effect of the thermodynamic properties of W/O microemulsions on samarium oxide nanoparticle size," *Journal of Colloid and Interface Science* 2009; 340: 119-125.
- Zaid M. H, Khamirul A. M, Sidek H. A. A, Azmi Z and Mohd S. M. G, "Effect of ZnO on the physical properties and optical band gap of soda lime silicate glass". *Int. J. Mol. Sci* 2012; 13: 7550-7558.