



UNIVERSITI PUTRA MALAYSIA

***DAMAGE DETECTION AND CHARACTERIZATION IN C-GLASS AND
E-GLASS FIBRE-REINFORCED POLYMER DUE TO LOW AND HIGH
VELOCITY IMPACT EVENTS***

SYAFIQAH NUR AZRIE BT SAFRI

FK 2014 115



**DAMAGE DETECTION AND CHARACTERIZATION IN C-GLASS AND
E-GLASS FIBRE-REINFORCED POLYMER DUE TO LOW AND HIGH
VELOCITY IMPACT EVENTS**

By

SYAFIQAH NUR AZRIE BT SAFRI

**Thesis Submitted to the School of Graduate Studies, Universiti Putra Malaysia,
in Fulfilment of the Requirements for the Degree of Master of Science**

November 2014

COPYRIGHT

All material contained within the thesis, including without limitation text, logos, icons, photographs and all other artwork, is copyright material of Universiti Putra Malaysia, unless otherwise stated. Use may be made of any material contained within the thesis for non-commercial purposes from the copyright holder. Commercial use of material may only be made with the express, prior, written permission of Universiti Putra Malaysia.

Copyright © Universiti Putra Malaysia



Abstract of thesis presented to the Senate of Universiti Putra Malaysia in fulfilment of the requirement for the degree of Master of Science

DAMAGE DETECTION AND CHARACTERIZATION IN C-GLASS AND E-GLASS FIBRE-REINFORCED POLYMER DUE TO LOW AND HIGH VELOCITY IMPACT EVENTS

By

SYAFIQAH NUR AZRIE BT SAFRI

November 2014

Chair: Mohamed Thariq Bin Hameed Sultan, PhD

Faculty: Engineering

This thesis presents low velocity impact testing and high velocity impact testing on fibreglass reinforced polymer. The materials used in this experiment are Type C-glass/Epoxy 600 g/m² and Type E-glass/Epoxy 800 g/m². The ultimate objective of this research is to conduct an experimental investigation using low velocity impact testing and high velocity impact testing to detect and quantify impact damage for Glass Fibre Reinforced Polymer Type C-glass/Epoxy 600 g/m² and Type E-glass/Epoxy 800 g/m² plate. The purpose of this research is to choose the best material for structural application by comparing the mechanical properties and damage characteristics of GFRP Type C-glass/Epoxy 600 g/m² and Type E-glass/Epoxy 800 g/m².

The experimental results of low-energy drop-weight impact tests on woven-roving Glass Fibre Reinforced Polymer (GFRP) type C-glass/Epoxy 600 g/m² and Type E-glass/Epoxy 800 g/m² are presented. The effects of specimen thickness based on the number of plies and impact energy are investigated. Impact damage and response was observed for eight levels of impact energies, 6, 12, 18, 24, 30, 36, 42 and 48 J. From the experimental studies, it can be concluded that for each type of GFRP, the impact energy showed excellent correlation with the impact response. The difference in the number of plies fabricated and the mechanical properties for both types of GFRP do affect the impact response and impact damage of the specimens tested.

The experimental results of the high velocity impact test using a Single Stage Gas Gun (SSGG) show that both types of GFRP exhibit damage in terms of fibre cracking, and fibre pull out after being tested with four different gas gun pressures. Before fibre failure occurs, they undergo matrix cracking and delamination processes first. As the gas gun pressure increases, the initial velocity of the projectile increases, the projectile kinetic energy increases, the maximum force exerted on the specimen increases, and the energy absorbed by the specimen also increases. Most of the impacted specimens show that GFRP type E-glass/Epoxy 800 g/m² experienced a smaller damage area compared to type C-glass/Epoxy 600 g/m². From the test, the effect of the shape of the projectile, the target thickness and the gas gun pressure affected the performance of GFRP.

It can be concluded that GFRP type E-glass/Epoxy 800 g/m² is stronger compared to GFRP type C-glass/Epoxy 600 g/m² since it has more fibre volume since it is higher in density and has good mechanical properties. Therefore, GFRP type E-glass/Epoxy 800 g/m² is recommended to be used in structural applications.



Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia sebagai memenuhi keperluan untuk ijazah Master Sains

**PENGESANAN DAN PENCIRIAN KEROSAKAN DALAM POLIMER
BERTETULANG GENTIAN KACA C DAN E AKIBAT PERISTIWA
KELAJUAN RENDAH DAN TINGGI**

Oleh

SYAFIQAH NUR AZRIE BT SAFRI

November 2014

Pengerusi: Mohamed Thariq Bin Hameed Sultan, PhD

Fakulti: Kejuruteraan

Tesis ini membentangkan ujian kesan halaju rendah dan ujian kesan halaju tinggi ke atas gentian kaca polimer bertetulang. Bahan-bahan yang digunakan dalam eksperimen ini adalah Jenis C-kaca/epoksi 600 g/m² dan Jenis E-kaca/epoksi 800 g/m². Objektif utama kajian ini adalah untuk menjalankan siasatan ujikaji menggunakan ujian kesan halaju rendah dan ujian kesan halaju tinggi untuk mengesan dan menentukan kuantiti kerosakan kesan untuk gentian kaca polimer bertetulang Jenis C-kaca/epoksi 600 g/m² dan Jenis E-kaca/epoksi 800 g/m². Tujuan kajian ini adalah untuk memilih bahan terbaik untuk aplikasi struktur dengan membandingkan sifat-sifat dan ciri-ciri mekanikal kerosakan Jenis C-kaca/epoksi 600 g/m² dan Jenis E-kaca/epoksi 800 g/m².

Bagi ujian halaju kelajuan rendah, keputusan eksperimen menunjukkan kesan ketebalan specimen berdasarkan bilangan helai dan tenaga kesan terhadap Polimer Bertetulang Gentian Kaca (GFRP) jenis C-kaca/epoksi 600 g/m² dan Jenis E-kaca/epoksi 800 g/m² dibentangkan. Lapan tahap tenaga kesan, 6, 12, 18, 24, 30, 36, 42 dan 48 J digunakan untuk melihat tindak balas bahan dan impak kerosakan. Dari kajian eksperimen, ia boleh disimpulkan bahawa bagi setiap jenis GFRP, tenaga kesan menunjukkan korelasi yang baik dengan kesan tindak balas. Perbezaan bilangan helai fabrikasi dan sifat-sifat mekanikal untuk kedua-dua jenis GFRP memberi kesan kepada impak dan kesan kerosakan daripada specimen yang diuji.

Keputusan eksperimen daripada ujian halaju tinggi menggunakan senapang gas termampat menunjukkan bahawa kedua-dua jenis polimer bertetulang gentian kaca mengalami kerosakan pameran dari segi keretakan serat, dan penarikan serat selepas diuji dengan empat tekanan gas yang berbeza. Sebelum kegagalan serat berlaku, mereka menjalani keretakan matriks dan proses delaminasi terlebih dahulu. Akibat daripada penambahan tekanan gas senapang, halaju awal peluru akan bertambah, tenaga kinetic peluru bertambah, daya maksimum dikenakan ke atas specimen, dan tenaga yang diserap oleh specimen juga meningkat. Kebanyakan specimen menunjukkan bahawa jenis GFRP E-kaca/epoksi 800 g/m² mengalami kerosakan yang lebih kecil berbanding dengan jenis C-kaca/epoksi 600 g/m². Berdasarkan ujian,

kesan bentuk peluru, ketebalan sasaran dan tekanan senapang gas menjejaskan prestasi GFRP.

Ia boleh disimpulkan bahawa jenis GFRP E-kaca/epoksi 800 g/m² lebih kuat berbanding dengan jenis GFRP C-kaca/epoksi 600 g/m² kerana ia mempunyai isipadu yang lebih seras, lebih tinggi kepadatan dan mempunyai sifat mekanik yang lebih baik. Oleh itu, GFRP Jenis E-kaca/epoksi 800 g/m² adalah disyorkan untuk digunakan dalam aplikasi struktur.



ACKNOWLEDGEMENTS

Foremost, Alhamdulillah, gives praises and thanks to the Allah, the Almighty, for His showers of blessings throughout my research work to complete the research successfully. Firstly, I would wish to convey my earnest gratitude to my supervisor, Dr. Mohamed Thariq Bin Hameed Sultan for the continuous support of my research, for his excellent guidance, patience, motivation, immense knowledge, and for providing me with an excellent atmosphere for doing research. His guidance helped me all through the time of the research and the writing of this thesis. Besides my supervisor, I would like to express my deepest gratitude to the rest of my supervisory committee, Dr. Faizal bin Mustapha and Dr. Noorfaizal bin Yidris for their encouragement and guidance throughout the research process.

I would like to thank my parents Haji Safri Bin Abdul Hamid and Hajjah Saidiah Bt Haji Abdul, for giving birth to me and supporting me throughout my life. Also, deepest thanks go to my siblings, Safwana Nurwidad Bt Safri, Muhamad Shukri Azim Bin Safri, Syazwani Nuraisyah Bt Safri, Ahmad Syakir Azam Bin Safri and Muhamad Syafiq Amal Bin Safri for their endless help, encouragement and support throughout my research. I thank my research partner, Noorshazlin Binti Razali, for her aid during the laboratory work, for the stimulating discussions and for all the fun we have had in the last two years. I would also like to thank all of my friends who supported me in writing and many thanks and appreciations to my undergraduate friends Chan Teng Yan and Mohd Syafiq in developing the project. Lastly, my thanks also go to all the technical staff in various laboratories; Mr. Khairul Dahri and Mr. Shazril (Malaysian Institute Of Aviation Technology), Mr. Farid (International Islamic University Malaysia), Mrs. Sakinah (University Malaysia Pahang) and to Mr. Saifol, Mr. Saffairus and Mr. Ropie from the Department of Aerospace Engineering, UPM.

I certify that a Thesis Examination Committee has met on 03 November 2014 to conduct the final examination of Syafiqah Nur Azrie bt Safri on her thesis entitled “Damage Detection and Characterization in C-Glass and E-Glass Fibre-Reinforced Polymer Due to Low and High Velocity Impact Events” in accordance with the Universities and University Colleges Act 1971 and the Constitution of the Universiti Putra Malaysia [P.U. (A) 106] 15 March 1998. The Committee recommends that the student be awarded the Master of Science.

Members of the Thesis Examination Committee were as follows:

Rizal Bin Zahari, PhD

Associate Professor,
Faculty of Engineering,
Universiti Putra Malaysia.
(Chairman)

Lt. Kol. (B) Mohamed Tarmizi Bin Ahmad, PhD

Associate Professor,
Faculty of Engineering,
Universiti Putra Malaysia.
(Internal Examiner)

Azmin Shakrine Bin Mohd Rafie, PhD

Associate Professor,
Faculty of Engineering,
Universiti Putra Malaysia.
(Internal Examiner)

Ahmad Mujahid Bin Ahmad Zaidi, PhD

Professor,
Faculty of Mechanical,
Universiti Pertahanan Nasional Malaysia
(External Examiner)



ZULKARNAIN ZAINAL, PhD
Professor and Deputy Dean
School of Graduate Studies
Universiti Putra Malaysia

Date: 9 December 2014

This thesis was submitted to the Senate of Universiti Putra and has been accepted as fulfilment of the requirement for the degree of Master of Science. The members of the Supervisory Committee were as follows:

Mohamed Thariq Bin Hameed Sultan, PhD

Senior Lecturer,
Faculty of Engineering,
Universiti Putra Malaysia.
(Chairman)

Faizal Bin Mustapha, PhD

Associate Professor,
Faculty of Engineering,
Universiti Putra Malaysia.
(Member)

Noorfaizal Bin Yidris, PhD

Senior Lecturer,
Faculty of Engineering,
Universiti Putra Malaysia.
(Member)

BUJANG KIM HUAT, PhD

Professor and Dean
School of Graduate Studies
Universiti Putra Malaysia

Date:

Declaration by graduate student

I hereby confirm that:

- this thesis is my original work;
- quotations, illustrations and citations have been duly referenced;
- this thesis has not been submitted previously or concurrently for any other degree at any other institutions;
- intellectual property from the thesis and copyright of thesis are fully-owned by Universiti Putra Malaysia, as according to the Universiti Putra Malaysia (Research) Rules 2012;
- written permission must be obtained from supervisor and the office of Deputy Vice-Chancellor (Research and Innovation) before thesis is published (in the form of written, printed or in electronic form) including books, journals, modules, proceedings, popular writings, seminar papers, manuscripts, posters, reports, lecture notes, learning modules or any other materials as stated in the Universiti Putra Malaysia (Research) Rules 2012;
- there is no plagiarism or data falsification/fabrication in the thesis, and scholarly integrity is upheld as according to the Universiti Putra Malaysia (Graduate Studies) Rules 2003 (Revision 2012-2013) and the Universiti Putra Malaysia (Research) Rules 2012. The thesis has undergone plagiarism detection software.

Signature: _____

Date: _____

Name and Matric No: Syafiqah Nur Azrie Bt Safri GS34928

Declaration by Members of Supervisory Committee

This is to confirm that:

- the research conducted and the writing of this thesis was under our supervision;
- supervision responsibilities as stated in the Universiti Putra Malaysia (Graduate Studies) Rules 2003 (Revision 2012-2013) are adhered to.

Signature: _____

Name of
Chairman of
Supervisory
Committee: Dr. Mohamed Thariq
Bin Hameed Sultan

Signature: _____

Name of
Member of
Supervisory
Committee: Assoc. Prof. Dr. Faizal
Bin Mustapha

Signature: _____

Name of
Member of
Supervisory
Committee: Dr. Noorfaizal Bin Yidris

TABLE OF CONTENTS

	Page
ABSTRACT	i
ABSTRAK	iii
ACKNOWLEDGEMENTS	v
APPROVAL	vi
DECLARATION	viii
LIST OF TABLES	xiii
LIST OF FIGURES	xv
LIST OF SYMBOLS AND ABBREVIATIONS	xviii
CHAPTER	
1 INTRODUCTION	
1.1 Overview	1
1.2 Problem Statements	4
1.3 Research Aim and Objectives	5
1.4 Structure of the Thesis	5
2 LITERATURE REVIEW	
2.1 Introduction	7
2.2 Composite Material Overview	7
2.3 Glass Fibre Reinforced Polymer (GFRP) Overview	10
2.3.1 History of Glass Fibre Reinforced Polymer (GFRP)	10
2.3.2 Properties of Glass Fibre Reinforced Polymer (GFRP)	11
2.3.3 Advantages and Disadvantages of Glass Fibre Reinforced Polymer (GFRP)	12
2.3.4 Glass Fibre Reinforced Polymer (GFRP) in Structural Application	12
2.4 Specimen Fabrication Overview	13
2.4.1 Matrices	13
2.4.2. Product Form	13
2.4.3 Fabrication Process	14
2.5 Low Velocity Impact Testing	15
2.5.1 Types of Low Velocity Impact Testing	15
2.5.2 Low Velocity Impact Test on Composite	16
2.6 High Velocity Impact Testing	17
2.6.1 Single Stage Gas Gun	17
2.6.2 High Velocity Impact Test on Composite	18
2.7 Factors Influencing Impact Characteristics	18
2.7.1 Effect of Fibre Properties	18
2.7.2 Effect of Specimen Thickness	18
2.7.3 Effect of Projectile Shape and mass	19
2.7.4 Effect of Projectile Velocity	19
2.8 Failure Modes in Impact Test	20
2.8.1 Matrix Cracking	20
2.8.2 Delamination	21
2.8.3 Fibre Failure	21

2.9	Structural Health Monitoring (SHM) for Composite Material	22
2.10	Conclusion	23
3	MATERIALS AND EXPERIMENTAL METHODOLOGY	
3.1	Introduction	25
3.2	Material Selection and Fabrication Processes	25
3.2.1	Material Preparation	26
3.2.2	Hand Lay-Up Process for Low Velocity Impact Testing	27
3.2.3	Fabrication Process for High Velocity Impact Testing	29
3.2.4	Specimen Cutting Process	33
3.3	Low Velocity Impact Test	34
3.3.1	Experimental Procedure for Using a Drop Weight Tester	34
3.4	High Velocity Impact Test	38
3.4.1	Experimental Procedure for Using the Single Stage Gas Gun (SSGG)	38
3.4.2	Impact Mechanics	41
3.4.3	Material Properties of the Projectile - Mild Steel	42
3.5	Experimental Procedure for Damage Detection	43
3.5.1	Dye Penetrant	43
3.5.2	Optical Microscope	44
3.5.3	Damage Area Calculation	45
3.6	Conclusion	45
4	LOW VELOCITY IMPACT TEST RESULTS AND DAMAGE ANALYSES	
4.1	Introduction	47
4.2	Results and Analyses from Low Velocity Impact Testing	47
4.2.1	Impact Force Analysis	47
4.2.2	Energy Absorbed Analysis	48
4.2.3	Variation of Maximum Impact Force and Impact Energy	54
4.2.4	Variation of Peak Energy and Impact Energy	55
4.2.5	Variation of Energy Absorbed and Impact Energy	55
4.2.6	Variation of Peak Displacement and Impact Energy	58
4.3	Results from Dye Penetrant Testing	60
4.4	Results from the Optical Microscope	63
4.5	Conclusion	64
5	HIGH VELOCITY IMPACT TEST RESULTS AND DAMAGE ANALYSES	
5.1	Introduction	67
5.2	Results and Analyses from High Velocity Impact Tests	67
5.2.1	Projectile Performance Analysis	69
5.2.2	Impact Force Analysis	71
5.2.3	Energy Absorbed Analysis	73
5.3	Results from Dye Penetrant Testing	77
5.3.1	Microscope Inspection	78
5.4	Conclusion	80

6	SUMMARY AND RECOMMENDATIONS FOR FUTURE RESEARCH	
	6.1 Summary Of Work Done	81
	6.1.1 Low Velocity Impact Test	81
	6.1.2 High Velocity Impact Test	82
	6.2 Recommendations for Future Research	82
	REFERENCES	83
	APPENDICES	92
	BIODATA OF STUDENT	119
	LIST OF PUBLICATIONS	120



LIST OF TABLES

Table		Page
1	Classes of composites	8
2	Fibre composites and their use in aircraft	8
3	Letter designation for Glass Fibre Reinforced Polymer (GFRP)	10
4	Mechanical properties of C-glass and E-glass	11
5	Typical tensile mechanical properties of epoxy	13
6	Elementary approaches of composites	14
7	Typical tensile mechanical properties of glass fibre composites manufactured by hand lay-up	15
8	Type of low velocity impact tester	16
9	Failure modes in an impacted plate	22
10	Properties of mixed compound	26
11	Laminate thickness for type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ² for the high velocity impact test	29
12	Number of plies used for type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ² for high velocity impact test	30
13	Apparatus needed for the process	32
14	GFRP laminates for both types with impact energy levels tested	37
15	Drop height and impactor velocity value based on impact energy level	38
16	Pressure tested for both GFRP laminates with three different shapes of projectile	42
17	Dimensions of the projectile	43
18	Low velocity impact testing results for Type C-glass/Epoxy 600 g/m ²	52
19	Low Velocity impact testing results for Type E-glass/Epoxy 800 g/m ²	53
20	Low velocity impact testing results for energy absorbed for Type C-glass/Epoxy 600 g/m ²	55
21	Low velocity impact testing results for energy absorbed for	56

	Type C-glass/Epoxy 800 g/m ²	
22	Low velocity impact testing results for peak displacement for Type C-glass/Epoxy 600 g/m ²	59
23	Low velocity impact testing results for peak displacement for Type E-glass/Epoxy 800 g/m ²	59
24	Low velocity impact testing results on damaged area for Type C-glass/Epoxy 600 g/m ²	61
25	Low velocity impact testing results on damaged area for Type E-glass/Epoxy 800 g/m ²	61
26	Microscope images for Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ²	63
27	Impact test results for GFRP Type C-glass/Epoxy 600 g/m ²	67
28	Impact test results for GFRP Type E-glass/Epoxy 800 g/m ²	68
29	Projectile velocity and kinetic energy for blunt, conical and hemispherical	69
30	Failure modes for GFRP Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ² for (a) 6 mm (b) 8 mm (c) 10 mm (d) 12 mm	79

LIST OF FIGURES

Figure		Page
1	Formation of composite material using fibres and resin	1
2	Typical composite structures used in A330 commercial aircraft	2
3	Properties that can be improved after producing a composite	2
4	Fibres-reinforced composites for infrastructural parts	3
5	Boeing 787 material distribution	9
6	Woven fabric Glass Fibre Reinforced Polymer (GFRP)	14
7	Possible failure modes in composites	20
8	Failure modes in impacted plate	21
9	Types of structural health monitoring method	23
10	Items needed for material cutting process (a) dry Glass Fibre Reinforced Polymer (GFRP) (b) cutting items (c) fibreglass cloth 350 mm × 350 mm	27
11	Apparatus needed for the lay-up process	28
12	Apparatus needed for cleaning process	30
13	Some of the apparatus needed for the process (a) hot bonder machine (b) thermocouple, flash tape, vacuum port (c) sealant tape (d) teflon (e) caul plate (f) heat blanket (g) breather (h) vacuum bag	31
14	Lay-up configuration using hot bonder machine	32
15	CNC Router Machine a) table b) controller	33
16	Situation during the cutting process a) before the specimen is cut b) specimen being cut for low velocity impact testing c) specimen being cut for high velocity impact testing	34
17	Parts of the drop weight apparatus; a) tower, b) control unit c) computer d) striker	35
18	Specimen holder for the impact machine	36
19	Procedure for using a drop weight tester	36
20	Schematic drawing for single stage gas gun used in Universiti Malaysia Pahang	38

21	Machine setup for single stage gas gun	39
22	Pressure reservoir unit and other mechanism units for the single stage gas gun	39
23	Catch chamber unit	40
24	Specimens within the specimen clamping section	40
25	Procedures in high velocity impact testing	41
26	Type of projectile used in impact testing a) blunt b) conical c) hemispherical	42
27	Spotcheck SKL-SP2 dye penetrant	43
28	Apparatus for dye penetrant testing	44
29	Equipment needed for optical microscope testing	44
30	Force-time history plots for 10, 12 and 14-ply Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ²	48
31	Energy-time curve for 10, 12 and 14-ply for Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ² .	49
32	Force-displacement curve at impact energy 12J for Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ²	50
33	Force-displacement curve at impact energy 48 J for Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ²	52
34	Peak Impact Force-Impact Energy curve for Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ²	54
35	Peak Energy-Impact Energy curve for Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ²	55
36	Energy Absorbed-Impact Energy curve for Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ²	57
37	Percentage of Energy Absorbed-Impact Energy curve for Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ²	58
38	Peak Displacement-Impact Energy for Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ²	60
39	Damaged Area-Impact Energy for Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ²	62
40	Projectile Velocity-Pressure curve for blunt, conical and hemispherical shapes of projectile	70
41	Kinetic Energy-Pressure curve for blunt, conical and hemispherical shapes of projectile	71

42	Maximum Force–Pressure curve for (a) 6 mm (b) 8 mm (c) 10 mm (d) 12 mm thickness for Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ²	72
43	Absorbed Energy-Pressure curve for 6 mm, 8 mm, 10 mm and 12 mm thickness for Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ²	74
44	Absorbed Energy-Maximum Force curve for (a) 6 mm (b) 8 mm (c) 10 mm (d) 12 mm thickness for Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ²	76
45	Averaged Damaged Area-Pressure for Type C-glass/Epoxy 600 g/m ² and Type E-glass/Epoxy 800 g/m ² for (a) 6 mm (b) 8 mm (c) 10 mm (d) 12 mm	78



LIST OF SYMBOLS AND ABBREVIATIONS

LVI	Low velocity impact
GFRP	Glass Fibre Reinforced Polymer
BSS	Boeing Specification Support
ASTM	American Society for Testing and Materials
ASME	American Society of Mechanical Engineers
IATA	International Air Transport Association
UV	Ultraviolet
VID	Visible impact damage
BVID	Barely visible impact damage
AE	Absorbed energy
E_o	Maximum energy
F	Force
J	Joule
N	Newton
mm	Millimetre
m/s	Metre per second
ms	Millisecond
t	Time
m	Mass
g	Gravitational acceleration

CHAPTER 1

INTRODUCTION

1.1 Overview

A composite material is a combination of two or more materials and it creates a new material with a unique combination of properties. Normally, composite material is formed by reinforcing fibres in a matrix resin as shown in Figure 1. The strength and stiffness of the composites is provided by the reinforcing fibre or fabric, while the rigidity and environmental resistance of the composite is provided by the matrix.

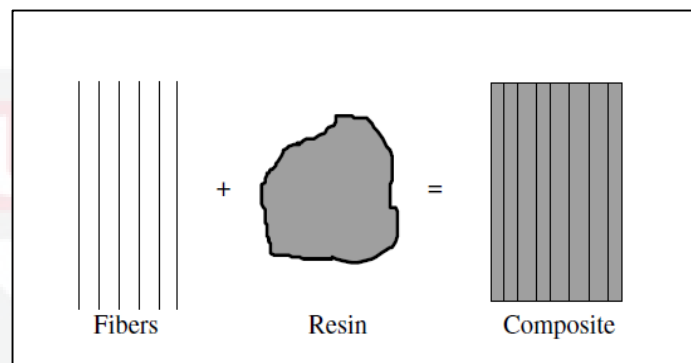


Figure 1: Formation of composite material using fibres and resin (Mazumdar, 2002).

Composites made with a polymer matrix have become more common and are widely used in various industries. In the mid-1960s and early-1970s, composites started to be developed in the aircraft industry. The military were the initial inventors and users of composites where the high performance composites were applied on the empennages of the F-14 and F-15 fighter aircraft. The F-15 fighter aircraft used Boron/epoxy for the horizontal stabilisers, rudders and vertical fins. In the mid-1970s, the fighter aircraft F-15 used carbon/epoxy for the speed brake (Campbell, 2006). In the past few decades, the use of composites in structural applications, especially in the aerospace industry has been increasing as shown in Figure 2.

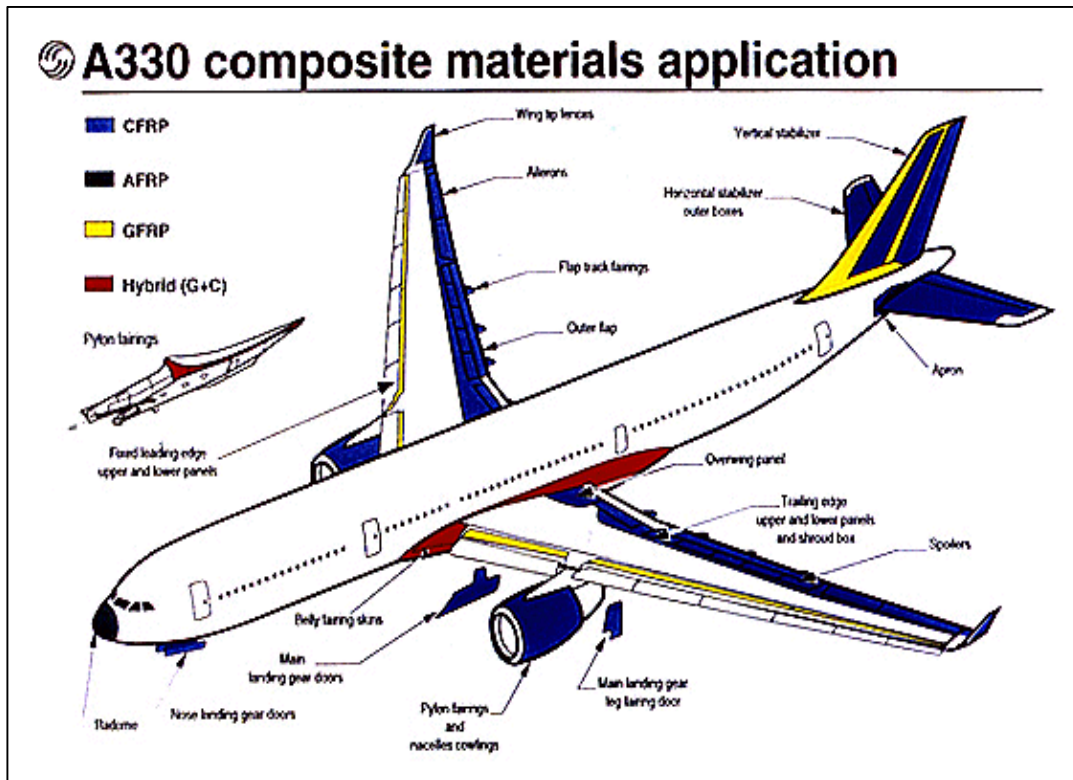


Figure 2: Typical composite structures used in A330 commercial aircraft (Crown, 2003).

The manufacturers have used various techniques to improve the impact resistance and damage tolerance characteristics of fibre composites. The advantages of composite materials are that they can have the best qualities of their original material and often some qualities that neither element possesses. Some of the properties that can be improved by forming a composite material are as shown in Figure 3.

Strength	Weight	Stiffness	Wear resistance
Corrosion resistance	Fatigue life	Thermal conductivity	Acoustical insulation

Figure 3: Properties that can be improved after producing a composite (Jones, 1998)

Composites are used not only for their mechanical properties, which are best for the applications that need good weight to strength ratio, but also for electrical, thermal, tribological and environmental applications (Vijaykumar, 2014). The application of composite materials has become increasingly popular, especially in aerospace structures.

The advantages of using composites in aircraft structures are; weight reduction, high corrosion resistance and high resistance to damage from fatigue. These factors play a role in reducing the operating costs of the aircraft in the long term, further improving its efficiency. Lately composites have been used in beam-type structures under high loading rates, such as the drive shafts in vehicles, the rotor blades of helicopters, the intake fan blades of jet engines and the entire composite wing of a spacecraft (Chatelet, Lornage, & Jacquet-Richardet, 2002).

In structural industry however, corrosion is one of the biggest problems experienced. As an example, in the marine industry, they start to use composites in boats or ships structure since composites do not corrode like metals. This advantage of composites is also chosen for roads and bridges, since roads and bridges are easily corroded. Composites offer a longer life span with less maintenance due to their corrosion resistance (Campbell, 2006). Figure 4 shows the composite designs in infrastructural applications.



Figure 4: Fibres-reinforced composites for infrastructural parts (Park & Seo, 2011).

Glass Fibre Reinforced Polymer (GFRP) is a type of polymer matrix composite (PMC) that has been widely used throughout the structure of large civil aircraft due to its high specific strength, stiffness and good fatigue resistance. It is the most economical choice depending on the cost of the material, the production cost, the life cycle cost, and the material's properties. In recent years, there has been an increasing demand to reduce the weight of the armour structures used in various applications such as tanks and helicopters. This weight reduction results in improved mobility, improved fuel efficiency and the transportability of the armoured vehicle. Glass Fibre Reinforced Polymer (GFRP) is light weight with the ability to resist heavy loads and supply excellent resistance to impact.

However, laminated composite, as example, aircraft components are at risk of impact from runway debris, hail and birds. This research studies the structural integrity of Glass Fibre Reinforced Polymer (GFRP) structures under low and high velocity impacts. Impact damage is an important issue for composites because composites are brittle. Composites only absorb energy in elastic deformation and damage mechanisms. The term damage resistance denotes the sum of the impact damage which is induced in a composite structure (Agrawal, Singh, & Sarkar, 2014).

Impact behaviours and impact damage depend on many parameters such as the projectile/impactor shape, impact velocity and energy, boundary conditions and lay-up sequence (Chib, 2006). Furthermore, laminated fibre reinforced composite materials have various damage modes such as fibre breakage, matrix cracking, and delamination. These various damage modes appear together under the impact loading (Kim, Rim, Lee, & Hwang, 2013).

GFRP has many important properties which make it suitable to be widely used in any structural applications. More on the structural application for GFRP are discussed in chapter 2. Therefore, this research is intended to determine the performance of GFRP under low velocity impact and high velocity impact loading since structures are always at risk of experiencing these events.

1.2 Problem Statements

A question that is naturally raised is how to improve the survivability of structures regarding low and high velocity impacts. Since structural failure is caused primarily by fracture, a fundamental understanding of the mechanisms and mechanics of the material is one of the most important steps needed to solve the problem. In a high velocity impact, fracture often occurs in an impacted zone where compression is dominant. For a low velocity impact, invisible cracks often occur, but they cannot be seen using the naked eye. It is important to understand the deformation and damage mechanisms involved in the impact of targets, for the effective design of composite structures.

There are a lot of Glass Fibre Reinforced Polymer (GFRP) types based on their special characteristics. Glass Fibre Reinforced Polymer (GFRP) type E is mostly used to reinforce composite structures compared to others. Glass Fibre Reinforced Polymer (GFRP) type E and Glass Fibre Reinforced Polymer (GFRP) type C are similar, but each are designed to serve to their advantage in specific end user. However, Glass Fibre Reinforced Polymer (GFRP) type C has high corrosion resistance in acidic environment and type E is useful when strength and high electrical resistivity is needed (Richerson, 1997).

The ultimate objective of this research is to conduct an experimental investigation using low velocity impact testing and high velocity impact testing to detect and quantify impact damage for Glass Fibre Reinforced Polymer Type C-glass/Epoxy 600 g/m² and Type E-glass/Epoxy 800 g/m² plate. Therefore, the purpose of this research is to choose the best material for structural application by comparing the mechanical properties and damage characteristics of GFRP Type C-glass/Epoxy 600 g/m² and Type E-glass/Epoxy 800 g/m².

Previous researches have usually involved experiments on the impact parameter effects that may affect the impact test result. Very limited researches have been carried out in comparing these two types of materials. It is important to understand the differences in impact response between Glass Fibre Reinforced Polymer (GFRP) Type C-glass/Epoxy 600 g/m² and Type E-glass/Epoxy 800 g/m² since both of these materials are rarely used in structural application even though it is the best choice for weight to strength application.

Therefore, this thesis is intended to compare the impact response of Glass Fibre Reinforced Polymer (GFRP) Type C-glass/Epoxy 600 g/m² and Type E-glass/Epoxy 800 g/m² using two different types of impact test, which are low velocity impact testing and high velocity impact testing.

For the high velocity impact test, Glass Fibre Reinforced Polymer Type C-glass/Epoxy 600 g/m² and Type E-glass/Epoxy 800 g/m² plates were tested using a single stage gas gun (SSGG) with varying gas gun pressures, different projectile shapes and different target specimen thicknesses. For the low velocity impact test, Glass Fibre Reinforced Polymer Type C-glass/Epoxy 600 g/m² and Type E-glass/Epoxy 800 g/m² plates were tested using the drop weight impact test, where the impact energy and the specimen thickness are varied. These tests will produce results that will show the impact performance for both materials.

1.3 Research Aim and Objectives

The present research aims to conduct an experimental investigation on two types of Glass Fibre Reinforced Polymer (GFRP) Type C-glass/Epoxy 600 g/m² and Type E-glass/Epoxy 800 g/m² using low velocity impact testing and high velocity impact testing.

The study is divided into three objectives. The objectives in this work are:

- i. To fabricate low velocity impact test specimens using a traditional hand lay-up techniques and to manufacture high velocity impact test specimens with the aid of a hot bonder machine and vacuum bagging.
- ii. To investigate the effect of the number of layers on the impact characteristics and failure modes of Glass Fibre Reinforced Polymer (GFRP) Type C-glass/Epoxy 600 g/m² and Type E-glass/Epoxy 800 g/m² at different impact energy levels using a drop weight tester and non-destructive testing.
- iii. To investigate the effect of specimen's thickness, the type of projectiles and the impact velocity on the impact characteristics and failure modes of Glass Fibre Reinforced Polymer (GFRP) Type C-glass/Epoxy 600 g/m² and Type E-glass/Epoxy 800 g/m² using a single stage gas gun (SSGG) and non-destructive testing.

1.4 Structure of the Thesis

This thesis consists of six chapters, which can be described as follows:

- i. Chapter 1 presents an overview of the whole thesis including the problem statement and the research objectives for the whole research and the contribution from this research.
- ii. Chapter 2 presents a critical literature review on composite material, especially Glass Fibre Reinforced Polymer (GFRP), an overview on low velocity impact testing and high velocity impact testing, and damage identification using structural health monitoring.

- iii. Chapter 3 describes the procedure for fabricating impact test specimens and the experimental work performed using low velocity and high velocity impact test rigs. This chapter also explains in detail the damage detection method use to examine the failure mode for the impacted test specimen.
- iv. Chapter 4 presents and discusses the low velocity impact test results for Glass Fibre Reinforced Polymer (GFRP) Type C-glass/Epoxy 600 g/m² and Type E-glass/Epoxy 800 g/m². Critical analysis and damage analysis of the impacted specimen is also presented in this chapter.
- v. Chapter 5 presents the high velocity impact test results for Glass Fibre Reinforced Polymer (GFRP) Type C-glass/Epoxy 600 g/m² and Type E-glass/Epoxy 800 g/m². This chapter also discusses and analyses impact specimens using the damage detection method.
- vi. Chapter 6 presents the research conclusions, summarises the major results, and gives suggestions for future work.

REFERENCES

- Magnaflux. (2014). Retrieved July 5, 2014, from Magnaflux Web Site: [http://www.magnaflux.com/Products/LiquidPenetrantInspection/MaterialsVisible\(Spotcheck\)/SolventRemovablePenetrant/SKLSP2/tabid/91/Default.aspx](http://www.magnaflux.com/Products/LiquidPenetrantInspection/MaterialsVisible(Spotcheck)/SolventRemovablePenetrant/SKLSP2/tabid/91/Default.aspx)
- Agrawal, S., Singh, K., & Sarkar, P. (2014). Impact damage on fibre-reinforced polymer matrix composite - A review. *Journal of Composite Materials*, 317.
- Amaro, A., Reis, P., Moura, M. d., & Neto, M. (2013). Influence of multi-impacts on GFRP composites laminates. *Composites: Part B*, 93-99.
- Aslan, Z., Karakuzu, R., & Okutan, B. (2003). The response of laminated composites under low-velocity impact loading. *Composite Structures*, 119-127.
- ASTM, A. S. (2006). *ASTM D4812-06: Standard Test Method for Unnotched Cantilever Beam Impact Resistance of Plastics*.
- Atas, C., Icten, B., & Küçük, M. (2013). Thickness effect on repeated impact response of woven fabric composite plates. *Composites: Part B*, 80-85.
- Awerbuch, J., & Bodner, S. R. (1974). Analysis of the mechanics of perforation of projectiles in metallic plates. *International Journal of Solids and Structures*, 671-684.
- Belingardi, G., & Vadori, R. (2002). Low velocity impact tests of laminate glass-fibre-epoxy matrix composite material plates. *International Journal Impact Engineering*, 27, 213-229.
- Bernier, H. (2005). Scaling and Designing Large-Bore Two-Stage High Velocity Guns. In L. C. Chhabildas, L. Davison, & Y. Horie, *High-Pressure Shock Compression of Solids VIII- The Science and Technology of High-Velocity Impact* (pp. 37-83). New York : Springer .
- Bibo, G., & Hogg, P. (1998). Influence of reinforcement architecture on glass-fibre/epoxy composite systems. *Composite Science Technology*, 803-813.
- Boeing. (1988). Advanced composite compression tests BSS 7260. In *Boeing Specification Support Standard BSS 7260*. Washington: Boeing Spec Support Std.
- Borvik, T., Langseth, M., Hopperstad, O. S., & Mal, K. A. (2002). Perforation of 12mm thick steel plates by 20mm diameter projectiles with flat, hemispherical and conical noses Part I: Experimental study. *International Journal of Impact Engineering*, 19-35.
- Breen, C., Guild, F., & Pavier, M. (2005). Impact of thick CFRP laminates: the effect of impact velocity. *Composites Part A*, 205-211.

- C. Atas, D. L. (2008). Impact response of woven composites with small weaving angles. *International Journal Impact Engineering*, 80-97.
- Campbell, F. C. (2006). Introduction. In F. C. Campbell, *Manufacturing Technology for Aerospace Structural Materials* (pp. 5-13). USA: Elsevier Ltd.
- Cantwell, W. J., & Morton, J. (1989). Geometrical Effects in the Low Velocity Impact Response of CFRP. *Composite Structures*, 39-59.
- Cantwell, W. J., & Morton, J. (1991). The Impact Resistance of Composite Materials – A review. *Composites*, 347-362.
- (2008). Composite Materials. In F. Cardarelli, *Materials Handbook* (pp. 1020-1035). Arizona: Springer Science & Business Media .
- Chatelet, E., Lornage, D., & Jacquet-Richardet, G. (2002). A three-dimensional modelling of the dynamic behaviour of composite rotors. *International Journal Rotating Machinery*, 185-192.
- Chib, A. (2006). *Parametric study of low velocity impact analysis on composite tubes*. India: University of Pune.
- Corran, R., Shadbolt, P. J., & Ruiz, C. (1983). Impact loading of plates Fan experimental investigatio. *International Journal of Impact Engineering*, 3-22.
- Cromer, K., Gillespie, J., & Keefe, M. (2012). Effect of non-coincident impacts on residual properties of glass/epoxy laminates. *Journal of Reinforced Plastics and Composites*, 815-827.
- Crown. (2003). *Material Solutions Polymer Composite*. Retrieved August 21, 2014, from Material Solutions Polymer Composite: <http://www.admc.esrtechnology.com/CDKB/Sectors/Aerospace/Approach.aspx?Sector=1&Element=-1>
- D. Ghelli, G. M. (2011). Low velocity impact and compression after impact tests on thin carbon/epoxy laminates. *Composites: Part B*, 2067-2079.
- Davies, G. (1996). Impact damage and residual woven fabric glass/polyester strengths of laminates. *Composite A: Applied Science Manufacturing*, 1147-1156.
- Davies, G., Hitchings, D., & Ankersen, J. (2006). Predicting delamination and debonding in modern aerospace composite structures. *Composite Science Technology*, 846-54.
- Diamanti, K., & Soutis, C. (2010). Structural health monitoring techniques for aircraft composite structures. *Progress in Aerospace Sciences*, 343-352.

- Duell, J. M. (2004). Impact Testing of Advanced Composites. In M. R. Kessler, *Advanced Topics in Characterization of Composites* (pp. 97-112). Trafford Publishing.
- E. Sevkhat, B. L. (2010). Effect of repeated impacts on the response of plain-woven hybrid composites. *Composite: Part B*, 403-413.
- Epoxy Resin/ Hardener Zeepoxy HL002 TA/B. (n.d.). Shah Alam, Selangor, Malaysia: My East Sdn Bhd.
- FAA. (2012). Advanced Composite Materials . In F. A. Administration, *Volume 1 of Aviation Maintenance Technician Handbook - Airframe* (pp. 7-1 - 7-56). AMT Exams.
- Farooq, U., & Gregory, K. (2009). Finite Element Simulation of Low Velocity Impact Damage Morphology in Quasi-Isotropic Composite Panels under Variable Shape Impactors. *European Journal of Scientific Research*, 636-648.
- Findlay, S. J., & Harrison, N. D. (2002, November). Why aircraft fail. *Materials Today*, 5(11), 18-25.
- García-Castillo, S., Sánchez-Sáez, S., Santiuste, C., Navarro, C., & Barbero, E. (2013). Perforation of Composite Laminate Subjected to Dynamic Loads. In S. Abrate, B. Castanié, & Y. Rajapakse, *Dynamic Failure of Composite and Sandwich Structures* (pp. 291-337). Springer Netherlands.
- Gellert, E. P., Cimpoeru, S. J., & Woodward, R. L. (2000). A study of the effect of target thickness on the ballistic perforation of glass fibre-reinforced plastic composites. *International Journal of Impact Engineering*, 445-456.
- Ghasemnejad, H., Soroush, V. R., & Mason, P. J. (2012). To improve impact damage response of single and multi-delaminated FRP composites using natural Flax yarn. *Materials and Design*, 865-873.
- Ghasemnejad, H., Furquan, A. S., & Mason, P. J. (2010). Charpy impact damage behaviour of single and multi-delaminated hybrid composite beam structures. *Materials and Design*, 3653-3660.
- Giurgiutiu, V., & Soutis, C. (2012). Enhanced Composites Integrity Through Structural Health Monitoring. *Applied Composite Materials*, 19(5), 813-829.
- GmbH, S. I. (1998). *Saint Mary University*. Retrieved June 9, 2014, from Saint Mary University: <http://www.smu.ca/webfiles/analysis30.pdf>
- Goel, V. (2007). *Fundamentals of Physics Xi*. New Delhi : Tata McGraw-Hill Education.

- Grady, D. E., & Winfree, N. A. (2001). Impact fragmentation of high-velocity compact projectiles on thin plates: a physical and statistical characterization of fragment debris. *International Journal Impact Engineering*, 249-62.
- Grytten, F. (2008). *Low-Velocity Penetration of Aluminium Plates*. Trondheim.
- Handbook. (2002). MIL-HDBK-17-3F: Composite Materials Handbook, Polymer Matrix. *Composites: Materials Usage, Design, and Analysis*, 3.
- Hassan, M., Guan, Z., Cantwell, W., Langdon, G., & Nurick, G. (2012, December). The influence of core density on the blast resistance of foam-based sandwich structures. *International Journal of Impact Engineering*, 50, 9-16.
- Hausrath, R. L., & Longobardo, A. V. (2010). High-Strength Glass Fibers and Markets. In F. T. Wallenberger, & P. A. Bingham, *Fiberglass and Glass Technology* (pp. 197-225). USA: Springer Science+Business Media.
- Hirai, Y., Hamada, H., & Kim, J.-K. (1998). Impact Response Of Woven Glass Fabric Composites-1 Effect of Fibre Surface Treatment . *Composites Science and Technology*, 91-104.
- Hollaway, L. C. (2010). A review of the present and future utilisation of FRP composites in the civil infrastructure with reference to their important in-service properties. *Construction and Building Materials*, 2419-2445.
- Hollaway, L. C., & Head, P. R. (2001). Manufacture and properties of advanced polymer composites relevant to civil engineering. In L. C. Hollaway, & P. R. Head, *Advanced Polymer Composites and Polymers in the Civil Infrastructure* (pp. 37-88). Elsevier .
- Hosur, M., Chowdhury, F., & Jeelani, S. (2007). Low Velocity Impact Response and Ultrasonic NDE of Woven Carbon/Epoxy - Nanoclay Nanocomposites . *Journal of Composite Materials*, 2195-2212.
- Hufenbach, W., Ibraim, F. M., Langkamp, A., Böhm, R., & Hornig, A. (2008, September). Charpy impact tests on composite structures – An experimental and numerical investigation. *Composites Science and Technology*, 68(12), 2391-2400.
- Ilcewicz, L., Cheng, L., Hafenricher, J., & Seaton, C. (2009). *Guidelines for the Development of a Critical Composite Maintenance and Repair Issues Awareness Course*. Washington : U.S. Department of Transportation .
- Imatek. (n.d.). *Imatek*. Retrieved July 15, 2014, from Imatek: <http://www.imatek.co.uk/downloads/product-brief-im10t.pdf>
- Jones, R. M. (1998). *Mechanics Of Composite Materials*. CRC Press.

- Kim, E.-H., Rim, M.-S., Lee, I., & Hwang, T.-K. (2013). Composite damage model based on continuum damage mechanics and low velocity impact analysis of composite plates. *Composites Structures*, 123–134.
- L.S. Sutherland, C. S. (2005). Impact characterisation of low fibre-volume glass reinforced polyester circular laminated plates. *International Journal of Impact Engineering*, 1-23.
- Laliberté, J. F., Poon, C., Straznicky, P. V., & Fahr, A. (2004). Applications of fiber-metal laminates. *Polymer Composite*, 558-567.
- Lee, L., Huang, K., & Fann, Y. (1993). Dynamic Responses of Composite Sandwich Plate Impacted by a Rigid Ball. *Journal of Composite Materials*, 1238-1256.
- Lessard, L., Hosseinzadeh, R., & Shokrich, M. M. (2006). Damage Behavior of Fibre Reinforced Composite Plates Subjected to Drop Weight Impacts. *Composite Science and Technology*, 61-68.
- Manikandan, V., Jappes, J., Kumar, S., & Amuthakkannan, P. (2012). Investigation of the Effect of Surface Modifications on the Mechanical Properties of Basalt Fibre Reinforced Polymer Composites. *Composites: Part B*, 812-818.
- Mathivanan, N. R., & Jerald, J. (2010). Experimental investigation of low-velocity impact characteristics of woven. *Materials and Design*, 4553-4560.
- Mazumdar, S. K. (2002). *Composites Manufacturing: Materials, Product and Process Engineering*. CRC Press.
- Meola, C., & Carlomagno, G. M. (2010). Impact damage in GFRP: New insights with infrared thermography. *Composites: Part A*, 1839-1847.
- Mili, F. (2012). Effect of the Impact Velocity on the Dynamic Response of E-Glass/Epoxy Laminated Composites. *Arabian Journal for Science and Engineering*, 413-419.
- Mitrevski, T., Marshall, I., Thomson, R., & Jones, R. (2006). Low-velocity impacts on preloaded GFRP specimens with various impactor shapes. *Composite Structures*, 209-217.
- Mitrevski, T., Marshall, I., Thomson, R., & Jones, R. (2006). The influence of impactor shape on the damage to the composite laminates. *Composite Structures*, 116-122.
- Mitrevski, T., Marshall, I., Thomson, R., Jones, R., & Whittingham, B. (2005). The effect of impactor shape on the impact response of composite laminates. *Composite Structures*, 139-148.
- Mortensen, A. (2006). *Concise Encyclopedia of Composite Materials*. Elsevier.

- Murphy, J. (1998). Reinforcements. In J. Murphy, *The Reinforced Plastics Handbook* (pp. 24-108). Elsevier .
- Naik, N. K., & Doshi, A. (2008). Ballistic impact behaviour of thick composites: Parametric studies. *Composite Structures*, 447-464.
- Naik, N. K., & Shrirao, P. (2004). Composite structures under ballistic impact. *Composite Structures*, 579-590.
- Naik, N. K., Sekher, Y. C., & Meduri, S. (2000). Damage in woven-fabric composites subjected to low-velocity impact. *Composites Science and Technology*, 731-744.
- Nasirzadeh, R., & Sabet, A. (2014). Study of Foam Density Variations in Composite Sandwich Panels under High Velocity Impact Loading. *International Journal of Impact Engineering*, 63, 129-139.
- Nkurunziza, G., Debaiky, A., & Cousin, P. (2005, October 10). Durability of GFRP bars: A critical review of the literature. *Progress in Structural Engineering and Materials*, 7(4), 194-209.
- Olympus America*. (n.d.). Retrieved June 15, 2014, from Microscopy Resource Center: <http://www.olympusmicro.com/brochures/pdfs/bx51.pdf>
- Othe, S., Yoshizawa, H., Chiba, N., & Shida, S. (1982). Impact strength of steel plates struck by projectiles. *Bulletin JSME*, 1226-1231.
- Pahang, U. M. (2013). Operation Manual- One (01) Unit Single Stage Compressed Gas Gun . Pekan, Pahang, Malaysia: Universiti Malaysia Pahang .
- Pandya, K. S., Pothnis, J. R., & Ravikumar, G. (2013). Ballistic impact behavior of hybrid composites. *Materials and Design*, 128-135.
- Park, S., & Seo, M.-K. (2011). *Interface Science and Composites*. Academic Press.
- Pernas-Sánchez, J., Pedroche, D., Varas, D., López-Puente, J., & Zaera, R. (2012, July). Numerical modeling of ice behavior under high velocity impacts. *International Journal of Solids and Structures*, 49(14), 1919–1927.
- Petrone, G., D'Alessandro, V., Franco, F., Maceb, B., & De Rosaa, S. (2014, July). Modal characterisation of recyclable foam sandwich panels. *Composite Structures*, 113, 362-368.
- Prichard, J., & Hogg, P. (1990). The role of impact damage in post-impact compression testing. *Composites*, 503-511.

- Raju, B., Liu, D., & Dang, X. (1998). Thickness effects on impact response of composite laminates. *13th Annual Technical Conference on Composite Materials*. Baltimore, Maryland: American Society for Composites.
- Richardson, M., & Wisheart, M. (1996). Review of low-velocity impact properties of composite materials. *Composites Part A*, 1123-1131.
- Richerson, D. (1997). Ceramic Matrix Composites. In P. Mallick, *Composites Engineering Handbook Materials Engineering* (pp. 983-1039). CRC Press.
- Rilo, N., & Ferreira, L. (2008). Experimental study of low-velocity impacts on glass-epoxy laminated composite plates. *International Journal of Mechanics and Materials in Design*.
- Rocha, B., Silva, C., Keulen, C., & Yildiz, M. (2013). Structural Health Monitoring of Aircraft. In W. Ostachowicz, & J. Güemes, *New Trends in Structural Health Monitoring* (pp. 81-148). Springer Vienna.
- Shaktivesh, Nair, N. S., Sesa Kumar, C. V., & Naik, N. K. (2013). Ballistic impact performance of composite targets. *Materials and Design*, 833-846.
- Shivakumar, K. N., Elber, W., & Illg, W. (1985). Prediction of low velocity impact damage in thin circular laminates. *American Institute of Aeronautics and Astronautics Journal*, 442-449.
- Sikarwar, R., Velmurugan, R., & Gupta, N. (2014). Influence of fiber orientation and thickness on the response of glass/epoxy composites subjected to impact loading. *Composites: Part B*, 627-636.
- (2012). Penetrant Testing . In R. Singh, *Applied Welding Engineering: Processes, Codes and Standards*. (pp. 283-291). Oxford : Elsevier .
- Sjoblom, P. O., Hartness, J. T., & Cordell, T. M. (1988). On low-velocity impact testing of composite materials. *Journal of Composite Materials* , 30-52.
- Sultan, M. (2007). *High Velocity Impact Analysis of Glass Epoxy Laminated Plates*. Serdang: Universiti Putra Malaysia.
- Sultan, M., Worden, K., Pierce, S., Hickey, D., Staszewski, W., Dulieu-Barton, J., et al. (2011). On impact damage detection and quantification for CFRP laminates using structural response data only. *Mechanical Systems and Signal Processing*, 25, 3135–3152.
- Sultan, M., Worden, K., Staszewski, W., & Hodzic, A. (2012). Impact Damage Characterisation of Composite Laminates Using A Statistical Approach. *Composites Science and Technology*, 1008-1120.

- Sun, C. T., & Potti, S. V. (1996). A Simple Model To Predict Residual Velocities of Thick Composites Laminates Subjected to High Velocity Impact . *International Journal of Impact Engineering* , 339-353.
- Sutherland, L., & Soares, C. (2005). Impact of low fibre-volume, glass/polyester rectangular plates. *Composite Structure*, 13-22.
- Swift, H. F. (2005). Light-Gas Gun Technology: A Historical Perspective. In L. C. Chhabildas, L. Davison, & Y. Horie, *High-Pressure Shock Compression of Solids VIII* (pp. 1-35). Springer Berlin Heidelberg.
- Taylor, R. (2008). *Fibre Composite Aircraft - Capability and Safety*. Australia: Australian Transport Safety Bureau.
- Thanomsilp, C., & Hogg, P. (2003). Penetration impact resistance of hybrid composites based on commingled yarn fabrics. *Composite Science Technology*, 467-482.
- Tita, V., Carvalho, J. d., & Vandepitte, D. (2008). Failure analysis of low velocity impact on thin composite laminates: Experimental and numerical approaches. *Composite Structures*, 413-428.
- Tobin, L., & Iremonger , M. (2006). *Modern body armour and helmets: An introduction*. Canberra : Argos Press.
- Udatha, P., Sessa Kumar, C., Nair NS, N., & Naik, N. (2012). High velocity impact performance of three-dimensional woven composites. *The Journal of Strain Analysis for Engineering Design* , 419-431.
- Ude, A., Ariffin, A., & Azhari, C. (2013). Impact damage characteristics in reinforced woven natural silk/epoxy composite face-sheet and sandwich foam, coremat and honeycomb materials. *International Journal of Impact Engineering*, 31-38.
- Ujihashi, S. (1993). An intelligent method to determine the mechanical properties of composites under impact loading. *Composite Structures*, 149-163.
- Uyaner, M., Kara, M., & Sahin , A. (2014). Fatigue behavior of filament wound E-glass/epoxy composite tubes. *Composites: Part B*, 61, 358–364.
- Vaidya, U. K. (2011). Impact Response of Laminated and Sandwich Composites. In S. Abrate, *Impact Engineering of Composite Structures* (pp. 97-191). Brimingham: Springer Wien New York .
- Vijaykumar, H. K. (2014). Analysis of the Flexure Behavior and Compressive Strength of Fly Ash Core Sandwiched Composite Material. *International Journal of Engineering Research and Applications*, 41-48.

- Vlot, A. (1993). Impact Properties of Fiber-Metal Laminates. *Composite Engineering*, 3, 911-927.
- Vlot, A. (1993). *Low velocity impact loading on fiber reinforced aluminium laminates (arall and glare) and other aircraft sheet material*. Delft University of Technology.
- Volf, M. (1990). *Technical Approach To Glass*. New York : Elsevier.
- Wallenberger, F. T., Watson, J. C., & Li, H. (2001). Glass Fibers. In *ASM Handbook* (pp. 27-34). Ohio: ASM International.
- Wen, H. (2000). Predicting the penetration and perforation of FRP laminates struck normally by projectiles with different nose shapes. *Composite Structures*, 321–329.
- Wen, H. (2001). Penetration and perforation of thick FRP laminates. *Composite Science Technology* , 1163-1172.
- Williams, J., & Birch, M. (2013). The Impact Testing of Polymers - A Reassessment. In D. Taplin, *Advances in Research on the Strength and Fracture of Materials: An Overview* (pp. 501-528). New York: Elsevier.
- Yashiro, S., Ogi, K., & Nakamura, T. (2013). Characterization of high-velocity impact damage in CFRP laminates: Part I – Experiment. *Composites: Part A*, 93-100.
- Zhang, Z., & Richardson, M. (2007). Low velocity impact induced damage evaluation and its effect on the residual flexural properties of pultruded GRP composites. *Composite Structures*, 195-201.
- Zhou, G. (1995). Damage mechanisms in composite laminates impacted by a flat-ended impactor. *Composites Science and Technology* , 267-273.
- Zhou, G. (1995). Prediction of impact damage thresholds of glass fibre reinforced laminates. *Composite Structure*, 185-193.
- Zukas, J. A. (1980). *Impact Dynamics: Theory and experiments*. Virginia: US ARMY ARMAMENT RESEARCH AND DEVELOPMENT COMMAND.