



UNIVERSITI PUTRA MALAYSIA

***EFFECTS OF pH ON THE PHYSICOCHEMICAL PROPERTIES OF
MoVTeNbO_x CATALYSTS FOR OXIDATION OF PROPANE***

SYAZWANI BINTI MOHD NOOR

FS 2015 33



**EFFECTS OF pH ON THE PHYSICOCHEMICAL PROPERTIES OF
MoVTeNbO_x CATALYSTS FOR OXIDATION OF PROPANE**

By

SYAZWANI BINTI MOHD NOOR

**Thesis Submitted to the School of Graduate Studies, Universiti Putra Malaysia, in
Fulfilment of the Requirements for the Degree of Master of Science**

June 2015

All material contained within the thesis, including without limitation text, logos, icons, photographs and all other artwork, is copyright material of Universiti Putra Malaysia unless otherwise stated. Use may be made of any material contained within the thesis for non-commercial purposes from the copyright holder. Commercial use of material may only be made with the express, prior, written permission of Universiti Putra Malaysia.

Copyright © Universiti Putra Malaysia



Abstract of thesis presented to the Senate of Universiti Putra Malaysia in fulfilment of the requirement for the degree of Master of Science

**EFFECTS OF pH ON THE PHYSICOCHEMICAL PROPERTIES OF
MoVTeNbO_x CATALYSTS FOR OXIDATION OF PROPANE**

By

SYAZWANI BINTI MOHD NOOR

June 2015

Chairman : Assoc. Prof. Irmawati Ramli, PhD
Faculty : Science

Mo_{0.1}V_{0.3}Te_{0.23}Nb_{0.12} mixed metal oxide catalysts were prepared via slurry method followed by microwave irradiation. The effect of pH was studied by varying the pH of the resultant solution at pH = 1.0, 3.0, 5.0 and 7.0 (± 0.01). The catalysts precursor obtained were calcined for 1 h in air at 553 K and 2 h in N₂ stream at 873 K. The catalysts were post treated by washing with 30% H₂O₂. An Anderson-type heteropolyanion was formed in samples prepared at pH 3.0–7.0 (± 0.01). After calcination, X-ray Diffraction Analysis (XRD) explained that the active orthorhombic M1 phase was obtained for samples prepared at lower pH (pH 1.0 and pH 3.0 (± 0.01)). From Fourier Transform-Infrared (FT-IR) spectra, no significant difference in the formation of functional group of different synthesised pH of the MoVTeNbO_x catalysts. Thermo Gravimetry-Differential Thermal Gravimetric Analysis (TG-DTG) for all samples show a similar thermal behaviour with four decomposition signals. Inductive Coupled Plasma-Atomic Emission Spectroscopy (ICP-AES) revealed that a remarkable loss of tellurium was observed after calcination. The catalysts borne rod-shaped morphology under Field Emission-Scanning Electron Microscopy (FE-SEM). XRD analysis after post treatment suggested the elimination of hexagonal M2 phase and modification of orthorhombic M1 crystal surfaces. Washing with hydrogen peroxide also gave better reducibility of the catalysts in Temperature Programmed Reduction in Hydrogen (H₂-TPR) by shifting the peak maximum to lower temperature compared to the unwashed catalysts. Brunauer-Emmett-Teller surface area analysis (S_{BET}) exposed that the catalysts prepared at lower pH value has a higher surface area than catalysts prepared at higher pH value. Overall, the catalytic study of MoVTeNbO_x catalysts revealed that catalyst prepared at pH 1.0 (± 0.01) has high selectivity towards acrylic acid in anaerobic oxidation of propane. Thus, the different synthesis pH has a strong effect on the final phase composition and distinct activities of MoVTeNbO_x catalysts.

Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia sebagai memenuhi keperluan untuk ijazah Master Sains

KESAN-KESAN pH TERHADAP SIFAT FIZIKOKIMIA MANGKIN MoVTeNbOx UNTUK PENGOKSIDAAN PROPANA

Oleh

SYAZWANI BINTI MOHD NOOR

Jun 2015

Pengerusi : Prof. Madya Irmawati Ramli, PhD
Fakulti : Sains

Mangkin $\text{Mo}_{0.1}\text{V}_{0.3}\text{Te}_{0.23}\text{Nb}_{0.12}$ campuran logam oksida telah disediakan dengan kaedah buburan diikuti oleh penyinaran gelombang mikro. Kesan pH telah dikaji dengan mengubah pH larutan yang dihasilkan kepada $\text{pH} = 1.0, 3.0, 5.0$ dan $7.0 (\pm 0.01)$. Mangkin prekursor yang diperoleh telah dikalsin selama 1 jam di dalam udara pada 553 K dan 2 jam di dalam aliran N_2 pada 873 K. Mangkin melalui pasca rawatan dengan pembasuhan menggunakan 30% H_2O_2 . Heteropolianion jenis Anderson telah terbentuk dalam sampel yang disediakan pada $\text{pH} 3.0-7.0 (\pm 0.01)$. Selepas dikalsinasi, analisis Pembelauan Sinar-X (XRD) menjelaskan bahawa fasa aktif ortorombik M1 diperoleh daripada sampel yang disediakan pada pH yang rendah ($\text{pH} 1.0$ dan $3.0 (\pm 0.01)$). Daripada spektrum Fourier Transformasi-Inframerah (FT-IR), tidak ada perbezaan yang signifikan terhadap pembentukan kumpulan berfungsi bagi mangkin MoVTeNbOx yang disintesis pada pH yang berbeza. Analisis Termogravimetri-Terbitan Termogravimetri (TG-DTG) bagi semua sampel menunjukkan sifat terma yang serupa dengan empat signal penguraian. Plasma Gandingan Teraruh-Spektroskopi Pancaran Atom (ICP-AES) menunjukkan bahawa pengurangan elemen telurium yang ketara diperhatikan selepas dikalsinasi. Mangkin menunjukkan morfologi berbentuk rod di bawah Mikroskopi Imbasan Elektron-Pancaran Medan (FE-SEM). Analisis XRD selepas pasca rawatan mencadangkan penghapusan fasa heksagonal M2 dan pengubahsuaian permukaan hablur fasa ortorombik M1. Pembasuhan dengan hidrogen peroksida juga memberikan mangkin kebolehturunan yang lebih baik dalam Penurunan Berprogramkan Suhu dalam Hidrogen (H_2 -TPR) dengan menganjakkkan puncak maksimum kepada suhu yang lebih rendah berbanding dengan mangkin yang tidak dibasuh. Analisis luas permukaan Brunauer-Emmett-Teller (S_{BET}) mendedahkan mangkin yang disediakan pada nilai pH yang lebih rendah mempunyai luas permukaan yang lebih tinggi berbanding mangkin yang disediakan pada nilai pH yang lebih tinggi. Secara keseluruhan, kajian pemangkin MoVTeNbOx mendedahkan bahawa mangkin yang disediakan pada $\text{pH} 1.0 (\pm 0.01)$ lebih selektif terhadap asid akrilik di dalam pengoksidaan anaerobik propana. Oleh itu, pH sintesis yang berbeza mempunyai pengaruh yang kuat terhadap komposisi fasa terakhir dan perbezaan aktiviti bagi mangkin MoVTeNbOx.

ACKNOWLEDGEMENTS

In the name of Allah, The Benevolent and Merciful.

I am using this opportunity to express my gratitude to everyone who supported me throughout the completion of this study. I am thankful for their aspiring guidance, invaluable constructive criticism and friendly advice during the research work. I am sincerely grateful to them for sharing their truthful and illuminating views on a number of issues related to the study.

I express my warm thanks, gratitude to my project supervisor, Associate Prof Dr. Irmawati binti Ramli for her extra supervision, guidance, suggestion, constructive supports and continuous supports throughout this study. I really appreciate her commitments towards this study and without supervision from her this study may become impossible.

I would also like to thank my Co-Supervisor, Prof Taufiq Yap Yun Hin for his constructive comments and suggestion to make this research became better. I also would like to thank to all the staff of Chemistry Department especially their kind assistance in order to get my project done in terms of technical guidance and material preparations which has contributed towards the success of this research.

In addition, my grateful thanks to all my friends in PutraCAT Laboratory for their help during my laboratory work. Your invaluable help make this study possible. We go through the up and down together and encourage each other for the future.

Last but not least, lots of love for my parents and family for their support and understanding through this journey.

Finally, I would like to express my deepest appreciation to all those who provided me the possibility to complete this research study.

I certify that a Thesis Examination Committee has met on 10 June 2015 to conduct the final examination of Syazwani binti Mohd Noor on her thesis entitled "Effects of pH on the Physicochemical Properties of MoVTenNbO_x Catalysts for Oxidation of Propane" in accordance with the Universities and University Colleges Act 1971 and the Constitution of the Universiti Putra Malaysia [P.U.(A) 106] 15 March 1998. The Committee recommends that the student be awarded the Master of Science.

Members of the Thesis Examination Committee were as follows:

Gwendoline Ee Cheng Lian, PhD

Professor
Faculty of Science
Universiti Putra Malaysia
(Chairman)

Tan Yen Ping, PhD

Senior Lecturer
Faculty of Science
Universiti Putra Malaysia
(Internal Examiner)

Mohd Zaizi bin Desa, PhD

Associate Professor
Faculty of Science
Universiti Putra Malaysia
(Internal Examiner)

Salasiah Endud, PhD

Associate Professor
Universiti Teknologi Malaysia
Malaysia
(External Examiner)



ZULKARNAIN ZAINAL, PhD

Professor and Deputy Dean
School of Graduate Studies
Universiti Putra Malaysia

Date: 12 August 2015

This thesis was submitted to the Senate of Universiti Putra Malaysia and has been accepted as fulfilment of the requirement for the degree of Master of Science. The members of the Supervisory Committee were as follows:

Irmawati Ramli, PhD

Associate Professor
Faculty of Science
Universiti Putra Malaysia
(Chairman)

Taufiq Yap Yun Hin, PhD

Professor
Faculty of Science
Universiti Putra Malaysia
(Member)

BUJANG KIM HUAT, PhD

Professor and Dean
School of Graduate Studies
Universiti Putra Malaysia

Date:

Declaration by graduate student

I hereby confirm that:

- this thesis is my original work;
- quotations, illustrations and citations have been duly referenced;
- this thesis has not been submitted previously or concurrently for any other degree at any other institutions;
- intellectual property from the thesis and copyright of thesis are fully-owned by Universiti Putra Malaysia, as according to the Universiti Putra Malaysia (Research) Rules 2012;
- written permission must be obtained from supervisor and the office of Deputy Vice-Chancellor (Research and Innovation) before thesis is published (in the form of written, printed or in electronic form) including books, journals, modules, proceedings, popular writings, seminar papers, manuscripts, posters, reports, lecture notes, learning modules or any other materials as stated in the Universiti Putra Malaysia (Research) Rules 2012;
- there is no plagiarism or data falsification/fabrication in the thesis, and scholarly integrity is upheld as according to the Universiti Putra Malaysia (Graduate Studies) Rules 2003 (Revision 2012-2013) and the Universiti Putra Malaysia (Research) Rules 2012. The thesis has undergone plagiarism detection software.

Signature: _____ Date: _____

Name and Matric No.: Syazwani Binti Mohd Noor (GS31585)

Declaration by Members of Supervisory Committee

This is to confirm that:

- the research conducted and the writing of this thesis was under our supervision;
- supervision responsibilities as stated in the Universiti Putra Malaysia (Graduate Studies) Rules 2003 (Revision 2012-2013) are adhered to.

Signature: _____

Name of
Chairman of
Supervisory
Committee:

Irmawati Ramli, PhD

Signature: _____

Name of
Member of
Supervisory
Committee:

Taufiq Yap Yun Hin, PhD

TABLE OF CONTENTS

	Page
ABSTRACT	i
ABSTRAK	ii
ACKNOWLEDGEMENTS	iii
APPROVAL	iv
DECLARATION	vi
LIST OF TABLES	x
LIST OF FIGURES	xi
LIST OF SCHEMES	xiii
LIST OF ABBREVIATIONS	xiv
CHAPTER	
1 INTRODUCTION	1
1.1 Background of study	1
1.1.1 Catalyst	1
1.1.2 Heterogeneous Catalysis	3
1.1.3 Acrylic Acid	4
1.1.4 Acrylic Acid Production	5
1.1.5 Propane as an Alternative Feedstock	6
1.2 Problem statement	7
1.3 Objectives of the study	8
1.4 Scope of the study	8
11 LITERATURE REVIEW	9
2.1 MoVTeNbOx Catalyst	9
2.1.1 Active Phase of MoVTeNbOx Catalyst	9
2.1.2 Role of Elements in MoVTeNbOx Catalyst	11
2.2 Synthesis of MoVTeNbOx Catalyst	12
2.2.1 Hydrothermal method	12
2.2.2 Slurry method	13
2.2.3 Microwave-assisted method	13
2.3 Synthesis Parameters	14
2.3.1 Effects of pH on MoVTeNbOx Catalyst	14
2.3.2 Effects of washing on MoVTeNbOx Catalyst	15
111 MATERIALS AND METHODS	17
3.1 Materials	17
3.2 Catalyst preparation	18
3.3 Characterisations	20
3.3.1 X-ray Diffraction Analysis (XRD)	20
3.3.2 Fourier Transform-Infrared Spectroscopy (FT-IR)	20
3.3.3 Thermo Gravimetry-Differential Thermal Gravimetric Analysis (TG-DTG)	21

3.3.4	Inductive Couple Plasma-Atomic Emission Spectroscopy (ICP-AES)	21
3.3.5	Field Emission-Scanning Electron Microscopy (FE-SEM)	22
3.3.6	Temperature Programmed Reduction in Hydrogen (H ₂ -TPR)	22
3.3.7	Brunauer-Emmett-Teller Surface Area Measurement (S _{BET})	22
3.3.8	Anaerobic Temperature Programmed Reduction (TPRn)	23
IV	RESULTS AND DISCUSSION	24
4.1	Preparation of MoVTeNbO _x catalysts	24
4.2	X-ray Diffraction Analysis (XRD)	24
4.3	Fourier Transform-Infrared Spectroscopy (FT-IR)	31
4.4	Thermo Gravimetry-Differential Thermal Gravimetric Analysis (TG-DTG)	37
4.5	Inductive Couple Plasma-Atomic Emission Spectroscopy (ICP-AES)	41
4.6	Field Emission-Scanning Electron Microscopy (FE-SEM)	43
4.7	Temperature Programmed Reduction in Hydrogen (H ₂ -TPR)	45
4.8	Brunauer-Emmett-Teller Surface Area Measurement (S _{BET})	51
4.9	Anaerobic Temperature Programmed Reduction (TPRn)	52
V	CONCLUSION AND RECOMMENDATIONS	57
5.1	Conclusion	57
5.2	Suggestions and Recommendations for Future Studies	58
	REFERENCES	59
	APPENDIX	64
	BIODATA OF STUDENT	66
	LIST OF PUBLICATIONS	67

LIST OF TABLES

Table		Page
1.1	Catalysts used for industrial production of acrylic acid (Lin, 2001)	6
3.1	List of chemicals used	17
3.2	List of gases used	17
4.1	List of samples synthesised in this study	24
4.2	Crystallite size of MVTN _{1c} , MVTN _{3c} , MVTN _{5c} and MVTN _{7c}	29
4.3	Crystallite size of MVTN _{1w} , MVTN _{3w} , MVTN _{5w} and MVTN _{7w}	31
4.4	FT-IR functional groups of MVTN _{1p} , MVTN _{3p} , MVTN _{5p} and MVTN _{7p}	33
4.5	FT-IR functional groups of MVTN _{1c} , MVTN _{3c} , MVTN _{5c} and MVTN _{7c}	35
4.6	FT-IR functional groups of MVTN _{1w} , MVTN _{3w} , MVTN _{5w} and MVTN _{7w}	37
4.7	Thermal decomposition of MVTN _{1p} , MVTN _{3p} , MVTN _{5p} and MVTN _{7p}	40
4.8	Elemental composition of calcined MoVTeNbOx catalysts	41
4.9	Elemental composition of washed MoVTeNbOx catalysts	42
4.10	The reduction activation energy, E_r and total O ₂ removed determined from H ₂ -TPR for MVTN _{1c} , MVTN _{3c} , MVTN _{5c} and MVTN _{7c}	48
4.11	The reduction activation energy, E_r and total O ₂ removed determined from H ₂ -TPR for (a) MVTN _{1w} (b) MVTN _{3w} (c) MVTN _{5w} (d) MVTN _{7w}	51
4.12	BET surface area of MoVTeNbOx catalysts of MVTN _{1w} , MVTN _{3w} , MVTN _{5w} and MVTN _{7w}	52

LIST OF FIGURES

Figure		Page
1.1	Comparison of activation energy between reaction with and without catalyst	2
1.2	Chemical structure of acrylic acid	4
1.3	World consumption of acrylic acid in 2013 (CEH Superabsorbent Polymers Report 2014)	5
2.1	Structure of $\text{Mo}_{7.8}\text{V}_{1.2}\text{NbTe}_{0.94}\text{O}_{29}$ (M1 phase) (Grasselli <i>et al.</i> , 2004)	10
2.2	Structure of $\text{Mo}_{4.67}\text{V}_{1.33}\text{Te}_{1.82}\text{O}_{19.82}$ (M2 phase) (Grasselli <i>et al.</i> , 2004)	10
3.1	Flowchart of MoVTeNbOx catalysts preparation, characterisation and catalytic performance	19
4.1	XRD patterns of precursor MoVTeNbOx catalysts (a) MVTN _{1p} (b) MVTN _{3p} (c) MVTN _{5p} (d) MVTN _{7p}	25
4.2	Schematic representation of the Anderson-type anion $[\text{Mo}_6\text{TeO}_{24}]^{6-}$ (Beato <i>et al.</i> , 2006)	26
4.3	XRD patterns of calcined MoVTeNbOx catalysts (a) MVTN _{1c} (b) MVTN _{3c} (c) MVTN _{5c} (d) MVTN _{7c}	27
4.4	XRD patterns of washed MoVTeNbOx catalysts (a) MVTN _{1w} (b) MVTN _{3w} (c) MVTN _{5w} (d) MVTN _{7w}	30
4.5	FT-IR spectra of precursor MoVTeNbOx catalysts (a) MVTN _{1p} (b) MVTN _{3p} (c) MVTN _{5p} (d) MVTN _{7p}	32
4.6	FT-IR spectra of calcined MoVTeNbOx catalysts (a) MVTN _{1c} (b) MVTN _{3c} (c) MVTN _{5c} (d) MVTN _{7c}	34
4.7	FT-IR spectra of washed MoVTeNbOx catalysts (a) MVTN _{1w} (b) MVTN _{3w} (c) MVTN _{5w} (d) MVTN _{7w}	36
4.8	TG-DTG thermogram of MVTN _{1p} precursor MoVTeNbOx catalyst	38
4.9	TG-DTG thermogram of MVTN _{3p} precursor MoVTeNbOx catalyst	38
4.10	TG-DTG thermogram of MVTN _{5p} precursor MoVTeNbOx catalyst	39

4.11	TG-DTG thermogram of MVTN _{7p} precursor MoVTeNbOx catalyst	39
4.12	FE-SEM image of calcined MoVTeNbOx catalysts (a) MVTN _{1c} (b) MVTN _{3c} (c) MVTN _{5c} (d) MVTN _{7c}	43
4.13	Schematic drawing of <i>ab</i> plane for rod-shaped particle of MoVTeNbOx catalysts	44
4.14	FE-SEM image of washed MoVTeNbOx catalysts (a) MVTN _{1w} (b) MVTN _{3w} (c) MVTN _{5w} (d) MVTN _{7w}	45
4.15	Eley-Rideal mechanism (Fadoni and Lucarelli, 1999)	46
4.16	H ₂ -TPR profiles of calcined MoVTeNbOx catalysts (a) MVTN _{1c} (b) MVTN _{3c} (c) MVTN _{5c} (d) MVTN _{7c}	47
4.17	H ₂ -TPR profiles of washed MoVTeNbOx catalysts (a) MVTN _{1w} (b) MVTN _{3w} (c) MVTN _{5w} (d) MVTN _{7w}	50
4.18	TPRn profiles of anaerobic propane oxidation for (a) MVTN _{1w} and (b) MVTN _{3w} .	53
4.19	TPRn profile for the acrylic acid signal for (a) MVTN _{1w} and (b) MVTN _{3w}	55
4.20	Percentage of yield of acrolein, acrylic acid, and carbon dioxide	56

LIST OF SCHEMES

Scheme		Page
4.1	Proposed reaction of propane dehydrogenation and propane oxidation	54
4.2	Proposed reaction scheme of anaerobic oxidation of propane of MoVTeNbO _x catalysts synthesised in this work	55



LIST OF ABBREVIATIONS

MoVTeNbOx	Molybdenum, Vanadium, Tellurium, Niobium oxide catalyst
MVTN _{1p}	MoVTeNbOx catalyst precursor sample prepared at pH 1.0 (± 0.01)
MVTN _{3p}	MoVTeNbOx catalyst precursor sample prepared at pH 3.0 (± 0.01)
MVTN _{5p}	MoVTeNbOx catalyst precursor sample prepared at pH 5.0 (± 0.01)
MVTN _{7p}	MoVTeNbOx catalyst precursor sample prepared at pH 7.0 (± 0.01)
MVTN _{1c}	MoVTeNbOx catalyst calcined sample prepared at pH 1.0 (± 0.01)
MVTN _{3c}	MoVTeNbOx catalyst calcined sample prepared at pH 3.0 (± 0.01)
MVTN _{5c}	MoVTeNbOx catalyst calcined sample prepared at pH 5.0 (± 0.01)
MVTN _{7c}	MoVTeNbOx catalyst calcined sample prepared at pH 7.0 (± 0.01)
MVTN _{1w}	MoVTeNbOx catalyst washed sample prepared at pH 1.0 (± 0.01)
MVTN _{3w}	MoVTeNbOx catalyst washed sample prepared at pH 3.0 (± 0.01)
MVTN _{5w}	MoVTeNbOx catalyst washed sample prepared at pH 5.0 (± 0.01)
MVTN _{7w}	MoVTeNbOx catalyst washed sample prepared at pH 7.0 (± 0.01)
XRD	X-ray Diffraction Analysis
FT-IR	Fourier Transform - Infrared Spectroscopy
TG-DTG	Thermo Gravimetry - Differential Thermal Gravimetric Analysis
ICP-AES	Inductive Coupled Plasma - Atomic Emission Spectroscopy
FE-SEM	Field Emission - Scanning Electron Microscopy
H ₂ -TPR	Temperature Programmed Reduction in Hydrogen
S _{BET}	Brunauer-Emmett-Teller Surface Area Measurement
TPR _n	Anaerobic Temperature Programmed Reaction

CHAPTER I

INTRODUCTION

1.1 Background of study

Lower alkanes (C1-C4) are global affluent revenue from the natural gas and petroleum refinery off-gases. In the recent time, much effort has been attempted to convert these alkanes into more beneficial petrochemicals or feedstocks in the development of novel selective oxidation catalysts. This great interest is due to their possible application as a feedstock of low-cost raw materials especially for replacing corresponding olefins.

Among selective oxidations of alkane, the conversion of propane to acrylic acid has gained focus of comprehensive research worldwide since the early of 1990s (Lin, 2001). Upon this, the most promising mixed metal oxide catalyst to accomplish this conversion is the bulk mixed Mo-V-Te-Nb-O system (Yu *et al.*, 2009; Beato *et al.*, 2006; Lin, 2001). This catalyst was studied in this research as it has been revealed as highly active and selective catalyst for the propane oxidation to acrylic acid.

The method applied for the synthesis of MoVTeNbOx catalyst is the microwave-assisted slurry method. The presence of microwaves has been reported in greatly improves the rate of many chemical reactions, with a strong reduction of the reaction time, without altering the final yield (Fini and Breccia, 1999).

1.1.1 Catalyst

The origin of word catalyst is from the Greek word. The word “kata” means down and “lyein” means loosen or split. These two words are combined to develop the word of catalyst. A catalyst is a substance that speeds up the chemical reaction by lowering the activation energy of a particular reaction. A catalyst is not being consumed in the reaction and can be recovered chemically unchanged at the end of the reaction it has catalysed.

Thermodynamically, during the operation of catalysis, the reactants and the catalyst are combined and undergo a rearrangement of chemical bonds which head to the formation of transition states. Energy that is required to form the transition state is called the activation energy, E_a . Reactants with lower energy than E_a cannot go through the transition state to react will become products.

The energy profile for the reaction as a function of a reaction pathway, moving from reactants to products is schematically illustrated in Figure 1.1. Clearly, in order to

transform the reactants into products, molecules must overcome the energy barrier represent by the activation energy.

The role of the catalyst is therefore to modify this energy profile, provide an alternative reaction pathway, featuring lower activation energy compared to non-catalysed system (Farnetti *et al.*, 2009). From the Figure 1.1, a clear difference can be observed in term of activation energy between catalysed and uncatalysed reaction. In the existence of catalyst, the activation energy is lowered and speed up the rate of reaction.

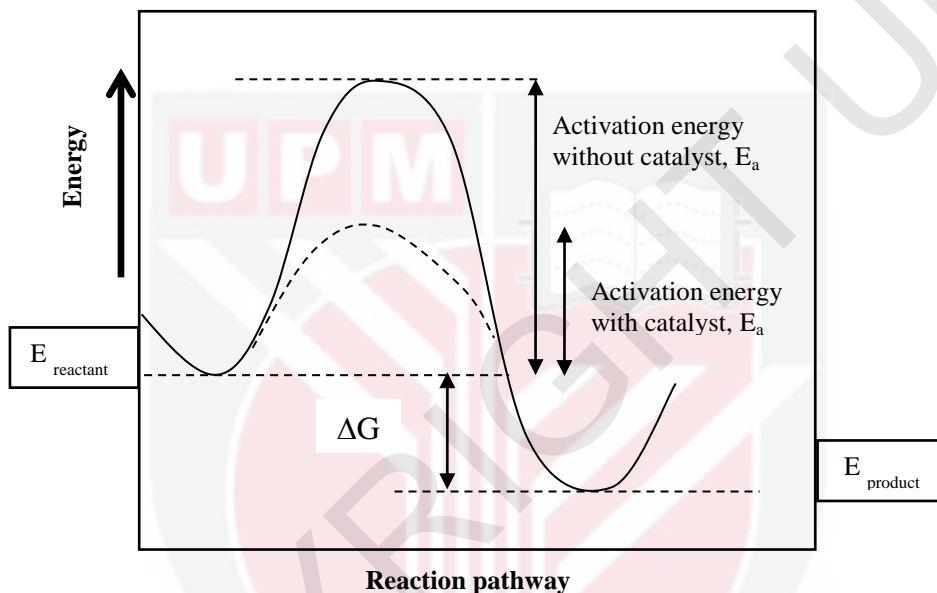


Figure 1.1: Comparison of activation energy between reaction with and without catalyst

Catalysts can be categorised into homogeneous catalysts and heterogeneous catalysts. Heterogeneous catalysts can be distinguished over homogeneous catalysts by the different phases present during the reaction. Most of the processes using homogeneous catalysts occur when catalyst and reactants present in the same phase, usually liquid. Meanwhile, in heterogeneous catalysts, the catalyst and reactants usually present in a different phase, which is the catalyst is usually in a solid form and the reaction occurs either in the liquid or gaseous phase. The conversion of propane in a gas phase over a solid MoVTenbOx catalyst to acrylic acid is one of the examples of heterogeneous catalyst.

1.1.2 Heterogeneous Catalysis

Selective heterogeneous oxidation catalysis is indispensable to the society, since it recovers about 25% of the most essential chemical industry and intermediates were used in the manufacture of industrial products and consumer goods (Grasselli, 2002). The products include intermediates such as acrolein, acrylic acid, acrylonitrile, ethylene, maleic anhydride, methacrylic acid and propylene oxide.

A heterogeneous catalytic reaction involves both adsorption of reactant and desorption of product on various sites of the catalyst. Since the heterogeneous catalysis involves the complex mechanism, it is important to study the principles of heterogeneous catalysis in order to develop an efficient reaction system. Grasselli, (2002) has highlighted the seven principles of selective heterogeneous oxidation catalysis towards a better understanding of catalyst behaviour. The seven principles of selective heterogeneous oxidation catalysis are described as follows;

- 1) The first principle is the lattice oxygen. It has been postulated that the lattice oxygen of a reducible metal oxide might serve as a selective oxidising agent in the oxidation process.
- 2) The second principle is the metal–oxygen bond strength. The metal–oxygen bond of active oxygen atoms must be in intermediate strength under the reaction conditions (Callahan and Grasselli, 1963). If the metal–oxygen bond is too strong, no reaction will occur, if it is too weak, over-oxidation will occur, leading to undesired waste products.
- 3) The third principle is the host structure. An appropriate host structure is required to contain the desired lattice oxygen(s) and metal–oxygen bonds. The chosen host structure must be able to accommodate anion vacancies without being collapsed in structure.
- 4) The fourth principle is the redox. Metal oxides must also exhibit redox properties, in order to become useful either in a cyclic oxidant process or a catalytic oxidation process.
- 5) The fifth principle is the multifunctionality of active sites. The active sites of selective metal oxide catalysts are generally multifunctional and multimetallic or usually at least bifunctional and bimetallic to perform various functions in the catalytic cycle.
- 6) The sixth principle is the site isolation. The site isolation hypothesis that reactive surface lattice oxygens must be isolated from each other on a catalyst surface, so that the selectivity can be obtained and overoxidation can be avoided.
- 7) The seventh principle is the phase cooperation. Two or more phases that contain the necessary functions for catalytic reaction should be in close contact so that they can disclose to each other and thereby cooperate between the phases.

The main advantage of using a heterogeneous catalysis is the ease of separation of the catalyst from the product leading to the continuous chemical processes. Additionally,

compared to homogenous catalysts, heterogeneous catalysts are normally more tolerant in extreme operating conditions.

1.1.3 Acrylic Acid

Acrylic acid (IUPAC: 2-propenoic acid) is the unsaturated carboxylic acid with the chemical structure shown in Figure 1.2. It is consisting of a vinyl group and the carboxylic acid functional group, with the vinyl group attached directly to the carboxylic acid terminal. This polar molecule is miscible in water, alcohols, ethers and chloroform.

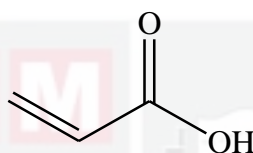


Figure 1.2: Chemical structure of acrylic acid

Acrylic acid has two reactions points for polymerisation process which are carbon-carbon double bond and carboxyl group. These two points made the acrylic acid can be manipulated for a broad range of usage in chemical reactions. Acrylic acid and its esters go through double bond reaction and easily combine with themselves or other monomer to form homopolymers and co-polymers which are indispensable for the formation of various products in the chemical industry.

The Dow Chemical Company has summarised that there are mainly two uses for acrylic acid (Product Safety Assessment: DOW™ Acrylic Acid, 2014). Firstly, it has served as a chemical intermediate to produce acrylic acid esters (such as ethyl acrylate). These esters are used to make ingredients in adhesives, paints, coatings, textiles, plastics, and many other applications. Secondly, it acts as a building block to produce polyacrylic acid, or crosslinked polyacrylic acid compounds. These products are the key element in the hygienic products such as diapers, detergents and chemicals for wastewater treatment.

Based on the Chemical Economics Handbook *Superabsorbent Polymers* Report (2014), growth in demand for crude acrylic acid is forecast at almost 4.5% annually during 2015–2018, govern by growth in acrylate esters at 4.3% and superabsorbent polymers at 4.8%. For global glacial acrylic acid (purified crude acrylic acid), the consumption was estimated for about 45% of total crude acrylic acid consumption in 2014 and were forecast to grow at 5.4% annually during 2015–2018. Thus, there will be a huge challenge for the industries to cope with the world demand of acrylic acid. The pie chart in Figure 1.3 summarises the world consumption of acrylic acid in 2013.

Hence, acrylic acid is an important intermediate in the chemical industry for the manufacture of acrylates and polyacrylic acid. In industries, acrylic acid is the fastest growing commodity chemicals with current worldwide demand approximately 3-4 million tons per year (Trunschke, 2011).


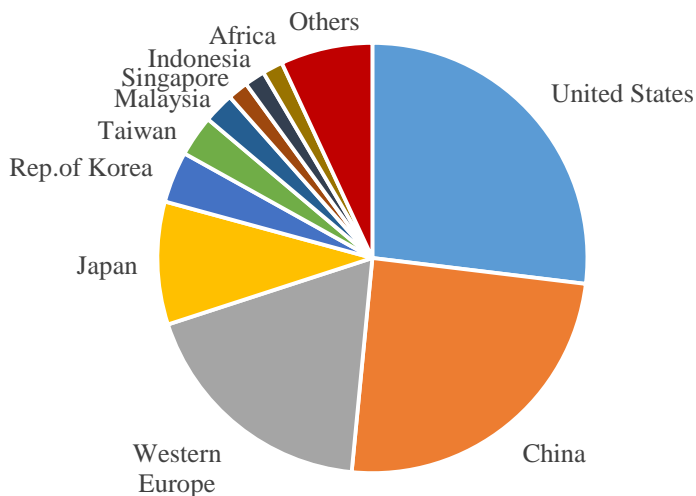


Figure 1.3: World consumption of acrylic acid in 2013 (CEH *Superabsorbent Polymers Report 2014*)

1.1.4 Acrylic Acid Production

Acrylic acid is known to be produced by using unsaturated hydrocarbon, propylene. There is also other chemical pathway to produce acrylic acid, for example, using acetylene as a starting material.

Since the last decades, the use of acetylene has been important for chemical industries as a starting material. Before the modern plant was developed, acrylic acid was manufactured mainly by carbon-carbon coupling reactions (Eq 1.1) until the mid-1990s. In this process, acetylene was converted in the presence of carbon monoxide and water over catalysts containing carbonyl-forming metals, such as NiBr_2/CuI in the BASF process (Beller *et al.*, 1995).




Currently, the major industrial acrylic acid production is via the catalytic partial oxidation of propylene (Eq 1.2 and Eq 1.3). This industrial process required acrylic acid production via a two-step process by converting propylene to acrolein and then followed by oxidation of acrolein to acrylic acid (Voge and Adam, 1967).

Step 1:



Step 2:



However, oxidation of reactants and products resulting the in the occurrence of several side reactions. Therefore, this two step process required two separate reactors with acrolein as an intermediate. The first reactor is usually performed at a higher temperature than the second reactor. These two steps of the reaction usually run over a different catalyst and at a different operating environment to maximise the acrylic acid production. Table 1.1 shows the list of catalysts used for industrial production of acrylic acid and the catalyst component used in this process.


Table 1.1: Catalysts used for industrial production of acrylic acid (Lin, 2001)

Company	Catalyst component	Reaction	Temperature (K)	Product yield (%)
Nippon Shokubai	Mo-Bi-Fe-W-Co-K-Si-O	Propylene acrolein	→ 593	90.2
Ube Industries	Mo-Bi-Fe-Co-V-K-O	Propylene acrolein	→ 603	90.3
Nippon Kayaku	Mo-V-Cu-Fe-Mn-Mg-P-O	Acrolein acrylic acid	→ 483	97.5
Nippon Shokubai	Mo-V-W-Cu-Sr-Al-O	Acrolein acrylic acid	→ 528	97.5

1.1.5 Propane as an Alternative Feedstock

Propane is a saturated hydrocarbon which naturally exists in a gas phase. This lower alkanes are remarkable raw materials in the manufacture of olefins and oxygen containing products by partial oxidation reaction due to its abundances and less expensive than corresponding olefins. To date, only the partial oxidation of *n*-butane to maleic anhydride over VPO catalysts has achieved commercial operation (Ballarini *et al.*, 2006).

Propane can be alternatively used as a feedstock through one-step oxidation in the gas phase with molecular oxygen over a MoVTeNbOx catalyst to produce acrylic acid (Eq 1.4).



Replacing alkenes as the starting materials by much cheaper alkanes can be highly profitable to the industries and end-users. The employing of alkenes as a starting material cost of around 50% or more of the total manufacturing costs. Hence, a great cost saving can be achieved by substituting propylene with much cheaper propane as the starting material to produce acrylic acid (Lin, 2003a).

1.2 Problem statement

In industry, there are two commercial sources of propylene, either a by-product of ethylene production or a by-product of refinery operations. The reduction of propylene supplies from steam crackers and refineries, resulting in the higher price levels. Utilising propane as a feedstock for the acrylic acid production could bring huge economic incentive since currently the olefin is approximately as twice as expensive than alkanes. However, lots of improvement is needed to ensure that the desirable transformation meets the industrial requirement.

The MoVTeNbOx catalyst is generally prepared using hydrothermal and slurry method. In the case of hydrothermal method, it requires high synthesis temperature and pressure to form active and selective catalyst. The synthesis is commonly done in an autoclave with the inside volume requires about 150-200 ml for a long initial heating period for at least 20 h and the yield of catalyst produced is relatively low, which is estimated in the range of 10 g. In addition, this method requires expensive autoclave and hence the huge production cost is required to upgrade this process to the industrial scale.

The microwave-assisted method that will be applied is an unconventional energy source that generates rapid heating of polar substances with resultant reductions in reaction times. This method easier to work up compared to conventional heating with cleaner reactions and usually produce greater yields. This method can be scaled-up for industrial chemical development since it gives faster reaction time with the improved product yield.

In this study, the effect of pH will be specifically investigated since the pH of the resultant slurry strongly effects both the crystallinity and the nature of the precursors. In addition, pH value of the resultant mixture is a crucial determinant in controlling the phase formation and morphology of phase produced.

1.3 Objectives of the study

The objectives of this study are:

1. To synthesise MoVTeNbO_x catalyst through microwave-assisted slurry method at pH 1.0 to 7.0 (± 0.01).
2. To characterise the precursor, calcined and washed MoVTeNbO_x catalysts through XRD, FT-IR, TG-DTG, ICP-AES, FE-SEM, H₂-TPR and S_{BET}.
3. To evaluate performance of catalysts through selective oxidation of propane to produce acrylic acid.

1.4 Scope of the study

This study focused on the preparation of MoVTeNbO_x mixed metal oxide catalyst which has been prepared by the slurry method followed by microwave irradiation. The effect of pH was studied by changing the pH of the resultant solution from 1.0 to 7.0 (± 0.01). The catalyst obtained after heat treatment and post-synthesis treatment was further analysed using XRD, FT-IR, TG-DTG, ICP-AES, FE-SEM, H₂-TPR and S_{BET} to investigate the physicochemical properties of the catalyst for selective oxidation of propane to acrylic acid. The performance of catalysts towards acrylic acid was evaluated using TPRn.

REFERENCES

- Baca, M., Pigamo, A., Dubois, J.L. and Millet, J.M.M. (2005). Fourier transform infrared spectroscopic study of surface acidity by pyridine adsorption on the M1 active phase of the MoVTe(Sb)NbO catalysts used in propane oxidation. *Catalysis Communications*, 6:215–220.
- Ballarini, N., Cavani, F., Cortelli, C., Ricotta, M., Rodeghiero, F., Trifirò, F., Fumagalli, C. and Mazzoni, G. (2006). Non-steady catalytic performance as tool for the identification of the active surface in VPO, catalyst for n-butane oxidation to maleic anhydride. *Catalysis Today*, 117:174-179.
- Beato, P., Blume, A., Girgsdies, F., Jentoft, R.E., Schlögl, R., Timpe, O., Trunschke, A., Weinberg, G., Basher, Q., Hamid, F.A., Hamid, S.B.A., Omar, E. and Mohd Salim, L. (2006). Analysis of structural transformations during the synthesis of a MoVTeNb mixed oxide catalyst. *Applied Catalysis A: General*, 307:137-147.
- Beller, M., Cornils, B., Frohning, C. D. and C. W. Kohlpaintner. (1995). Progress in hydroformylation and carbonylation. *Journal of Molecular Catalysis A: Chemical*, 104:17–85.
- Botella, P., López Nieto, J.M., Solsona, B., Mifsud, A. and Márquez, F. (2002). The preparation, characterization, and catalytic behavior of MoVTeNbO catalysts prepared by hydrothermal synthesis. *Journal of Catalysis*, 209:445-455.
- Botella, P., Garcí'a-Gonzalez, E., Dejoz, A., Lo'pez Nieto, J.M., Va'zquez, M.I. and Gonzá'lez-Calbet, J. (2004). Selective oxidative dehydrogenation of ethane on MoVTeNbO mixed metal oxide catalysts. *Journal of Catalysis*, 225:428-438.
- Botella, P., Garcí'a-Gonzalez, E., Lo'pez Nieto, J.M. and González-Calbet, J.M. (2005). MoVTeNbO multifunctional catalysts: Correlation between constituent crystalline phases and catalytic performance. *Solid State Sciences*, 7:507–519.
- Callahan, J. L. and Grasselli, R. K. (1963). A selectivity factor in vapor-phase hydrocarbon oxidation catalysis. *AIChE Journal*, 9:755-760.
- CEH: Acrylic Acid, Acrylate Esters & Polymers, HIS Inc., 1 June 2014, Retrieved 3 October 2014 from <http://www.sriconsulting.com/CEH/Public/Reports/606.4000/>.
- Deniau, B., Bergeret, G., Jouguet, B., Dubois, J.L. and Millet, J.M.M. (2008). Preparation of single M1 phase MoVTe(Sb)NbO catalyst: Study of the effect of M2 phase dissolution on the structure and catalytic properties. *Topics in Catalysis*, 50:33-42.

- Fadoni, M. and Lucarelli, L. (1999). Temperature programmed desorption, reduction, oxidation and flow chemisorption for the characterisation of heterogeneous catalysts. Theoretical aspects, instrumentation and applications. *Studies in Surface Science and Catalysis*, 120:177-225.
- Farnetti, E., Monte, R. D. and Kaspar, J. (2009). Homogeneous and heterogeneous catalysis. In *Inorganic and Bio-inorganic Chemistry Vol 2*. pp. 50-86, Encyclopedia of Life Support Systems
- Fini, A. and Breccia, A. (1999). Chemistry by microwaves. *Pure Appl. Chem*, 71:573–579.
- Grasselli, R.K. (2002). Fundamental principles of selective heterogeneous oxidation catalysis. *Topics in Catalysis*, 21:79-88.
- Grasselli, R.K., Burrington, J.D., Buttrey, D.J., DeSanto Jr, P., Lugmair, C.G., Volpe Jr, A. F. and Weingand, T. (2003). Multifunctionality of active centres in (amm) oxidation catalysts: From Bi-Mo-O_x to Mo-V-Nb-(Te,Sb)-O_x. *Topics in Catalysis*, 23:5-22.
- Grasselli, R.K., Buttrey, D.J., DeSanto Jr, P., Burrington, J.D., P., Lugmair, C.G., Volpe Jr, A. F. and Weingand, T. (2004). Active centers in Mo-V-Nb-Te-O_x (amm)oxidation catalysts. *Catalysis Today*, 91–92: 251-258.
- Guan, J., Wang, H., Yang, Y., Liu, B., Yu, X., Ma, Y. and Kan, Q. (2009). Effect of pH on the catalytic properties of Mo-V-Te-P-O catalysts for selective oxidation of isobutane. *Catalysis Letters*, 131:512-516.
- Holmberg, J., Grasselli R.K. and Andersson, A. (2004). Catalytic behaviour of M1, M2 and M1/M2 physical mixtures of Mo-V-Nb-Te-oxide system in propane and propene ammoxidation. *Applied Catalysis A: General*, 270:1221-134.
- Irmawati, R., Botella, P., Ivars, F., Meng, W. P., Zawawi, S.M.M., Ahangar, H.A., Hernández, S. and López Nieto, J.M. (2011a). Reflux method as a novel route for the synthesis of MoVTenbO_x catalysts for selective oxidation of propane to acrylic acid, *Journal of Molecular Catalysis A: Chemical*, 342–343:50-57.
- Irmawati, R., Muda, A. A., Ismail, A.Z. and Ahangar, H.A. (2011b). Patent Pending no PI2011003855.
- Ivars, F., Botella, P., Dejoz, A., López Nieto, J.M., Concepción, P. and Vázquez, M.I. (2006). Selective oxidation of short-chain alkanes over hydrothermally prepared MoVTenbO catalysts. *Topics in Catalysis*, 38:59-67.
- Ivars, F., Solsona, B., Rodríguez-Castellón, E. and López Nieto, J.M. (2009). Selective propane oxidation over MoVSbO catalysts: On the preparation, characterization and catalytic behavior of M1 phase. *Journal of Catalysis*, 262:35-43.

- Ivars, F., Solsona, B., Hernández, S. and López Nieto, J.M. (2010). Influence of gel composition in the synthesis of MoVTeNb catalysts over their catalytic performance in partial propane and propylene oxidation. *Catalysis Today*, 149:260-266.
- Jiang, H. C., Lu, W. M. and Wan, H. L. (2004). The effect of $\text{MoV}_{0.3}\text{Te}_{0.23}\text{P}_x\text{O}_n$ catalysts with different phosphorus content for selective oxidation of propane to acrolein, *Journal of Molecular Catalysis A-Chemical*, 208:213-217.
- Katou, T., Vitry, D. and Ueda, W. (2004). Structure dependency of Mo-V-O-based complex oxide catalysts in the oxidations of hydrocarbons. *Catalysis Today*, 91-92: 237-240.
- Langa, F., De la Cruz, P., De la Hoz, A., Díaz-Ortiz A. and Díez-Barra, E. (1997). Microwave irradiation: more than just a method for accelerating reactions. *Contemporary Organic Synthesis*, 5:373-386.
- Lin, M.M., Desai, T.B., Kaiser, F. W. and Klugherz, P.D. (2000). Reaction pathways in the selective oxidation of propane over a mixed metal oxide catalyst. *Catalysis Today*, 61:223-229.
- Lin, M. M. (2001). Selective oxidation of propane to acrylic acid with molecular oxygen. *Applied Catalysis A: General*, 207:1-16.
- Lin, M. M. (2003a). Complex metal-oxide catalysts for selective oxidation of propane and derivatives: I. Catalysts preparation and application in propane selective oxidation to acrylic acid. *Applied Catalysis A: General*, 250:305-318.
- Lin, M. M. (2003b). Complex metal oxide catalysts for selective oxidation of propane and derivatives: II. The relationship among catalyst preparation, structure and catalytic properties. *Applied Catalysis A: General*, 250:287-303.
- Lo'pez Nieto, J.M., Botella, P., B. Solsona, B. and Oliver, J.M. (2003). The selective oxidation of propane on Mo-V-Te-Nb-O catalysts: The influence of Te-precursor. *Catalysis Today*, 81:87-94.
- Lo'pez Nieto, J.M. (2006). The selective oxidative activation of light alkanes. From supported vanadia to multicomponent bulk V-containing catalysts. *Topics in Catalysis*, 41:3-15.
- Naraschewski, F.N., Kumar, C.N., Jentys, A. and Lercher, J.A. (2011). Phase formation and selective oxidation of propane over MoVTeNbO_x catalysts with varying compositions. *Applied Catalysis A: General*, 391:63-69.
- Oliver, J.M., López Nieto, J.M., Botella, P. and Mifsud, A (2004). The effect of pH on structural and catalytic properties of MoVTeNbO catalysts. *Applied Catalysis A: General*, 257:67-76.
- Oshihara, K., Hisana, T. and Ueda, W. (2001). Catalytic oxidative activation of light alkanes over Mo-V-based oxides having controlled surface. *Topics in Catalysis*, 15:153-160.

- Pavia, D.L., Lampman, G.M. and Kriz, G.S. (2001). *Introduction to spectroscopy*. United States of America: Thomson Learning, Inc.
- Pereira, E. B., Pereira, M. M., Lam, Y. L., Perez, C. A. C. and Schmal, M., (2000). Synthesis and characterization of niobium oxide layers on silica and the interaction with nickel. *Applied Catalysis A: General*, 97:99-106.
- Popova, G.Y., Andrushkevich, T.V., Chesalov, Y.A., Plyasova, L.M., Dovlitova, L.S., Ischenko, E.V., Aleshina, G.I. and Khramov, M.I. (2009). Formation of active phases in MoVTeNb oxide catalysts for ammoxidation of propane. *Catalysis Today*, 144:312-317.
- Product Safety Assessment: DOW™ Acrylic Acid, The DOW Chemical Company, N.d. Retrieved 19 October 2013 from <http://www.dow.com/productsafety/finder/>.
- Raj, J.A.K. and Viswanathan, B., (2009). Effect of surface area, pore volume and particle size of P25 titania on the phase transformation of anatase to rutile. *Indian Journal of Chemistry*, 48A:1378-1382.
- Riley, B.J., Johnson, B. R., Schaef, H.T. and Sundaram, S.K. (2013). Sublimation Condensation of Multiscale Tellurium Structures. *Journal of Physical Chemistry*, 117:10128–10134.
- Sanfiz, A.C., Hansen, T.W., Girgsdies, F., Timpe, O., Rodel, E., Ressler, T., Trunschke, A. and R. Schlogl, R. (2008). Preparation of phase-pure M1 MoVTeNb oxide catalysts by hydrothermal synthesis—Influence of reaction parameters on structure and morphology. *Topic in Catalysis*, 50:19–32.
- Scherrer, P. (1918). Bestimmung der Grösse und der inneren Struktur von Kolloidteilchen mittels Röntgenstrahlen, *Göttinger Nachrichten Gesell* 26:98-100.
- Shiju, N. R. and Gulians, V. V. (2007). Microwave-assisted hydrothermal synthesis of monophasic Mo-V-Te-Nb-O mixed oxide catalyst for the selective ammoxidation of propane. *ChemPhysChem*, 8:1615-1617.
- Solsona, B., López Nieto, J.M., Oliver, J.M. and Gumbau, J.P. (2004). Selective oxidation of propane and propene on MoVNbTeO catalysts: Effect of chemical composition in catalysts prepared by slurry. *Catalysis Today*, 91–92:247-250.
- Trunschke, A. (2011). Chapter 4 Propane-Selective Oxidation to Acrylic Acid. *Nanostructure Catalysts: Selective Oxidations*, 56-95. The Royal Society Chemistry.
- Tu, X., Furuta, N., Sumida, Y., Takahashi, M. and Niiduma, H. (2006). A new approach to the preparation of MoVNbTe mixed oxide catalysts for the oxidation of propane to acrylic acid. *Catalysis Today*, 117:259-264.

- Ueda, W., Oshihara, K., Vitry, D., Hisano, T. and Kayashima, Y. (2002). Hydrothermal synthesis of Mo-based oxide catalysts and selective oxidation of alkanes. *Catalysis Surveys of Jpn*, 6:33-44.
- Ueda, W., Vitry, D. and Katou, T. (2004). Structural organization of catalytic functions in Mo-based oxides for propane selective oxidation. *Catalysis Today*, 96:235-240.
- Ueda, W., Vitry, D. and Katou, T. (2005). Crystalline MoVO based complex oxides as selective oxidation catalysts of propane. *Catalysis Today*, 99:43-49.
- Ueda, W., Vitry, D., Katou, T., Watanabe, N. and Endo, Y. (2006). Key aspects of crystalline Mo-V-O-based catalysts active in the selective oxidation of propane. *Research on Chemical Intermediates*, 32:217-233.
- Ushikubo, T., Oshima, K., Kayo, A., Umezawa, T., Kiyono, K. and Sawaki, I. (1992). EP Patent 529 853 A2.
- Ushikubo, T., Iizuka, T., Hattori, H. and Tanabe, K. (1993). Preparation of highly acidic hydrated niobium oxide. *Catalysis Today*, 16:291-295.
- Ushikubo, T., Nakamura, H., Koyasu, Y. and Wajiki, S. (1995). Method for producing an unsaturated carboxylic acid. US Patent 5 380 933.
- Ushikubo, T., Oshima, K., Kayo, A. and Hatano, M. (1997). Ammoxidation of propane over Mo-V-Nb-Te mixed oxide catalysts. *Studies in Surface Science and Catalysis*, 112:473-480.
- Vitry, D., Dubois, J. and Ueda, W. (2004). Strategy in achieving propane selective oxidation over multi-functional Mo-based oxide catalysts. *Journal of Molecular Catalysis A: Chemical*, 220:67-76.
- Voge, H. H. and Adams, C. R. (1967). Catalytic oxidation of olefins. *Advances in Catalysis*, 17:151.
- Woi, P.M., Irmawati, R. and Taufiq-Yap, Y.H. (2007). Influence of organic species on the characteristics of Mo-V oxide. *The Malaysian Journal of Analytical Sciences*, 11:160-165.
- Wong, M.S., Irmawati, R., Ahangar, H.A., Taufiq-Yap, Y.H., Tan, Y.P. and Muhamad E.N. (2012). Physicochemical studies of Ni-, Co-, Pt- promoted MoVNbOx catalysts synthesised by impregnation method. *Oriental Journal of Chemistry*, 28:59-65.
- Yu, Z., Zheng, W., Xu, W., Zhang, Y., Fu, H. and Zhang, P. (2009). Effect of preparation conditions on selective oxidation of propane to acrylic acid. *Transactions of Nonferrous Metals Society of China*, 19:476-479.
- Yu, Z., Zheng, W., Xu, W., Zhang, P., Fu, H. and Zhang, Y. (2011). Crystalline structure of mixed metal oxide catalysts for propane selective oxidation to acrylic acid. *Transactions of Nonferrous Metals Society of China*, 21:405-411.