



***PHYSICAL AND DIELECTRIC PROPERTIES OF BORO-TELLURITE
GLASS DOPED WITH COBALT AND IRON OXIDES***


ERNY SAFARINA SAAD

FS 2012 93



UPM
UNIVERSITI PUTRA MALAYSIA
BERILMU BERBAKTI

**PHYSICAL AND DIELECTRIC PROPERTIES OF BORO-TELLURITE GLASS
DOPED WITH COBALT AND IRON OXIDES**

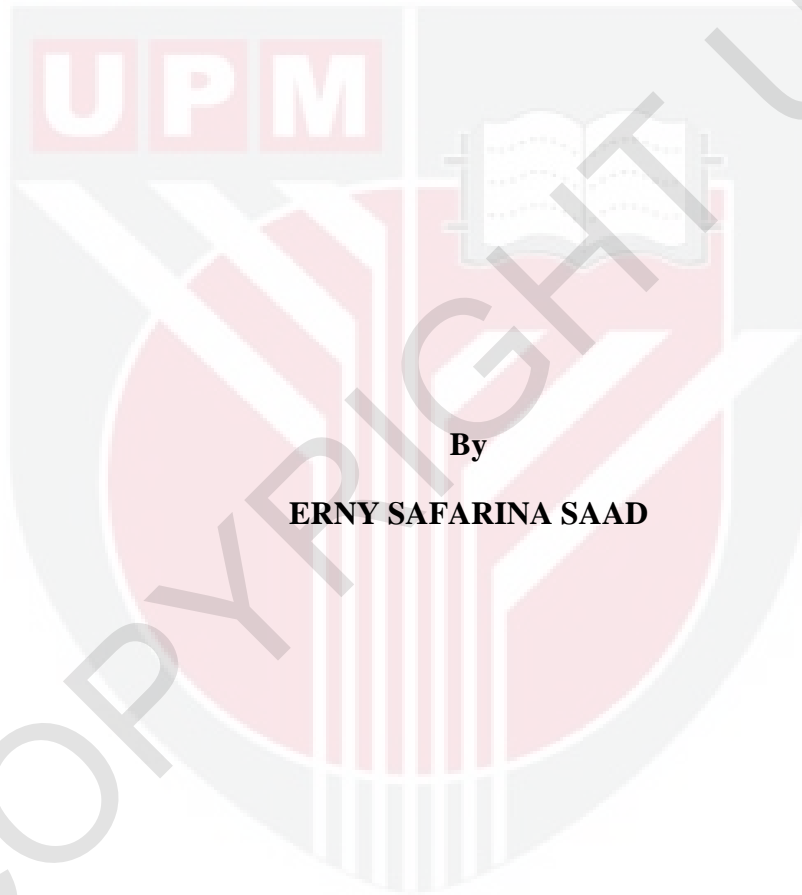

By

ERNY SAFARINA SAAD

**Thesis Submitted to the School of Graduate Studies, Universiti Putra Malaysia, in
Fulfillment of Requirement for the Degree of Master of Science**

January 2012

DEDICATION

Specially dedicated to:

**My Husband,
My Son,
My Father,
My Mother,
My Sisters,
My Brothers,
My Lecturers,
My Friends,**

for their encouragement and support. ☺

Abstract of thesis presented to the Senate of Universiti Putra Malaysia in fulfillment of the requirement for the degree of Master of Science.

PHYSICAL AND DIELECTRIC PROPERTIES OF BORO-TELLURITE GLASS DOPED WITH COBALT AND IRON OXIDES.

By

ERNY SAFARINA BINTI SAAD

January 2012

Chair: Halimah Mohamed Kamari, PhD

Faculty: Science

The glass system with composition $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{1-x}[\text{Co}_3\text{O}_4]_x$ with $x = 0.01, 0.02, 0.03, 0.04, 0.05$ and 0.06 , and $\{[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}\}_{1-y}\{\text{Fe}_2\text{O}_3\}_y$ with $y = 0.01, 0.02, 0.03, 0.04, 0.05$ and 0.06 has been successfully prepared by the melt quenching technique. The amorphous nature of glass system was determined by using XRD measurement. The glass transition temperature, (T_g), was determined using the DTA technique at room temperature. Density of variation glasses sample was measured at room temperature using the Archimedes technique. The values of molar volume were calculated from density data. The infrared absorption spectra of the glasses sample in the wavenumber range of $280\text{-}4000\text{ cm}^{-1}$ were recorded by using Fourier Transform Infrared Spectroscopy. The magnetic behaviour in the glass system was studied using VSM (vibrating sample magnetometer) at room temperature with magnetic field range $\pm 15\text{kOe}$. The susceptibility was determined from the relationship between magnetic field, H (Oe) and magnetic moment/mass, M (emu/mass). The magnetization, of the glass sample increases with increasing of magnetic field, H .

Dielectric properties have been investigated in the frequency range 10^{-2} to 10^3 Hz and temperature range 30 °C-200 °C. From this measurement, the dielectric properties such as dielectric permittivity, ϵ' , and dielectric loss, ϵ'' , was determined. The ϵ' and ϵ'' of glasses sample increases with temperature and decreases with frequency. The activation energy of dielectric properties was determined from normalization curve using the Arrhenius equation. The activation energy of both glasses sample increases with increasing cobalt and iron oxide content. The conductivity, σ of glasses sample also been calculated from equation, $\sigma_{ac} = \omega\epsilon_0\epsilon''$. The value of dc conductivity, σ_{dc} was determined from “ac universal power law”, and the value activation energy of σ_{dc} , has been calculated using the Arrhenius implied. The activation energy of σ_{dc} was increased with increasing of cobalt and iron oxide. The activation energy of dc conductivity was almost equal with dielectric loss relaxation indicating the same species took part in both the process. The dielectric behaviour of these glass systems also has been analyzed using electric modulus, M and impedance, Z, formalism. The graph of M'' and Z'' peaks were found overlapping each other. This behaviour indicated a long range conductivity process appears in this glasses sample. For first series glasses sample, the value of activation energy of impedance plot, Z'' vs. Z', increases with increasing of cobalt oxide content. For the second series glass samples, the curve of Z'' vs. Z' plot will compose of two semicircle with increases of iron oxide content. The activation energy for second series glass samples decreases with increasing iron oxide content.

Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia sebagai memenuhi keperluan untuk ijazah Master Sains.

**CIRI FIZIKAL DAN DIELEKTRIK BAGI KACA BORO-TELLURITE
APABILA DITAMBAH DENGAN KOBALT DAN FERUM OKSIDA.**

Oleh

ERNY SAFARINA BINTI SAAD

Januari 2012

Pengerusi: Halimah Mohamed Kamari, PhD

Fakulti: Sains

Sistem kaca dengan pelbagai komposisi bagi $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{1-x}[\text{Co}_3\text{O}_4]_x$ dengan $x=0.01, 0.02, 0.03, 0.04, 0.05$ dan 0.06 , dan $\{[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}\}_{1-y}\{\text{Fe}_2\text{O}_3\}_y$ dengan $y=0.01, 0.02, 0.03, 0.04, 0.05$ dan 0.06 dengan jayanya disediakan menggunakan kaedah peleburan lazim dan sepuh lindap. Sifat bahan amorfus bagi kaca ditentukan dengan menggunakan pengukuran XRD. Suhu transisi kaca, T_g ditentukan dengan menggunakan teknik Analisis Pembebezaan Termal, DTA, pada suhu bilik. Ketumpatan bagi pelbagai variasi sampel kaca, diukur pada suhu bilik menggunakan teknik Archimedes. Nilai isipadu molar telah dikira daripada nilai ketumpatan kaca yang diperolehi. Spektra penyerapan inframerah bagi sampel kaca dalam julat $280-4000\text{cm}^{-1}$ telah direkodkan menggunakan alatan spektroskopi infra merah, FTIR. Sifat-sifat magnet dalam sampel kaca telah dikaji menggunakan sistem pengukuran VSM (*vibrating sample magnetometer*) pada suhu bilik dengan julat medan magnet $\pm 15\text{kOe}$. Kerentanan magnetik telah ditentukan daripada hubungan antara medan magnet, $H(\text{Oe})$

dan momen magnet/jisim, M (emu/mass). Kemagnetan kaca meningkat dengan kadar peningkatan medan magnet. Sifat dielektrik telah diselidik dalam julat frekuensi dari 10^2 hingga 10^3 Hz pada julat suhu $30\text{ }^\circ\text{C}$ - $200\text{ }^\circ\text{C}$. Daripada pengukuran ini, perilaku sifat dielektrik seperti dielektrik permitiviti, ϵ' dan faktor kehilangan dielektrik, ϵ'' telah didapati. ϵ' dan ϵ'' didapati meningkat dengan peningkatan suhu dan menurun dengan peningkatan frekuensi. Tenaga pengaktifan bagi sifat dielektrik ditentukan dari lengkungan normalisasi menggunakan persamaan Arrhenius. Tenaga pengaktifan bagi kedua-dua sampel kaca meningkat dengan kadar peningkatan kobalt dan ferum oksida. Kekonduksian, σ bagi sampel kaca juga telah dikira daripada persamaan, $\sigma_{ac} = \omega\epsilon_0\epsilon''$. Nilai bagi arus terus, σ_{dc} , telah ditentukan daripada "ac power law", dan nilai tenaga pengaktifan, σ_{dc} dikira menggunakan persamaan Arrhenius. Tenaga pengaktifan kekonduksian arus terus, σ_{dc} , meningkat dengan peningkatan kandungan kobalt dan ferum oksida. Nilai tenaga pengaktifan kekonduksian, σ_{dc} adalah hampir sama dengan tenaga pengaktifan bagi kehilangan dielektrik menunjukkan spesies yang sama mengambil bahagian dalam kedua-dua process. Sifat dielektrik bagi kedua-dua sistem kaca ini juga dianalisa menggunakan modulus, M dan impedance spektroskopi, Z . Puncak graf M "dan Z " didapati bertindih antara satu sama lain. Ini menunjukkan kekonduksian proses jangka panjang berlaku dalam sampel ini. Bagi sampel kaca siri pertama, nilai tenaga pengaktifan bagi impedan plot, Z'' melawan Z' , meningkat dengan kadar peningkatan kobalt oksida. Bagi sampel kaca bagi siri kedua, lengkungan dari plot Z'' terhadap Z' akan menjadi dua semibulatan dengan peningkatan kandungan ferum oksida. Bagi nilai tenaga pengaktifan bagi sampel kaca siri kedua menurun dengan peningkatan kadar kandungan ferum oksida.

ACKNOWLEDGEMENTS

Bismillahirrahmanirrahim

First and foremost, Alhamdulillah, I'm very grateful to Allah s.w.t that has given me the patience, strength, determination, and courage to complete this research.

It is a great pleasure to gratefully acknowledge my supervisor, Dr Halimah Mohamed Kamari for guiding me from the beginning of my research until the completion of my thesis writing. I'm also like to thank my co-supervisor, Assoc. Prof Dr. Mansor Hashim for his guidance in my research.

I would also like to thank all the staff in Faculty of Science who had contributed to this research. Not to forget, to all my friends for their support, guidance and encouragement throughout my postgraduate study.

Last but not least, most importantly I would like to thank my husband, Mohd Adzlizam B. Che Azmi, my parents, Saad B. Kassim and Zaiton Bt. Ramli and also to my sister and brothers for their constant love and support.

I certify that a Thesis Examination Committee has met on 10 January 2012 to conduct the final examination of Erny Safarina binti Saad on her thesis entitled “Physical and Dielectric Properties of Boro-Tellurite Glass Doped with Cobalt and Iron Oxides” in accordance with the Universities and University College Act 1971 and the Constitution of the Universiti Putra Malaysia [P.U.(A) 106] 15 March 1998. The committee recommends that the student be awarded the Master of Science.

Members of the Thesis Examination Committee were as follows:

Zaidan bin Abdul Wahab, PhD

Associate Professor
Faculty of Science
Universiti Putra Malaysia
(Chairman)

Wan Mohamad Daud bin Wan Yusoff, PhD

Associate Professor
Faculty of Science
Universiti Putra Malaysia
(Internal Examiner)

Sidek bin Hj Ab Aziz, PhD

Professor
Faculty of Science
Universiti Malaysia
(Internal Examiner)

Rosli Hussin, PhD

Professor
Faculty of Science
Universiti Teknologi Malaysia
(External Examiner)



ZULKARNAIN ZAINAL, PhD

Professor and Deputy Dean
School of Graduate Studies
Universiti Putra Malaysia

Date: 23 April 2012

This thesis was submitted to the Senate of Universiti Putra Malaysia and has been accepted as fulfilment of the requirement for the degree of Master of Science. The members of the Supervisor Committee were as follows:

Halimah Mohamed Kamari, PhD

Senior Lecturer
Faculty of Science
Universiti Putra Malaysia
(Chairman)

Mansor Hashim, PhD

Associate Professor
Faculty of Science
Universiti Putra Malaysia
(Member)


BUJANG BIN KIM HUAT, PhD

Professor and Dean
School of Graduate Studies
Universiti Putra Malaysia

Date:

DECLARATION

I declare that the thesis is my original work except for quotations and citations which have been duly acknowledged. I also declare that it has not been previously, and is not concurrently, submitted for any other degree at Universiti Putra Malaysia or at any other institution.

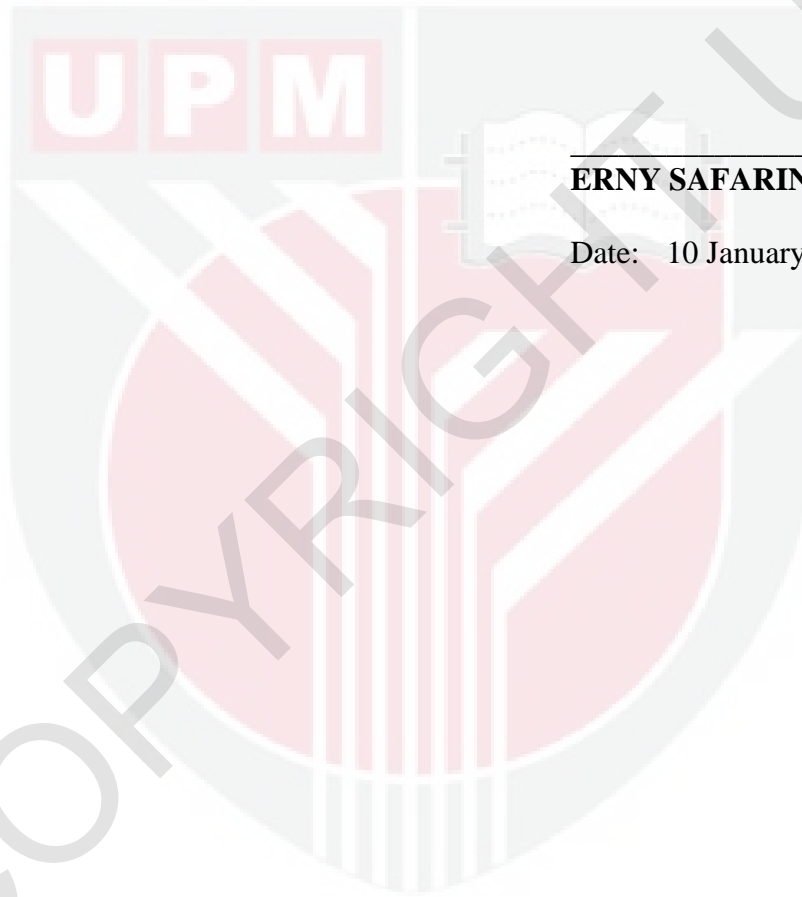

ERNY SAFARINA SAAD

Date: 10 January 2012

TABLES OF CONTENTS

	Page
DEDICATION	ii
ABSTRACT	iii
ABSTRAK	v
ACKNOWLEDGEMENTS	vii
APPROVAL	viii
DECLARATION	x
LIST OF TABLES	xiii
LIST OF FIGURES	xv
LIST OF ABBREVIATIONS	xix
CHAPTER	
1	
INTRODUCTION	1
1.1 Introduction	1
1.2 Introduction of the glass	1
1.3 Important of Tellurite glasses	3
1.4 Introduction to Cobalt and Iron oxide	4
1.5 Scope of study	5
1.6 Problem statement	6
1.7 Objectives	6
2	
LITERATURE REVIEW	7
2.1 Introduction	7
2.2 Review of Tellurite Glass	7
2.3 Borate Glass	10
2.4 Cobalt Oxide and Iron oxide	13
2.5 Magnetic properties	14
2.6 Magnetization	15
2.7 Susceptibility	16
2.8 Dielectric properties	17
2.9 Polarization	21
3	
METHODOLOGY	24
3.1 Introduction	24
3.2 Appearing of glasses sample	25
3.3 Sample preparation	26
3.3.1 Weighing	26
3.3.2 Preheat and melting process	27
3.3.3 Cutting	27
3.3.4 Polishing	28
3.3.5 Coating	28

3.4	X-ray Diffraction (XRD) measurement	29
3.5	Density measurement	30
3.6	Differential Thermal Analysis (DTA) measurement	32
3.7	Fourier Transform Infrared Spectroscopy (FTIR)	32
3.8	Dielectric measurement	33
3.9	Magnetic measurement	34
4	RESULTS AND DISCUSSIONS	35
4.1	Introduction	35
4.2	X-ray Diffractometry (XRD)	35
4.3	Fourier Transform Infrared Spectroscopy (FTIR)	37
4.4	Densities and molar volume analysis	43
4.5	Thermal Analysis (Transition temperature, T _g)	47
4.6	Magnetic properties	50
4.7	Dielectric properties	55
4.7.1	Dielectric Permittivity, ϵ' and Dielectric Loss, ϵ''	55
4.7.2	Master plot	70
4.7.3	Conductivity	81
4.7.4	Electrical modulus, M and impedance, Z plot	98
4.7.5	Impedance plots	112
5	CONCLUSIONS	121
5.1	Conclusion	121
5.2	Suggestions	125
	REFERENCES	126
	APPENDICES	132
	BIODATA OF STUDENT	157
	LIST OF PUBLICATIONS	158

LIST OF TABLES

Table		Page
4.1	The value of FTIR absorption spectra of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{1-x}[\text{Co}_3\text{O}_4]_x$	42
4.2	The value of FTIR absorption spectra of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}]_{1-y}[\text{Fe}_2\text{O}_3]_y$	42
4.3	The density, ρ and molar volume, V_m of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{1-x}[\text{Co}_3\text{O}_4]_x$ glasses.	43
4.4	The density, ρ and molar volume, V_m of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}]_{1-y}[\text{Fe}_2\text{O}_3]_y$ glasses	45
4.5	The value of transition temperature, T_g of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{1-x}[\text{Co}_3\text{O}_4]_x$, glasses.	50
4.6	The value of transition temperature, T_g of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}]_{1-y}[\text{Fe}_2\text{O}_3]_y$, glasses.	50
4.7	The value of activation energy of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{1-x}[\text{Co}_3\text{O}_4]_x$ glasses system and their uncertainty	
4.8	The values of dielectric behavior parameters of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{1-x}[\text{Co}_3\text{O}_4]_x$ glasses system used in equivalent circuit modeling, at temperature 200°C.	76
4.9	The value of activation energy of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}]_{1-y}[\text{Fe}_2\text{O}_3]_y$ glasses system and their uncertainty.	80
4.10	The values of dielectric behavior parameters of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}]_{1-y}[\text{Fe}_2\text{O}_3]_y$ glasses system used in equivalent circuit modeling, at temperature 200°C.	80
4.11	The value of σ_0 , ω_p and n of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.99}[\text{Co}_3\text{O}_4]_{0.01}$ glasses	83
4.12	The value of σ_0 , ω_p and n of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.98}[\text{Co}_3\text{O}_4]_{0.02}$ glasses	84

4.13	The value of σ_0 , ω_p and n of [(TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{0.97} [Co ₃ O ₄] _{0.03} glasses	85
4.14	The value of σ_0 , ω_p and n of [(TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{0.96} [Co ₃ O ₄] _{0.04} glasses	86
4.15	The value of σ_0 , ω_p and n of [(TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{0.95} [Co ₃ O ₄] _{0.05} glasses	87
4.16	The value of σ_0 , ω_p and n of [(TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{0.94} [Co ₃ O ₄] _{0.06} glasses	88
4.17	The value of σ_0 , ω_p , and n of [[TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{0.95} [Co ₃ O ₄] _{0.05}] _{0.99} [Fe ₂ O ₃] _{0.01} glasses	91
4.18	The value of σ_0 , ω_p and n of [[TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{0.95} [Co ₃ O ₄] _{0.05}] _{0.98} [Fe ₂ O ₃] _{0.02} glasses	92
4.19	The value of σ_0 , ω_p and n of [[TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{0.95} [Co ₃ O ₄] _{0.05}] _{0.97} [Fe ₂ O ₃] _{0.03} glasses	93
4.20	Table 4.20: The value of σ_0 , ω_p and n of [[TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{0.95} [Co ₃ O ₄] _{0.05}] _{0.96} [Fe ₂ O ₃] _{0.04} glasses	94
4.21	The value of σ_0 , ω_p and n of [[TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{0.95} [Co ₃ O ₄] _{0.05}] _{0.95} [Fe ₂ O ₃] _{0.05} glasses.	95
4.22	The value of σ_0 , ω_p and n of [[TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{0.95} [Co ₃ O ₄] _{0.05}] _{0.94} [Fe ₂ O ₃] _{0.06} glasses	96
4.23	The value of activation energy of impedance plot for [(TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{1-x} [Co ₃ O ₄] _x glasses system	120
4.24	The value of activation energy of impedance plot for [[TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{0.95} [Co ₃ O ₄] _{0.05}] _{1-y} [Fe ₂ O ₃] _y glasses system	120

LIST OF FIGURES

Figure	Page
1.1 Amorphous structure of a glassy solid (left) and lattice structure of a crystalline solid	2
2.1 Crystalline TeO ₂ : (a)and (b) tellurite; (c) paratellurite	10
2.2 Boroxol ring structures in vitreous boric oxide and alkali borate glasses	13
2.3 Magnetization curves fir dia-, para- and antiferromagnets	17
2.4 Magnetization curves for ferri- and ferromagnets	17
2.5 Various polarization processes	23
3.1 The picture of sample Co ₃ O ₄ - B ₂ O ₃ - TeO ₂ glass system	25
3.2 The picture of sample Fe ₂ O ₃ - Co ₃ O ₄ - B ₂ O ₃ - TeO ₂ glass system	25
3.3 Schematic diagram of sample preparation process	29
4.1 The XRD pattern of [(TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{1-x} [Co ₃ O ₄] _x glasses	36
4.2 The XRD pattern of [[(TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{0.95} [Co ₃ O ₄] _{0.05}] _{1-y} [Fe ₂ O ₃] _y glasses	36
4.3 FTIR absorption spectra of [(TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{1x} [Co ₃ O ₄] _x glasses	40
4.4 FTIR absorption spectra of [[(TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{0.95} [Co ₃ O ₄] _{0.05}] _{1-y} [Fe ₂ O ₃] _y glasses	41
4.5 The density, ρ and molar volume, V _m of [(TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{1-x} [Co ₃ O ₄] _x with x=0.01,0.02,0.03,0.04,0.05 and 0.06.	44
4.6 The density, ρ and molar volume, V _m of [[(TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{0.95} [Co ₃ O ₄] _{0.05}] _{1-y} [Fe ₂ O ₃] _y glasses.	46
4.7 Transition temperature of [(TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{1-x} [Co ₃ O ₄] _x , glass	49
4.8 Transition temperature of [[(TeO ₂) _{0.7} (B ₂ O ₃) _{0.3}] _{0.95} [Co ₃ O ₄] _{0.05}] _{1-y} [Fe ₂ O ₃] _y , glass.	49

4.9	The magnetization against applied field of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{1-x}[\text{Co}_3\text{O}_4]_x$ glasses	53
4.10	The magnetic susceptibility of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{1-x}[\text{Co}_3\text{O}_4]_x$ glass	53
4.11	The magnetization against applied field of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}]_{1-y}[\text{Fe}_2\text{O}_3]_y$ glasses	54
4.12	The magnetic susceptibility of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}]_{1-y}[\text{Fe}_2\text{O}_3]_y$ The (a) dielectric permittivity ϵ' , (b) dielectric loss ϵ'' , at different frequencies and temperatures. The solid line with slope -1 indicated the dc conductivity.	54
	Figure 4.13: $x=0.01$	58
	Figure 4.14: $x=0.02$	59
	Figure 4.15: $x=0.03$	60
	Figure 4.16: $x=0.04$	61
	Figure 4.17: $x=0.05$	62
	Figure 4.18: $x=0.06$	63
	Figure 4.19: $y=0.01$	64
	Figure 4.20: $y=0.02$	65
	Figure 4.21: $y=0.03$	66
	Figure 4.22: $y=0.04$	67
	Figure 4.23: $y=0.05$	68
	Figure 4.24: $y=0.06$	69
4.25	The graph of $\ln f$ vs. $1000/T$ for $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}]_{0.95}[\text{Fe}_2\text{O}_3]_{0.05}$ Normalization curve of ϵ' and ϵ'' of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{1-x}[\text{Co}_3\text{O}_4]_x$ glasses sample against frequency and the locus of the displacement point at different temperature is shown to give a measure of the displacements required. The solid line show the best fitted to data	71
	Figure 4.26: $x=0.01$	72
	Figure 4.27: $x=0.02$	73
	Figure 4.28: $x=0.03$	73
	Figure 4.29: $x=0.04$	74
	Figure 4.30: $x=0.05$	74
	Figure 4.31: $x=0.06$	75
4.32	Activation of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{1-x}[\text{Co}_3\text{O}_4]_x$ glasses system against mol fraction of Co_3O_4 Normalization curve of ϵ' and ϵ'' of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}]_{1-y}[\text{Fe}_2\text{O}_3]_y$ glasses sample against frequency and the locus of the displacement point at different temperature is shown to give a measure of the	75

displacements required. The solid line show the best fitted to data.

	Figure 4.33:y=0.01	77
	Figure 4.34:y=0.02	77
	Figure 4.35:y=0.03	78
	Figure 4.36:y=0.04	78
	Figure 4.37:y=0.05	79
	Figure 4.38:y=0.06	79
4.39	Activation energy of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}]_{1-y}[\text{Fe}_2\text{O}_3]_y$ glasses system against mol fraction of Fe_2O_3 . The a.c Conductivity as a function of frequency, in $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{1-x}[\text{Co}_3\text{O}_4]_x$ glasses at different temperature. The solid lines are the best fits to Eq.(4.5).	80
	Figure 4.40: x=0.01	83
	Figure 4.41: x=0.02	84
	Figure 4.42: x=0.03	85
	Figure 4.43: x=0.04	86
	Figure 4.44: x=0.05	87
	Figure 4.45: x=0.06	88
	The a.c Conductivity as a function of frequency, in $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}]_{1-y}[\text{Fe}_2\text{O}_3]_y$ glasses at different temperature. The solid lines are the best fits to Eq.(4.5)	
	Figure 4.46: y=0.01	91
	Figure 4.47: y=0.02	92
	Figure 4.48: y=0.03	93
	Figure 4.49: y=0.04	94
	Figure 4.50: y=0.05	95
	Figure 4.51: y=0.06	96
4.52	The activation energy, E_{dc} , of dc conductivity against mol fraction, (a) $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{1-x}[\text{Co}_3\text{O}_4]_x$, (b) $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}]_{1-y}[\text{Fe}_2\text{O}_3]_y$ glasses system	97
4.53	Imaginary part of modulus spectra, M'' of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{1-x}[\text{Co}_3\text{O}_4]_x$ for $x = 0.01, 0.02, 0.03, 0.04, 0.05$ and 0.06 glasses system at various frequencies and temperatures. (b) $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}]_{1-y}[\text{Fe}_2\text{O}_3]_y$ glasses system	102
4.54	Imaginary part of modulus spectra, M'' of $[(\text{TeO}_2)_{0.7}(\text{B}_2\text{O}_3)_{0.3}]_{0.95}[\text{Co}_3\text{O}_4]_{0.05}]_{1-y}[\text{Fe}_2\text{O}_3]_y$ for $y=0.01, 0.02, 0.03, 0.04, 0.05$ and 0.06 glasses system at	105

various frequencies and temperatures.

4.55 M'' and Z'' plot versus log frequency of 108
 $[(TeO_2)_{0.7}(B_2O_3)_{0.3}]_{1-x}[Co_3O_4]_x$
for $x = 0.01, 0.02, 0.03, 0.04, 0.05$ and 0.06 glasses system
with various frequencies at temperature $200^\circ C$.

4.56 M'' and ρ'' plot versus log frequency of 111
 $[(TeO_2)_{70}(B_2O_3)_{30}]_{0.95}[Co_3O_4]_{0.05}]_{1-y}[Fe_2O_3]_y$ for
 $y=0.01, 0.02, 0.03, 0.04, 0.05$ and 0.06 glasses system with
various frequencies at temperature $200^\circ C$

Complex of impedances, Z plot for
 $[(TeO_2)_{0.7}(B_2O_3)_{0.3}]_{1-x}[Co_3O_4]_x$ glass sample.
Solid line is fitting to the data.

Figure 4.57: $x=0.01$	114
Figure 4.58: $x=0.02$	114
Figure 4.59: $x=0.03$	115
Figure 4.60: $x=0.04$	115
Figure 4.61: $x=0.05$	116
Figure 4.62: $x=0.06$	116

Complex of impedances, Z plot for
 $[(TeO_2)_{70}(B_2O_3)_{30}]_{0.95}[Co_3O_4]_{0.05}]_{1-y}[Fe_2O_3]_y$ glass sample.
Solid line is fitting to the data

Figure 4.63: $y=0.01$	117
Figure 4.64: $y=0.02$	117
Figure 4.65: $y=0.03$	118
Figure 4.66: $y=0.04$	118
Figure 4.67: $y=0.05$	119
Figure 4.68: $y=0.06$	119

LIST OF ABBREVIATIONS

β	Beta
\AA	Angstrom
ρ	Density
λ	Wavelength
θ	Theta
FT-IR	Fourier Transform Infrared
χ	Susceptibility
B	Induction
H	Applied field
π	Pi
m	Magnetic moment
v	Volume of solid
μ_0	Permeability of free space
μ	Permeability
ϵ^*	Complex permeability
ϵ'	Real part of permittivity
ϵ''	Imaginary part of permittivity
TD	Time-domain
FD	Frequency-domain
ω	Angular frequency
χ'	Real part of susceptibility
χ''	Imaginary part of susceptibility

∞	Infinity
ϵ_0	Permittivity of free space($8.854 \times 10^{-12} Fm^{-1}$)
M^*	Complex electrical modulus
M'	Real part electrical modulus
M''	Imaginary part electrical modulus
C^*	Complex capacitor
i	Imaginary number ($\sqrt{-1}$)
G	Conductance
Y^*	Complex admittance
Z^*	Complex impedance
ω_p	Loss peak frequency
C	Capacitance
R	Resistance
α	Alpha
E	Electric field
ϵ_r	Relative permittivity
P	Polarization
C_0	Capacitance of the air-filled parallel plate capacitor
σ	Conductivity of the medium
τ	Relaxation time

CHAPTER 1

INTRODUCTION

1.1 Introduction

Boro-tellurite glass is one of the amorphous materials. Its preparation steps are involving the quenching of molten or liquid cooling of the melt at a certain rate and temperature. Due to intensive application in nowadays, it's being the interesting glasses to study. In this chapter will introduce about the glass, important of Tellurite glass, introduction to the cobalt and iron oxide, scope of study, problem statement and the objectives of this study.

1.2 Introduction of the Glass

Many types of glasses will produce by melt quenching technique. The phenomenon due to the quenching are called the glass transition phenomenon. The glass transition phenomenon will occur only at certain temperature called the glass transition temperature (Rahim Sahar, 2000).

The others definition of glass is, glass are an inorganic product of fusion which has cooled to rigid condition without crystallizing. Thus, non-crystalline solids can be made by deposition from the vapor phase, or by sputtering in low pressure system, and these have the same chemical composition as, and apparently identical properties to, glass

produced by cooling from the melt. The committee of the U.S. National Research Council recently proposed a more general definition there is; glass is an x-ray amorphous material which exhibits the glass transition, this being exhibits the glass transition, this being defined as that phenomenon in which a solid amorphous phase exhibits with changing temperature a more or less sudden change in the derivative thermodynamic properties, such as heat capacity and expansion coefficient from crystal-like to liquid-like values.

Since the glass is amorphous materials, in x-ray diffraction experiment does not reveal any sharp peaks but only broad humps the nature of the glass system (Rawson, 1980). The Figure 1.1 shows the different of atoms arrangement in amorphous and crystal state.

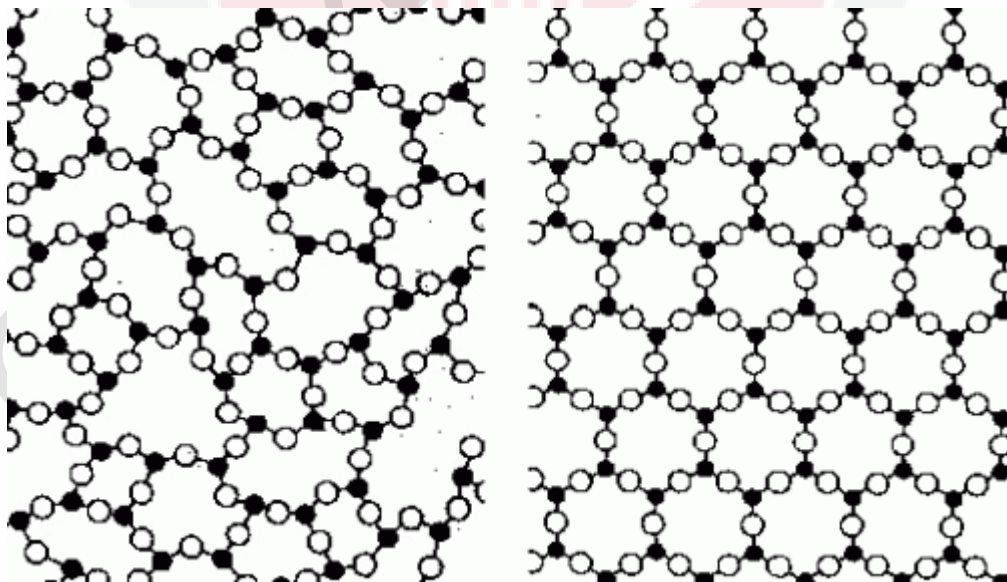


Figure 1.1: Amorphous structure of a glassy solid (left) and lattice structure of a crystalline solid (right)

(www.e-education.psu.edu/eart520/node/1689)

1.3 Important of Tellurite glasses

During two decade, tellurite glasses have been studied for many years due to numerous applications and great research effort. Therefore, tellurite glasses are now under consideration in many others applications. It has potential application in pressure sensors or as a new laser hosts because of their exhibited a range of unique properties (El-Mallawany, 2002). The tellurite glasses also interesting on account of their high values of refractive index and dielectric constant (Rawson, 1980). Munoz-Martin *et al.* (2011) state, tellurite glass is the promising materials for the development of integrated photonic devices due to their interesting in physical and chemical properties.

In important field of application like telecommunication technology, laser and optical fiber technology and optical device technology, tellurium glasses are be the ideal materials. This is due to their properties in high refractive index (in the range from 1.85 to 2.2), high non-linear third order optical susceptibility (50 times higher than one of SiO₂ systems), high transmittance from ultraviolet to near infrared, low transition temperature and electrical semi conductivity. It is also important for high ionic conductivity (Rada *et al.*, 2011).

With containing transition metal ions, it been observed that the TeO₂ have higher electronic conductivity than this glasses based on other conventional network formers such as P₂O₅, B₂O₃ and other glass former (Pan and Ghosh, 1999).

1.4 Introduction to Cobalt and Iron oxide

Transition metal glass such as iron ions, have a strong bearing on optical, magnetic and electrical properties. The environment of iron ions in various inorganic glass system such as silicate, borate, phosphate, germanate and tellurite, are available in a large number of interesting studies. In the glasses matrices, these ions exist in different valence states with different coordinations. An example, as Fe^{2+} with octahedral and as Fe^{3+} with both, tetrahedral and octahedral environment. Both of these ions are well-known paramagnetic ions. A large magnetic anisotropy of Fe^{2+} is due to its strong spin-orbit interaction of the 3d orbital. The energy of Fe^{3+} ions is small because its orbital angular moment is zero (Rada *et al.*, 2011)

From Zhang *et al.* (2007), cobalt oxide has a normal spinel structure and bulk. It exhibits antiferromagnetic with Neel temperature at around 30K. At the octahedral sites, the $\text{Co}_{3+}(3d_6)$ are diamagnetic in the octahedral crystal field and at the tetrahedral sites, the Co_{2+} are form antiferromagnetic sub lattice with the diamond structure below the Neel temperature. From Shelby (2005) iron oxides, which are common impurities in the sands used to produce commercial silicate glasses. Its can act as unintentional colorants in many products.

Cobalt oxide with the formula Co_3O_4 , is in organic compound. It has a molar mass 240.80gmol^{-1} with appearance in black solid. It's has melting point $895\text{ }^\circ\text{C}$ and boiling point $900\text{ }^\circ\text{C}$. The density value of Co_3O_4 is 6.11gcm^{-3} . Iron oxide with molecular

formula Fe_2O_3 , is paramagnetic, reddish brown and readily attacked by acids. It has molar mass 159.69 gmol^{-1} and density value 5.24 gcm^{-3} , with melting point $1566 \text{ }^\circ\text{C}$.

1.5 Scope of study

A glass system containing transition metal oxide can be interesting material to study. Besides that, due to technological applications, the glass study doped with transition metal has been considerable interest study. This is because of their very sensitive responses to the surrounding cations and their outer d electron orbital function, it is used to probe the glass structure (Sreekanth Chakradhar, 2000). Because of that, the scopes of these studies are to produce new boro-tellurite glass system with adding cobalt oxide and iron oxide. In this work, the physical properties of glasses system has been determine. The dielectric properties in frequency range between 1.0^{-2}Hz to 1.0^3Hz of the glass system also have been analyzed such as ϵ' and ϵ'' , conductivity, σ , modulus, M , and impedance plot, Z . As adding the cobalt oxide and iron oxide in the borotellurite glass system, it can give the magnetic properties behavior. For that, respond of the glasses sample with magnetic field also been investigated due to the magnetic properties behavior.

1.6 Problem statement

Due to the industrial important, boro-tellurite have been extensively studied. Tellurites is important in making glasses with desirable optical properties. Classical glass former B_2O_3 and conditional glass former TeO_2 present in boro-tellurite, leads complex

specification and interesting properties in glass structure(Suresh *et al.*, 2010). With introduction of transition metal such as Fe_2O_3 in glass system, which is a semiconducting glasses whose electrical properties and mechanism of the electronic conduction have been investigated extensively (Tanaka *et al.*, 1990). Although many properties of boro-tellurite glass such as the silver borotellurite (Chowdari and Kumari, 1996), nickel borotellurite glasses(Khaled, 1992) and etc have attracted a number of researchers because of their wide range application, there is no systematic study of physical and dielectric properties of boro-tellurite glass doped with cobalt and iron oxide has been report. Therefore, an investigation of the physical and dielectric properties will be carried out and the results of this study are presented in this thesis.

1.7 Objectives

The objectives of this research as follows:

- To determine the physical properties of boro-tellurite glass system doped with cobalt oxide and iron oxide
- To study the dielectric behavior of the glass system such as dielectric permittivity, ϵ' and loss, ϵ'' , conductivity, normalization curve (master plot), modulus, M and impedance plots, Z.
- To investigate the magnetic properties of the glasses system.

REFERENCES

- Abdel Wahab, F., Aziz, M.S., Mostafa, A.G., and Ahmed, E.M., (2006). *Electrical Conductivity and Dielectric Properties of Some Vanadium-Strontium-Iron Unconventional Oxide Glasses*, Journal of Materials Science and Engineering B, 134, pp: 1-8.
- Abdel Wahab, F.A., Manal Abdel-Baki , (2009). *Electrical Conduction and Dielectric Properties of Lithium Aluminum Silicate Glasses Doped With Cr^{3+} Ions*, Journal of Non-Crystalline Solids, 355, pp: 2239-2249.
- Ahamad, M.N., Varma, K.B.R., (2010). *Dielectric Properties of (100-X) $Li_2B_4O_7$ -X ($Ba_5Li_2Ti_2Nb_8O_{30}$) Glasses and Glass Nanocrystal Composites*, Journal of Material Science and Engineering B, 167,pp: 193-201.
- Alhawery, A.S., (1997). *Infrared Absorption and Differential Scanning Calorimetry Studies of Sodium Tungstate Dehydrate Glasses Containing Iron Oxide*, Journal of Phys. Chem. Solids vol58, no9, pp: 1325-1328.
- Bahgat, A.A., Shaltout, I.I., and Abu-Elazm, A.A.,(1992). *Structural and Thermal Properties of Some Tellurite Glasses*, Journal of Non-Crystalline Solids 150, pp: 179-184.
- Biljana Pejova, Ardijana Isahi, Metodija Najdoski, Ivan Grozdanov , (2001). *Fabrication and Characterization of Nanocrystalline Cobalt Oxide Thin Films*, journal of Materials Research Bulletin 36, pp: 161–170.
- Braglia, M., Mosso, S.,Dai, G., Billi, E.,Bonelli, L.,Baricco, M., Battezzati, L.,(2000). *Rheology of Tellurite glasses*, Journal of Materials Research Bulletin,35, pp: 2343-2351.
- Bretcanua, O., Verne, E., Coissonb, M., Tibertob, P., Allia, P., (2006). *Magnetic Properties of the Ferrimagnetic Glass-Ceramics for Hyperthermia*, Journal of Magnetism and Magnetic Materials, 305, pp: 529–533.
- Chowdari, B.V.R., Kumari, P. P., (1996), *Synthesis and Characterization of Silver Borotellurite Glasses*, Journal of Solid State Ionics 86, pp: 521-526.
- Delbert Day, E.(1975). *Mixed Alkali Glasses-Their Properties And Uses*, Journal of Non-Crystalline Solids. 21,pp:343-372.
- Dillip, K. P., Choudhary, R. N. P., Samantaray, B.K., (2008). *Studies of Dielectric Relaxation and AC Conductivity Behavior of Plasticized Polymer Nanocomposite Electrolytes*, Int. J. Electrochem. Sci., 3, pp: 597-608.

- Doweidar , H., Saddeek Y.B., Doweidar, H., (2009). *FTIR and Ultrasonic Investigations on Modified Bismuth Borate Glasses*, Journal of Non-Crystalline Solids, 355, pp:348–354.
- Doweidar, H., El-Damrawi, G.M., Moustafa, Y.M., Ramadan, R.M., (2005). *Density Of Mixed Alkali Borate Glasses: A Structural Analysis*, Journal of Physica B, 362, pp: 123-132.
- Edward Price,(2006). *Magnetic Dipoles, Hysteresis and Core Losses*, Enviromental Potentials, Inc.
- El Mkami, H., Deroide, B., Backov, R., Zanchetta, J. V., (2000). *Dc and Ac Conductivities Of $(V_2O_5)_x(B_2O_3)_{1-x}$ Oxide Glasses*, Journal of Physics and Chemistry of Solids, 61, pp: 819-826.
- Elkholy, M.M., Sharaf El-Deen, L.M., (2000). *The Dielectric Properties of $TeO_2-P_2O_5$ Glasses*, Journal of Materials Chemistry and Physics, 65, pp: 192-196.
- El-Mallawany Rauf, A. A. (2001). *Tellurites Glass Handbook: Physical Properties and Data*, CRC Press.
- El-Moneim Abd, A., (2002). *DTA and IR Absorption Spectra of Vanadium Tellurite Glasses*, Journal of Materials Chemistry and Physics, 73, pp: 318-312.
- FT-IR Spectroscopy Attenuated Total Reflectance (ATR)*, Technical Note, Retrieved on 13 January 2011, from www.perkinelmer.com.
- Gerhardt, R.,(1994). *Impedance and Electric Spectroscopy Revisited: Distinguishing Localized Relaxation From Long-Range Conductivity*, Journal of Phys. Chem. Solids, Vol. 55, No.12, pp: 1491-1506.
- Granados-Correa, F., Serrano-Gómez, J., (2010). *Removal of Chromium Hexavalent Ions from Aqueous Solution by Retention onto Iron Phosphate*, Institution National of Investigation Nuclear. Departament of Química, A. P., 18, pp: 1018-1027.
- Halimah M.K., Daud W.M., Sidek H.A.A., Zainal A.S., Zainul A.H. and Jumiah H., (2007). *Structural Analysis of Borotellurite Glass*, American Journal of Applied Science, 4, pp: 323-327.
- Helmi Hammami, Mourad Arous, Manuel Lagache and Ali Kallel, (2008). *Electrical Conduction and Dielectric Properties in Piezoelectric Fiber Composites*, Smart materials for Energy, Communications and Security, pp: 169-188.
- Human Health Fact Sheet*, Argonne National Laboratory, EVS, August 2005, Retrieved on 12 January 2011, from <http://www.ead.anl.gov/pub/doc/Cobalt.pdf>

Investigation of Ac Conductivity and Electric Modulus of LBS, LPBS and LVP Samples, Chapter IV, Retrieved on 20 September 2010 from http://117.240.228.70/bitstream/10603/966/10/10_chapter%204.pdf

Jonscher, A.K., (1999). *Dielectric Relaxation in Solids*, Journal of Phys. D: Appl. Phys. 32, pp: 57-70.

Kabir Md. Firoz, 1998, *Dielectric, Ultrasonic and Viscoelastic Properties Of Rubber Wood*, PhD Thesis, Department of Physics, University Putra Malaysia.

Kaewkhao, J., Sriprom, W., Insiripong, S., Ratana, T., Kedkaew, C., and Limsuwan, P., (2011). *Structural and Magnetic Properties of Glass Doped With Iron Oxide*, Journal of Physics: Conference Series 266.

Karan, N.K., Natesan, B., Katiyar, R.S., (2006) .*Structural and Lithium Ion Transport Studies In Borophosphate Glasses*, Journal of Solid State Ionics 177, pp: 1429–1436.

Kashif, (1990). *Magnetic Susceptibility of Lithium Borosilicate Glasses Containing Metal Oxide*, Journal of Materials Science: Materials In Electronics, 1, pp: 4- 50.

Khafagy, A.H., Elwadawy, A.A., Higazy, A.A., El-Rabaie, S., Eid, A.S., (2008) .*The Glass Transition Temperature and Infrared Absorption Spectra of: (70-x)(TeO₂) 15(B₂O₃)15(P₂O₅)x(Li₂O) Glasses*, Journal of Non-Crystalline Solids 354, pp: 1460-1466.

Khaled, M.A., Elzahed, H., Fayek, S.A., and El-Ocker, M.M., (1994). *Optical Absorption, Infrared and Differential Thermal Analysis Studies of Borotellurite Glass Cointaning Nickel*, Journal of Material Chemistry and Physics, 37, pp: 329-332.

Khor, S.F., Talib, Z.A., Daud, W.M., Sidek, H.A.A., Ng, B.H., (2009). *Effects of Mgo On Dielectric Properties And Electrical Conductivity of Ternary Zinc Magnesium Phosphate Glasses.*, Journal Of Non-Crystalline Solids 355, pp: 2533-2539.

Kumar Prashant, M., and Sankarappa, T., (2008). *DC Conductivity In Some Alkali Doped Vanadotellurite Glasses*, Solid State Ionics, Vol. 178, Issues 33-34, pp: 1719-1724.

Loh Yen Nee (2005). *Structural, Optical and Dilectric Properties of Lithium Fluoro and Chloro and Magnesium Chloro Phosphate Glasses*, Master Thesis, Department of Physics, University Putra Malaysia.

Mekki, A., Ziq, K.A., (1998). *Magnetic Properties of a Sio₂-Na₂O-Fe₂O₃ Glass and Glass Ceramic*, Journal of Magnetism and Magnetic Materials ,189, pp: 207-213.

- Moulson and Herbert,(1987), *Electroceramis Materials*, John Wiley and Sons, Edition July 7, 2003.
- Munoz-Martin, D., Fernandez-Navarro, J.M.,Gonzalo, J.,Jose, G., Jha, A., Fierro, J.L.G., Domingo, C.,Garcia-Lopez,J., (2011). *Structural and Optical Properties of Tellurite Thin Film Glasses Deposited By Pulsed Laser Deposition*, Journal of Thin Solid Films, 520, pp: 131–137
- Nicola A. Apaldin,(2003). *Magnetic Materials: Fundamental and Device Applications*, 1st Publised 2003, Cambridge University Press.
- Niyaz Ahamad, M., Varma, K.B.R., (2010). *Dielectric Properties of $(100-x) Li_2B_4O_7-x (Ba_5Li_2Ti_2Nb_8O_{30})$ Glasses and Glass Nano Crystal Composites*, Journal of Materials Science and Engineering B, 167,pp: 193-201.
- Pan,A.and Ghosh, A, (1999). Activation Energy and Conductivity Relaxation of Sodium Tellurite Glasses, Journal of Physical Review B, 59, pp: 899-904.
- Paramagnetism, Retrieved on 15 February 2010, from <http://en.wikipedia.org/wiki/Magnetization#Paramagnetism>
- Rada, S., Culea, M., and Culea, E., (2008). *Structure of $TeO_2 \cdot B_2O_3$ Glasses Inferred from Infrared Spectroscopy and DFT Calculations*, Journal of Non-Crystalline Solids, Vol. 354, Issues 52-54, pp: 5491-549.
- Radaa, S., Deheleana, A., Stanb, M., Chelceaa, R., Culea, E., (2011). *Structural Studies on Iron–Tellurite Glasses Prepared By Sol–Gel Method*, Journal of Alloys and Compounds, 509, pp: 147–151
- Rahim Sahar, Md. (2000). *Fizik Bahan Amorfus*. Universiti Teknologi Malaysia, Malaysia.
- Rajendra Kumar Singh, Kothiyal, G.P., Srinivasan, A., (2008). *Magnetic and Structural Properties of $CaO-SiO_2-P_2O_5-Na_2O-Fe_2O_3$ Glass Ceramics*, Journal of Magnetism and Magnetic Materials, 320, pp: 1352-1356.
- Raju Gorur, G.,(2003). *Dielectric in Electric Fields*, Markel Dekker, Inc
- Ramli Arifin, Md. Rahim Sahar and Sulhadi, (2007). *Ftir Spectroscopy Study on Tellurite Doped Eu_2O_3 Glass*, Solid State Science and Technology, Vol. 15, No 1,pp: 122-126.
- Rawson, H. (1980). *Properties and Applications of Glass:Glass Science and Technology 3*, Elsevier.

- Romero-Perez Maxima, Jesus Ma, Rincon, Carlos J.R Gonzalez Oliver, Claudio D' Ovidio, Daniel Esparza, (2001). *Magnetic Properties of Glasses With High Iron Oxide Content*, Journal of Materials Research Bulletin, 36, pp: 1513-1520.
- Saddeek, Y. B., Gaafar, M.S., (2009). *Physical and Structural Properties of Some Bismuth Borate Glasses*, Journal of Materials Chemistry and Physics, 115, pp: 280-286.
- Saddeek, Y.B.(2004). *Ultrasonic Study and Physical Properties of Some Borate Glasses*, Journal of Materials Chemistry and Physics, 83, pp: 222–228.
- Saddeek, Y.B.,Essam R.Shaaban, Aly, K.A.,Sayed, I.M., (2009). *Crystallization Kinetics of $\text{Li}_2\text{O-PbO-V}_2\text{O}_5$ Glasses*, Physica B 404, pp: 2412–2418.
- Saddek, Y.B., El Latif Lamia Abd, (2004). *Effect of TeO_2 on the Elastic Module of Sodium Borate Glasses*, Physica B, 348, pp: 475-484.
- Saddek, Y.B., Gaffar, M.S., (2009). *Physical and Structural Properties of Some Bismuth Borate Glasses*, Journal of Materials Chemistry and Physics, 115, pp:280-286.
- Sankarappa, T., Prashant Kumar, M., Devidas, G.B., Nagaraja, N., Ramakrshnareddy, R., (2008). *AC Conductivity and Dielectric Studies in $\text{V}_2\text{O}_5\text{-TeO}_2$ and $\text{V}_2\text{O}_5\text{-CoO-TeO}_2$ Glasses*, Journal of Molecular Structure, 889, pp: 308-315.
- Schott, (2007). *Technical Glasses, Physical and Technical Properties*, North America, Inc, USA.
- Shelby, J.E. (2005). *Introduction to Glass Science and Technology*, 2nd Edition.,RSC.
- Sheorana, A., Sanghia, S., Rania, S., Agarwala, A., Seth, V.P., (2009). *Impedance Spectroscopy and Dielectric Relaxation in Alkali Tungsten Borate Glasses*, Journal of Alloys and Compounds, 475, pp:804–809.
- Sreekanth Chakradhar, R.P. Murali, A. Lakshmana Rao, J. (2000). *A Study of Electron Paramagnetic Resonance and Optical Absorption Spectra of VO_2 Ions in Alkali Calcium Borate Glasses*, Journal of Physica B, 293, pp: 108-117.
- Sreekanth Chakradhar, R.P., Murali, A., Lakshmana Rao, J., (2000). *A Study of Electron Paramagnetic Resonance and Optical Absorption Spectra of VO_2 Ions In Alkali Calcium Borate Glasses*, Journal of Physica B, 293, pp: 108-117.
- Sundaram, S.K.,Schaffer, C.B., Mazur, E.,(2002). *Microexplosions in Tellurite glasses*, Journal of Applied Physics A: Materials Science & Processing, Vol.76, No. 3, pp: 379-384.

- Suresh, S., Prasad, M., Chandra Mouli, V., (2010). *AC Conductivity and Impedance Measurements In Alkali Boro-Tellurite Glasses*, Journal of Non-Crystalline Solids, 356, pp:1599–1603
- Tanaka, K., Yoko, T., Nakano, M., Nakamura, M., Kamiya, K.,(1990). *Electronic Conduction in Fe_2O_3 - TeO_2 - P_2O_5 Glasses: an Explication for High Conductivity of Iron-Containing Tellurite Glasses*, Journal of Non-Crystalline Solids, 125, pp: 264-271.
- Tanya Tsoncheva, Ljubomira Ivanova, Christo Minchev, Michael Froba, (2009). *Cobalt-Modified Mesoporous MgO , ZrO_2 , and CeO_2 Oxides as Catalysts for Methanol Decomposition*, Journal of Colloid and Interface Science 333, pp: 277–284.
- Thermo Nicolet Corporation, (2001). *Introduction to Fourier Transform Infrared Spectrometry*, retrieved on 12 February 2011 from <http://mmrc.caltech.edu/FTIR/FTIRintro.pdf>.
- Toderas, M., Filip, S., Ardelean, I., (2006), *Structural Study of the Fe_2O_3 - B_2O_3 - BaO Glass System by FTIR Spectroscopy*, Journal of Optoelectronic and Advance Materials, 8, pp: 1121-1123.
- Wells, A.F.(1984). *Structural Inorganic Chemistry*, Fifth Edition, Clarendon press, Oxford.
- Weng, L., Hodson, S., Bao, X., Sagoe-Crentsil, K., (2004). *Achieving Controllable Sol-Gel Processing Of Tellurite Glasses Through The Use Of $Te(VI)$ Precursors*, Journal of Material Science and Engineering B, 1007, pp: 89-93.
- Yahia, I. S., Saddeek, Y. B., Sakr, G. B., Knoff, W., Story, T., Romcevic, N., Dobrowolski, W., (2009). *Spectroscopic Analysis and Magnetic Susceptibility of CuO - TeO_2 - V_2O_5 Glasses*, Journal of Magnetism and Magnetic Mater, Vol. 321, Issue 24, pp: 4039-4044.
- Yuan-guang Zhang, You-cun Chen, Yin-guo Zhao, (2007). *Synthesis and Magnetic Properties of Co_3O_4 Nanoflowers*, Chinese Journal of Chemical Physics, Vol. 20, pp: 601-606.
- Zarifah, N.A., Halimah, M. K., Hashim, M., Azmi, B. Z., Daud, W. M.,(2010). *Magnetic Behaviour of $(Fe_2O_3)_x (TeO_2)_{1-x}$ Glass System Due To Iron Oxide*, Journal of Chalcogenide Letters,7,pp: 565 – 571.

BIODATA OF STUDENT

Erny Safarina Binti Saad was born in Kuala Lumpur on the 30 October 1986. She attended her primary education at Sekolah Kebangsaan Sungai Lalang, Kedah, and then continued to secondary school at Sekolah Menengah Kebangsaan Agama Yan and Sekolah Menengah Teknik Alor Star, Kedah. After completed her secondary school, she pursued her study at Kedah Matriculation College in physical science. In 2005, she joined Faculty of Science, Universiti Putra Malaysia, UPM, Serdang and obtained her first degree in Bachelor of Science Instrumentation (Hons.) in 2008. In July 2009, she continued her master studies in Dielectric field under the same faculty.

LIST OF PUBLICATIONS

1. Erny S.S, Halimah M.K, Mansor H, Daud W.M, (2010). Dielectric Behaviors of $\text{Co}_3\text{O}_4 - \text{B}_2\text{O}_3 - \text{TeO}_2$ Glass System, 3rd International Conference on Solid State Science & Technology, ICSSST2010, 1-3rd December 2010, Hilton Hotel, Kuching Sarawak.
2. Erny Safarina Saad, M.K Halimah, Mansor Hashim, (2010). Magnetic Properties of $\text{Co}_3\text{O}_4 - \text{B}_2\text{O}_3 - \text{TeO}_2$ Glass System, Fundamental Science Congress 2010, 18-19th May 2010, Academic Complex, Universiti Putra Malaysia.
3. Erny Safarina Saad, Halimah Mohamed kamari, Mansor Hashim, (2011). Dielectric and Structural Properties of $\text{Fe}_2\text{O}_3 - \text{Co}_3\text{O}_4 - \text{B}_2\text{O}_3 - \text{TeO}_2$ Glasses System, Fundamental Science Congress 2011, 5-6th July 2011, Academic Complex, Universiti Putra Malaysia.