



UNIVERSITI PUTRA MALAYSIA

***EFFECTS OF ELECTRIC FIELD ON THE THERMAL DIFFUSIVITY OF
CONDUCTORS IN THREE-LAYER SOLID CONFIGURATIONS***

SANI JIBRIN

FS 2015 85



**EFFECTS OF ELECTRIC FIELD ON THE THERMAL
DIFFUSIVITY OF CONDUCTORS IN THREE-LAYER SOLID
CONFIGURATIONS**

By

SANI JIBRIN

**Thesis Submitted to the School of Graduate Studies, Universiti Putra
Malaysia, in Fulfilment of the Requirements for the Degree of Doctor of
Philosophy**

March, 2015

COPYRIGHT

All materials contained within the thesis, including without limitation text, logos, icons, photographs and all other artwork, is copyright material of Universiti Putra Malaysia unless otherwise stated. Use may be made of any material contained within the thesis for non-commercial purposes from the copyright holder. Commercial use of material may only be made with the express, prior, written permission of Universiti Putra Malaysia.

Copyright ©Universiti Putra Malaysia



DEDICATIONS

This work is dedicated to the memory of my late parents and brother who together, initiated me into this endeavour but who couldn't live long to see me through it.

May their souls rest in perfect peace.



Abstract of thesis presented to the Senate of Universiti Putra Malaysia in fulfilment of the requirement for the degree of Doctor of Philosophy

EFFECTS OF ELECTRIC FIELD ON THE THERMAL DIFFUSIVITY OF CONDUCTORS IN THREE-LAYER SOLID CONFIGURATIONS

By

SANI JIBRIN

March, 2015

Chair: Azmi Bin Zakaria, Ph.D.

Faculty: Science

In order to extract the thermal properties of thin films from their thermal responses an analytical model is developed by solving the heat diffusion equation. In this study, a novel mathematical theory essential for the experimental determination of thermal diffusivity of conductors in three-layer solid configurations by the Converging Thermal Wave Technique is developed. This is achieved by expressing the hyperbolic Laplace associated solution of the derived equation in negative exponential form. Binomial series expansion is then used to simplify the solution and hence, Laplace conversion tables, in place of the tedious integral inversion technique are finally used to retrieve the temporal temperature profile for the three-layer solid sample in real space and time domains. The equation is plotted using Mathematica Software and its accuracy is checked by performing sensitivity analysis on all the physical parameters contained in the derived equation. The result of the sensitivity analysis shows that the mathematical model is sensitive to all relevant parameters needed for the evaluation of the thermal diffusivity of the sample.

Using the Converging Thermal Wave Technique, three different sets of thermal diffusivity experiments are performed on previously prepared samples. The first set of experiment comprising four three-layer samples is performed to test the mathematical theory and calibrate the measuring scheme and apparatuses. Results obtained in this series of experiments show that the mathematical model and the measuring scheme adopted for the thermal diffusivity evaluation of the samples are accurate to within about 5% error.

The second set of experiments were performed on different three-layer solid samples when direct electric current pass across the samples. Results obtained here indicate that the thermal diffusivity value of the metal foils in three-layer solid configurations increase with the potential difference applied across the metal foils. It is also observed in this series of experiments that the temperature of the metal foils increases slightly as a result of the Joule heating effects.

When different three-layer solids are placed in a uniform static electric field and are being charged either positive or negative as the PD is varied from 1.00 V to 10.00 V in a step of 1 V each, the effect of electrostatic field on the thermal diffusivity of metal is investigated. At both positive and negative static charge on the sample, ten different temperature signal readings are obtained as the potential difference of the DC power source is varied. In this way, the free electrons in the conductor are made to move either towards or away from the temperature signal detection point respectively and hence the effect of the flow of free electrons in an open circuitry is established. It is found out that free electrons flowing both normal and parallel to thermal dissipation path in a metal affect its thermal diffusivity significantly. When electrons flow towards the thermal dissipation path due to electrostatic repulsion, the thermal diffusivity value of the metal is observed to increase and when the direction of electrons flow and thermal dissipation path due to electrostatic attraction are opposite one another, the thermal diffusivity value for the sample decreases.

The last phenomenon is understood to be the results of the fact that electrons in a metal behave like a collection of gas particles, 'Fermi-Gas' such that they move about through the metal unhindered and unaffected by the potentials of the ion core and hence remained un scattered for quite a long time. Within the limit of the room temperature at which the experiment is carried out, scattering of electrons in the metal by phonons is negligible. Similarly, for metals free from point defects, impurity and imperfections scattering by point defects and crystal imperfection is also ruled out. Hence, the applied potential difference accelerates the electrons towards or away from the temperature probe. When the electrons move towards the probe the thermal diffusivity value for the metal increases, and decrease when the electrons flow in the opposite direction. We also note that all these happened with no additional heat in the solid as the phenomenon occur in an open circuitry such that the Joule heating effects of flowing electrons are eliminated.

Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia sebagai memenuhi keperluan untuk ijazah Doctor Falsafah

**KESAN MEDAN ELEKTRIK KE ATAS RESAPAN TERMA KONDUKTOR
DIDALAM KONFIGURASI PEPEJAL TIGA-LAPISAN**

Oleh

SANI JIBRIN

March, 2015

Pengerusi: Azmi Bin Zakaria, Ph.D.

Fakulti: Sains

Satu model analitikal telah dibangunkan dengan menyelesaikan persamaan resapan haba untuk mendapatkan sifat-sifat terma film nipis daripada isyarat termanya. Penyelesaian matematik yang novel ini adalah teras untuk menentukan resapan terma konduktor dalam konfigurasi tiga-lapis secara eksperimen dengan menggunakan Teknik Gelombang Terma Menumpu. Ia dapat dilakukan dengan mengungkapkan penyelesaian yang berkaitan Laplace hiperbolik bagi persamaan yang diturunkan dalam bentuk eksponential negatif. Pengembangan siri Binomial kemudian digunakan untuk meringkaskan penyelesaian dan dari sini jadual penukaran Laplace, menggantikan teknik songsangan kamiran yang rumit, digunakan untuk memperolehi profil suhu temporal untuk sampel pepejal tiga-lapis dalam domain masa dan ruang nyata. Kemudian persamaan tersebut diplot menggunakan perisian Mathematica dan kejituannya diperiksa dengan melakukan analisis kepekaan ke atas parameter fizikal yang terkandung dalam persamaan yang diturunkan.

Dengan menggunakan Teknik Gelombang Terma Menumpu, tiga set eksperimen berasingan telah dijalankan ke atas sampel yang disediakan. Set pertama eksperimen yang terdiri dari empat sampel tiga-lapis dilakukan untuk menguji teori matematik dan untuk penentuan peralatan dan skema pengukuran. Hasil yang diperolehi dari siri eksperimen ini menunjukkan model matematik dan skema pengukuran yang ditetapkan untuk penilaian resapan terma sampel tersebut adalah jitu dalam lingkungan ralat 5%.

Set eksperimen kedua dilakukan untuk sampel pepejal tiga-lapis berbeza apabila arus terus dilalukan menerusi sampel. Hasil yang diperolehi menunjukkan nilai re-

sapan terma bagi kerajang logam dalam pepejal tiga-lapis bertambah dengan beza keupayaan merentasi kerajang. Didapati juga suhu kerajang logam meningkat sedikit hasil daripada kesan pemanasan Joule. Dalam siri ketiga eksperimen pepejal tiga-lapis berkenaan ditempatkan dalam medan elektrik statik dan dengan demikian tercas sama ada positif atau negatif sewaktu beza keupayaan berubah dari 1.00 V ke 10.00 V dengan setiap kenaikan 1 V, kesan medan elektrostatik ini telah dikaji. Pada kedua-dua keadaan sampel tercas positif dan negatif, 10 bacaan isyarat suhu berbeza telah diperolehi sebaik beza keupayaan DC diubah. Dengan cara ini, elektron bebas dalam konduktor digerak masing-masing sama ada ke arah atau menjauhi titik pegasan isyarat suhu dan dengan ini kesan elektron bebas mengalir kedua-duanya normal atau selari terhadap laluan susutan terma dalam sekeping logam memberi kesan yang signifikan kepada resapan termalnya. Apabila elektron mengalir ke arah laluan susutan terma disebabkan tolakan elektrostatik, nilai resapan terma logam didapati bertambah dan apabila laluan susutan terma melawan arah elektron mengalir disebabkan tarikan elektrostatik, nilai resapan terma sampel berkurangan.

Fenomena terakhir ini dapat difahami sebagai natijah bahawa elektron dalam logam pada kenyataannya merupakan sekumpulan zarah-zarah gas, 'Gas-Fermi' sehingga mereka bergerak menerusi logam tanpa halangan dan tidak terkesan oleh keupayaan teras ion dan dengan demikian kekal tidak tersebar untuk masa yang agak panjang. Dalam lingkungan suhu bilik yang mana eksperimen dijalankan, penyebaran elektron oleh fonon adalah boleh diabaikan. Demikian juga, untuk logam yang bebas dari cacat titik, bendasing dan ketaksempurnaan penyebaran oleh titik cacat dan ketaksempurnaan hablur adalah boleh dinafikan. Dengan ini, beza keupayaan yang dikenakan memecut elektron ke arah atau menjauhi penduga suhu. Apabila elektron bergerak ke arah penduga nilai resapan terma bagi logam bertambah, dan berkurangan apabila elektron mengalir dalam arah berlawanan. Kami juga mendapati kesemua ini berlaku tanpa penambahan haba dalam pepejal kerana fenomena berlaku dalam keadaan litar terbuka sehingga kesan pemanasan Joule kepada elektron yang mengalir dapat dihapuskan.

ACKNOWLEDGEMENTS

In the name of Allah the most Gracious the most merciful. I will like to begin by first thanking Allah the most merciful and most knowledgeable for making it possible for me to accomplish this task in my life time.

Special thanks and gratitudes go to my late parents for their role in seeing to my upbringing and education when they were alive. Theirs is a love, commitment, sacrifice, will and strength I'm yet to find its similarity. I pray that Allah rewards them abundantly, forgive their mistakes and shortcomings and makes Jannatul-firdaus their final abode.

Special thanks and mention must to be made of the chairman of my supervisory committee in person of Prof. (Dr.) Mohd. Maarof Bin Hj Abd Moxsin for his tireless efforts and commitments from the start and completion of this work. His constructive criticism, comments, suggestions and advice are actually what make this work focused and successful. The whole idea behind the work is owed to his resourcefulness. I pray that Allah will continue to increase his vast knowledge, forgive his shortcomings and rewards him with His best of rewards here and in the hereafter.

Other members of my research supervisory committee including Prof. (Dr.) Azmi Bin Zakaria, Prof. (Dr.) Zainal Abidin Bin Talib (the Dean, Faculty of Science) and Associate Prof. (Dr.) Jumiah Bint Hassan are equally appreciated for their supervisory role, comments, commitments and advice throughout this work.

For Prof. (Dr.) Azmi Bin Zakaria I actually have no enough words to describe his believe, understanding and commitments in the execution and success of this work and particularly his acceptance to continue as the chairman of the supervisory committee when Prof. (Dr.) Mohd. Maarof Bin Hj Abd Moxsin retired from the services of the Univerisity before my graduation. May Allah continue to increase his vast knowledge, forgive his shortcomings and rewards him with His best of rewards here and hereafter.

To my immediate and larger family I say a very big thank you for your patience, understanding and reasoning with self throughout this work. Your believe, good wishes, patience and prayers have really helped me especially during the difficult times of this research. May Allah continue to strengthen us in love, understanding and patience to one another.

To my best friends and co-researcher here in Malaysia, Shahril Husin I want to say thank you so much for the friendship, understanding and help throughout this work and my stay here in Malaysia. As we belong to the same research group and carried

out similar experiments, Shahril put me through all the soft and hard- wares needed for this work. To friends and family members back in Nigeria I say thank you all for your love, prayers and understanding throughout this programme. I also wish to appreciate my friend Sirajo Lawan Bichi for his extraordinary input in the mathematical analysis of this work and his friendly gesture toward self and family during the course of my studies. Mention must also be made of such friends and colleagues including but not limited to Dr. Sabo Wada Dutse, Salahu Hamza Muhammed, DR. Eng. Bashir Ahmed D/Zomo, Shamsu Abubakar, Alhassan Shu'aibu, Yusuf Zuntu, and many more that time and space will not allow self to put down. Thank you all



I certify that a Thesis Examination Committee has met on 24 March 2015 to conduct the final examination of Sani Jibrin on his thesis entitled "Effects of Electric Field on the Thermal Diffusivity of Conductors in Three-Layer Solid Configurations" in accordance with the Universities and University Colleges Act 1971 and the Constitution of the Universiti Putra Malaysia [P.U.(A) 106] 15 March 1998. The Committee recommends that the student be awarded the Doctor of Philosophy.

Members of the Thesis Examination Committee were as follows:

Zulkifly bin Abbas, PhD

Associate Professor
Faculty of Science
Universiti Putra Malaysia
(Chairman)

Abdul Halim bin Shaari, PhD

Professor
Faculty of Science
Universiti Putra Malaysia
(Internal Examiner)

Halimah binti Mohamed Kamari, PhD

Associate Professor
Faculty of Science
Universiti Putra Malaysia
(Internal Examiner)

Alberto Oleaga, PhD

Associate Professor
Universidad Del Pais Vasco
Spain
(External Examiner)



ZULKARNAIN ZAINAL, PhD

Professor and Deputy Dean
School of Graduate Studies
Universiti Putra Malaysia

Date: 13 May 2015

This thesis was submitted to the Senate of Universiti Putra Malaysia and has been accepted as fulfilment of the requirement for the degree of Doctor of Philosophy.

The members of the Supervisory Committee were as follows:

Azmi Zakaria, Ph.D.

Professor
Faculty of Science
Universiti Putra Malaysia
(Chairperson)

Zainal Abidin Talib, Ph.D.

Professor
Faculty of Science
Universiti Putra Malaysia
(Member)

Jumiah Hassan, Ph.D.

Associate Professor
Faculty of Science
Universiti Putra Malaysia
(Member)

BUJANG KIM HUAT, Ph.D.

Professor and Dean
School of Graduate Studies
Universiti Putra Malaysia

Date:

DECLARATION

Declaration by graduate student

I hereby confirm that:

- this thesis is my original work;
- quotations, illustrations and citations have been duly referenced;
- this thesis has not been submitted previously or concurrently for any other degree at any other institutions;
- intellectual property from the thesis and copyright of thesis are fully-owned by University Putra Malaysia, as according to the University Putra Malaysia (Research) Rules 2012;
- written permission must be obtained from supervisor and the office of Deputy Vice-Chancellor (research and Innovation) before thesis is published (in the form of written, printed or in electronic form) including books, journals, modules, proceedings, popular writings, seminar papers, manuscripts, posters, reports, lecture notes learning modules or any other materials as stated in the Universiti Putra Malaysia (Research) Rules 2012;
- there is no plagiarism or data falsification/fabrication in the thesis, and scholarly integrity is upheld as according to the Universiti Putra Malaysia (Graduate Studies) Rules 2003 (Revision 2012-2013) and the Universiti Putra Malaysia (Research) Rules 2012. The thesis has undergone plagiarism detection software.

Signature _____ Date: _____

Name and Matric No.: _____

Declaration by Members of Supervisory Committee

This is to confirm that:

- the research conducted and the writing of this thesis was under the supervision;
- supervision responsibilities as stated in the Universiti Putra Malaysia (Graduate Studies) Rules 2003 (Revision 2012-2013) are adhered to.

Signature: _____
Name of
Chairman of
Supervisory
Committee: _____

Signature: _____
Name of
Member of
Supervisory
Committee: _____

Signature: _____
Name of
Member of
Supervisory
Committee: _____



TABLE OF CONTENTS

	Page
ABSTRACT	i
ABSTRAK	iii
ACKNOWLEDGEMENTS	v
APPROVAL	vii
DECLARATION	ix
LIST OF TABLES	xiv
LIST OF FIGURES	xv
LIST OF ABBREVIATIONS	xviii
CHAPTER	
1 INTRODUCTION	1
1.1 Conduction of Heat in Solids	2
1.1.1 Conduction of Heat in Metals	2
1.1.2 Conduction of Heat in Metallic Alloys	3
1.1.3 Conduction of Heat in Non Metallic Solids	3
1.1.4 Conduction of Heat in Carbon-Based Materials	3
1.2 Photothermal Analysis	3
1.3 Thermal Diffusivity and Thermal Conductivity	5
1.4 Classification of Thermal Conductivity	6
1.4.1 Types of Heat Conduction	6
1.4.2 Dimensionality of Heat Conduction	6
1.5 Thermal Diffusivity	7
1.6 General Overview of Thermal Diffusivity Measurement	8
1.6.1 The Heating Source	8
1.6.2 The Sample and Sample Holder	9
1.6.3 The Temperature Probe	10
1.7 Research Question	10
1.8 Research Objectives	10
1.9 Research Scope	11
2 LITERATURE REVIEW	12
2.1 Thermal Diffusivity of Solids	12
2.2 Experimental Determination of Thermal Diffusivity of Solids	12
2.2.1 Effect of Finite Pulse	14
2.2.2 Effect of Heat Loss	16
2.2.3 Effect of Sample Thickness	18
2.2.4 Effect of Temperature on Thermal Diffusivity	20
2.3 Thermal Diffusivity by Converging Thermal Wave Technique	21

2.4	Effect of Current on the Temperature Profile and Thermal Diffusivity of Materials	22
2.5	Thermal Diffusivity of Thin and Highly Conducting Films	24
3	MATHEMATICAL MODELLING	29
3.1	Fourier's Law and the Heat Balance Equation	29
3.2	Initial and Boundary Conditions	30
3.3	General Differential Equation for Heat Conduction	31
3.3.1	The Heat Balanced Equation in Isotropic medium	33
3.3.2	The Heat Balanced Equation for Steady-State Conduction	33
3.3.3	The Heat Balanced Equation with no Internal Heat Generation	33
3.4	The Heat Balanced Equation in Cylindrical Polar Coordinates	34
3.5	Formulation of the Problem	35
3.5.1	Single-Layer Solid with Adiabatic Boundary Conditions	39
3.5.2	Two-Layer Solid with Adiabatic Boundary Conditions at the Rear Surface	40
3.5.3	Three-Layer Solid Structure	42
3.6	ALTERNATIVE INVERSION TECHNIQUE	46
3.6.1	Solution for a Single-Layer Solid	47
3.7	Mathematical Treatment of Heat Loss	49
3.7.1	Convective Heat Loss	49
3.7.2	Radiative Heat Loss	49
4	METHODOLOGY	51
4.1	Preparing Coating Material for Thermal Characterizations	51
4.1.1	Preparing the Required Powder and Weighing	51
4.1.2	Moulding and Casting Powder to Pellets	52
4.1.3	Sintering of the Pellets	52
4.1.4	Pellets Characterizations	52
4.2	Sample Preparations	53
4.3	Three-Layer Solid Samples	53
4.3.1	Three-Layer Sample by Electrophoretic Deposition	55
4.3.2	Three-Layer Sample by Dip Coating	57
4.3.3	Three-Layer Sample by Spin Coating	58
4.4	Sample's Characterizations	58
4.5	Experimental Set Up	58
4.5.1	Thermal Diffusivity Experiment I	59
4.5.2	Thermal Diffusivity Experiment II	61
4.5.3	Thermal Diffusivity Experiment III	62
4.6	Treatment of Data in Origin Software	63
4.7	Treatment of Data in Mathematica Software	66
4.7.1	Thermal Conductivity of the Metal Foils	68
4.7.2	Treatment of Data in QTI PLOT Software	68

5 RESULTS AND DISCUSSIONS	70
5.1 Temperature Profiles	70
5.1.1 Heat Loss Effect	73
5.1.2 Time of Maximum Height	73
5.2 Testing the Sensitivity of the Theoretical Curve	74
5.3 Effect of Thermal Conductivity of Coatings on Thermal Diffusivity of Metals	76
5.4 Thermal Diffusivity of Coatings	77
5.4.1 Starch Coat	80
5.4.2 Epoxy Adhesive Dp 110 Gray Coat	82
5.4.3 Zinc Oxide Coat	83
5.4.4 Manganese Dioxide Coat	85
5.5 Calibrations	86
5.6 Effect of Three-Layer Solid Configuration on Thermal Diffusivity of Metals	91
5.6.1 Thermal Diffusivity of Aluminium in Four Different Solid Matrices	91
5.6.2 Thermal Diffusivity of Copper in Four Different Configurations	95
5.6.3 Thermal Diffusivity of Nickel in Four Different Solid Matrices	98
5.6.4 Thermal Diffusivity of Silver in Four Different Configurations	101
5.6.5 Thermal Diffusivity of Tungsten in Four Different Configurations	104
5.6.6 Variation of Thermal Diffusivity of Metal Foils with Thermal Conductivity of Coatings	107
5.7 Thermal Diffusivity of Metals Due to Flowing Electric Current	108
5.8 Thermal Diffusivity of Metals Due to Static Electric Field	113
5.8.1 Positively Charged Sample	114
5.8.2 Negatively Charged Sample	119
5.8.3 Results for Charged Samples	124
5.9 Error Analysis	128
6 SUMMARY, CONCLUSIONS AND RECOMMENDATIONS	131
6.1 Summary	131
6.2 Conclusions	132
6.3 Recommendations	132
REFERENCES	134
APPENDICES	142
BIODATA OF STUDENT	144
LIST OF PUBLICATIONS	145

LIST OF TABLES

Table	Page
1.1 Common detection techniques used in photothermal spectroscopy	4
2.1 Summary of Essential Literature Reviewed	21
4.1 Mass of Powder and Thickness of Pellets Produced	51
4.2 Three-Layer Solid Configurations Formed	53
5.1 Thermal Conductivity of Coating Versus Thermal Diffusivity of Metals	77
5.2 Thermal Diffusivity Values of Coating Materials	78
5.3 Thermo-Physical Properties of Coatings	79
5.4 Parameter Values of Metal Foils Used	87
5.5 Parameter Values for Epoxy1/Al/Epoxy2	87
5.6 Parameter Values for Epoxy1/Cu/Epoxy2	87
5.7 Parameter Values for Epoxy1/Ni/Epoxy2	87
5.8 Parameter Values for Epoxy1/Ag/Epoxy2	87
5.9 Comparison with Literature Values	91
5.10 Three-Layer Configurations	91
5.11 Thermal Diffusivity Values of Al Foil	94
5.12 Thermal Diffusivity Values of Cu Foil	97
5.13 Thermal Diffusivity Values of Ni Foil	100
5.14 Thermal Diffusivity Values of Ag Foil	103
5.15 Thermal Diffusivity Values of W Foil Versus Thickness of Coating	106
5.16 Thermal Conductivity of Coating Versus Thermal Diffusivity of Aluminium	107
5.17 Thermal Conductivity of Coating Versus Thermal Diffusivity of Copper	107
5.18 Thermal Conductivity of Coating Versus Thermal Diffusivity of Nickel	108
5.19 Thermal Conductivity of Coating Versus Thermal Diffusivity of Silver	108
5.20 Change in Thermal Diffusivity Values for Al with Current	108
5.21 Change in Thermal Diffusivity Values for Cu with Current	108
5.22 Change in Thermal Diffusivity Values for Ni with Current	109
5.23 Change in Thermal Diffusivity Values for Ag with Current	109
5.24 Change in Thermal Diffusivity Values for W with Current	109
5.25 Temperature and Power Generated in Aluminium Metal Foil	111
5.26 Temperature and Power Generated in Copper Metal Foil	111
5.27 Temperature and Power Generated in Nickel Metal Foil	111
5.28 Temperature and Power Generated in Silver Metal Foil	112
5.29 Temperature and Power Generated in Tungsten Metal Foil	112

LIST OF FIGURES

Figure	Page
1.1 Processes involved in photothermal analysis	4
1.2 Photothermal phenomenon caused by sample illumination	9
3.1 Differential control volume for conduction analysis in cartesian coordinates	31
3.2 Coordinates in cylindrical polar system	34
3.3 Geometry of the problem	36
3.4 Transmission line with current source terminated in a load impedance	44
3.5 Transmission line with current source terminated in a load impedance	45
4.1 Schematic diagram of sample for experimental set II	54
4.2 Circuit for electrophoretic deposited of ZnO	56
4.3 Snap shot of ZnO layer deposited by EPD on copper substrate	57
4.4 Dip coating deposition process	58
4.5 Schematic diagram of sample holder showing heating rings	59
4.6 Schematic diagram of the experimental set-up I	60
4.7 Labview programme front panel	61
4.8 Schematic diagram of the experimental set-up III	62
4.9 Schematic diagram of the experimental set-up	63
4.10 Temperature-time history for sample at room temperature	64
4.11 Fitting rough data with built-in polynomials	64
4.12 Normalized rough data	65
4.13 Normalized and noiseless data	66
4.14 Plotting data and theory	66
4.15 Simulated fittings session	67
4.16 Final Simulated fittings session	68
4.17 Fitting results in QTIPlot	69
5.1 Theoretical Curve for Single-Layer Solid	70
5.2 Theoretical Curve for Two-Layer Solid	71
5.3 Theoretical Curve for Three-Layer Solid	72
5.4 Heat Lost by Convection and Conduction	73
5.5 Simulation in Change in (a) α_1 and (b) α_2 on Theoretical Curve	74
5.6 Simulation in Change in (a) α_3 and (b) d_1 on Theoretical Curve	75
5.7 Simulation in Change in (a) d_2 and (b) d_3 on Theoretical Curve	75
5.8 Simulation in Change in (a) k_1 and (b) k_2 , on Theoretical Curve	76
5.9 Simulation in Change in (a) r and (b) q on Theoretical Curve	76
5.10 LFA 457 Results for DP 110 (Epoxy) and Starch	78
5.11 LFA 457 Results for Manganese dioxide and Zinc Oxide	78
5.12 AFM Image for Starch Deposited Film	80
5.13 AFM Image for Starch Deposited Film	81

5.14 Apparent Opacity of Different Starch Films, (Galdeano et al., 2013)	81
5.15 AFM Image for Epoxy-Resin Hardener Mixture Deposited Film	82
5.16 AFM Image for Epoxy-Resin Hardener Mixture Deposited Film	83
5.17 AFM Results for Zinc Oxide Thin Film	84
5.18 AFM Results for Zinc Oxide Thin Film	84
5.19 AFM Images for Deposited Film of Manganese Dioxide	86
5.20 Fitting Results for Aluminium in Configuration 1	88
5.21 Fitting Results for Copper in Configuration 1	89
5.22 Fitting Results for Nickel in Configuration 1	90
5.23 Fitting Results for Silver in Configuration 1	90
5.24 Fitting Results for Aluminium in Configuration 1	92
5.25 Fitting Results for Aluminium in Configuration 2	92
5.26 Fitting Results for Aluminium in Configuration 3	93
5.27 Fitting Results for Aluminium in Configuration 4	93
5.28 Fitting Results for Copper in Configuration 1	95
5.29 Fitting Results for Copper in Configuration 2	96
5.30 Fitting Results for Copper in Configuration 3	96
5.31 Fitting Results for Copper in Configuration 4	97
5.32 Fitting Results for Nickel in Configuration 1	98
5.33 Fitting Results for Nickel in Configuration 2	99
5.34 Fitting Results for Nickel in Configuration 3	99
5.35 Fitting Results for Nickel in Configuration 4	100
5.36 Fitting Results for Silver in Configuration 1	101
5.37 Fitting Results for Silver in Configuration 2	102
5.38 Fitting Results for Silver in Configuration 3	102
5.39 Fitting Results for Silver in Configuration 4	103
5.40 Fitting Results for Tungsten in Configuration 1	104
5.41 Fitting Results for Tungsten in Configuration 2	105
5.42 Fitting Results for Tungsten in Configuration 3	105
5.43 Fitting Results for Tungsten in Configuration 4	106
5.44 Steady State Temperature Versus Potential Difference Across A Rod, (Young, 1986)	110
5.45 Change in Thermal Diffusivity of Al with (a) 2v and (b) 4V	114
5.46 Change in Thermal Diffusivity of Al with (a) 6v and (b) 8V	114
5.47 Change in Thermal Diffusivity of Cu with (a) 2v and (b) 4V	115
5.48 Change in Thermal Diffusivity of Cu with (a) 6v and (b) 8V	115
5.49 Change in Thermal Diffusivity of Ni with (a) 2v and (b) 4V	116
5.50 Change in Thermal Diffusivity of Ni with (a) 6v and (b) 8V	116
5.51 Change in Thermal Diffusivity of Ag with (a) 2v and (b) 4V	117
5.52 Change in Thermal Diffusivity of Ag with (a) 6v and (b) 8V	117
5.53 Change in Thermal Diffusivity with Applied Positive PDs	118
5.54 Change in Thermal Diffusivity of Al with (a) 2v and (b) 4V	119
5.55 Change in Thermal Diffusivity of Al with (a) 6v and (b) 8V	120
5.56 Change in Thermal Diffusivity of Cu with (a) 2v and (b) 4V	120
5.57 Change in Thermal Diffusivity of Cu with (a) 6v and (b) 8V	121

5.58	Change in Thermal Diffusivity of Ni with (a) 2v and (b) 4V	121
5.59	Change in Thermal Diffusivity of Ni with (a) 6v and (b) 8V	122
5.60	Change in Thermal Diffusivity of Ag with (a) 2v and (b) 4V	122
5.61	Change in Thermal Diffusivity of Ag with (a) 6v and (b) 8V	122
5.62	Change in Thermal Diffusivity with Applied Negative PDs	123
5.63	Change in Thermal Diffusivity with Applied PDs	124
5.64	Change in Thermal Diffusivity with Applied PDs	125
5.65	Fermi Sphere with and without Applied Field	125
5.66	Plot of Thermal Conductivity Against Electrical Conductivity	126
5.67	Error Analysis	129
A.1	Epoxy adhesive dp 110 gray	142
B.1	Hydraulic press	143

LIST OF ABBREVIATIONS

AC	Alternating Current
d	Thickness of Layer/Material
DE	Differential Equation
DC	Direct Current
e	Electronic Charge
E	Electric Field Strength
F	Force Field
I	Current
k	Thermal Conductivity
m	Mass
ODE	Ordinary Differential Equation
P	Power
PD	Potential Difference
PDE	Partial Differential Equation
q	Quantity of Camera Heating Energy
r	Radius of Camera Flash Heating Ring
R	Radius of Sample
s	Laplace Parameter
t	Time
t_0	Characteristic Rise Time
T	Temperature
V	Velocity
α	Thermal Diffusivity
β	Small-Value Negative Integer
τ	Pulse Duration
ρ	Density

CHAPTER 1

INTRODUCTION

Recent advances in science and technology bring about sophistication in electronics, photonics, sensors, photovoltaic and associated devices. These advances are made possible not only as a result of miniaturization or scaling down of transistors and associated components but also due to the fact that corresponding advances have been made in efficient heat removal from these systems. With less efficient heat removal techniques from these devices, sudden breakdown and or malfunction are bound to occur.

The use of layered materials in the efficient removal of heat from appliances is as imperative as the advances themselves. The Thermal Interface Materials (TIMs) for example used to remove heat from electronics and photonics devices is basically a multilayer device placed between the heat source and heat sink. Essential part of these TIMs is a metal or any thermal conducting material containing free electrons and or phonons that carries the generated and unwanted thermal energy for dissipation. In a situation where electrons are involved and also since most of these appliances work with applied Potential Difference (PD), the thermal diffusivity value of the metals conducting heat energy will change as a result of a change in the number and or velocity of the metals' free electrons. When the direction of flow of conducting electrons in a metal due to applied electric field coincides with the direction of heat dissipation path, or when more of the conducting electrons are made to flow in that direction, thermal diffusivity value of the metal is envisage to be enhanced. On the other hand, when the applied electric field makes conducting electron to flow in a path completely opposite to that of heat dissipation or when few electrons are made to flow in that direction, the metal's thermal diffusivity will likely be reduced greatly.

This work therefore, aims at using an extended version of Converging Thermal Wave (CTW) technique initially developed by Cielo and his co-workers to evaluate the possible change in the value of the thermal diffusivity of a metal in a three-layer device as the device carries Direct Current (DC) supply in both open and closed circuitries. The present chapter therefore gives a short and brief introduction of the topics and basic concepts to be covered in this thesis which include: thermal conductivity, thermal diffusivity, relationship between them and other thermo-physical quantities and classification of thermal conductivity into types and dimensions. Some highlights on the significance of experimental determination of thermal diffusivity are also given in this chapter. The general overview of the requirements for the experimental analysis of thermal diffusivity such as the heating source, the sample and sample holder, as well as the temperature probe is also briefly discussed. The chapter ends with the statement of our research problem, research objectives and an outline of our research scope.

1.1 Conduction of Heat in Solids

Sadik (1985) defines heat as the form of energy that crosses the boundary of a thermodynamic system by virtue of a temperature difference existing between the system and its surrounding, (Sadik, 1985). Heat is therefore understood as energy in transition and the potential that drives it along a certain path and or direction is the temperature gradient. Although heat transfer happens to be a very complex phenomenon in relation to processes through which it occurs, however three modes of heat transfer mechanisms have been observed as basic. These are conduction, convection and radiation. Temperature distribution in a medium is generally controlled by the combined effects of these modes of heat transfer. It is not therefore very easy to entirely isolate one mode of heat transfer from interactions with other modes. However, since in solids convection is altogether absent at working temperature of the present work while radiation is very negligible, (Carlslaw and Jaeger, 1959), only conduction, as the basic heat transfer mechanism in solids will be considered in this work.

Conduction of heat in solids is a microscopic phenomenon where more energetic particles of a substance transfer their energies to their less energetic neighbours. This energy transfer process in solids occurs by lattice vibrations (phonons) and or by motion of free electrons. Transfer of heat by phonons in non-metallic substances dominates that by free electrons in solids whereas electrons contributions dominate thermal conduction in metals, (Balandin, 2011).

1.1.1 Conduction of Heat in Metals

Since there is abundance of free electrons in metals, electronic contribution to thermal conduction dominates; with phonons contributing only about 1 - 2% of the total thermal conduction. This explains why all metallic substances are good electrical as well as good thermal conductors. The fact that free electrons are more numerous, free, light and interact with one another less often as a result of shielding and Pauli exclusion principle makes solids composed of electrons to conduct thermal energy better than solid composed of any other conducting quasi particle. The only possible exception to this is the pattern of thermal conduction in the recently discovered carbon-based materials where thermal conduction is extremely high, and yet brought about mostly by phonons contributions to thermal conduction.

Due to the similarity between the thermal and electrical conduction in metals, a relation based on experimental facts exists between the two phenomena. The Weidemann-Franz law gives this relationship and is stated as, the ratio of thermal and electrical conductivities is the same for all pure metals at the same temperature and is directly proportional to the absolute temperature of the metal. The constant of proportionality here is called the Lorentz number and is constant for all pure metals. Any effect which inhibits the flow of free electrons in a metal reduces both thermal and electrical conduction. Hence thermal conduction in pure metals is impeded by: rise in temperature of the metal, presence of impurities, mechanical forming and reduction

in the density of the metal.

1.1.2 Conduction of Heat in Metallic Alloys

Electrons are also the majority carriers of thermal energy in this class of materials owing to their large concentrations. Their motion which was hitherto free in pure metals is however impeded by scattering with the introduced foreign atoms. Since the free electrons can not move as free and as quickly as in pure metals, their contribution to thermal conduction is greatly reduced. The thermal conductivity of pure copper near room temperature, for example, is 401 W/mK, presence of traces of arsenic reduces the value to 142 W/mK, (Thirumaleshwar, 2006). Unlike pure metals however, the thermal conductivity of alloys increases with temperature.

1.1.3 Conduction of Heat in Non Metallic Solids

These are the class of solid materials with less free conducting electrons. They are therefore generally bad conductors of both heat and electric current. Thermal conduction in these materials is carried mostly by lattice vibrations (phonons), as such conduction increases with increase in temperature. The contribution of electrons to thermal conduction here is very small as very few of them can break free from the potentials of the ion core holding them rigid. Other factors which can affect thermal conduction of these class of materials include density and moisture contents.

1.1.4 Conduction of Heat in Carbon-Based Materials

These are the class of materials with less free conducting electrons like all non metallic solids and hence supposed to behave in a similar manner. Yet, carbon-based materials show a remarkable departure from other non-metallic materials as far as thermal conduction is concerned. The thermal conductivity of graphite, for example, is reported to be as high as 2000 W/mK, (Yan et al., 2012) and between 4840 W/mK to 5300 W/mK for single-layer graphene at room temperature (Balandin et al., 2008). This high thermal conductivity is the sole contributions of phonons and is explained by the strong covalent sp^2 bonding resulting in efficient heat transfer by lattice vibrations in these materials, (Balandin, 2011).

1.2 Photothermal Analysis

Solids can be heated by absorbing optical radiation which produces a thermal change in the state of the solids. This process often called photothermal spectroscopy involves absorption of modulated light energy and its subsequent liberation from the solid. The liberated thermal energy usually contains information about the absorbed energy as well as details in respect to the thermal properties of the solid. The fraction of the absorbed thermal energy not only causes a change in temperature of the material but also changes in other properties of the solid such as density and pressure. Figure 1.1 shows the basic processes involved in Photothermal spectroscopy and the three thermodynamic parameters which change as a result of optical absorption by the solids.

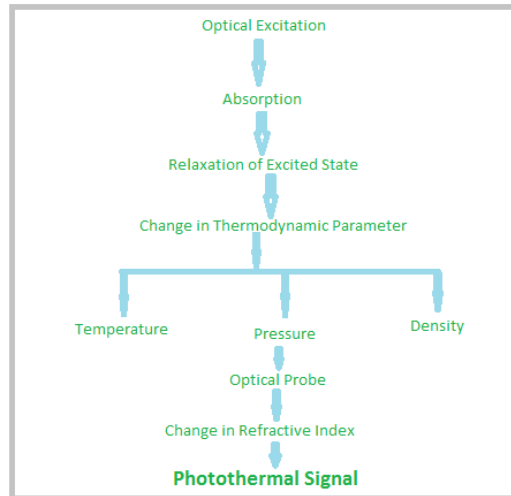


Figure 1.1: Processes involved in photothermal analysis

Each of these thermodynamic parameter is associated with some property/properties that can be measured from the interaction. If temperature is the thermodynamic property that changes as a result of the optical absorption, for example, this change can be measured in either of two ways. The temperature can be measured directly through a technique called calorimetric analysis using probes like thermocouples, thermistors, pyroelectric detection system, as done by majority of researchers in this field, (Parker et al., 1961), (Cielo et al., 1986), (Murphy et al., 2005), etc, or the temperature induced infrared emission can be measured through a process called photothermal transient radiometry as demonstrated by some researchers including (Vitkin et al., 1994), (Mandelis, 1991), (Imhof et al., 1998). Other measured properties and the detection techniques adopted for them are as summarised in Table 1.1.

Table 1.1: Common detection techniques used in photothermal spectroscopy

Thermodynamic Parameter	Measured Property	Detection Technique
Temperature	Temperature	Calorimetry
	Infrared Emission	Photothermal Radiometry
Pressure	Acoustic Waves	Photoacoustic Spectroscopy
Density	Refractive Index	Photothermal Lens Photothermal Interferometry Photothermal Deflection Photothermal Refraction Photothermal Diffraction
	Surface Deformation	Surface Deflection

1.3 Thermal Diffusivity and Thermal Conductivity

Thermal and electric fields coexist in electronics and photonics components and devices where electric field is needed and used to power the devices while thermal field is generated mostly by Joule heating. This generated thermal energy need to be removed from the devices for their proper functioning and most importantly to avoid breaking down of the devices. Since electrons are the major carriers of thermal energy in solids, their number, speed and direction will affect the amount of heat energy dissipated in a particular direction. The existence of both electric and temperature fields represents a closer approximation to the situation in any electronic device while in operation where problems associated with overheating are a major concern. As heat is therefore generated within current carrying materials, thermal diffusivity of the material may change from its known value depending on the magnitude and direction of the material's free electrons in relation to the direction of thermal dissipation in the material. To understand what really happens when electrons conduct heat in both the direction of heat dissipation path and in its completely opposite direction we need to understand some basics about heat conduction as enumerated below.

Whenever there is a temperature gradient within a body or when two or more bodies at different temperatures are brought in to thermal contact with one another, heat or thermal energy flows from the region of higher temperature to that at lower temperature. Apart from the temperature difference between the regions or bodies concerned, the most important intrinsic factor which determines the rate of thermal energy flow is a material property called thermal conductivity. Thermal conductivity may therefore be understood as that ability of a material which allows it to transport (conduct) heat from one point to the other. It is a direct microscopic exchange of kinetic energy of particles through the material boundary between two systems kept at different temperatures. At such instances heat flows from the region or material with highest temperature to that with lowest in accordance to the second law of thermodynamics, (Serway and Jewwet, 2010). At room temperature and fixed lower temperatures, electrons are the major carries of this heat energy in metals devoid of lattice imperfection and defects, whereas in carbon-based materials at the same temperature, phonons are the dominant carriers. Apart from conduction, convection and radiation are other known methods of transferring heat from one material to the other. However, in solids, convection is very negligible while radiation is all together absent hence, as far as heat transfer in solids is concerned, conduction processes are the leading methods.

The higher the thermal conductivity of a material, the better the material conducts heat, and vice versa. Consequently, in pure metals at room temperature, the higher the number of free electrons drifting in the direction of heat dissipation path, the better the metal conduct heat in that direction, and vice-versa. At fixed temperatures, thermal conductivity of a material is constant; otherwise it changes with a change in temperature of the substance (Carlslaw and Jaeger, 1959). The S.I. unit of thermal

conductivity is the Watt per metre Kelvin (W/mK) and its dimension is given as $M L T^{-3} \theta^{-1}$.

1.4 Classification of Thermal Conductivity

Thermal conduction in solids may be classified into types and dimensionality as explained in the next subsections.

1.4.1 Types of Heat Conduction

Conduction of heat in solids may generally be categorized into transient or steady state. Transient state conduction is that in which the rate of heat transfer changes continuously with time and hence, the transfer rate is time dependent whereas, steady-state heat conduction is that in which the heat transfer rate does not change with time and hence the transfer rate can be said to be time independent. All natural conduction transfer processes begin as transient and then steadily approach steady state over time until equilibrium is attained.

1.4.2 Dimensionality of Heat Conduction

Depending on the magnitude of heat transfer rate in different directions of a solid, heat transfer can take place in one of the following dimensions: one-dimension, two-dimensions or three-dimensions. In one-dimensional heat transfer, the transfer rate is more assertive and dominant in one direction than the others. Temperature distribution, T is characterized by only one spatial component and the heat flux q characterized by one dimensional component. One-dimensional heat transfer can happen in all classes of materials depending on the material's geometry, the level of accuracy desired, (Yunus and Afshin, 2011) and the direction of the vector normal to isothermal surface drawn on the material. Examples of physical systems in which the transfer rate is approximately one-dimensional include: the hot metal plate of a pressing iron, electrical resistance wire, a cast iron steam pipe, etc. The Fourier's law of heat conduction in one-dimension for example, x-direction, through isotropic material is written as (Thirumaleshwar, 2006);

$$\frac{\partial q}{\partial t} = -kA \frac{\partial T}{\partial x} \quad (1.1)$$

Here q = thermal energy, t = time, k = thermal conductivity, A = material's cross sectional area and T = temperature.

In two-dimensional heat transfer, the transfer rate is approximated to take place more along two directions than the other remaining direction. Hence temperature distribution, T is characterized by two spatial components and the heat flux q is also characterized by two dimensional components; for example T_x , T_y and q_x , q_y for heat transfer along the x and y directions respectively. The Fourier's law of heat conduction in the two-dimensions mentioned above and through isotropic material is

written as, (Carlslaw and Jaeger, 1959),

$$\frac{\partial^2 q_x}{\partial t^2} + \frac{\partial^2 q_y}{\partial t^2} = -kA \left(\frac{\partial T_x}{\partial x} + \frac{\partial T_y}{\partial y} \right) \quad (1.2)$$

In most general case, heat transfer problem is three-dimensional, i.e. that in which the heat conduction takes place through all the three principal directions (x, y, z in Cartesian coordinates). Here the temperature distribution is characterized by three different spatial components T_x , T_y , T_z while the heat flux term is characterized by three different components q_x , q_y , q_z . The three-dimensional heat conduction equation for a transient conduction in which no heat is generated is given as (Ozisik, 1993);

$$\frac{\partial^2 T_x}{\partial x^2} + \frac{\partial^2 T_y}{\partial y^2} + \frac{\partial^2 T_z}{\partial z^2} = \frac{1}{\alpha} \frac{\partial T}{\partial t} \quad (1.3)$$

1.5 Thermal Diffusivity

Closely related to thermal conductivity is a quantity called thermal diffusivity which specifies how fast a material conduct heat. The higher the thermal diffusivity value of a material the faster the material conducts heat and vice versa. Like thermal conductivity, thermal diffusivity is also a function of material's temperature apart from other physical quantities. Its S.I. unit is m^2s^{-1} while its dimension is L^2T^{-1} . Thermal diffusivity is mathematically related to thermal conductivity by the following relation;

$$k = \alpha \rho C \quad (1.4)$$

Here k = thermal conductivity, α = thermal diffusivity, ρ = density and C = specific heat capacity.

As a consequence of Equation (1.4) above, thermal diffusivity α is written as;

$$\alpha = \frac{k}{\rho C} \quad (1.5)$$

As the denominator to Equation (1.5) above is equivalent to the volumetric heat capacity of a material, thermal diffusivity can be thought to be a measure of the ratio of the total amount of heat conducted away by the material to that retained in it. Thermal diffusivity will also change when the direction of flow of metals' conducting electrons changes with that of the heat dissipation direction.

In the study of heat conduction in solids, thermal diffusivity is by far more important not only because of its mathematical relevance as given by Equations (1.4) and (1.5) above but, also because, it is more easier to determine experimentally than thermal conductivity or even other thermo-physical quantities. Some other advantages of

experimental determination of thermal diffusivity include:

1. All thermal diffusivity experiments are transient in nature hence, less time is required to perform experiment.
2. They are much more accurate than thermal conductivity values.
3. Its determination makes the evaluation of other thermo-physical quantities easier.
4. Thermal diffusivity experiments make use of small samples sizes with different geometry
5. They are usually non-contact and less prone to errors

1.6 General Overview of Thermal Diffusivity Measurement

All experimental determination of thermal diffusivity of materials involves transient heating of a sample usually of small dimension but of almost any geometry. The essential features of these types of experiments involves the heating source, the heated sample, sample holder and temperature probe. These are briefly discussed in the subsections that follow.

1.6.1 The Heating Source

This is the source of thermal energy which initiates the heating of the sample. It is usually either a pulsed laser (coherent sources) or broad spectrum range sources (incoherent sources) used to induced initial temperature profile in the sample. Some of the coherent sources include: helium-neon gas, argon fluoride, Nd:YAG, argon ion, gallium arsenide, semiconductor diode array, etc. The incoherent sources on the other hand include: xenon-lamp, global, nernst, and of recent camera flash, etc. Five types of sample heating used in photo-thermal method of thermal diffusivity experiments are as mentioned below (Park et al., 1995):

1. Large area surface heating.
2. Line heating.
3. Small spot heating
4. Grating heating and
5. Circular heating

In photo-thermal method of thermal diffusivity determination, the heating source is usually in a form of light source of high intensity. At the surface of the sample, and where the heating initiates, this light is converted to thermal energy and also causes other physical changes in and around the sample as shown in Figure 1.2, (Almond and Patel, 1996). Since after the first experiment in this series by Parker and his co-workers in 1966 (Parker et al., 1961), laser flash became the main source of heating in majority of transient thermal diffusivity experiments.

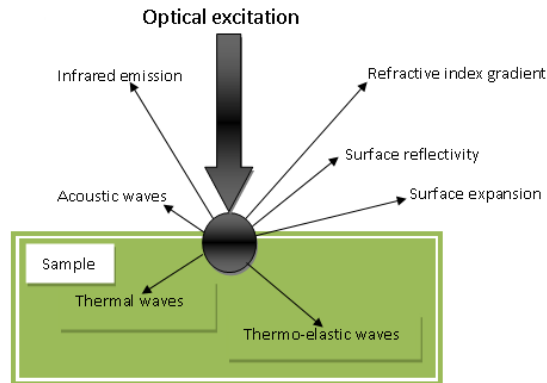


Figure 1.2: Photothermal phenomenon caused by sample illumination

The use of camera flash in place of laser as sample heating source in thermal diffusivity experiments is made possible due to the following reasons:

1. Camera flash is much cheaper to set up and maintain than laser flash apparatus.
2. It is much safer and easier to work with than the hazardous laser flash.
3. No much skill and or expertise is required to operate the camera flash set up.
4. It is small and portable and hence can be set up in almost all laboratories and can as well be moved about easily.
5. It can be operated with dry cell batteries and hence save a lot of trouble and energy in using electricity from the mains supply.
6. The fact that its width length is shorter than that of the laser flash affords the researcher a new but simpler mathematical method of evaluating the temporal temperature of the heated sample.

Generally, any other source of heating in the form of light may be used in as much as the converted thermal energy is just enough to initiates heating of the sample, high enough to be detected by the temperature probe and low enough so as not to produce any phase change in the sample.

1.6.2 The Sample and Sample Holder

Majority of the samples in transient thermal diffusivity experiments are some portion of solid, liquid or gas to be tested. The fluids are usually enclosed in a specially made container depending on its volume, type and weather the experiment is intended to be made for stationary or moving fluids. The solids on the other hand are most often small, thin and of almost any geometry. It is mounted on to a special surface called sample holder for the heating process.

Depending on the type of heating needed for the sample, different sample holders are made to hold the sample for the desired heating. The essential feature of all sample holders should be such that they held the sample fixed and rigid for the experiment, they neither block, absorb or reflect the light before its incident on the sample and also before it reaches the temperature probe, they should be appropriate to the type of heating required for the sample as explained in section 1.6.1 above.

1.6.3 The Temperature Probe

Thermal waves are detected using three general schemes: acoustic, optical and thermal, (Almond and Patel, 1996). Depending on whether the medium is solid or gas, acoustic detection techniques make use of either a piezoelectric transducer or a gas condenser microphone for the detection of thermoelastic waves in solid media or the detection of pressure variation in gas respectively. Optical methods of temperature probe makes use of probe beams and photo-detectors to monitor the variation in the optical properties of the heated sample or that of a fluid medium placed close to the heated sample. The last detection scheme listed above which is also employed in this work and majority of similar experimental works makes use of wide range of thermal detection apparatuses and appliances such as infrared detector, thermocouples, thermistor, pyroelectric transducers, etc., to detect thermal waves from the heated sample directly.

1.7 Research Question

In metals at room temperature, both phonons and electrons contribute to thermal conduction. The electrons' contribution however dominates with phonons contributing only about 1-2% of the total, (Balandin, 2011). In this class of materials therefore, and at the stated temperature and lower, electrons are the major carriers of heat and hence, their number, speed and direction of motion will affect the thermal conductivity and by extension thermal diffusivity of the material. The number, speed and direction of electrons may be affected by flowing or static electric field, whereas, temperature gradient is needed to initiate heat transfer process. The existence of both electric and temperature fields represents a closer approximation to the situation in any electronic device while in operation where problems associated with overheating are a major concern. As heat is therefore generated within current carrying materials, thermal diffusivity of the material may change from its known value depending on the magnitude and direction of the current in relation to the direction of thermal dissipation in the material. Current literature is however deficient on effect of flowing and static electric current on the thermal diffusivity of metals in three-layer solid configuration similar to thermal interface materials.

1.8 Research Objectives

The objectives of this research are as follows:

1. To derive and solve the two-dimensional unsteady-state heat conduction equation for a single-layer, two-layer and three-layer solid samples using the In-

tegral transform method so as to set up the basic theoretical scheme for the research work.

2. To fabricate different three-layer solid composites using different techniques and characterize same for use in the experimental determination of thermal diffusivity of a layer in the three-layer solid configuration.
3. To experimentally determine the thermal diffusivity of metal foils in three-layer solid configurations so as to calibrate the measuring scheme and apparatus.
4. To experimentally determine the effect of direct electric current passing across metal foils on the thermal diffusivity of the foils in three-layer solid configurations.
5. To experimentally determine the effect of static electric fields on the thermal diffusivity of metal foils in three-layer solid configurations.

1.9 Research Scope

This work aims at evaluating the effect of static and flowing direct electric current on the thermal diffusivity of metals occurring in three-layer solid composites. Unlike the flow of DC through a metal, it has been established that the flow of AC makes the sample's temperature profile non-parabolic and the volumetric power generated within the sample non-uniform, (Barletta and Zancini, 1995), (Abdel-Hamid, 1997), hence, this work will not focus on the effect of AC fields on the thermal diffusivity of the metal. Similarly, the work will concentrate more on the thermal diffusivity of three-layer solid samples under the influence of the fields mentioned above, as such single-layered and multi-layered solid samples with composite layers, $N \neq 3$ (N being the number of layers in the composite) will not be considered in this work. The work will only aimed at evaluating thermal diffusivity of the samples mentioned above; hence, no any other thermal property of the said three-layer solid composite will rigorously be evaluated in this work.

REFERENCES

- Abdel-Hamid, B. 1997. Transient temperature distribution of periodic heat diffusion in a flat plate crossed by an alternating electric current. *Applied Mathematical Modelling* 21: 387–393.
- Achille, T. F., George, A. N. and Alphonse, K. 2007. Contribution to light transmittance modelling in starch media. *African Journal of Biotechnology* 6 (5): 569–575.
- Adamczyk, W., Filip, S., Pawel, K., Ryszard, B. and Tadeusz, K. 2013. CFD Estimation of Heat Losses in Thermal Conductivity Measurements. *Computer Assisted Methods in Engineering and Science* 20.
- Almond, D. P. and Patel, P. M. 1996. *Photothermal Science and Techniques*. Chapman and Hall.
- Balageas, D. L. 1982. New Method of Interpretation of Thermograms for Determining the Thermal Diffusivity by the Pulse method (Flash). *Applied Physics Review (French)* 17: 227–237.
- Balandin, A. 2011. Thermal properties of graphene and nanostructured carbon materials. *Nature Materials* 10: 569–581.
- Balandin, A. A., Ghosh, S., Bao, W., Calizo, I., Teweldebrhan, D., Miao, F. and Lau, C. N. 2008. Superior Thermal Conductivity of Single-Layer Graphene. *Nano Letters* 8: 902–907.
- Barletta, A. and Zancini, E. 1995. Steady Periodic Heat Transfer in a Flat Plate Conductor Carrying an Alternating Electric Current. *International Communications in Heat and Mass Transfer* 22: 241–250.
- Blois, J. M. S. and Rieser, J. L. M. 1954. Apparent Density of Thin Evaporated Films. *Journal of Applied Physics* 25 (3): 338–340.
- Borden, P. G. 1980. A Novel Method for Measuring the Thermal Conductivity of Electrodeposited Gold Films. *Journal of The Electrochemical Society* 127 (11): 2454–2457.
- Brorson, S. D., Fujimoto, J. G. and Ippen, E. P. 1987. Femtosecond Electronic Heat-Transport Dynamics in Thin Gold Films. *Physical Review Letters* 59 (17): 1962.
- Bruls, R. J., Hintzen, H. T. and Metselaar, R. 2005. A New Estimation Method for the Intrinsic Thermal Conductivity of Nonmetallic Compounds: A Case Study for MgSiN₂, AlN and beta-Si₃N₄. *Journal of the European Ceramic Society* 25: 767–779.
- Cape, J. A. and Lehman, G. W. 1963. Temperature and finite pulse time effects in the flash methods for measuring thermal diffusivity. *Journal of Applied Physics* 34: 1909–1913.

- Carlslaw, H. S. and Jaeger, J. C. 1959. *Conduction of Heat in Solids*. 2nd edn. Walton Street, Oxford: Oxford University Press.
- Chen, G. and Hui, P. 1999. Pulsed Photothermal Modelling of Composite Samples Based on Transmission-Line Theory of Heat Conduction. *Thin Solid Films* 339 (58-67).
- Chen, L. and Clarke, D. R. 2009. A Numerical Solution Based Parameter Estimation Method for Flash Thermal Diffusivity Measurements. *Computational Materials Science* 45 (2): 342–348.
- Cielo, P., Utracki, L. A. and Lamontagne, M. 1986. Thermal Diffusivity Measurements by the Converging Thermal Wave Technique. *Canada Journal of Physics* 64: 1172 – 1177.
- Clark, L. M. and Taylor, R. E. 1975. Radiation loss in the flash method for thermal diffusivity. *Journal of Applied Physics* 46: 714–719.
- Claudia, S., M., O., Silvina, R., C., D. and E., M. T. 2014. Electrophoretic deposition of ZnO nanostructures: Au nanoclusters on Si substrates induce self-assembled nanowire growth. *Material Science and Engineering B* 187: 21–25.
- Cowan, R. D. 1963. Pulse Method of Measuring Thermal Diffusivity at High Temperatures. *Journal of Applied Physics* 34.
- Daegy, P., Heemoon, K. and Wooseok, R. 2008. Finite Pulse Time Effects for High Thermal Diffusivity Material. In *Transactions of the Korean Nuclear Society Spring Meeting*.
- Dean, M. I. 1996. Effect of Specimen Thickness on the Thermal Diffusivity of (Sr, K) Zr₄(PO₄)₆ Ceramic via a Laser-Flash Technique. *Journal of Material Science* 31: 86–89.
- Deem, H. W. and Wood, W. D. 1962. Flash Thermal-Diffusivity Measurements Using a Laser. *Review of Scientific Instruments* 33.
- Degiovanni, A. and Laurent, M. 1982. A New Technique for the Identification of the Thermal Diffusivity for the Flash Method. *Applied Physics Review (French)* 21: 229–237.
- Enguehard, E. D., D., B. A. and Balageas, D. 1990. Measurement of the Thermal Radial Diffusivity of Anisotropic Materials by the Converging Thermal Wave Technique. *Materials Science and Engineering* 127–134.
- Florescu, D. I., Mourikh, L. G., Pollak, F. H., Look, D. C., Cantwell, G. and Li, X. 2006. High spatial resolution thermal conductivity of bulk Zinc Oxide. *Journal of Applied Physics* 91 (2): 890–892.

- Gaal, P. S., Thermitus, M. A. and Stroe, D. E. 2004. Thermal Conductivity Measurements Using the Flash Method. *Journal of Thermal Analysis and Calorimetry* 78 (1): 185–189.
- Galdeano, M. C., Wilhelm, A. E., Mali, S. and Grossmann, M. V. E. 2013. Influence of Thickness on Properties of Plasticized Oat starch Films. *Brazilian Archives of Biological Technology* 56.
- Gesele, G., Linsmeier, J., Drach, V., Fricke, J. and Fischer, R. A. 1997. Temperature Dependent Thermal Conductivity of Porous Silicon. *Journal of Physics: D Applied Physics* 30.
- Groetzinger, G. 1935. Influence of an Electric Field on the Thermal Conductivity of a Solid. *Nature* 135: 1001.
- Groot, H. 1988. *Thermal Conductivity 20*. Plenum Press, New York.
- Hall, D. M. and Sayre, J. G. 1973. A Comparison of Starch Granules as Seen by Both Scanning Electron and Ordinary Light Microscopy. *Starch* 25: 119–123.
- Hartmann, J., Voigt, P., Reichling, M. and Matthias, E. 1996. Photothermal Measurement of Thermal Anisotropy in Pyrolytic Graphite. *Applied Physics B* 62 (5): 493–497.
- Hasselmann, D. P. H. and Donaldson, K. Y. 1990. Effects of Detector Nonlinearity and Specimen Size on the Apparent Thermal Diffusivity of NIST 8425 Graphite. *International Journal of Thermophysics* 3.
- Haydari, M., Moxsin, M. M., Abdelrahman, A. E., Deraman, M., Deraman, W. M. M., Yunus, W. M. M. and Grozescu, I. V. 2008. Thermal Diffusivity of Carbon Pellets (CPs) Treated with KOH. *American Journal of Applied Sciences* .
- Heckmann, R. C. 1973. Finite pulse time and Heat loss effects in pulse thermal diffusivity measurements. *Journal of Applied Physics* 44: 1455–1460.
- Holt, V. E. 1966. Thermal Resistivity at Interfaces Between Metal and Dielectric Films at 1.5 to 4.2 K. *Journal of Applied Physics* 37 (2): 798–802.
- Hui, P. and Tan, H. S. 1993. Modelling of thermal diffusivity of diamond thin films using a pulsed laser technique. *Surface and Coating Technology* 62 (361-366).
- Hui, P. and Tan, H. S. 1994. A Transition-Line Theory for Heat Conduction in Multilayer Thin Films. In *IEEE Transaction on Components, Packaging and Manufacturing Technology*.
- Huttner, B. 1998. On the temperature dependence of the electronic thermal conductivity in metals when the electron and phonon subsystems are not in local equilibrium. *Journal of Physics* 10: 6121–6126.

- Imhof, R. E., Whitters, C. J., Birch, D. J. S. and Thornley, F. R. 1998. Rapid communication: New opto-thermal radiometry technique using wavelength selective detection. *Journal of Physics. E.: Scientific Instruments* 21: 115–117.
- James, H. M. 1980. Some Extensions of the Flash Method of Measuring Thermal Diffusivity. *Journal of Applied Physics* 51: 4666–4672.
- Jasper, C., Edwin, J., Preyah, S., Natalya, G. and Wayne, E. J. J. 2013. Thermal Diffusivity and Thermal Conductivity of Epoxy-Based Nanocomposites by the Laser Flash and Differential Scanning Calorimetry Techniques. *Open Journal of Composite Materials* 3: 51–62.
- Jesus, M. E. P. and Imhof, R. E. 1995. Thermal Diffusivity Measurement of Thermally Conducting Films on Insulating Substrates. *Applied Physics A* 60 (6): 613–617.
- Joo, Y., Park, H., Chae, H. B., Lee, J. K. and Baik, Y. J. 2001. Measurement of thermal diffusivity for thin slabs by a converging thermal wave technique. *International Journal of Thermophysics* 22.
- Kading, O. W., Skurk, H. and Matthias, E. 1994. Thermal Diffusivities of Thin Films Measured by Transient Thermal Gratings. *Le Journal de Physique IV* 4 (C7): C7–619.
- Kaiser, V., Bramwell, S. T. and Holdsworth, P. C. W. and Moessner, R. 2013. Onsager's Wien Effect on a Lattice. *Nature Materials* 12: 1033–1037.
- Kakac, S. and Yener, Y. 1985. *Heat Conduction*. 2nd edn. Hemisphere.
- Kant, R. 1998. Laser-induced heating of a multilayered medium resting on a half-space: Part I-stationary source. *Journal of Applied Mechanics* 21.
- Kim, S. W., Kim, J. C. and Lee, S. H. 2006. Analysis of thermal diffusivity by parameter estimation in converging thermal-wave technique. *International Journal of Heat and Mass Transfer* 49: 611–616.
- Kurien, K. V. and Ittyachen, M. A. 1980. Effect of Electric Field on the Growth of Barium Molybdate Crystals in Silica Gel. *Journal of Materials Science* 15: 1724–1729.
- Langer, G., Hartmann, J. and Reichling, M. 1997. Thermal Conductivity of Thin Metallic Films Measured by Photothermal Profile Analysis. *Review of Scientific Instruments* 68 (3): 1510–1513.
- Larson, K. B. and Koyama, K. 1968. Measurement by the Flash Method of Thermal Diffusivity, Heat Capacity, and Thermal Conductivity in Two-Layer Composites Samples. *Journal of Applied Physics* 39.
- Lechner, T. and Hahne, E. 1993. Finite Pulse Time Effects in Flash Diffusivity Measurements. *Thermochimica Acta* 218: 341–350.

- Li, J., Berke, T. G. and Glover, D. V. 1994. Variation of Thermal Properties of Starch in Tropical Maize Germ Plasm. *Cereal Chemistry* 71.
- Lu, G. and Swann, W. T. 1991. Measurement of thermal diffusivity of polycrystalline diamond film by the converging thermal wave technique. *Applied Physics Letters* 59.
- Mandelis, A. 1991. Photothermal Applications to the Thermal Analysis of Solids. *Journal of Photothermal Analysis* 37: 1065–1101.
- Milosovic, N. D. and Raynaud, M. 2002. A parameter estimation procedure in thermal diffusivity measurements using the laser flash method. *Applied Physics Review (French)* .
- Mingwen, B., Fangwei, G. and Ping, X. 2014. Fabrication of thick YSZ thermal barrier coating using electrophoretic deposition. *Ceramics International* 40: 16611–16616.
- Moksin, M. M., Grozescu, I. V., Wahab, Z. A. and Yunus, W. M. M. 1999. Thermal Diffusivity Measurement of Black and Metallic Graphite Paints Coatings. *Measurements Science and Technology* 10: 7–10.
- Morgan, V. T. and Barton, N. G. 1986. The time-dependent temperature distribution in a cylindrical conductor with Joule heating and temperature-dependent properties. *Journal of Physics D: Applied Physics* 19 (6): 975.
- Murphy, F., Kehoe, T., Pietralla, M., Winfield, R. and Floyd, L. 2005. Development of an Algorithm to Extract Thermal Diffusivity for the Radial Converging Wave Technique. *International Journal of Heat and Mass Transfer* 48: 1395–1402.
- Olmstead, M. A., Amer, N. M., Kohn, S., Fournier, D. and Boccara, A. C. 1983. Photothermal Displacement Spectroscopy: An Optical Probe for Solids and Surfaces. *Applied Physics A* 32 (3): 141–154.
- Olorunyolemi, T., Birnboim, A., Carmael, Y., Wilson, O. and Loyd, J. 2002. Thermal conductivity of Zinc Oxide from green to sintered state. *American Ceramic Society* 85 (5): 1249–1253.
- Owen, W. L. 1970. Transient Temperature Distribution in a Flat Plate and Cylinder with Periodic Joulian Heating. In *Proceedings of the 1970 Heat Transfer and Fluids Mechanics Institute, Stanford*.
- Ozisik, M. N. 1993. *Heat Conduction*. 2nd edn. John Wiley and Sons Inc.
- Park, H. K., Grigoropoulos, I. C. P. and Tam, A. C. 1995. Optical Measurements of Thermal Diffusivity of Materials. *International Journal of Thermophysics* 16 (4).
- Parker, W. J. and Jenkins, W. J., Butler, C. P. and Abbott, G. L. 1961. A Flash Method of Determining Thermal Diffusivity, Heat Capacity and Thermal Conductivity. *Journal of Applied Physics* 32.

- Pawlowski, L. and Fauchais, P. 1986. The least square method in the determination of thermal diffusivity using a flash method. *Applied Physics Review (French)* 21: 83–86.
- Potter, W. G. 1975. *Uses of Epoxy Resins*. Newness-Butterworth.
- Preisler, E. 1976. Semiconductor properties of manganese dioxide. *Journal of Applied Electrochemistry* 6: 311–320.
- Raynaud, M., Beck, J. V., Shoemaker, R. and Taylor, R. 1989. *Sequential estimation of thermal diffusivity for flash tests, Thermal Conductivity 20*. Plenum Publishing Corporation.
- Robertson, W. C. 2005. *Electricity and Magnetism*. Virginia: National Science teachers Association Press.
- Sadik, K. 1985. *Heat Conduction*. Hemisphere Publishing Cooperation.
- Sahin, A. Z. and Yilba, B. S. and Al-Garni, A. Z. 1994. Transient Heat Conduction in a Slab During Direct Resistance and Induction Heating. *International communications in heat and mass transfer* 21 (2): 199–206.
- Sahu, N., Parija, B. and Panigrahi, S. 2009. Fundamental understanding and modeling of spin coating process : A review. *Indian Journal of Physics* 83: 493–502.
- Saka, M., Sun, Y. X. and Ahmed, S. R. 2009. Heat Conduction in a Symmetric Body Subjected to a Current Flow of Symmetric Input and Output. *International Journal of Thermal Sciences* 48 (1): 114–121.
- Sameshima, T. and Ozaki, K. 2001. Crystallization of Silicon Thin Films by Current-Induced Joule Heating. *Thin Solid Films* 383 (1): 107–109.
- Serway, A. R. and Jewwet, W. J. 2010. *Physics for Scientists and Engineers*. 20 Davis Drive, Belmont, CA94002-3098, USA: Books/Cole.
- Shibata, H., Okubo, K., Ohta, H. and Waseda, Y. 2002. A Novel Laser Flash Method for Measuring Thermal Diffusivity of Molten Metals. *Journal of non-crystalline solids* 312: 172–176.
- Shinzato, K. and Baba, T. 2001. A Laser Flash Apparatus for Thermal Diffusivity and Specific Heat Capacity Measurements. *Journal of Thermal Analysis and Calorimetry* 64: 413–422.
- Sing, V., H., O., H., T., S., I. and K., O. 2000. Thermal and physicochemical properties of rice grain, flour and starch. *Journal of Agricultural Foods and Chemicals* 7: 2639–2647.
- Singh, N. 2004. Relaxation of Femtosecond Photoexcited Electrons in a Metallic Sample. *Modern Physics Letters B* 18 (18): 979–986.

- Sopa, C., Cumnueng, W., Thavachai, T., Juntanee, U. and Jatuphong, V. 2008. Effects of temperature and concentration on thermal properties of cassava starch solutions. *Songklanakarin Journal of Science and Technology* 30 (3): 405–411.
- Sundqvist, B. and Backstrom, G. 1976. Thermal Conduction of Metals Under Pressure. *Review of Scientific Instruments* 47 (2): 177–182.
- Takahashi, Y., Yamamoto, K., Ohsato, T. and Terai, T. 1988. Usefulness of Logarithmic Method in Laser-Flash Technique for Thermal Diffusivity Measurement. In *Proceedings of the Ninth Japan Symposium on Thermophysical Properties*.
- Taylor, R. E. 1998. Thermal conductivity Determinations of Thermal Barrier Coatings. *Material Science and Engineering A245* (4): 160–167.
- Thirumaleshwar, M. 2006. *Fundamentals of Heat and Mass Transfer*. 482 FIE, Patpargani, Delhi, India: Dorling Kindersley.
- Thorn, R. J. and Simpson, O. C. 1953. Temperature Gradients in Inductively Heated Cylinders. *Journal of Applied Physics* 24 (3): 297–299.
- Ugo, F., Henk, V. Z. and Sybrand, V. D. Z. 2012. Increasing the reliability of solid state lighting systems via self-healing approaches: A review. *Microelectronics Reliability* 52 (4): 71–89.
- Uzgun, U., Gu, X., Chevtchenko, S., Spradlin, J. and Cho, S. 2006. Thermal Conductivity of Bulk ZnO After Different Thermal Treatments. *Journal of Electronic Materials* 35 (4).
- Vageswar, A., Balasubramaniam, K. and Krishnamurthy, C. V. 2010. Extending Flash Thermography Method for Thermal Diffusivity Measurements using Finite Pulse Widths. In *10th International Conference on Quantitative InfraRed Thermography*.
- Vitkin, I. A., Wilson, B. C., Anderson, R. R. and Prahl, S. A. 1994. Pulsed photothermal radiometry in optically transparent media containing discrete optical absorbers. *Physics in Medicine and Biology* 39.
- Volklein, F. 1990. Thermal Conductivity and Diffusivity of a Thin Film SiO₂/Si₃N₄ sandwich system. *Thin Solid Films* 188 (1): 27–33.
- Volklein, F. and Thomas, S. 1997. Thermal Conductivity of Thin Films - Experimental Methods and Theoretical Interpretation. In *16th International Conference on Thermoelectrics*.
- Walter, A. J., Dell, R. M. and Burgess, P. C. 1970. Measurements of Thermal Diffusivities using a Pulsed Electron Beam. *International Review of High Temperature and Refractory* 7.
- Watt, D. A. 1966. Theory of thermal diffusivity for pulse technique. *British Journal of Applied Physics* 17: 230–231.

- Weast, R. C. 1994. *Handbook of Chemistry and Physics*. CRC press.
- Wesley, M. D. and Scott, W. D. 2013. Thermal expansion of manganese dioxide using high-temperature in situ X-ray diffraction. *Journal of Applied Crystallography* 45.
- Worner, E., Wild, C., Muller-Sebert, W., Funer, M., Jehle, M. and Koidl, M. 1998. Electrically induced thermal transient experiments for thermal diffusivity measurements on chemical vapor deposited diamond films. *Review of Scientific Instruments* 69.
- Wrobel, G., Pawlak, S. and Muzia, G. 2011. Thermal diffusivity measurements of selected fiber reinforced polymer composites using heat pulse method. *Archives of Material Science and Engineering* 48 (1): 25–32.
- Xue, J., Liu, X., Lian, Y. and Taylor, R. 1993. The Effects of a Finite Pulse Time in the Flash Thermal Diffusivity Method. *International Journal of Thermophysics* 14.
- Yakaman, J. M., Munir, Z. A., Ocana, T. and Hirth, J. P. 1979. Sublimation of ionic crystals in the presence of an electrical field. *Applied Physics Letters* 32: 727–728.
- Yan, Z., Liu, G., Khan, J. M. and Balandin, A. A. 2012. Graphene quilts for thermal management of high-power GaN transistors. *Nature Communications* .
- Young, J. H. 1986. Steady state Joule heating with temperature dependent conductivities. *Applied Scientific Research* 55-65: 387–393.
- Yunus, A. C. and Afshin, J. G. 2011. *Heat and Mass Transfer: Fundamentals and Applications*. McGraw-Hill.
- Ziman, J. M. 1979. *Principles of the Theory of Solids*. Cambridge University Press, Cambridge.