



UNIVERSITI PUTRA MALAYSIA

PREPARATION AND CHARACTERIZATION OF POLY(LACTIC ACID)/POLY(BUTYLENE SUCCINATE)/GRAPHENE OXIDE COMPOSITE

NURAINI BINTI MD SUKUR

FS 2017 89



PREPARATION AND CHARACTERIZATION OF POLY(LACTIC ACID)/POLY(BUTYLENE SUCCINATE)/GRAPHENE OXIDE COMPOSITE

By

NURAINI BINTI MD SUKUR

**Thesis Submitted to the School of Graduate Studies, Universiti Putra Malaysia, in
Fulfilment of the Requirements for the Degree of Master of Science**

May 2017

COPYRIGHT

All material contained within the thesis, including without limitation text, logos, icons, photographs and all other artwork, is copyright material of Universiti Putra Malaysia unless otherwise stated. Use may be made of any material contained within the thesis for non-commercial purposes from the copyright holder. Commercial use of material may only be made with the express, prior, written permission of Universiti Putra Malaysia.

Copyright © Universiti Putra Malaysia



Abstract of thesis presented to the Senate of Universiti Putra Malaysia in fulfilment of the requirement for the degree of Master of Science

PREPARATION AND CHARACTERIZATION OF POLY(LACTIC ACID)/POLY(BUTYLENE SUCCINATE)/GRAPHENE OXIDE COMPOSITE

By

NURAINI BINTI MD SUKUR

May 2017

Chairman : Nor Azowa Binti Ibrahim, PhD
Faculty : Science

The present research study the effect of graphene oxide (GO) on the properties of poly(lactic acid)/poly(butylene succinate), (PLA/PBS). GO was synthesized from graphite through modified Hummers' method. The synthesized GO was characterized using Fourier Transform Infrared Spectroscopy (FTIR), X-ray Diffraction (XRD), Scanning Electron Microscopy (SEM), and Thermogravimetric analysis (TGA). FTIR and XRD results proved that GO was successfully synthesized. XRD showed that a new broad peak at 12.9° emerged with the occurrence of graphite layer oxidation.

PLA/PBS blends were prepared via melt blending technique. FTIR spectra revealed shifting of functional group peaks to lower wavenumber indicating chemical interaction occurred between PLA and PBS. Tensile strength and modulus decreased with increasing amount of PBS due to PBS elasticity. SEM micrographs of PLA/PBS blends showed immiscibility with more than 20 wt.% of PBS content. Thermal properties of PLA/PBS blend improved with the addition of PBS. From the mechanical and morphological studies, PLA with 20 wt.% PBS loading was chosen as optimum ratio and used for the preparation of PLA/PBS/GO composites.

The PLA/PBS/GO composites were prepared via melt blending technique. The mechanical property of the composites improved with the addition of 0.1 wt.% of GO. Thermal analysis of the composites also revealed significant improvement in thermal stability compared to PLA/PBS blend and pristine PLA. SEM micrographs results revealed rougher surfaces when more GO loaded to the PLA/PBS blend.

Furthermore, the PLA/PBS/GO composite with 0.1 wt.% GO loading was more water resistance than PLA/PBS blend because GO can act as barrier to the composite. Biodegradability test revealed that the PLA/PBS/GO has the lowest weight lost compared to PLA/PBS blend and neat PLA.

Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia sebagai memenuhi keperluan untuk Ijazah Master Sains

PENYEDIAAN DAN PENCIRIAN KOMPOSIT POLI(ASID LAKTIK)/POLI(BUTILIN SUK SINAT)/GRAFIN OKSIDA

Oleh

NURAINI BINTI MD SUKUR

Mei 2017

Pengerusi : Nor Azowa Binti Ibrahim, PhD
Fakulti : Sains

Matlamat kajian ini adalah untuk mengetahui kesan penggunaan grafin oksida (GO) ke atas sifat poli(asid laktik)/poli(butilin suksinat), (PLA/PBS). Grafin oksida telah disintesis daripada grafit melalui kaedah Hummer yang diubahsuai. GO yang disintesis telah dicirikan menggunakan spektroskopi Inframerah transformasi Fourier (FTIR), pembelauan sinar-X (XRD), mikroskopi elektron imbasan (SEM), dan analisis termogravimetri (TGA). Keputusan FTIR dan XRD menunjukkan GO telah berjaya disintesis. XRD menunjukkan puncak lebar baru telah muncul di 12.9° dengan kejadian pengoksidaan lapisan grafit.

Adunan PLA/PBS telah disediakan melalui teknik mengadun lebur. Spectrum FTIR mendedahkan pengalihan puncak kumpulan berfungsi ke nombor gelombang yang lebih rendah menunjukkan berlakunya interaksi kimia di antara PLA dan PBS. Kekuatan tegangan dan modulus menurun dengan dengan meningkatnya kandungan PBS kerana sifat elastik PBS. SEM mikrograf daripada PLA/PBS mempamerkan ketidakbolehcampuran dengan kandungan PBS lebih daripada 20 wt.%. Sifat terma adunan PLA/PBS meningkat dengan penambahan PBS. Daripada kajian mekanik dan morfologi, PLA dengan penambahan 20 wt.% PBS dipilih sebagai nisbah optima untuk penyediaan komposit PLA/PBS/GO.

Komposit PLA/PBS/GO telah disediakan melalui teknik mengadun lebur. Sifat mekanik komposit meningkat dengan penambahan 0.1 wt.% GO. Analisis terma komposit juga mendedahkan peningkatan pada kestabilan terma berbanding dengan PLA asli dan adunan PLA/PBS. Keputusan mikrogaraf SEM mendedahkan permukaan yang lebih kasar apabila lebih banyak GO ditambah kepada adunan PLA/PBS.

Tambahan pula, komposit PLA/PBS/GO dengan GO sebanyak 0.1 wt.% lebih tahan air berbanding campuran PLA/PBS oleh kerana GO bertindak sebagai penghalang kepada

komposit. Ujian biodegradasi mendedahkan PLA/PBS/GO mempunyai pengurangan berat terendah berbanding campuran PLA/PBS dan PLA.



ACKNOWLEDGEMENTS

In the name of Allah, The Most Merciful and Most Beneficent

First and foremost, I would like to express my deepest appreciation and gratitude to God and all those who provided me the possibility to complete this report. A special gratitude, heartfelt appreciation and extended thanks to my project supervisor, Prof. Madya Dr Nor Azowa Ibrahim and my co-supervisor, Dr Norizah for the supervision, useful comments, continuation support and superb tolerance throughout the course of this work.

I would like to express my biggest and deepest gratitude to my beloved family especially my parents, Mr. Md Sukur Bin Johan and Mrs. Hasni Binti Naoman who have always believe in me, support me in all possible ways and even endured with me during difficult times. Without their conditional loves and support, it would not have been possible for me to complete this Master thesis and throughout the whole years of study.

Also, special thanks to all seniors and lab mates especially Ms. Noraniza, Ms. Nur Fadhilah Aziz, Mrs. Siti Hasanah, Mrs. Nas Aulia, Ms. Nor Hayati, Mr. Abu Bakar, Mr. Saleh, and Dr Chieng Buong Woei for their invaluable assistance, unflinching helps and advices. My sincere thanks also go out to all Faculty of Science, University Putra Malaysia staffs and not to forget all the lecturers for the contribution in completing this project.

Last but not least, I would like to express my deepest gratitude to examiners for their guidance to improvise this thesis.

I certify that a Thesis Examination Committee has met on 12 May 2017 to conduct the final examination of Nuraini binti Md Sukur on her thesis entitled "Preparation and Characterization of Poly(Lactic Acid)/Poly(Butylene Succinate)/Graphene Oxide Composite" in accordance with the Universities and University Colleges Act 1971 and the Constitution of the Universiti Putra Malaysia [P.U.(A) 106] 15 March 1998. The Committee recommends that the student be awarded the Master of Science.

Members of the Thesis Examination Committee were as follows:

Mansor bin Hj. Ahmad @ Ayob, PhD

Professor
Faculty of Science
Universiti Putra Malaysia
(Chairman)

Lim Hong Ngee, Janet, PhD

Associate Professor
Faculty of Science
Universiti Putra Malaysia
(Internal Examiner)

Ishak bin Ahmad, PhD

Associate Professor
Universiti Kebangsaan Malaysia
Malaysia
(External Examiner)



NOR AINI AB. SHUKOR, PhD
Professor and Deputy Dean
School of Graduate Studies
Universiti Putra Malaysia

Date: 4 September 2017

This thesis was submitted to the Senate of Universiti Putra Malaysia and has been accepted as fulfilment of the requirement for the degree of Master of Science. The members of the Supervisory Committee were as follows:

Nor Azowa Ibrahim, PhD

Associate Professor
Faculty of Science
Universiti Putra Malaysia
(Chairman)

Norizah Abdul Rahman, PhD

Senior Lecturer
Faculty of Science
Universiti Putra Malaysia
(Member)

ROBIAH BINTI YUNUS, PhD

Professor and Dean
School of Graduate Studies
Universiti Putra Malaysia

Date:

Declaration by graduate student

I hereby confirm that:

- this thesis is my original work;
- quotations, illustrations and citations have been duly referenced;
- this thesis has not been submitted previously or concurrently for any other degree at any other institutions;
- intellectual property from the thesis and copyright of thesis are fully-owned by Universiti Putra Malaysia, as according to the Universiti Putra Malaysia (Research) Rules 2012;
- written permission must be obtained from supervisor and the office of Deputy Vice-Chancellor (Research and Innovation) before thesis is published (in the form of written, printed or in electronic form) including books, journals, modules, proceedings, popular writings, seminar papers, manuscripts, posters, reports, lecture notes, learning modules or any other materials as stated in the Universiti Putra Malaysia (Research) Rules 2012;
- there is no plagiarism or data falsification/fabrication in the thesis, and scholarly integrity is upheld as according to the Universiti Putra Malaysia (Graduate Studies) Rules 2003 (Revision 2012-2013) and the Universiti Putra Malaysia (Research) Rules 2012. The thesis has undergone plagiarism detection software.

Signature: _____

Date: _____

Name and Matric No.: Nuraini Binti Md Sukur (GS40510)

Declaration by Members of Supervisory Committee

This is to confirm that:

- The research conducted and the writing of this thesis was under our supervision;
- Supervision responsibilities as stated in the Universiti Putra Malaysia (Graduate Studies) Rules 2003 (Revision 2012-2013) are adhered to.

Signature: _____

Name of

Chairman of

Supervisory

Committee: Assoc. Prof. Dr. Nor Azowa Binti Ibrahim

Signature: _____

Name of

Member of

Supervisory

Committee: Dr. Norizah Abdul Rahman

TABLE OF CONTENTS

	Page
ABSTRACT	i
ABSTRAK	ii
ACKNOWLEDGEMENT	iv
APPROVAL	v
DECLARATION	vii
LIST OF TABLES	xi
LIST OF FIGURES	xii
LIST OF ABBREVIATIONS	xiv
CHAPTER	
1 INTRODUCTION	1
1.1 Overview of Study	1
1.2 Research Approach	3
1.3 Objectives	4
2 LITERATURE REVIEW	5
2.1 Biodegradable plastics	5
2.1.1 Poly(lactic acid)	6
2.1.2 Poly(butylene succinate)	8
2.2 Polymer Blending	9
2.3 Polymer composites	10
2.4 Effect of Adding Graphene oxide	13
3 METHODOLOGY	15
3.1 Materials	15
3.1.1 Poly(lactic acid)	15
3.1.2 Poly(butylene succinate)	16
3.1.3 Graphite	16
3.1.4 Chemicals	16
3.2 Method	16
3.2.1 Synthesis of GO	17
3.2.2 Preparation of PLA/ PBS blend	17
3.2.3 Preparation of PLA/PBS/GO composite	17
3.3 Characterization technique	18
3.3.1 Tensile Test	18
3.3.2 Flexural Tes	18
3.3.3 Impact Test	18
3.3.4 Fourier Transform Infrared Spectroscopy	18
3.3.5 X-ray Diffraction Analysis	19
3.3.6 Scanning Electron Microscopy	19
3.3.7 Thermogravimetric Analysis	19
3.3.8 Differential Scanning Calorimetry Analysis	19
3.3.9 Water Absorption Analysis	19
3.3.10 Biodegradability Test	20

4	RESULTS AND DISCUSSION	21
4.1	Synthesis of GO and Analysis	21
4.1.1	Fourier Transform Infrared Analysis	21
4.1.2	X-ray Diffraction Analysis	22
4.1.3	Scanning Electron Microscopy	23
4.1.4	Thermogravimetric Analysis	24
4.2	Characterization of PLA/PBS blend	27
4.2.1	Fourier Transform Infrared Analysis	27
4.2.2	Scanning Electron Microscopy Analysis	30
4.2.3	Thermogravimetric Analysis	33
4.2.4	Differential Scanning Calorimetry	35
4.2.5	Mechanical Properties of PLA/PBS Blends	37
4.3	PLA/PBS/GO Composite	39
4.4	Characterization of PLA/PBS/GO Composite	39
4.4.1	Fourier Transforms Infrared	39
4.4.2	Thermogravimetric Analysis	41
4.4.3	Differential Scanning Calorimetry Analysis	44
4.4.4	Scanning Electron Microscopy Analysis	47
4.5	Mechanical Testing	51
4.5.1	Tensile Properties of PLA/PBS/GO composite	51
4.5.2	Flexural Properties of PLA/PBS/GO composite	53
4.5.3	Impact Strength of PLA/PBS/GO composite	54
4.6	Physical Testing	55
4.6.1	Water absorption Analysis	55
4.6.2	Biodegradability Test	57
5	CONCLUSIONS AND RECOMMENDATIONS	59
5.1	Conclusions	59
5.2	Recommendations	60
	REFERENCES	61
	BIODATA OF STUDENT	68

LIST OF TABLES

Table		Page
2.1	Comparison of properties between different fillers	12
3.1	Properties of thermoplastic Poly(lactic acid)	15
3.2	Properties of PBS 1020MD	16
3.3	Properties of graphite	16
4.1	Analysis of TG and DTG thermograms for PLA, PBS, and PLA/PBS blends	35
4.2	Thermal properties of PLA, PBS, and PLA/PBS blends	37
4.3	Onset temperature, maximum decomposition temperature, and final degradation temperature for PLA, PLA/PBS blend and PLA/PBS/GO composite	44
4.4	Thermal transition temperatures of neat PLA, PLA/20 wt. % PBS blend, and PLA/PBS/GO composites	46

LIST OF FIGURES

Figure		Page
1.1	Types of renewable sources derived biodegradable polymer	2
2.1	Production steps of PLA	7
2.2	Production route of PBS	8
2.3	Overview of polymer composites	10
2.4	Structure of GO	13
4.1	FTIR spectrum of graphite and GO	21
4.2	XRD pattern of graphite and GO	22
4.3	SEM images of (a) graphite flakes and (b) synthesized GO	23
4.4	TG thermograms of graphite and GO	25
4.5	DTG thermogram of graphite	26
4.6	DTG thermogram of GO	26
4.7	FTIR spectra for (a) PLA, (b) PBS, and (c) PLA/ 20 wt.% PBS blend	28
4.8	Proposed chemical interaction between PLA and PBS	28
4.9	FTIR spectra of PLA, PBS, and PLA/PBS blends	29
4.10	SEM images of (a) neat PLA, (b) neat PBS, (c) PLA/10 wt.% PBS, (d) PLA/20 wt.% PBS, (e) PLA/30 wt.% PBS, and (f) PLA/50 wt.% PBS	30
4.11	TG thermograms of PLA, PBS and PLA/PBS blends	34
4.12	DTG of PLA, PBS, and PLA/PBS blends	34
4.13	DSC thermograms of PLA, PBS, and PLA/20wt.% PBS	36
4.14	DSC thermograms of PLA, PBS, and PLA/PBS blends	36
4.15	Effect of PBS loading on tensile strength and tensile modulus of PLA/PBS blend	38
4.16	Effect of PBS loading on elongation at break of PLA/PBS blend	38
4.17	FTIR spectra of a) neat PLA, b) PLA/20 wt.% PBS blend, and c) PLA/PBS/0.1 wt.% GO composite	40
4.18	FTIR spectra of PLA/20wt.% PBS and PLA/PBS/GO composites	41
4.19	TG thermograms of neat PLA, PLA/PBS, and PLA/20 wt.% PBS/ 0.1 wt.% GO composite	42

4.20	DTG thermograms of neat PLA, PLA/PBS, and PLA/20 wt% PBS/0.1 wt.% GO composite	42
4.21	TG thermograms of PLA, PLA/20wt.% PBS, and PLA/PBS/GO composites	43
4.22	DTG thermograms of PLA, PLA/20 wt.% PBS, PLA/PBS/GO composites	43
4.23	DSC thermograms of PLA/20 wt.% PBS blend, and PLA/20 wt.% PBS/0.1 wt.% GO composite	45
4.24	DSC thermograms of PLA/PBS/GO composites with different ratio of GO loading	46
4.25	SEM micrograph of (a) neat PLA, (b) PLA/20 wt.% PBS blend, (c) PLA/PBS/0.1 wt.% GO, and (d) PLA/PBS/0.3 wt.% GO, (e) PLA/PBS/0.5 wt.% GO, and (f) PLA/PBS/1.0 wt.% GO	47
4.26	Tensile strength and tensile modulus of PLA/PBS/GO composite	52
4.27	Elongation at break of PLA/PBS/GO composite	52
4.28	Flexural properties of PLA/PBS/GO composite	53
4.29	Impact strength of PLA/PBS/GO composite	54
4.30	Percentage of water uptake of PLA, PLA/PBS, and PLA/20 wt.%PBS/0.1 wt.% GO composite	55
4.31	Possible reaction sites of PLA with PBS through hydrogen bonding	56
4.32	Percentage of water uptake of PLA, PLA/20 wt.% PBS, and PLA/PBS/GO composite with different ratio of GO loading	57
4.33	Percentage of weight loss of neat PLA, PLA/20 wt.% PBS blend, and PLA/20 wt.% PBS/0.1 wt.% GO composite	58

LIST OF ABBREVIATIONS

ASTM	American Society for Testing and Materials
CAGR	Compound annual growth rate
CNT	Carbon nanotube
DCPDCE	Dicyclopentadiene bisphenol dicyanate ester
DNA	Deoxyribonucleic acid
DSC	Differential scanning calorimetry
DTG	Derivative thermogravimetric
EPO	Epoxidized palm oil
FTIR	Fourier transform infrared spectroscopy
GO	Graphene oxide
HBPGO	Hyperbranched polysiloxane functionalized-graphene
KDC	Kenaf-derived cellulose
M_w	Molecular weight
PA	Polyamide
PBAT	Polybutyrate
PBS	Poly(butylene succinate)
PEG	Poly(ethylene glycol)
PPO	Poly(phenylene oxide)
PVC	Poly(vinyl chloride)
PBAT	Polybutyrate
RNA	Ribonucleic acid
T_c	Crystallization temperature
T_{deg}	Final degradation temperature
T_g	Glass transition temperature
T_m	Melting temperature
T_{max}	Maximum degradation temperature
T_{onset}	Onset temperature
TGA	Thermogravimetric analysis
UATR	Universal attenuated total reflectance
UP	Unsaturated polyester
wt. %	Weight percentage
XRD	X-ray diffraction

CHAPTER 1

INTRODUCTION

1.1 Overview of Study

Polymer has become one of the most essential materials used in our live. In fact, most of the things around us are made up of polymer. Polymer can be defined as a large molecule which are made up of repeating structural units or monomers bonded by the same type of linkage. Different type of monomers and how they are linked together will form polymers with different properties. Polymers can exist naturally or synthetically. Examples of naturally occurring polymers include starch, silk, asbestos, as well as deoxyribonucleic acid (DNA) and ribonucleic acid (RNA). While examples of synthetic polymers are nylon, Teflon, silicon, poly(vinyl chloride) (PVC), and poly(ethylene terephthalate) (PET).

Due to the wide range of its properties, the application of polymers now extends from packaging, adhesives, automotive, textiles, electrical, agricultural, optical, to even medicine and biomedical. However, most of the materials are made from non-renewable sources such as petroleum and crude oil because of the availability at lower cost and having better properties than the polymer derived from renewable sources. The extensive use of the non-renewable sources materials now leads to environmental problems such as the decrement of petroleum stock and accumulation of domestic waste. It is not just the non-renewable sources that concern the community, the plastic waste generated is also not naturally degradable, takes years to decompose, and even gives off toxic gasses (e.g. dioxin) when incinerated.

Due to the alarming concerns, many research have been carried out to counteract the problems. One of the ways is by substituting the non-biodegradable polymers derived from non-renewable sources with biodegradable polymers derived from renewable sources. Biodegradable polymers from renewable sources play an important role in reducing the world dependency on petroleum-based materials and also help to alleviate solid waste disposal problems. Biodegradable polymers are polymers that can be broken down by the action of enzymes and/or microorganism into natural byproducts such as water, gasses (nitrogen and carbon dioxide), inorganic salts, and biomass. Biodegradable polymers from renewable sources can be categorized into three categories which are natural occurring polymers, synthetic polymers, and microbial fermentation derived polymers as depicted in **Figure 1.1** (Ramani, 2005).

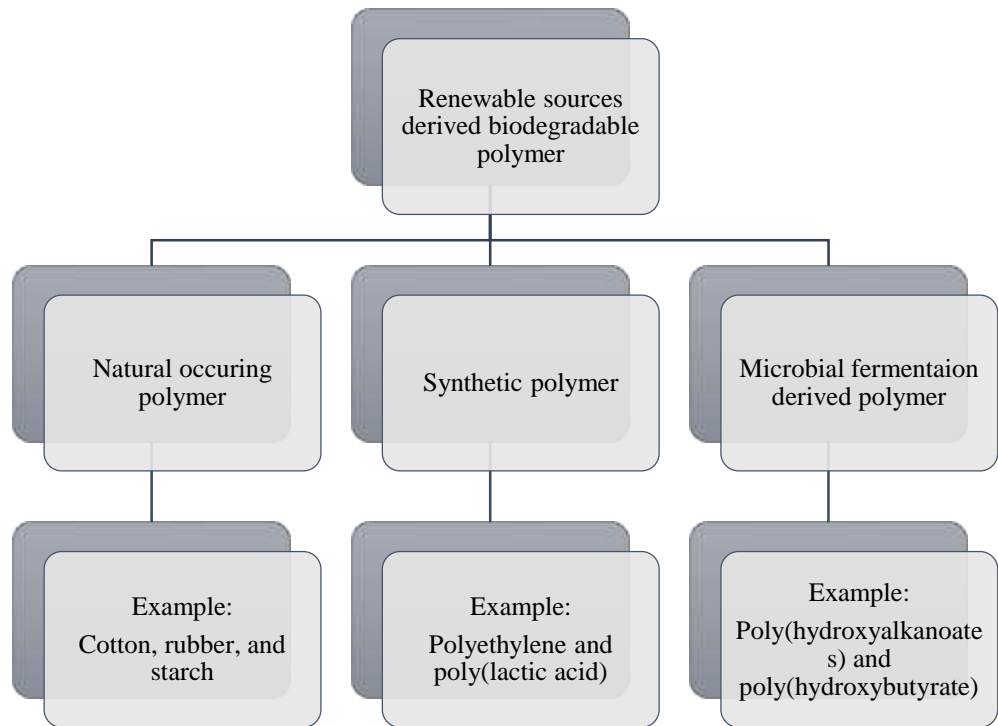


Figure 1.1: Types of renewable sources derived biodegradable polymer
(Ramani, 2005)

Poly(lactic acid) (PLA) is one of the most interesting and promising polymers used by researchers to achieve those goals as it is made from agricultural products and most importantly readily biodegradable (Gruber and Brien, 2002). PLA has very good properties such as good visual appearance, high mechanical strength and barrier properties, as well as low toxicity, which makes PLA flexible to be implied in various fields (Fang and Hanna, 1999). PLA also does not emit toxic gasses such as nitrogen oxide when burned and only one-third of the combustion heat generated by polyolefins that do not damage the incinerator and at the same time save energy.

The increasing appreciation of various intrinsic properties of PLA, coupled with knowledge of how such properties can be enhanced to achieve compatibility with manufacturing, thermoplastic processing, and end-use requirements has fuelled technological and commercial interest in PLA. Up to this day, development activities have spread throughout all countries at a compound annual growth rate (CAGR) of 19.5% from 2013 to 2020. Major applications will be packaging, building and construction products, automotive components, appliances materials and electrical/electronic parts.

Even though this type of polymer can help in the environmental problems, it is not very favourable in the industrial market because of the availability of petroleum at lower cost and better biochemical inertness of petroleum based-materials compared to the

renewable source derived-polymer. Besides that, some of the properties of the biodegradable polymer are rather too weak compared to conventional polymers. For example, PLA possess poor mechanical properties and high brittleness. Therefore, in order to compete with these conventional materials, modifications such as blending and composite formation have to be carried out to the polymers to improve the properties (Yu *et al.*, 2006).

Poly(butylene succinate) (PBS) is a potentially valuable polyester to replace the petroleum based materials because of its biodegradability, compostability, and good mechanical and thermal properties (Fujimaki, 1998). It is derived from the polycondensation reaction of succinic acid with 1,4-butanediol (Okada, 2002). PBS has been utilized in various applications such as laminates, blown bottles, foamed sheet, films, and injection-molded materials. Due to its high flexibility and crystallization rate, PBS is usually applied as modifier or plasticizer to enhance the deformation of PLA such as brittleness and low crystallization rate (Stoyanova *et al.*, 2014). Unfortunately, polymer blend tend to be immiscible due to the large mixing enthalpy which then lead to deterioration of the mechanical properties (Cao *et al.*, 2011). Furthermore, blending PLA with plasticizer such as PBS, PEG, and epoxidized palm oil would lead to decrement in tensile strength as well as tensile modulus although it does improve the elongation at break. Therefore, in order to overcome these problems, the polymer blend need to be reinforced by adding the third component such as filler. Fillers are commonly added to the polymer blend to enhance the properties of the materials (Gacitua *et al.*, 2005). Some examples of fillers are mica, graphene, kaolin, graphene oxide, feldspar, talc, ground calcium carbonate, and carbon black. Graphene oxide has drawn a great interest in research and composite productions mainly due to its unique electronic and material properties. The addition of graphene oxide as filler for composite production could offer desired properties to the polymer due to its excellent mechanical properties such as hardness, high Young's modulus, and flexibility, along with its large aspect ratio and lower cost production compared to carbon nanotube. Furthermore, presence of oxygen functionalities on graphene oxide would eventually help to interact non-covalently with other polymers (Zhao *et al.*, 2014).

1.2 Research Approach

This present work represents attempts toward introducing graphene oxide (GO) as filler to the biodegradable poly(lactic acid) (PLA)/poly(butylene succinate) (PBS) blend. The introduction of filler to the polymer as reinforcement agent is common for renewable sources based-polymers since most of them have drawbacks of low softening temperature and low modulus. Therefore, the main objective of this research is to improve the properties of PLA/PBS blend by incorporating GO as filler in the blend. GO is a monolayer of sp^2 -hybridized carbon atoms arranged in a flat honeycomb structure. It is similar to graphene but has several oxygen containing group functionalities attached to it such as hydroxyls, epoxides, and carbonyls. GO can be synthesized from natural graphite flakes which is cheap and abundant. Aside from that, GO is easier to manufacture compared to graphene. Thus, it can compete with other types of filler in the term of cost production. Due to its improvement of mechanical and thermal properties of many composites, GO has been chosen as filler to improve the properties of PLA/PBS blend.

This research is divided into three stages. Starting with the synthesis of GO from graphite flakes using modified Hummer's method and followed by preparation of PLA/PBS blend and determination of optimum ratio. PBS is added to PLA as a plasticizer in order to improve the flexibility of PLA. Finally, introduction of GO into the optimum ratio of PLA/PBS blend by melt blending technique. PLA and PBS are expected to interact with each other due to the presence of hydroxyl group for both of the polymer. Evaluation of mechanical, thermal, morphological and physical properties of the neat PLA, PLA/PBS blend, and PLA/PBS/GO composite were investigated.

1.3 Objectives

The objectives of this study are to:

1. prepare and optimize PLA blends with PBS as a plasticizer based on the mechanical properties.
2. prepare PLA/PBS/GO composites with different percentages of GO loading.
3. characterize the neat PLA, PLA/PBS blend and PLA/PBS/GO composites in terms of mechanical, thermal stability, and morphological properties.

REFERENCES

- Al-Mulla, E. A. J., Suhail, A. H., & Aowda, S. A. (2011). New biopolymer nanocomposites based on epoxidized soybean oil plasticized poly (lactic acid)/fatty nitrogen compounds modified clay: Preparation and characterization. *Industrial Crops and Products*, 33(1), 23-29.
- Al-Mulla, E. A. J., Ibrahim, N. A. B., Shameli, K., Ahmad, M. B., & Yunus, W. M. Z. W. (2014). Effect of epoxidized palm oil on the mechanical and morphological properties of a PLA–PCL blend. *Research on Chemical Intermediates*, 40(2), 689-698.
- Ammar, A., Al-Enizi, A. M., AlMaadeed, M. A., & Karim, A. (2016). Influence of graphene oxide on mechanical, morphological, barrier, and electrical properties of polymer membranes. *Arabian Journal of Chemistry*, 9(2), 274-286.
- Avérous, L. (2008). Polylactic acid: synthesis, properties and applications. *Monomers, polymers and composites from renewable resources*, 1.
- Ban, F. Y., Majid, S. R., Huang, N. M., & Lim, H. N. (2012). Graphene oxide and its electrochemical performance. *International Journal of Electrochemical Science*, 7(5), 4345-4351.
- Bhatia, A., Gupta, R., Bhattacharya, S., & Choi, H. (2007). Compatibility of biodegradable poly (lactic acid)(PLA) and poly (butylene succinate)(PBS) blends for packaging application. *Korea-Australia Rheology Journal*, 19(3), 125-131.
- Bozell, J. J., & Petersen, G. R. (2010). Technology development for the production of biobased products from biorefinery carbohydrates—the US Department of Energy’s “Top 10” revisited. *Green Chemistry*, 12(4), 539-554.
- Breuer, O., & Sundararaj, U. (2004). Big returns from small fibers: a review of polymer/carbon nanotube composites. *Polymer composites*, 25(6), 630-645.
- Cao, Y., Zhang, J., Feng, J., & Wu, P. (2011). Compatibilization of immiscible polymer blends using graphene oxide sheets. *Acs Nano*, 5(7), 5920-5927.
- Chieng, B. W., Ibrahim, N. A., Yunus, W. M. Z. W., & Hussein, M. Z. (2013). Plasticized poly (lactic acid) with low molecular weight poly (ethylene glycol): Mechanical, thermal, and morphology properties. *Journal of Applied Polymer Science*, 130(6), 4576-4580.
- Chuai, C. Z., Zhao, N., Li, S., & Sun, B. X. (2011). Study on PLA/PBS blends. In *Advanced Materials Research*, 197, 1149-1152
- Datta, R., & Henry, M. (2006). Lactic acid: recent advances in products, processes and technologies—a review. *Journal of Chemical Technology and Biotechnology*, 81(7), 1119-1129.
- Deshmukh, K., & Joshi, G. M. (2014). Thermo-mechanical properties of poly (vinyl

- chloride)/graphene oxide as high performance nanocomposites. *Polymer Testing*, 34, 211-219.
- Drumright, R. E., Gruber, P. R., & Henton, D. E. (2000). Polylactic acid technology. *Advanced materials*, 12(23), 1841-1846.
- Eigler, S., & Hirsch, A. (2014). Chemistry with graphene and graphene oxide—challenges for synthetic chemists. *Angewandte Chemie International Edition*, 53(30), 7720-7738.
- Faghihi, S., Gheysour, M., Karimi, A., & Salarian, R. (2014). Fabrication and mechanical characterization of graphene oxide-reinforced poly (acrylic acid)/gelatin composite hydrogels. *Journal of Applied Physics*, 115(8), 083513.
- Fujimaki, T. (1998). Processability and properties of aliphatic polyesters, 'BIONOLLE', synthesized by polycondensation reaction. *Polymer degradation and stability*, 59(1-3), 209-214.
- Gacitua, W., Ballerini, A., & Zhang, J. (2005). Polymer nanocomposites: synthetic and natural fillers a review. *Maderas. Ciencia y tecnología*, 7(3), 159-178.
- Gao, W. (2015). The chemistry of graphene oxide. In *Graphene Oxide* pp. 61-95.
- Ghosh, T. K., Gope, S., Mondal, D., Bhowmik, B., Mollick, M. M. R., Maity, D., & Chakraborty, M. (2014). Assessment of morphology and property of graphene oxide-hydroxypropylmethylcellulose nanocomposite films. *International journal of biological macromolecules*, 66, 338-345.
- Glenn, G. M., Orts, W., Imam, S., Chiou, B. S., & Wood, D. F. (2014). Starch plastic packaging and agriculture applications. *Starch Polymers: From Genetic Engineering to Green Applications*, 421-52.
- Gupta, A. P., & Kumar, V. (2007). New emerging trends in synthetic biodegradable polymers—Polylactide: A critique. *European polymer journal*, 43(10), 4053-4074.
- Hassan, E., Wei, Y., Jiao, H., & Muhuo, Y. (2013). Dynamic mechanical properties and thermal stability of poly (lactic acid) and poly (butylene succinate) blends composites. *Journal of Fiber Bioengineering and Informatics*, 6(1), 85-94.
- Homklin, R., & Hongsriphan, N. (2013). Mechanical and thermal properties of PLA/PBS co-continuous blends adding nucleating agent. *Energy Procedia*, 34, 871-879.
- Huang, H. D., Ren, P. G., Xu, J. Z., Xu, L., Zhong, G. J., Hsiao, B. S., & Li, Z. M. (2014). Improved barrier properties of poly (lactic acid) with randomly dispersed graphene oxide nanosheets. *Journal of Membrane Science*, 464, 110-118.
- Ibrahim, B. A., & Kadum, K. M. (2010). Influence of polymer blending on mechanical and thermal properties. *Modern Applied Science*, 4(9), 157.
- Jain, S., Reddy, M. M., Mohanty, A. K., Misra, M., & Ghosh, A. K. (2010). A new biodegradable flexible composite sheet from poly (lactic acid)/poly (ϵ -

- caprolactone) blends and Micro-Talc. *Macromolecular materials and engineering*, 295(8), 750-762.
- Jia, W., Gong, R. H., Soutis, C., & Hogg, P. J. (2014). Biodegradable fibre reinforced composites composed of polylactic acid and polybutylene succinate. *Plastics, Rubber and Composites*, 43(3), 82-88.
- Jin, T. X., Liu, C., Zhou, M., Chai, S. G., Chen, F., & Fu, Q. (2015). Crystallization, mechanical performance and hydrolytic degradation of poly (butylene succinate)/graphene oxide nanocomposites obtained via in situ polymerization. *Composites Part A: Applied Science and Manufacturing*, 68, 193-201.
- Jompang, L., Thumsorn, S., On, J. W., Surin, P., Apawet, C., Chaichalermwong, T., & Srisawat, N. (2013). Poly (lactic acid) and poly (butylene succinate) blend fibers prepared by melt spinning technique. *Energy Procedia*, 34, 493-499.
- Kuilla, T., Bhadra, S., Yao, D., Kim, N. H., Bose, S., & Lee, J. H. (2010). Recent advances in graphene based polymer composites. *Progress in polymer science*, 35(11), 1350-1375.
- Kun, H., Wei, Z., Xuan, L., & Xiubin, Y. (2012). Biocompatibility of a novel poly (butyl succinate) and polylactic acid blend. *ASAIO Journal*, 58(3), 262-267.
- Lee, S. M., Cho, D., Park, W. H., Lee, S. G., Han, S. O., & Drzal, L. T. (2005). Novel silk/poly (butylene succinate) biocomposites: the effect of short fibre content on their mechanical and thermal properties. *Composites Science and Technology*, 65(3), 647-657.
- Leja, K., & Lewandowicz, G. (2010). Polymer biodegradation and biodegradable polymers—a review. *Polish Journal of Environmental Studies*, 19(2), 255-266.
- Lerf, A., He, H., Forster, M., & Klinowski, J. (1998). Structure of graphite oxide revisited. *The Journal of Physical Chemistry B*, 102(23), 4477-4482.
- Liu, X., Wang, T., Chow, L. C., Yang, M., & Mitchell, J. W. (2014). Effects of inorganic fillers on the thermal and mechanical properties of poly (lactic acid). *International journal of polymer science*, 2014.
- Lu, D. R., Xiao, C. M., & Xu, S. J. (2009). Starch-based completely biodegradable polymer materials. *Express polymer letters*, 3(6), 366-375.
- Lunt, J., & Shafer, A. L. (2000). Polylactic acid polymers from com. Applications in the textiles industry. *Journal of Coated Fabrics*, 29(3), 191-205.
- Ma, H., Su, W., Tai, Z., Sun, D., Yan, X., Liu, B., & Xue, Q. (2012). Preparation and cytocompatibility of polylactic acid/hydroxyapatite/graphene oxide nanocomposite fibrous membrane. *Chinese Science Bulletin*, 57(23), 3051-3058.
- Meng, B., Deng, J., Liu, Q., Wu, Z., & Yang, W. (2012). Transparent and ductile poly

- (lactic acid)/poly (butyl acrylate)(PBA) blends: Structure and properties. *European Polymer Journal*, 48(1), 127-135.
- Mohanty, S., Nayak, S. K., Verma, S. K., & Tripathy, S. S. (2004). Effect of MAPP as coupling agent on the performance of sisal-PP composites. *Journal of reinforced plastics and composites*, 23(18), 2047-2063.
- Naebe, M., Wang, J., Amini, A., Khayyam, H., Hameed, N., Li, L. H., ... & Fox, B. (2014). Mechanical property and structure of covalent functionalised graphene/epoxy nanocomposites. *Scientific reports*, 4, 4375.
- Nanda, M. R., Misra, M., & Mohanty, A. K. (2011). The effects of process engineering on the performance of PLA and PHBV blends. *Macromolecular Materials and Engineering*, 296(8), 719-728.
- Narayan, R. (2006). "Biobased and Biodegradable Polymer Materials: Rationale, Drivers, and Technology Exemplars." *Degradable Polymers and Materials*: 282-306.
- Netravali, A. N., & Chabba, S. (2003). Composites get greener. *Materials today*, 6(4), 22-29.
- Nilani, P., Pranavi, A., Duraisamy, B., Damodaran, P., Subhashini, V., & Elango, K. (2010). Formulation and Evaluation of Polysaccharide Based Biopolymer- An Ecofriendly Alternative for Synthetic Polymer. *Journal of Pharmaceutical Sciences and Research* 2(3): 178-84.
- Norazlina, H., & Kamal, Y. (2015). Graphene modifications in polylactic acid nanocomposites: a review. *Polymer Bulletin*, 72(4), 931-961.
- Okada, M. (2002). Chemical syntheses of biodegradable polymers. *Progress in polymer science*, 27(1), 87-133.
- Paredes, J. I., Villar-Rodil, S., Martínez-Alonso, A., & Tascon, J. M. D. (2008). Graphene oxide dispersions in organic solvents. *Langmuir*, 24(19), 10560-10564.
- Park, J. W., & Im, S. S. (2002). Phase behavior and morphology in blends of poly (L-lactic acid) and poly (butylene succinate). *Journal of applied polymer science*, 86(3), 647-655.
- Paulchamy, B., Arthi, G., & Lignesh, B. D. (2015). A simple approach to stepwise synthesis of graphene oxide nanomaterial. *Journal of Nanomedicine & Nanotechnology*, 6(1), 1.
- Pinto, A. M., Cabral, J., Tanaka, D. A. P., Mendes, A. M., & Magalhães, F. D. (2013). Effect of incorporation of graphene oxide and graphene nanoplatelets on mechanical and gas permeability properties of poly (lactic acid) films. *Polymer International*, 62(1), 33-40.
- Rafiq, R., Cai, D., Jin, J., & Song, M. (2010). Increasing the toughness of nylon 12 by the incorporation of functionalized graphene. *Carbon*, 48(15), 4309-4314.

- Rozploch, F., Patyk, J., & Stankowski, J. (2007). Graphenes bonding forces in graphite. *Acta Physica Polonica A*, *112*, 557.
- Shahriary, L., & Athawale, A. A. (2014). Graphene oxide synthesized by using modified hummers approach. *Int. J. Renew. Energy Environ. Eng*, *2*(01), 58-63.
- Shibata, M., Inoue, Y., & Miyoshi, M. (2006). Mechanical properties, morphology, and crystallization behavior of blends of poly (L-lactide) with poly (butylene succinate-co-L-lactate) and poly (butylene succinate). *Polymer*, *47*(10), 3557-3564.
- Silva, F., Njuguna, J., Sachse, S., Pielichowski, K., Leszczynska, A., & Giacomelli, M. (2013). The influence of multiscale fillers reinforcement into impact resistance and energy absorption properties of polyamide 6 and polypropylene nanocomposite structures. *Materials & Design*, *50*, 244-252.
- Silverajah, V. S., Ibrahim, N. A., Zainuddin, N., Yunus, W. M. Z. W., & Hassan, H. A. (2012). Mechanical, thermal and morphological properties of poly (lactic acid)/epoxidized palm olein blend. *Molecules*, *17*(10), 11729-11747.
- Song, J., Wang, X., & Chang, C. T. (2014). Preparation and characterization of graphene oxide. *Journal of Nanomaterials*, *2014*.
- Stankovich, S., Dikin, D. A., Piner, R. D., Kohlhaas, K. A., Kleinhammes, A., Jia, Y., & Ruoff, R. S. (2007). Synthesis of graphene-based nanosheets via chemical reduction of exfoliated graphite oxide. *carbon*, *45*(7), 1558-1565.
- Stankovich, S., Piner, R. D., Nguyen, S. T., & Ruoff, R. S. (2006). Synthesis and exfoliation of isocyanate-treated graphene oxide nanoplatelets. *Carbon*, *44*(15), 3342-3347.
- Stoyanova, N., Paneva, D., Mincheva, R., Toncheva, A., Manolova, N., Dubois, P., & Rashkov, I. (2014). Poly (l-lactide) and poly (butylene succinate) immiscible blends: from electrospinning to biologically active materials. *Materials Science and Engineering: C*, *41*, 119-126.
- Syuhada, N. I., Rahman, S. A., GS, T., Ibrahim, N. A., & Ahmad, M. (2014). Enhanced mechanical properties of chitosan/EDTA-gO nanocomposites thin films. *Sains Malaysiana*, *43*(6), 851-859.
- Tawakkal, I. S. M., Talib, R. A., Abdan, K., & Ling, C. N. (2012). Mechanical and physical properties of kenaf-derived cellulose (KDC)-filled polylactic acid (PLA) composites. *BioResources*, *7*(2), 1643-1655.
- Teamsinsungvon, A., Ruksakulpiwat, Y., & Jarukumjorn, K. (2013). Preparation and characterization of poly (lactic acid)/poly (butylene adipate-co-terephthalate) blends and their composite. *Polymer-Plastics Technology and Engineering*, *52*(13), 1362-1367.
- Vink, E. T., Rabago, K. R., Glassner, D. A., & Gruber, P. R. (2003). Applications of life

- cycle assessment to NatureWorks™ polylactide (PLA) production. *Polymer Degradation and stability*, 80(3), 403-419.
- Wan, C., & Chen, B. (2011). Poly (ϵ -caprolactone)/graphene oxide biocomposites: mechanical properties and bioactivity. *Biomedical Materials*, 6(5), 055010.
- Wan, C., & Chen, B. (2013). Reinforcement of biodegradable poly (butylene succinate) with low loadings of graphene oxide. *Journal of Applied Polymer Science*, 127(6), 5094-5099.
- Wang, L. F., Rhim, J. W., & Hong, S. I. (2016). Preparation of poly (lactide)/poly (butylene adipate-co-terephthalate) blend films using a solvent casting method and their food packaging application. *LWT-Food Science and Technology*, 68, 454-461.
- Wang, X. W., Zhang, C. A., Wang, P. L., Zhao, J., Zhang, W., Ji, J. H., & Li, X. P. (2012). Enhanced performance of biodegradable poly (butylene succinate)/graphene oxide nanocomposites via in situ polymerization. *Langmuir*, 28(18), 7091-7095.
- Wang, Y., Chiao, S. M., Hung, T. F., & Yang, S. Y. (2012). Improvement in toughness and heat resistance of poly (lactic acid)/polycarbonate blend through twin-screw blending: Influence of compatibilizer type. *Journal of Applied Polymer Science*, 125(S2).
- Wilson, N. R., Pandey, P. A., Beanland, R., Young, R. J., Kinloch, I. A., Gong, L., & Sloan, J. (2009). Graphene oxide: structural analysis and application as a highly transparent support for electron microscopy. *ACS nano*, 3(9), 2547-2556.
- Xu, J., & Guo, B. H. (2010). Microbial succinic acid, its polymer poly (butylene succinate), and applications. *Plastics from Bacteria*, pp. 347-388
- Xu, J., & Guo, B. H. (2010). Poly (butylene succinate) and its copolymers: research, development and industrialization. *Biotechnology journal*, 5(11), 1149-1163.
- Xu, Y. X., Kim, K. M., Hanna, M. A., & Nag, D. (2005). Chitosan–starch composite film: preparation and characterization. *Industrial crops and Products*, 21(2), 185-192.
- Yew, G. H., Yusof, A. M., Ishak, Z. M., & Ishiaku, U. S. (2005). Water absorption and enzymatic degradation of poly (lactic acid)/rice starch composites. *Polymer Degradation and Stability*, 90(3), 488-500.
- Yokohara, T., & Yamaguchi, M. (2008). Structure and properties for biomass-based polyester blends of PLA and PBS. *European Polymer Journal*, 44(3), 677-685.
- Yoo, B. M., Shin, H. J., Yoon, H. W., & Park, H. B. (2014). Graphene and graphene oxide and their uses in barrier polymers. *Journal of Applied Polymer Science*, 131(1).
- Zhang, M. M., Yan, H. X., Gong, C., & Li, T. T. (2014). Hyperbranched polysiloxane

functionalized graphene oxide for dicyclopentadiene bisphenol dicyanate ester nanocomposites with high performance. *eXPRESS Polymer Letters*, 8(6).

Zhao, L., Liu, X., Zhang, R., He, H., Jin, T., & Zhang, J. (2015). Unique Morphology in Polylactide/Graphene Oxide Nanocomposites. *Journal of Macromolecular Science, Part B*, 54(1), 45-57.

Zhou, J., Yao, Z., Zhou, C., Wei, D., & Li, S. (2014). Mechanical properties of PLA/PBS foamed composites reinforced by organophilic montmorillonite. *Journal of Applied Polymer Science*, 131(18).

Zhu, Y., Murali, S., Cai, W., Li, X., Suk, J. W., Potts, J. R., & Ruoff, R. S. (2010). Graphene and graphene oxide: synthesis, properties, and applications. *Advanced materials*, 22(35), 3906-3924.