



**UNIVERSITI PUTRA MALAYSIA**

***EFFECTS OF STEAMING PRE-TREATMENT AND COMPRESSION  
LEVEL ON PROPERTIES OF OIL PALM WOOD***

**ALHASSAN YAKUBU ABARE**

**FH 2015 14**



**EFFECTS OF STEAMING PRE-TREATMENT AND COMPRESSION  
LEVEL ON PROPERTIES OF OIL PALM WOOD**

By

**ALHASSAN YAKUBU ABARE**

**Thesis submitted to the School of Graduate Studies, Universiti Putra Malaysia,  
in Fulfillment of the Requirements for the Degree of Master of Science.**

**June 2015**

## **COPYRIGHT**

All material contained within the thesis, including without limitation text, logos, icons, photographs and all other artwork, is copyright material of Universiti Putra Malaysia unless otherwise stated. Use may be made of any material contained within the thesis for non-commercial purposes from the copyright holder. Commercial use of material may only be made with the express, prior, written permission of Universiti Putra Malaysia.

Copyright © Universiti Putra Malaysia



## DEDICATIONS

I would like to dedicate this work to my parents  
**Alh. Yakubu Abare** and **Hajiya Hadiza Abare**  
Who are my inspiration and for their affection, love, continuous support and prayers  
My loving Wife **Aishatu Salihu Baba**  
And my son **Yaqub A. Abare**  
For the sacrificed they made and their continuous support and prayers



Abstract of thesis presented to the Senate Universiti Putra Malaysia in the fulfillment of the requirement for the degree of Master of Science

## **EFFECTS OF STEAMING PRE-TREATMENT AND COMPRESSION LEVEL ON PROPERTIES OF OIL PALM WOOD**

By

**ALHASSAN YAKUBU ABARE**

**June 2014**

**Chairman: Assoc. Prof. Edi Suhaimi Bakar, PhD**

**Faculty: Forestry**

There are various technical problems in the current processing technology to convert oil palm trunks to lumber and other useful products. Sawing of oil palm wood and time in drying and heating are generally considered difficult by industry. The main objective of this study was to evaluate the effect of steaming pre-treatment and compression level during hot press on the properties of oil palm wood produced using integrated processing and approach method. The research was divided into two phases viz; Comparison of sawing patterns and treatment processes of oil palm wood (OPW). In the comparison of sawing patterns, two of sawing patterns were adopted from cant sawing and named as modified cant sawing (MCS) and reverse cant sawing (RCS). The process of each sawing pattern was divided into 5 work elements: (a) sawing pattern mapping (b) transporting log from log-yard to log-deck (c) loading log to carriage (d) sawing (Head rig) and (e) re-sawing. The total sawing time for each sawing pattern was calculated. The total sawing time comprises both the effective and ineffective time. This was used in the comparison of the two sawing methods. For the treatment processes, three palm trees ( $\geq 28$ -year) were harvested and debarked using the Spindle-less peeler and thereafter sawn with a reverse cant sawing pattern (RCS) to get slabs which were edged to form samples with measurements of 30cm long, 6 cm thickness and 15cm width. The samples were then steamed and cold compressed at various compression percent (0%, 20%, 30%, and 40%), drying was carried out at a targeted moisture content of 15 percent. Then it was treated with low molecular weight phenol formaldehyde (LMW-PF) in an impregnation cylinder. Subsequently, the samples were further dried to moisture target of 70 percent in an oven, and finally hot densification to 50% of the original thickness for 45 minutes. The results obtained from comparison of the two sawing patterns were further compared with secondary data of polygon sawing (PS). The total sawing time of reverse cant sawing, modified cant sawing, and polygon sawing was 842 seconds, 919 seconds and 2760 respectively. The total sawing time of PS was more than three times (2760 second) any of these two types of sawing pattern. The result from the treated test samples showed that the physical properties showed that, steamed samples with 40% compression level has the highest density ( $1065.23 \text{ kg/m}^3$ ) while the lowest density was recorded at un-steamed samples with 0% compression level ( $766.13 \text{ kg/m}^3$ ). The density showed an increasing trend from 0%

to 40% level for both the steamed and un-steamed samples. Similarly, the density gain and weight percent gain showed almost the same trend. The analysis of variance showed that steaming was not significant on most of the physical properties while the compression level was significant in most of the physical properties. The mean values of the Modulus of Elasticity (MOE) and Modulus of rupture (MOR) ranges from 5687.34 MPa -15046.53 MPa and 42.57 MPa to 114.57MPa respectively. Steaming does not have significant effect on both MOE and MOR while compression level showed significant for both MOE and MOR. From the result, it was found that RCS is the most suitable sawing pattern to produce OPW, because it consumed the shortest total sawing time and it is easy to carry out. In the treatment processes, steaming of the wood samples for this research did not give much effect on variables measured for this study, this implies that it is not necessary for this study. The compression level (%) has great role in this research because it helps in improving the properties of the treated compreg OPW. The compression levels that can be consider most suitable is either 30% or 40%. A patent has already been applied for this research work.

Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia sebagai memenuhi keperluan untuk Ijazah Master Sains

**KESAN PRA- RAWATAN KUKUSAN DAN TINGKAT PEMAMPATAN  
BAGI SIFAT KAYU KELAPA SAWIT**

Oleh

**ALHASSAN YAKUBU ABARE**

**Jun 2015**

**Pengerusi : Prof.Madya. Edi Suhaimi Bakar, PhD**  
**Fakulti : Perhutanan**

Terdapat beberapa masalah teknikal didalam teknologi pemprosesan semasa untuk menukarkan batang kepala sawit kepada papan kayu dan produk penting lain. Menggergaji kayu kelapa sawit dan masa pengeringan dan pemanasan umumnya dianggap sukar oleh industri. Objektif utama penyelidikan ini adalah untuk mengkaji kesan pra-rawatan kukusan dan tahap mampatan semasa proses mampatan panas terhadap sifat kayu kelapa sawit yang dihasilkan melalui proses bersepadu dan pendekatan kaedah. Penyelidikan ini dibahagikan kepada dua fasa iaitu; Membandingkan corak penggergajiandan proses rawatan kayu kelapa sawit (OPW). Didalam membandingkan corak penggergajian, dua corak penggergajian telah diterima pakai daripada penggergajian cant dan dinamakan sebagai penggergajian cant yang diubahsuai (MCS) dan penggergajian cant berbalik. Proses bagi setiap corak penggergajian telah dibahagikan kepada 5 unsurkerja: (a) pemetaan corak penggergajian (b) mengangkut balak daripada kawasan pembalakan ke dek pembalakan (c) memindahkan balak kepengangkut (d) penggergaji (Kepalapelantar) dan (e) penggergajian semula. Jumlah masa penggergajian untuk setiap corak penggergajian telah dikira. Jumlah masa menggergaji terdiri daripada kedua-duamasaberkesandantidakberkesan. Initelahdigunakandalammembandingankedua-duakaedahpenggergajian. Bagi proses rawatan, tigakayukelapasawit ( $\geq 28$  tahun) telah ditebang dan dibuang kulit menggunakan alat mengupas Spindle-kurang dan selepas itu dipotong dengan corak penggergajian cant berbalik (RSC) untuk mendapatkan papan kayu yang mempunyaiukuran 30cm panjang, 6 cm tebal dan 15cm lebar. Sampel telah dikukus dan dimampat sejuk kepada pelbagai peratus mampatan (0%, 20%, 30%, and 40%),pengeringan kayu telah dilakukan bagi mencapai tahap 15% kelembapan kayu. Setelah itu, ianya telah dirawat dengan fenol formaldehid berat molekul rendah (LMW-PF) didalam silinder penghamilan. Setelah itu, sampel dikeringkan lagi sehingga mencapai 70 % tahap kelembapan didalam ketuhar, dan akhir sekali dimampat panas sehingga 50% daripada ketebalan asal untuk 45 minit. Keputusan diperolehi daripada perbandingan dua corak penggergajian telah disbanding dengan lebih lanjut dengan data sekunder oleh penggergajian polygon (PS). Jumlah masa penggergajian cant berbalik, penggergajian cant yang diubahsuai, dan penggergajian polygon ialah 842 saat, 919 saat dan 2760 saat. Jumlah masa penggergajian PS adalahtiga kali lebih (2760 saat)

diantara mana-mana dua jenis corak penggergajian. Keputusan daripada sampel yang telah dirawat menunjukkan sifat fizikal, sampel kukusan dengan 40% tahap mampatan mempunyai ketumpatan paling tinggi iaitu ( $1065.23 \text{ kg/m}^3$ ) sementara itu, ketumpatan paling rendah direkodkan adalah sampel yang tidak dikukus dengan 0% tahap mampatan ( $766.13 \text{ kg/m}^3$ ). Ketumpatan menunjukkan trend peningkatan daripada tahap 0% kepada 40% untuk kedua-dua sampel yang dikukus atau tidak dikukus. Begitu juga, ketumpatan kepadatan dan berat ketumpatan kepadatan menunjukkan trend yang sama. Analisis kepelbagaian menunjukkan tahap kemampatan yang tidak signifikan untuk hampir semua sifat fizikal manakala tahap kemampatan adalah signifikan didalam hampir semua sifat fizikal. Nilai min Modulus Keanjalan (MOE) dan Modulus Keampuhan (MOR) berjulat daripada  $5687.34 \text{ MPa}$  -  $15046.53 \text{ MPa}$  dan  $42.57 \text{ MPa}$  kepada  $114.57 \text{ MPa}$ . Kukusan tidak signifikan untuk kedua-dua MOE dan MOR. Keputusan diperolehi, menunjukkan RCS ialah merupakan corak penggergajian paling sesuai untuk menghasilkan OPW, kerana ia mengambil masa paling singkat dan ianya mudah untuk dijalankan. Didalam proses rawatan, sampel kukusan kayu bagi penyelidikan ini tidak begitu memberikan kesan terhadap pemboleh ubah yang diukur dalam kajian ini, ini menunjukkan bahawa ianya tidak perlu untuk kajian ini. Tahap kemampatan (%) mempunyai peranan yang besar didalam penyelidikan ini kerana ia membantu dalam meningkatkan sifat-sifat compreg OPW dirawat. Tahap mampatan yang paling sesuai dipertimbangkan ialah samaada 30% atau 40%. Patent telah diterima pakai didalam kajian ini.



## ACKNOWLEDGEMENTS

All praises be to Allah (SWT), the creator, nourisher, cherisher, sustainer and provider of one and all who bestowed the ability in me making my dreams a reality. I would like to express my sincere appreciation and profound gratitude to the Chairman of my supervisory committee Assoc. Prof. Dr. Edi Suhaimi Bakar for his unwavering support, scholarly criticisms throughout the research and the program as a whole. His thorough scrutiny and suggestions made this reality. I am grateful and indebted to supervisory committee members, Prof. Dr. Zaidan Ashaari for his valuable suggestions throughout this study.

Many thanks to Mr Zamani, Mr Fadruddin of composite Lab and all the staff of the Faculty of Forestry for their kind support, assistance and cooperation throughout my laboratory work. I am indeed very grateful to my lab mates Mr Rogerson Anokye, Lawrence, Aizat, Aizat, Lakarim, Nisha, Taty, and Jessy for their friendly support and cooperation which I cherish a lot.

I am very thankful to my friends and house mates Goni, Jalo, Sadeeq, Zamani, Alimo, Alibe, Ngab, Goje, Umar, Taiwo, Goronyo, Ali, Abdullahi, Mahmud, Mohammed, Hamza, Hassan, Usman, Abdulaziz, and many whom space would not permit me to mention. All have been good friends and supportive brothers.

My special gratitude and thanks go to my family, relatives and all well wishes for their prayers and support.

I certify that a Thesis Examination Committee has met on 4 June 2015 to conduct the final examination of Alhassan Yakubu Abare on his thesis entitled "Effects of Steaming Pre-Treatment and Compression Level on Properties of Oil Palm Wood" in accordance with the Universities and University Colleges Act 1971 and the Constitution of the Universiti Putra Malaysia [P.U.(A) 106] 15 March 1998. The Committee recommends that the student be awarded the Master of Science.

Members of the Thesis Examination Committee were as follows:

**Jegatheswaran a/l Ratnasingam, PhD**

Professor  
Faculty of Forestry  
Universiti Putra Malaysia  
(Chairman)

**H Ng Paik San, PhD**

Associate Professor  
Faculty of Forestry  
Universiti Putra Malaysia  
(Internal Examiner)

**Othman Sulaiman, PhD**

Professor  
Universiti Sains Malaysia  
Malaysia  
(External Examiner)



---

**ZULKARNAIN ZAINAL, PhD**  
Professor and Deputy Dean  
School of Graduate Studies  
Universiti Putra Malaysia

Date: 17 June 2015

This thesis was submitted to the Senate of Universiti Putra Malaysia and has been accepted as fulfilment of the requirement for the degree of Master of Science. The members of the Supervisory committee were as follows:

**Edi Bakar Suhaimi, PhD**

Associate Professor  
Faculty of Forestry  
Universiti Putra Malaysia  
(Chairman)

**Zaidon Ashaari, PhD**

Professor  
Faculty of Forestry  
Universiti Putra Malaysia  
(Member)



---

**BUJANG BIN KIM HUAT, PhD**

Professor and Dean  
School of graduate studies  
Universiti Putra Malaysia

Date:

## Declaration by graduate student

I hereby confirm that:

- this thesis is my original work
- quotations, illustrations and citations have been duly referenced
- the thesis has not been submitted previously or concurrently for any other degree at any institutions
- intellectual property from the thesis and copyright of thesis are fully-owned by Universiti Putra Malaysia, as according to the Universiti Putra Malaysia (Research) Rules 2012;
- written permission must be owned from supervisor and deputy vice –chancellor (Research and innovation) before thesis is published (in the form of written, printed or in electronic form) including books, journals, modules, proceedings, popular writings, seminar papers, manuscripts, posters, reports, lecture notes, learning modules or any other materials as stated in the Universiti Putra Malaysia (Research) Rules 2012;
- there is no plagiarism or data falsification/fabrication in the thesis, and scholarly integrity is upheld as according to the Universiti Putra Malaysia (Graduate Studies) Rules 2003 (Revision 2012-2013) and the Universiti Putra Malaysia (Research) Rules 2012. The thesis has undergone plagiarism detection software

Signature: \_\_\_\_\_ Date: \_\_\_\_\_

Name and Matric No.: AlhassanYakubuAbare (GS34993)

## Declaration by Members of Supervisory Committee

This is to confirm that:

- the research conducted and the writing of this thesis was under our supervision;
- supervision responsibilities as stated in the Universiti Putra Malaysia (Graduate Studies) Rules 2003 (Revision 2012-2013) were adhered to.

Signature: \_\_\_\_\_

Name of

Chairman of  
Supervisory


Committee: \_\_\_\_\_

Signature: \_\_\_\_\_

Name of

Member of  
Supervisory

Committee: \_\_\_\_\_

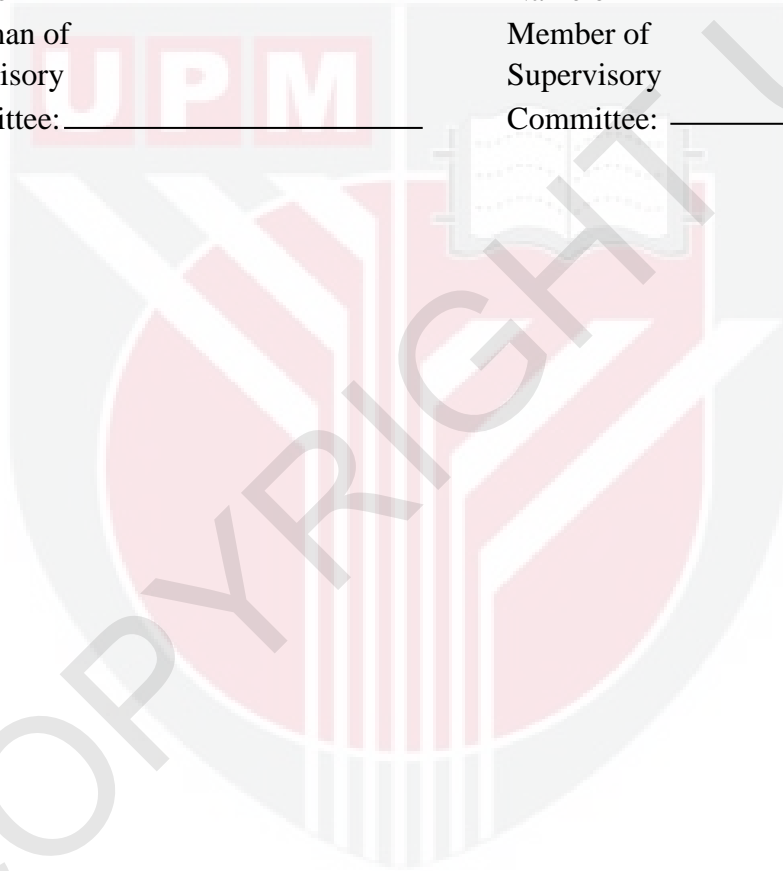

## TABLE OF CONTENTS

	<b>Page</b>
<b>ABSTRACT</b>	i
<b>ABSTRAK</b>	iii
<b>ACKNOWLEDGEMENTS</b>	v
<b>APPROVAL</b>	vi
<b>DECLARATION</b>	viii
<b>LIST OF TABLES</b>	xii
<b>LIST OF FIGURES</b>	xiii
<b>LIST OF ABBREVIATIONS</b>	xv
<b>CHAPTER</b>	
<b>1 INTRODUCTION</b>	<b>1</b>
1.1 Background of the Study	1
1.2 Problem Statement	2
1.3 Research Objectives	3
<b>2 LITERATURE REVIEW</b>	<b>4</b>
2.1 Present Forest Situation and Wood Demand	4
2.2 Development of Oil palm Plantation in Malaysia	4
2.3 Oil palm Biomass and Utilization	6
2.4 Anatomical Review of Oil palm wood	7
2.4.1 Cortex	7
2.5 Physical Properties of Oil palm wood	8
2.5.1 Moisture Content	8
2.5.2 Shrinkage	9
2.5.3 Density	9
2.5.4 Durability	10
2.6 Machining characteristic	11
2.7 Sawing of Oil palm wood: Polygon Sawing	11
2.8 Mechanical Properties of Oil palm wood	12
2.9 Wood Modification	13
2.10 Impregnation Modification	14
2.10.1 Impreg	15
2.10.2 Compreg	15
2.11 Phenol Formaldehyde	16
2.12 Sawing of Oil Palm Wood	18
2.12.1 Polygon Sawing	18
<b>3 METHODOLOGY</b>	<b>20</b>
3.1 Materials	20
3.2 Samples Preparation	20
3.3 Reverse Cant Sawing	20
3.3.1 Sawing Time	20
3.3.2 Steaming	22
3.3.3 Cold Pressing and Drying	23
3.4 Low molecular weight phenol formaldehyde (LMW-PF)	24

3.5	Impregnation Treatment	25
3.6	Evaluation of the Physical Properties	28
3.6.1	Moisture Content	28
3.6.2	Density and Density Gain	28
3.6.3	Weight Percent Gain (WPG)	29
3.6.4	Water Absorption and Thickness Swelling	29
3.7	Evaluation of Mechanical Properties	29
3.7.1	Static bending	30
3.7.2	Compression Strength Parallel to the Grain	30
3.7.3	Shear Strength Parallel to the Grain	31
3.7.4	Hardness Test	32
3.8	Statistical Analysis	33
<b>4</b>	<b>RESULTS AND DISCUSSION</b>	<b>34</b>
4.1	Reverse Cant Sawing	34
4.1.1	Total Sawing Time	34
4.1.2	Total Sawing Time	36
4.2	Physical and Mechanical properties of Compreg OPW (Steamed and Un-steamed) at Different Compression Level	37
4.3	Evaluation of Physical Properties	41
4.3.1	Density and Density Gain	41
4.3.2	Weight Percentage Gain (WPG)	43
4.3.3	Water Absorption and Thickness Swelling	44
4.4	Evaluation of Mechanical Properties	46
4.4.1	Static bending	46
4.4.2	Compression Strength Parallel to the Grain	48
4.4.3	Shear Strength Parallel to the Grain and Hardness	49
<b>5</b>	<b>CONCLUSION AND RECOMMENDATION</b>	<b>52</b>
5.1	Conclusion	52
5.2	Recommendation	53
	<b>REFERENCES</b>	<b>54</b>
	<b>APPENDICES</b>	<b>62</b>
	<b>BIODATA OF STUDENT</b>	<b>65</b>
	<b>LIST OF PUBLICATIONS</b>	<b>66</b>

## LIST OF TABLES

<b>Table</b>	<b>Page</b>
2.1 Total no planted Oil palm area in Malaysia from 1975-2011	5
2.2 The mechanical properties of the treated OPT	13
2.3 Physical and chemical properties of phenol formaldehyde	16
3.1 Experiment design	27
4.1 Average of time taken for Each Element in Reverse Cant Sawing and Modified Cant Sawing	34
4.2 Physical Properties of High grade Compreg OPW (Steamed and Un-steamed) at Different Compression Level	39
4.3 Mechanical Properties of high grade Compreg OPW (Steamed and Un-steamed) at Different Compression Level	39
4.4 ANOVA Of The Effect of Steaming And Compression Level On The Properties of High Grade Compreg Opw	40
4.5 Mean comparison of Density ( $\text{kg/m}^3$ ) using Turkey's HSD for different compression level	41
4.6 Mean comparison of Density Gain (%) using Turkey's HSD for different compression level	42
4.7 Mean comparison of <sup>1</sup> WPG (%) using Turkey's HSD for different compression level	44
4.8 Mean comparison of <sup>1</sup> WA (%) using Turkey's HSD for different variables	45
4.9 Mean comparison of <sup>1</sup> TS (%) using Turkey's HSD for different compression level	46
4.10 Mean comparison of <sup>1</sup> MOE (MPa) using Turkey's HSD for different compression level	47
4.11 Mean comparison of <sup>1</sup> MOR (kN) using Turkey's HSD for different variables	48
4.12 Mean comparison of H (kN) using Turkey's HSD for different variables	51



## LIST OF FIGURES

<b>Figure</b>		<b>Page</b>
2.1	Cross-section of a vascular bundle. V: vessel, Px: protoxylem, Pp: protophloem, F: fiber.	8
2.2	Shrinkage of OPW cut from a different zones of trunk.	9
2.3	Polygon Sawing (Bakar et al., 2006)	12
2.5	Polygon Sawing (Bakar et al., 2006)	19
3.1	Samples preparation: debarking and Sawing	21
3.2	Different Sawing methods of OPW	22
3.3	Dipping the samples into Borax Solution	22
3.4	Steaming of the Samples	23
3.5	Cold Pressing of the Slab	24
3.6	Research flow of production of high grade compreg oil palm wood.	26
3.7	Static Bending Test	30
3.8	Compression Strength parallel to the grain.	31
3.9	Shear Strength Parallel to the Grain	32
3.10	Janka Hardness Test	32
4.1	Average Effective time for Each Element (Reverse Cant Sawing)	35
4.2	Average Effective Time for each element (Modified Cant Sawing)	35
4.3	Process of cutting the Slab (Reverse cant Sawing)	36
4.4	Process of cutting the Slab (Modified Cant Sawing)	36
4.5	The total Sawing Time of 3 Different Sawing Patterns of OPW	37
4.6	Density of Compreg OPW (Steamed and Un-steamed) with different Compression Levels	41
4.7	Density Gain (%) of Compreg OPW (Steamed and Un-steamed) with different Compression Levels	42
4.8	WPG of Compreg OPW (Steamed and Un-steamed) with different Compression Levels	43

4.9	WA of Compreg OPW (Steamed and Un-steamed) with different Compression Levels	44
4.10	TS (%) of Compreg OPW (Steamed and Un-steamed) with different Compression Levels	45
4.11	The Modulus of Elasticity (MOE) of Compreg OPW (Steamed and Un-steamed) with different Compression Levels	47
4.12	The Modulus of Rupture (MOR) Density of Compreg OPW (Steamed and Un-steamed) with different Compression Levels.	48
4.13	CS (MPa) of Compreg OPW (Steamed and Un-steamed) with different Compression Levels	49
4.14	Shear Strength (MPa) of Compreg OPW (Steamed and Un-steamed) with different Compression Levels	50
4.15	Hardness (kN) Density of Compreg OPW (Steamed and Un-steamed) with different Compression Levels	51

## LIST OF ABBREVIATIONS

ANOVA	Analysis of Variance
CS	Compression Strength
DG	Density Gain
EFB	Empty Fruit Bunch
FRIM	Forest Reserve Institute of Malaysia
H	Hardness
LMW-PF	Low Molecular Weight Phenol Formaldehyde
MC	Moisture Content
MCS	Modified Cant Sawing
MMW	Medium Molecular Weight
MOE	Modulus of Elasticity
MOR	Modulus of Rapture
MW	Molecular Weight
OPF	Oil palm Frond
OPT	Oil palm Trunk
OPW	Oil palm Wood
PF	Phenol Formaldehyde
PS	Polygon Sawing
RCS	Reverse Cant Sawing
SS	Shear Strength
TS	Thickness Swelling
WA	Water Absorption
WPG	Weight Percent Gain

# CHAPTER 1

## INTRODUCTION

### 1.1 Background of the Study

Wood demand is increasing day in and day out and the supply is decreasing as a result of declining forest productivity (Giz, 2012). This happens because of over exploitation of the forest resulting from activities such as indiscriminate cutting of trees, forest fire, urban expansion, lack of tree planting campaign etc. (Hosonuma *et al.*, 2012). The production capacity of our forest cannot fulfil the high demand of wood industries. This problem necessitates providing alternative to complement the supply of wood to the wood based industries.

All over the world, researches are ongoing on non-wood resources from agricultural waste as an alternative for raw materials to wood based industries (Suhaily *et al.*, 2012). One of such alternatives is oil palm tree which can serve as a substitute for wood due to its abundance in Indonesia and Malaysia. Oil palm (*Elaeis guineensis*) is known to be originated from West Africa, which is now cultivated in larger hectares in Indonesia and Malaysia, making them the largest and the second largest producers of oil palm in the world (UNEP, 2012). It is believed that these countries obtained their palm oil from the West African countries. Indonesia is the highest oil palm producing country in the world with the total planted land mass of 10.13 million hectares (Statistics Indonesia, 2013). The second largest oil palm producing country is Malaysia, having a total planted land mass of 5.4 million hectare (MPOB, 2014). Nigeria is the fourth largest oil palm producing country, after Thailand.

Oil palm is a monocotyledonous plant with a life span of economic production between 25-30 year (Ismail and Mamat, 2001). This means that, at this age, the productivity of the oil palm has been reduced drastically and it is ready for replanting exercise. Generally, huge amount of oil palm trunk (OPT) are generated each year, and these can be used as an alternative for other woody materials especially the outer part of the trunk. The best part to be utilised is the outer part of the OPT.

Oil palm wood is gotten from oil palm trunk. It is a by-product of oil palm tree after replanting. Oil palm wood is a woody material that can serve as a substitute for other wood. The Oil palm wood from the outer part has some imperfections such as being very low in strength and dimensionally unstable - having low durability and very poor machining characteristics (Way *et al.*, 2006). Ibach and Dale (2005), suggested that, the many properties of wood such as strength, dimensional stability and durability can be improve through treatment with phenolic resin. This imperfection of oil palm wood was practically solved through the modified compreg method. The method include four step processes such as drying, resin impregnation, re-drying and hot densification (Bakar *et al.*, 2005). This method consist of drying in two cycles, which is considered to be time consuming and delicate to be practiced by practitioners. This research will try to find an alternative to address this problem by adjusting and improving upon previous studies. Therefore, there are lots unknown parameters and variables in every step in the process that need to be optimized. In compression

alone, there are various compression variables needed to be optimized, that gives maximum advantage (fast drying) but not negatively affecting or reducing the physical or mechanical properties of compreg OPW. Therefore, there are many further studies on this new method needed to be carried out. In addition, the optimum compression level to produce high performance compreg OPW has not been known yet. If the whole study on this research is concluded, it will help save time, money and energy and thereby producing high grade compreg OPW with integrated process approach. This study therefore incorporates the integrated sawing and treatment process of oil palm wood.

## 1.2 Problem Statement

Oil palm plantation in Malaysia is about 5.4 million hectares (MPOB, 2014), making it the highest palm oil producer in the world. This higher number of planted hectares calls for concern in many sectors of the country, because this will generate a lot of waste to the environment. More importantly, looking at the age of optimum productivity gives an issue to worry a lot about, i.e. the 25-30 years age limit of effective productivity.

Presently, Malaysia's total oil palm area has 65% between the ages of 9-28+ and 26% are between 20-28+ years old (USDA, 2012). This indicates that majority of the plants have reached their replanting age, and it is expected that their annual yield will drastically reduce. Malaysian government has put in place measures to replace the old plants with new ones. It was reported that 365,000 hectares, which is about 8% of the planted areas is between the ages of 27-30 years, it further forecasted that in the next ten years, each year will have an additional 126,000 hectares that will fall into this category (USDA, 2012). The government has made plans to address this problem by replacing old plants with new ones. This means that if such replanting campaign will go on as indicated by government, more waste will be generated. These wastes are in a form of oil palm trunk, empty fruit bunch (EFB) and Oil palm frond (OPF). These wastes caused a lot of problem to the environment and they need to be addressed. In line with Malaysian government's policy of turning waste into wealth, various works have been done to convert under-utilized oil palm trunk (OPT) (Anwar *et al.*, 2009; Way *et al.*, 2006). Oil palm wood (OPW) is gotten from oil palm trunk after it has been sawn using the head rig sawing machine.

Oil palm wood has high moisture content, bad dimensional stability, low in strength, poor durability and poor in machining behaviour. These imperfections were practically solved by four-step modified compreg method (Drying- resin impregnation-re-drying or heating-hot pressing densification) thereby producing high grade wood composite in which properties can be compared to that of wood (Faizatul *et al.*, 2011).

This method was also considered not suitable because of the polygon sawing which is used in converting OPT into OPW which has been considered very difficult and needs professionals to handle it, because of its advanced carriage system. Another problem that is associated with this method is the drying which takes place in two cycles which is longer and consumes time. These problems necessitate a new method that can solve these pending problems. The integrated sawing and treatment process on

improving the properties of oil palm wood is expected to practically solve these problems. It is comprehensive method that consists of 7-step processes used in producing high grade compreg OPW. The steps or processes involves sawing, steaming, cold press, drying, resin impregnation, re-drying, and hot densification. Amongst these processes, sawing and cold press are the most important variables in this study. A new modified type of sawing pattern, known as a reverse cant sawing, that can fasten the sawing process will be introduced. It is easy to carry out and saves a lot of energy. The cold press (compression level) will also be introduced to reduce the amount of moisture content in the green wood, to facilitate fast drying without having any negative effect or reducing the physical and mechanical properties. This research will produce high grade compreg OPW with a process that is easier and saves time.

### **1.3 Research Objectives**

The main objective of this study is to determine the effect of steaming, pre-treatment and compression level during cold press on the properties of oil palm wood produced using integrated processing and approach method. Other specific objectives are as follows;

1. To compare reverse cant sawing with other sawing patterns such as modified cant sawing and polygon sawing in terms of sawing time.
2. To determine the effects of steaming on the physical properties and mechanical properties of OPW composite
3. To evaluate the effects of compression on the physical and mechanical properties of OPW composite

## REFERENCES

- Ab.Wahab, N. H., Tahir, P., Hoong, Y., & Ashaari, Z. (2012). Adhesive characteristics of phenol formaldehyde pre-preg oil palm veneers, 7(4), 4545–4562.
- Abdul Khalil, H. P. S., Bhat, A. H., Jawaid, M., Amouzgar, P., Ridzuan, R., & Said, M. R. (2010). Agro-Wastes: Mechanical and physical properties of resin impregnated oil palm trunk core lumber. *Polymer Composites*, 31, 638–644.
- Amarullah, M., Bakar, E., & Zaidon, A. (2010). Reduction of formaldehyde emission from phenol formaldehyde treated oil palm wood through improvement of resin curing state. I. *Trop. Wood Sci. Tech*, 8(1), 9–14.
- Anwar, U. M. K., Hiziroglu, S., Hamdan, H., & Abd.Latif, M. (2011). Effect of outdoor exposure on some properties of resin-treated plybamboo. *Industrial Crops and Products*, 33(1), 140–145.
- Anwar, U. M. K., Paridah, M. T., Hamdan, H., Sapuan, S. M., & Bakar, E. S. (2008). Effect of curing time on physical and mechanical properties of phenolic-treated bamboo strips. *Industrial Crops and Products*.
- Ashaari, Z., E.S, B., & M.T, P. (2010). Comreg laminates from density tropical hardwoods. In *Proceeding of the International Convention of Society of Wood Science and Technology and United Nations Economic Commission for Europe-Timber Committee*. Geneva Switzerland.
- Bakar, E. . (2000). Pemanfaatan Batang Kepala Sawit (*Elaeis guineensis jacq*) Sebagai Bahan Bangunan dan Furniture.Laporan Penelitian Hibah Bersaing (VI) Perguruan Tinggi. Jurusan Teknologi Hasil Hutan,120p. Institut Pertanian Bogor. Unpublished.
- Bakar, E. S., Fauzi, F., Imam, W., & Ashari, Z. (2006). Polygon Sawing: An Optimum Sawing Pattern for Palm Stems. *Journal of Biological Sciences*, 6(4), 744–749.
- Bakar, E. S., Hao, J., & Ashaari, Z. (2010). Durability of Low-Molecular Weight Phenol Formaldehyde Treated Oil Palm Wood against Termite *Coptotermes Curvignathus* and White-Rot Fungi *Pycnoporous Sanguineus*. In *Developing Wood Science and Technology to Support the Implementation of Climate Change Program* (pp. 182–190). Indonesian Wood Research Society(2011).
- Bakar, E. S., Hao, J., Ashaari, Z., & Choo Cheng Yong, A. (2013). Durability of phenolic-resin-treated oil palm wood against subterranean termites a white-rot fungus. *International Biodeterioration and Biodegradation*, 85, 126–130.
- Bakar, E. S., Rachman, O., Hermawan, D., Sari, L. K., & Rosdiana, N. (1998). Utilization of oil palm trees as building and furniture materials (1): Physical and

chemical properties and durability of oil palm wood. *Jurnal Teknologi Hasil Hutan*, 11(1), 1–12.

Bakar, E. S., Rachman, O., Massijaya, M. ., & Bahrani. (2000). Pemanfaatan Batang Kelapa Sawit (*Elaeis guineensis* Jacq.) sebagai Bahan Bangunan dan Furniture. Menuju Kemandirian Teknologi Pertanian Unggul. *Jurusan Teknologi Hasil HutanHutan. Bogor: Institut Pertanian Bogor.*, 150–152.

Bakar, E. S., Sahr, M. H., & San, H. P. (2008). Anatomical Characteristics and Utilization of Oil Palm Wood. In . In M. H. Sahri Tadahi Nobuchi (Ed.), *the formation of trees in tropical forest trees. A* (pp. 116–180). Serdang: Penerbit Universiti Putra Malaysia, Serdang.

Bakar, E.S., O. Rachman, W. D. and I. H. (1999). Utilization of Oil Palm Trees as Building and Furniture Material (II): Mechanical Properties of Oil Palm Wood. *Journal Technology Hasil Hutan*, 12(1), 10–20.

Bakar, E.S., P. Md. Tahir, Moh. H. Sahri, and H. S. Y. (2005). Properties Enhancement of Oil Palm wood through the Compreg Method. *Journal of Wood Science and Technology*, 2, 91–92.

Bowyer, J. ., Shmulsky, R., & J.G., H. (2005). *Forest Products and Wood Science- An Introduction* (4th ed.). Iowa State Press, Iowa.

BS 373. (1957). *Method of Testing Small Clear Specimens of Timber*. British Standard Institution, London.

Carrere, R. (2006). The expansion of another Destructive Monoculture. World Rainforest Movement International Coordinator, Maldonado 1858-11200 Montevideo, Uruguay.

Chew, L. ., & Ong, C. . (1985). Particle board from the trunks of oil palm (*Elaeis* [*Elaeis*] *guineensis*). *Malaysian Forester*, 48(1-2), 130–136.

Chong, Y. W., Bakar, E. S., Ashaari, Z., & Sahri, M. H. (2010). Treatment of oil palm wood with low-molecular weight phenol formaldehyde resin and its planing performance. *Wood Research Journal*, 1, 7–12.

Choo, A. C. Y., Md. Tahir, P., Karimi, A., Bakar, E. S., Abdan, K., Ibrahim, A., & Feng, L. Y. (2010). Density and humidity gradients in veneers of oil palm stems. *European Journal of Wood and Wood Products*, 69(3), 501–503.

Choon, K. ., Killmann, W., Choon, L. S., & Mansor, H. (1991). Characteristics of the oil palm stem. In K. Shaari, K. . Khoo, & A. R. . Ali (Eds.), *Oil Palm Stem Utilization* (pp. 15–28). Forest Research Institute Malaysia, Kuala Lumpur, Malaysia.

Deka, M., Das, P., & Saikia, C. . (2000). Chemical modification of wood with thermosetting resin: effect on dimensional stability and strength property. *Bioresource Technology*, 73, 179–181.



- Desch, H. ., & Dinwoodie, J. . (1996). *Timber: Structure, Properties, Conversion and Use* (7th ed.). Macmillan Press Ltd., London.
- Dungani, R., Jawaid, M., Khalil, H. P. S. A., & Aprilia, S. (2013). A Review on Quality Enhancement of Oil Palm Trunk, *2004*(2), 3136–3156.
- E. S. Bakar, O. Rachman, D. Hermawan, L. Karlinasari, and N. R. (1998). Utilization of oil palm trees as building and furniture materials (1): Physical and chemical properties and durability of oil palm wood. *Jurnal Teknologi Hasil Hutan*, *11*(1), 1–12.
- Ernst, W. M., and Fairhurst, H. . (1999). *Oil Palm-The Great Crop of South East Asia, Potentials, Nutrition and Management*, Potash & Phosphate Institute, Canada.
- Erwinsyah. (2008). *Improvement of Oil Palm Wood Properties Using Bioresin*. Unpublished doctoral dissertation, Fakultat für Forst-, Geo- und Hydrowissenschaften der Technische Universität Dresden.
- Faizatul Farhana Zulkifli, Edi S Bakar, Zaidon Ashaari, M. H. S. (2011). Quality Improvement of Oil Palm with Modified Compreg Method: The Effect of Microwave Heating Power and Re-Drying Moisture Content on the Physical and Mechanical Properties. In *Developing Wood Science and Technology to Support the Implementation of Climate Change Program* (pp. 200–210). Indonesian Wood Research Society(IWoRS),2011.
- Furuno, T., Imamura, Y., & Kajita, H. (2004). The modification of wood by treatment with low molecular weight phenol-formaldehyde resin: a properties enhancement with neutralized phenolic-resin and resin penetration into wood cell walls. *Wood Science and Technology*, *37*(5), 349–361.
- Gabrielli, C. P., & Kamke, F. a. (2009). Phenol–formaldehyde impregnation of densified wood for improved dimensional stability. *Wood Science and Technology*, *44*(1), 95–104.
- Gan, K. ., CHOO, K. ., & Lim, S. C. (2001). Basic density and moisture content distributions in 30-year-old oil palm (*Elaeis guineensis*) stems. *Journal of Tropical Forest Products*, *7*(2), 184–191.
- Giz. (2012). *Analysis of Key Drivers of Deforestation and Forest Degradation in the Philippines*.
- Goh, T. H. (2014). *Effect of Compression Ratio and Density on Drying Period for Integrated treatments and processes of Oil Palm Wood (OPW)*. Universiti Putra Malaysia(unpublished).
- Hassan, K. B., Husin, M., Darus, A., and Jalani, B. S. (1997). An estimated availability of oil palm biomass in Malaysia. *PORIM Occasional Paper*, *37*(100).

- Hazan, R., Sreekantan, S., Khalil, A. A., Nordin, I., & Mat, I. (2009). Surface Engineering of Titania for Excellent Fibroblast 3T3 Cell-Metal Interaction. *Journal of Physical Science*, 20(1), 35–47.
- Hill, C. A. S. (2006). *Wood modifications: Chemical, Thermal, and other Processes*. John Wiley & Sons, Ltd.
- Hill Callum. (2006). *Wood Modification Chemical , Thermal and Other Processes*.
- Ho, K. ., K.T, C., & Hong, L. . (1985). Processing, Seasoning and Protection of Oil palm lumber. In *Processings of the national Symposium on Oil pam By-Products for Agro-based Industries* (pp. 43–51). Kuala Lumpur, Malaysia.
- Homan, W. J., & Jorissen, A. J. M. (2004). Wood modification developments. *Heron*, 49(4), 361–386.
- Hon, D. N. S. (2003). Analysis of adhesives. In A. Pizzi & K. L. Mittal (Eds.), *Handbook of Adhesive Technology* (pp. 293–324). Marcel Dekker, Inc.
- Hong, L. T. and W. K. (1989). Some aspects of parenchymatous tissues in palm stems. In *The 2nd Pacific Regional Wood Anatomy Conference* (pp. 449–459).
- Hortono, R. (2012). *Quality Enhancement of Oil Palm trunk of inner part by close system compression method and compronation phenol formaldehyde*. Bogor Agricultural University[Dissertation]. School of Postgraduate. Bogot Agricultural University.
- Hosonuma, N., Herold, M., De Sy, V., De Fries, R. S., Brockhaus, M., Verchot, L., ... Romijn, E. (2012). An assessment of deforestation and forest degradation drivers in developing countries. *Environmental Research Letters*.
- Hsu, W. E., Schwald, W., Schwald, M. J., & Shields, M. J. (1988). Chemical and physical changes required for producing dimensionally stable wood-based composites. *Wood Science and Technology*, 22(3), 281–289.
- Indonesia, S. (2013). Estates Area by Crops, Indonesia (000 Ha), 1995 - 2013. Retrieved March 1, 2015, from <http://www.bps.go.id/webbeta/frontend/linkTabelStatis/view/id/1665>
- Ismail, A., & Mamat, M. N. (2001). The Optimal Age of Oil Palm Replanting Azman Ismail and, vol 2(1), 11–18.
- Kajita, H., & Imamura, Y. (1991). Improvement of physical and biological properties of particleboards by impregnation with phenolic resin. *Wood Science and Technology*, 70, 63–70.
- Laborie, M.-P. . (2002). investigation of the wood / phenol-formaldehyde adhesive interphase morphology.

- Lim, S. C. and T. F. (1997). A note on the structure of oil palm trunk by scanning electron microscopy. *Journal of Tropical Forest Products*, 3(1), 105–109.
- Lim, S. C., & Gan, K. S. (2009). Identification and utilization of lesser-known commercial timbers in peninsular malaysia 11 : ngilas , nipis kulit , nyireh and otak udang, 3(47), 1–8.
- Loh, Y. F., Paridah, M. T., Hoong, Y. B., Bakar, E. S., Hamdan, H., & Anis, M. (2010). Properties Enhancement of Oil Palm Plywood through Veneer Pretreatment with Low Molecular Weight Phenol-Formaldehyde Resin. *Journal of Adhesion Science and Technology*, 24(8-10), 1729–1738.
- Loh, Y. F., Paridah, T. M., Hoong, Y. B., Bakar, E. S., Anis, M., & Hamdan, H. (2011). Resistance of phenolic-treated oil palm stem plywood against subterranean termites and white rot decay. *International Biodeterioration & Biodegradation*, 65(1), 14–17.
- Marutzky, R. (1989). Release formaldehyde by wood products. *Wood Adhesives, Chemistry and Technology*, 2, 307–315.
- Marutzky, R. (1989). Release of formaldehyde by wood products. *Wood Adhesives—Chemistry and Technology*, 2, 307–387.
- Mitchell, P. . (1998). Irreversible property changes of small loblolly pine specimens heated in the air, nitrogen, or oxygen, 20(3), 320–335.
- Moubarik, A., Pizzi, A., Allal, A., Charrier, F., & Charrier, B. (2009). Cornstarch and tannin in phenol-formaldehyde resins for plywood production. *Industrial Crops and Products*, 30, 188–193.
- MPOB. (2014). Oil Palm Planted Area As At Dec 2014. Retrieved March 1, 2015, from <http://bepi.mpob.gov.my/index.php/statistics/area/132-area-2014/713-oil-palm-planted-area-dec-2014.html>
- Omar, N. S., Bakar, E. S., Jalil, N., Tahir, P., Zin, W., & Yunus, W. (2011). Distribution of Oil Palm Starch for Different Levels and Portions of Oil Palm Trunk, 2(2), 73–77.
- Pizzi, A. (1994). *Phenolic Resin Adhesives*, In *Handbook of Adhesive Technology*(Eds. Pizzi, A., and Mittal, K.L). *handbook of Adhesive Technology*. Marcel Dekker Inc. Newyork.
- Prayitno T.A. (1995). Trunk shape and physical properties of oil palm trunk. *Buletin Fak. Kehutanan UGM, Yogyakarta, Indonesia.*, 29, 43–59.
- R.E. Ibach and W. Dale Ellis. (2005). Lumen Modifications. In Roger M. Rowell (Ed.), *Handbook of Wood Chemistry and Wood Composites* (pp. 421–441). CRC Press.

- Rahayu, I. S. (2001). *Basic Properties of Vascular Bundles and Parenchyma Tissues of Oil Palm Trunk*. M.Sc. Thesis. Bogor Agricultural University (IPB), Bogor, Indonesia.
- Rowell, R. M., & Konkol, P. (1987). Treatments that enhance physical properties of wood. *USDA Forest Service, Forest Products Laboratory, Madison, WI*.
- Rowell, R. M., & Youngs, R. L. (1981). Dimensional Stabilization of Wood in Use (No. FSRN-FPL-0243).. *FOREST PRODUCTS LAB MADISON WI*.
- Ryu, J. ., Takahashi, M., Imamura, Y., & Sato, T. (1991). Biological resistance of phenol-resin treated wood. *Mokuzai Gakkaishi*, 37(9), 852–858.
- S. C. Lim and K. Khoo. (1986). Characteristics of oil palm trunk and its potential utilization. *The Malaysian Forester*, 49(1), 3–22.
- Salim, N., Hashim, R., Sulaiman, O., Nordin, N. A., Ibrahim, M., Akil, H. M., ... Hiziroglu, S. (2013). Effect of Steaming on Some Properties of Compressed Oil Palm Trunk Lumber, 8, 2310–2324.
- Schwarz, H. . (1985). Cement-bonded boards in Malaysia. *Fibre and Particleboards Bonded with Inorganic Binders*. Forest Products Research Soc., Madison, WI, USA.
- Sellers, T. (1985). *Plywood and adhesive technology*. CRC Press.
- Shams, M. I., & Yano, H. (2009). Development of selectively densified surface laminated wood based composites. *European Journal of Wood and Wood Products*, 67(2), 169–172.
- Shams, M. I., Yano, H., & Endou, K. (2004). Compressive deformation of wood impregnated with low molecular weight phenol formaldehyde (PF) resin I: effects of pressing pressure and pressure holding. *Journal of Wood Science*, 50(4), 337–342.
- Shirley, M. B. (2002). *Cellular Structure of Stems and Fronds of 14 and 25 Year-Old Elaeis guineensis Jacq.* School of Graduate Study UPM. Serdang. Unpublished.
- Stamm, A. J. ., & Seborg, R. M. (1962). Resin treated wood - Impreg. *USDA Forest Service, Forest Products Laboratory, Report No. 1380*.
- Stamm, A. J., & Seborg, R. M. (1939). Resin-treated plywood. *Industrial and Engineering Chemistry*, 31(7), 897–902.
- Stamm, A. J., & Seborg, R. M. (1951). Resin-treated laminated, compressed wood—Compreg. *USDA Forest Service, Forest Products Laboratory, Report No. 1381*.
- stephen, R. S., Kutscha, N. P. (1987). Effect of resin molecular weight on bonding flakeboard. *Wood and Fibre Science*, 9(4), 353–361.

- Suhaily, S. S., Jawaid, M., Abdul Khalil, H. P. S., & Ibrahim, F. (2012). A review of oil palm biocomposites for furniture design and applications: Potential and challenges. *BioResources*, 7(3), 4400–4423.
- Sulaiman, O., Salim, N., Nordin, N. A., Hashim, R., Ibrahim, M., & Sato, M. (2012). THE POTENTIAL OF OIL PALM TRUNK BIOMASS AS AN ALTERNATIVE SOURCE FOR COMPRESSED WOOD. *Bioresources*, 7(2), 2688–2706.
- Sumathi, S., Chai, S. P., & Mohamed, A. R. (2008). Utilization of oil palm as a source of renewable energy in Malaysia. *Renewable and Sustainable Energy Reviews*.
- Teck, C. ., & Ong, C. . (1985). Particleboard from oil palm trunk. *PoRIM Bulletin*, pp. 99–108.
- Tomlinson, P. B. (1961). *Anatomy of the Monocotyledons, II Palmae*. Clarendon Press. Oxford.
- U.M.K Anwar, M.T Paridah, H. Hamdan, S.M. Sapuan, E. S. B. (2009). Effect of Curing time on physical and mechanical properties of phenolic-treated bamboo strips. *Industrial Crops and Products*, 29(1), 214–219.
- UNEP. (2012). *Converting Waste Oil Palm Trees into a resource*.
- USDA(Foreign Agricultural Service). (2012). [www.pecad.fas.usda.gov/highlights/2012/12/Malaysia/Share](http://www.pecad.fas.usda.gov/highlights/2012/12/Malaysia/Share).
- W. Killmann and L. S. Choon. (1985). Anatomy and properties of oil palm stem. *Bulletin PORIM*, 11, 18–42.
- Wallstrom, L., & Lindberg, K. A. H. (1999). Measuring of cell wall penetration in wood of water-base chemicals using SEM/EDS technique. *Wood Sci Technol*, 33, 111–122.
- Way, C. Y., Bakar, E. S., & Ashaari, Z. (2010). Assessment on the Effects of Different Diameter and Rake Angle of Forstner Bit towards the Quality of Cut on Oil Palm Wood. In *Developing Wood Science and Technology to Support the Implementation of Climate Change Program* (pp. 191–199).
- Way, C. Y., Bakar, E. S., Ashaari, Z., & Sahri, M. H. (2006a). Treatment of Oil Palm Wood with Low-Molecular Weight Phenol Formaldehyde Resin and Its Planing Characteristics. *Wood Research Journal*, 1(1), 7–12.
- Way, C. Y., Bakar, E. S., Ashaari, Z., & Sahri, M. H. (2006b). Treatment of Oil Palm Wood with Low-Molecular Weight Phenol Formaldehyde Resin and Its Planing Characteristics, (Figure 1), 7–12.
- Winandy, E. ., & Rowell, R. . (2005). *Chemistry of Wood Strength. Handbook of Wood Chemistry and Wood Composites*. Taylor and Francis.

Yuliansyah, A. ., Hirajima, T., & Rochmadi. (2009). Development of Indonesian palm oil industry and Utilization of solid Waste. *Journal of MMIJ*, 125(12), 583–589.



© COPYRIGHT UPM