



UNIVERSITI PUTRA MALAYSIA

***EPOXIDATION OF JATROPHA METHYL ESTERS AND EVALUATION OF
ITS PROPERTIES***

AISHAH DERAHMAN

FK 2017 26



**EPOXIDATION OF JATROPHA METHYL ESTERS AND EVALUATION OF
ITS PROPERTIES**

By

AISHAH DERAHMAN

**This thesis submitted to the School of Graduate Studies, Universiti Putra Malaysia in
Fulfilment of the Requirements for the Degree of Master of Science**

February 2017

All material contained within the thesis, including without limitation text, logos, icons, photographs and all other artwork, is copyright material of Universiti Putra Malaysia unless otherwise stated. Use may be made of any material contained within the thesis for non-commercial purposes from the copyright holder. Commercial use of material may only be made with the express, prior, written permission of Universiti Putra Malaysia.

Copyright © Universiti Putra Malaysia



*To abah and ma
for their endless support of my success;
dunyā and 'akhirat*



Abstract of thesis presented to the Senate of Universiti Putra Malaysia in fulfillment of the requirement for the degree of Master of Science

EPOXIDATION OF JATROPHA METHYL ESTERS AND EVALUATION OF ITS PROPERTIES

By

AISHAH DERAHMAN

February 2017

Chair: Zurina Zainal Abidin, PhD
Faculty: Engineering

Epoxides are known to have many applications in various industries because it contains highly reactive materials. Depletion of current resources is prompting researchers to find a replacement that is highly available. Jatropha seed oil is currently gaining attention because of its availability and versatility. The objectives of this study are to investigate various factors affecting production of bio-epoxides from Jatropha methyl esters (JME) through epoxidation method, to optimize production of bio-epoxides using RSM and to characterize bio-epoxides in term of physicochemical and spectroscopic characterization. JME was first synthesized using two-step transesterification method from crude Jatropha oil (CJO). Factors affecting epoxidation methods; temperature and time, molar ratio of hydrogen peroxide and acetic acid to unsaturation and catalyst loading were investigated. Physicochemical properties of JME were identified; iodine value was found out to be 107.7. Highest percentage yield of JME obtained is 90.6 with total reaction time of 4 hours. Obtained JME further used in epoxidation process. Based on RSM results, optimum temperature 70 °C, molar ratio of hydrogen peroxide 1.9 mol, molar ratio of acetic acid 0.75mol and reaction time of 3.2 hours. Maximum relative conversion to oxirane was 92.8. Spectroscopic characterization of epoxy resin was conducted using FTIR and NMR. In FTIR, unsaturation peaks were present at 3008.67 cm^{-1} in CJO and JME and this peak diminished in epoxidized JME and oxirane rings surface at 825 and 843 cm^{-1} . ^1H NMR analysis showed unsaturation peaks in between 5.27-5.32 and oxirane at 2.85 and 2.97. ^{13}C NMR analysis presents unsaturation peaks in between 127.94-130.13 and oxirane at 56.88 ppm. In addition, blends of bio-epoxides with synthetic epoxy resin were prepared and subjected to flexural and tensile strength test. Bio-epoxides and synthetic epoxy resins blends had low tensile and flexural strength and were not suitable for applications as alternative to synthetic epoxy resin. However, it may find other application as biolubricants or polymeric coatings.

Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia
sebagai memenuhi keperluan untuk ijazah Master Sains

**PENGOKSIDAHAN JATROPHA METIL ESTER DAN PENILAIAN
TERHADAP SIFAT-SIFATNYA**

Oleh

AISHAH DERAHMAN

Februari 2017

Pengerusi: Zurina Zainal Abidin, PhD
Fakulti: Kejuruteraan

Resin epoksi mempunyai banyak aplikasi dalam pelbagai industri kerana ia mengandungi bahan-bahan yang sangat reaktif. Pengurangan sumber semasa mendorong penyelidik untuk mencari alternatif yang terdapat secara meluas. Minyak biji daripada pokok Jarak Pagar (CJO) kini semakin mendapat perhatian kerana ketersediaan dan serba boleh. Objektif kajian ini adalah untuk menyiasat pelbagai faktor yang mempengaruhi pengeluaran bio-epoksi daripada metil ester (JME), mengoptimumkan penghasilan bio-epoksi menggunakan RSM dan mencirikan bio-epoksi dari segi fizikokimia dan spektroskopi dan untuk menyediakan dan menilai sifat mekanikal sintetik epoxy resin campuran resin bio-epoksi dan resin sintetik epoksi. JME terlebih dahulu disintesis menggunakan kaedah transesterifikasi daripada CJO. Faktor yang mempengaruhi kaedah pengoksidaan; suhu dan masa, nisbah molar hidrogen peroksida dan asid asetik kepada ketaktepuan, dan pemangkin telah disiasat. Sifat fizikokimia JME telah dikenal pasti; nilai iodin didapati menjadi 107.7. Hasil peratusan tertinggi JME diperolehi adalah 90.6 dengan masa tindak balas 4 jam. JME kemudiannya digunakan dalam proses pengoksidaan. Berdasarkan keputusan RSM, suhu optimum 70 °C, nisbah molar hidrogen peroksida 1.9 mol, nisbah molar asid asetik 0.75 dan tindak balas masa 3.2 jam. Penukaran relatif maksimum kepada oxirane adalah 92.8. Spektroskopi pencirian resin epoksi dijalankan menggunakan FTIR dan NMR. Dalam FTIR, puncak ketaktepuan hadir pada 3008.67 cm⁻¹ dalam CJO dan JME dan puncak ini tidak hadir dalam ester metil Jatropha yang dioksidakan (EJME) dan cincin oxirane wujud pada 825 dan 843 cm⁻¹. ¹H NMR menunjukkan puncak ketaktepuan di antara 5.27-5.32 dan oxirane pada 2.85 dan 2.97. ¹³C NMR menunjukkan puncak ketaktepuan di antara 127.94-130.13 dan ikatan oxirane di 56.88 ppm. Di samping itu, bio-epoksi telah dicampurkan dengan resin epoksi sintetik, kemudian dikenakan ujian kekuatan lenturan dan tegangan. Campuran ini mempunyai kekuatan tegangan dan lenturan yang rendah dan tidak sesuai digunakan sebagai alternatif kepada sintetik epoksi resin. Walaubagaimanapun, ia boleh digunakan sebagai minyak pelincir dan salutan polimer.

ACKNOWLEDGEMENTS

In the name of Allah, The most Gracious, The most Compassionate. Thanks to Allah for giving me the courage, patience, and confidence in completing this project.

First and foremost, I would like to thank my thesis supervisors Assoc. Prof Dr. zurina Zainal Abidin, Dr. Francisco Cardona, Dr Dayang Radiah Awang Biak and Dr Fazlena Hamzah for their guidance, encouragement and support throughout the entire process as well as valuable comments and suggestion towards completion of the manuscript. I would also like to thank Dr. Umer Rashid for his assistance during the early stage of this project.

Next, I would like to acknowledge the financial support provided by Ministry of Higher Education of Malaysia and University Teknologi MARA (UiTM). In addition, I would like to thank the UPM Grant for Bioresins Project (CC No. 27799) and also acknowledge the financial contribution provided by the Aerospace Malaysian Innovation Centre (AMIC) that have made it possible to carry out this Master research project.

I would also like to express my gratitude to Mr. Adli Nazri for his help and assistance inside and outside of the lab. Special thanks to my lovely friend, Mdm. Farah Ezzah for her endless support from the beginning till the end.

Last but not least, I would like to thanks my family for their understanding and encouragement. Thanks you for always being there for me!

I certify that a Thesis Examination Committee has met on 27 February 2017 to conduct the final examination of Aishah binti Derahman on her thesis entitled "Epoxidation of Jatropha Methyl Esters and Evaluation of its Properties" in accordance with the Universities and University Colleges Act 1971 and the Constitution of the Universiti Putra Malaysia [P.U.(A) 106] 15 March 1998. The Committee recommends that the student be awarded the Master of Science.

Members of the Thesis Examination Committee were as follows:

Shafreeza binti Sobri, PhD
Senior Lecturer
Faculty of Engineering
Universiti Putra Malaysia
(Chairman)

Robiah binti Yunus, PhD
Professor
Faculty of Engineering
Universiti Putra Malaysia
(Internal Examiner)

Abdul Rahman Mohamed, PhD
Professor
Universiti Sains Malaysia
Malaysia
(External Examiner)



NOR AINI AB. SHUKOR, PhD
Professor and Deputy Dean
School of Graduate Studies
Universiti Putra Malaysia

Date: 2 June 2017

This thesis was submitted to the Senate of Universiti Putra Malaysia and has been accepted as fulfilment of the requirement for the degree of Master of Science. The members of the Supervisory Committee were as follows:

Zurina Zainal Abidin, PhD

Associate Professor
Faculty of Engineering
Universiti Putra Malaysia
(Chairman)

Francisco Cardona, PhD

Research Fellow- Lecturer
Faculty of Engineering
Universiti Putra Malaysia
(Member)

Dayang Radiah Awang Biak, PhD

Senior Lecturer
Faculty of Engineering
Universiti Putra Malaysia
(Member)

Fazlena Hamzah, PhD

Faculty of Chemical Engineering
University Teknologi MARA
Shah Alam
(Member)

ROBIAH BINTI YUNUS, PhD

Professor and Dean
School of Graduate Studies
Universiti Putra Malaysia

Date:

Declaration by graduate student

I hereby confirm that:

- this thesis is my original work;
- quotations, illustrations and citations have been duly referenced;
- this thesis has not been submitted previously or concurrently for any other degree at any other institutions;
- intellectual property from the thesis and copyright of thesis are fully-owned by Universiti Putra Malaysia, as according to the Universiti Putra Malaysia (Research) Rules 2012;
- written permission must be obtained from supervisor and the office of Deputy Vice-Chancellor (Research and Innovation) before thesis is published (in the form of written, printed or in electronic form) including books, journals, modules, proceedings, popular writings, seminar papers, manuscripts, posters, reports, lecture notes, learning modules or any other materials as stated in the Universiti Putra Malaysia (Research) Rules 2012;
- there is no plagiarism or data falsification/fabrication in the thesis, and scholarly integrity is upheld as according to the Universiti Putra Malaysia (Graduate Studies) Rules 2003 (Revision 2012-2013) and the Universiti Putra Malaysia (Research) Rules 2012. The thesis has undergone plagiarism detection software.

Signature: _____ Date: _____

Name and Matric No: Aishah Binti Derahman (GS 40888)

Declaration by Members of Supervisory Committee

This is to confirm that:

- the research conducted and the writing of this thesis was under our supervision;
- Supervision responsibilities as stated in the Universiti Putra Malaysia (Graduate Studies) Rules 2003 (Revision 2012-2013) are adhered to.

Signature : _____

Name of
Chairman of
Supervisory
Committee :

Assoc. Prof. Dr. Zurina Zainal Abidin

Signature: _____

Name of
Member of
Supervisory
Committee:

Dr. Francisco Cardona

Signature: _____

Name of
Member of
Supervisory
Committee:

Dr. Dayang Radiah Awang Biak

Signature: _____

Name of
Member of
Supervisory
Committee:

Dr Fazlena Hamzah

TABLE OF CONTENTS

	Page
ABSTRACT	i
ABSTRAK	ii
ACKNOWLEDGEMENTS	iii
APPROVAL	iv
DECLARATION	vi
LIST OF TABLES	xi
LIST OF FIGURES	xii
LIST OF ABBREVIATIONS	xiv
CHAPTER	
1 INTRODUCTION	1
1.1 Background	1
1.2 Problem Statements	3
1.3 Research Objectives	4
1.4 Scope of works	4
2 LITERATURE REVIEW	7
2.1 Plant oils and its derivatives	7
2.2 <i>Jatropha curcas</i> in Malaysia	11
2.3 Types of resins	13
2.3.1 Alkyd resin	13
2.3.2 Epoxy resins	14
2.3.3 Polyurethane (PU) resin	14
2.4 Transesterification process	15
2.5 Methods of epoxidation	16
2.5.1 Conventional epoxidation process	16
2.5.2 Epoxidation in the presence of acidic-ion exchange catalyst	17
2.5.3 Chemoenzymatic epoxidation	18
2.5.4 Epoxidation in the presence of metal catalyst	19
2.5.5 Advantages and disadvantages of various epoxidation method	20
2.6 Factors affecting epoxidation process	21
2.6.1 Reaction temperature	21
2.6.2 Molar ratio of hydrogen peroxide to unsaturation	21
2.6.3 Molar ratio of organic acid to unsaturation	22
2.6.4 Concentration of catalyst	23
2.6.5 Stirring speed	23
2.7 Applications of bio-epoxides	25
2.7.1 Plasticizer and stabilizer in PVC	25
2.7.2 Additives in polymers, detergents and lubricants	25
2.7.3 Reactive diluents in paints	26
2.7.4 Polymeric coatings	27
2.8 Bio-epoxides polymers	27
2.9 Conclusion	29

3	MATERIALS AND METHODOLOGY	31
3.1	Introduction	31
3.2	Materials	32
3.2.1	Raw materials	32
3.2.2	Chemicals	33
3.3	Experimental Procedures	33
3.3.1	Analysis by Gas Chromatography–Mass Spectrometry	33
3.3.2	Determination of physicochemical properties	33
3.3.3	Production of Jatropha methyl esters	33
3.3.4	Epoxidation of Jatropha methyl ester	36
3.4	Optimization using response surface methodology (RSM)	40
3.5	Analytical methods	42
3.5.1	Viscosity	42
3.5.2	Oxirane Oxygen Content	42
3.5.3	FTIR Spectroscopy Analysis	43
3.5.4	NMR Spectral analysis	43
3.6	Preparations of EJME/synthetic epoxamide blends	43
3.7	Mechanical Test	44
3.7.1	Tensile test	44
3.7.2	Flexural test	45
3.8	Summary	46
4	RESULTS AND DISCUSSIONS	47
4.1	Analysis of fatty acid composition using gas chromatography-mass spectrometry	47
4.2	Physicochemical characterization of crude Jatropha oil, Jatropha methyl esters and epoxidized Jatropha methyl esters	48
4.3	Preliminary studies of epoxidation of JME	50
4.3.1	Effect of reaction temperature	50
4.3.2	Effect of molar ratio of hydrogen peroxide to unsaturation	51
4.3.3	Effect of molar ratio of acetic acid to unsaturation	53
4.3.4	Effect of catalyst loading	54
4.4	Optimization studies	55
4.4.1	ANOVA analysis	55
4.4.2	Influence of process variables on maximum epoxidation yield	59
4.5	Spectroscopic characterizations	68
4.5.1	FTIR	68
4.5.2	NMR	72
4.6	Mechanical characterizations of EJME/synthetic epoxy resins blends	80
4.6.1	Tensile strength	81
4.6.2	Flexural strength	84
4.7	Summary	86
5	CONCLUSIONS AND RECOMMENDATIONS FOR FUTURE WORKS	89
5.1	Conclusions	89
5.2	Recommendations	90

REFERENCES	91
APPENDICES	105
BIODATA OF STUDENT	113



LIST OF TABLES

Table		Page
2.1	Summary of the characteristics, applications, availability, advantages and disadvantages of plant oils	7
2.2	Chemical composition of fatty acid profile	9
2.3	Comparison properties of CJO and JME	11
2.4	Advantages and disadvantages of epoxidation method	20
2.5	Optimum condition for reaction parameters	24
3.1	Compositions of Jatropha methyl esters and properties of its fatty acids	36
3.2	Values of studied parameters	40
3.3	Reaction variables levels	40
3.4	Central composite design (CCD) matrix of four variables	41
4.1	Fatty acid compositions of JME	47
4.2	Comparison of fatty acid compositions of CJO and JME	48
4.3	Physicochemical characteristics of CJO, JME and EJME	49
4.4	Experimental design matrix and results of epoxidation yield of JME as affected by temperature, molar ratio of hydrogen peroxide, acetic acid and time	55
4.5	Analysis of variance (ANOVA) for the fitted quadratic polynomial model	57
4.6	Numerical optimization solutions	59
4.7	Comparisons between previous researches and this study	68
4.8	The main wavelengths in the FTIR functional groups of CJO, JME and EJME	71
4.9	The main spectrums in CJO, JME and EJME	76
4.10	The main spectrums in CJO, JME and EJME	80
4.11	Curing temperature and time of bio-epoxides and synthetic resins blends	81
4.12	Tensile strength and tensi modulus	81
4.13	Flexural strength and flex modulus	84

LIST OF FIGURES

Figure		Page
1.1	Different parts of <i>Jatropha</i> plants	3
2.1	Typical molecular composition of triglyceride	7
2.2	Iodine value of plant oils	10
2.3	<i>Jatropha curcas</i> seed	12
2.4	<i>Jatropha curcas</i> seed oil	12
2.5	Transesterification reaction of a triglyceride with alcohol	15
2.6	Epoxidation using in-situ production of peracetic acid process	16
3.1	Overall process flow diagram	32
3.2	Process diagram and photograph of synthesis of <i>Jatropha</i> methyl esters	34
3.3	Process flow diagram of two-stage transesterification method	35
3.4	Separation of JME and glycerol	35
3.5	<i>Jatropha</i> methyl esters after washing and drying process	36
3.6	Schematic diagram and photograph of synthesis of epoxy resin from <i>Jatropha</i> methyl esters	38
3.7	Process flow diagram of epoxidation methods using peroxyacetic acid generated in-situ	39
3.8	EJME samples for each one hour of reaction	40
3.9	EJME after washing and drying process	42
3.10	Preparation bio-epoxy resin/synthetic resin blends	44
3.11	Standard test configuration for flexural properties	45
4.1	GC-MS chromatogram of JME	47
4.2	CJO, JME, and EJME	50
4.3	Effect of reaction temperature on relative percentage conversion to oxirane	50
4.4	Effect of hydrogen peroxide per mole of ethylenic unsaturation on relative percentage conversion to oxirane.	52
4.5	Effect of acetic acid per mole of ethylenic unsaturation on relative percentage conversion to oxirane.	53
4.6	Effect of catalyst loading on relative percentage conversion to oxirane.	54
4.7	Normal probability plot of internally studentized residuals	58
4.8	Comparison of actual and predicted values of response	59
4.9	(a) Response surface plots and (b) Contour for the effect of the temperature (A) and molar ratio of hydrogen peroxide (B) on the maximum epoxidation yield	61
4.10	(a) Response surface plots and (b) Contour for the effect of the temperature (A) and molar ratio of acetic acid (C) on the maximum epoxidation yield	62
4.11	(a) Response surface plots and (b) Contour for the effect of the temperature (A) and time (D) on the maximum epoxidation yield	63
4.12	(a) Response surface plots and (b) Contour for the effect of the molar ratio hydrogen peroxide (B) and molar ratio acetic acid (C) on the maximum epoxidation yield	64
4.13	(a) Response surface plots and (b) Contour for the effect of the molar ratio hydrogen peroxide (B) and time (D) on the maximum epoxidation yield	66
4.14	(a) Response surface plots and (b) Contour for the effect of the molar ratio acetic acid (C) and time (D) on the maximum epoxidation yield	67
4.15	FTIR spectra of CJO, JME and JME epoxides	70

4.16	¹ H NMR spectra of CJO	73
4.17	¹ H NMR spectra of JME	74
4.18	¹ H NMR spectra of EJME	75
4.19	¹³ C NMR spectra of CJO	77
4.20	¹³ C NMR spectra of JME	78
4.21	¹³ C NMR spectra of EJME	79
4.22	Percentage compositions five samples of bio-epoxy resin/ epoxamite blends	80
4.23	Tensile stress-strain curve (Sample 1)	82
4.24	Tensile stress-strain curve (Sample 2)	83
4.25	Tensile stress-strain curve (Sample 3)	83
4.26	Flexural stress-strain curve (Sample 1)	85
4.27	Flexural stress-strain curve (Sample 2)	86
A.1	Metabo BAS 260 swift vertical saw machine	105
A.2	Instron universal testing machine for tensile test	106
A.3	Instron universal testing machine for flexural test	106

LIST OF ABBREVIATIONS

AIER	Acidic-ion exchange resin
AA	Acetic acid
CJO	Crude Jatropha oil
CNMR	Carbon Nuclear Magnetic Resonance
CH ₃ OH	Methanol
DB	Double bond
EJME	Epoxidized Jatropha methyl esters
FAME	Fatty Acid Methyl Esters
FFA	Free fatty acid
FTIR	Fourier transforms infrared spectroscopy
H ₂ SO ₄	Sulphuric acid
HNMR	Proton Nuclear Magnetic Resonance
HP	Hydrogen peroxide
JME	Jatropha methyl esters
MAG	Monoglyceride
MM	Molar mass
Na ₂ SO ₄	Sodium sulphate
CH ₃ NaO	Sodium methoxide
NaOH	Sodium hydroxide
PVC	Polyvinyl Chloride
RCO	Relative conversion to oxirane

CHAPTER 1

INTRODUCTION

1.1 Background

Bioresins are defined as resins supplied from renewable sources such as plant oils and its derivatives. Bio-epoxides or also known as epoxides, are bioresins produced using epoxidation method utilizing hydrogen peroxide and peroxyacids generated *in-situ* (Cai & Wang, 2011; Goud et al., 2007; Mungroo et al., 2008). Bio-epoxides are known to have many applications in various industries because of their highly reactive materials. The main content of bio-epoxides is oxirane ring which is very reactive and enables epoxides to be used as biolubricants (Borugadda & Goud, 2015a, 2015b; Hwang & Erhan, 2001; Susana et al., 2015), reactive diluents (Das & Karak, 2009; Muturi et al., 1994), stabilizers in PVC and plasticizers (Chua et al., 2012; Witnauer et al., 1955). Besides, epoxides also have been used as intermediates in production of polyols and polyurethanes (Chen et al., 2015; Lligadas et al., 2006). This research provides brief information on epoxidation methods to produce bio-epoxides synthesized from methyl esters derived from *Jatropha* oil and evaluation of its mechanical properties to be used as an alternative to epoxy resins.

Currently, most available epoxy resins are synthesized from non-renewable and non-biodegradable resources such as petroleum and mineral oils. Mineral oils are important components in the synthesis of polymers known as epoxy monomer (Aouf et al., 2013), phenolic compounds (Khalil et al., 2013) and plastics (Mohanty et al., 2002) utilized for various applications in the industries. Even though the main composition of mineral oils is hydrocarbon, there are also other constituents such as sulphur, nitrogen and traces of metals which pose threat to the ecosystem due to their high toxicity. The major concern for this study was to promote the use of green technology in the chemical industries. Moreover, arising problems associated with mineral oils include depletion of reservoirs which leads to insufficient supply due to high demands and finally price increase. These problems urge researchers to find alternatives and most importantly, the new resources are preferred to be environmentally friendly in order to promote the concept of greener chemistry. A number of alternative resources have been identified such as plant oils, polysaccharide (cellulose or starch), sugar, and wood (Meier et al., 2007). All these resources are renewable and biodegradable.

This study focused on plant oils and their products of transformation because of their high availability and versatility. Plant oils mainly composed of mixtures of triacylglycerol, diacylglycerol, monoacylglycerol and free fatty acid at different percentages (Salimon et al., 2014). Physiochemical properties of plants oils depend on the composition of fatty acid content. The presence of unsaturation or double bonds

indicated by their iodine value (IV) contributes to unique chemical structures that allow chemical modifications to improve their characteristics.

Epoxidation is one of the modification methods to produce biopolymer from plant oils and its derivatives. It is described as the formation of an oxirane group by the reaction of peroxyacids and aromatic double bonds. There are a few factors that affect epoxidation reaction and must be observed carefully, including methods of epoxidation, properties of raw materials, types of epoxidation reagents and solvents, and the presence and type of catalyst (Okieimen et al., 2002). Basically this process is conducted with the presence of organic acid (formic or acetic acid), hydrogen peroxide and catalysts (Campanella et al., 2008; Mushtaq et al., 2013). Organic acids react with hydrogen peroxide to produce peroxyacids, either *in-situ* formed or preformed peroxyacids, with or without presence of catalysts. As a matter of fact, hydrogen peroxide is regarded as a very powerful oxidizing agent which may lead to spontaneous combustion when come in contact with organic material. Concentrated peroxyacids are also unstable and may cause explosion. Because of safety concerns, *in-situ* formed peroxyacids process is a preferable method compare to preformed peroxyacids (Goud et al., 2007).

Jatropha curcas L. are parts of Euphorbiaceae family and originated from South America and Africa. However, it also can be found in South East Asia and India. It is a small tree with large shrub. Their size is between 5 m height and at certain conditions; the height can reach to 8 to 10 m (Insanu et al., 2013). *Jatropha curcas* seed oil was chosen as the feedstock material in this study. *Jatropha* oil can be extracted from leaves, fruits or seed of the plant, shown in Figure 1.1. The seeds of *Jatropha* plant are toxic to animals and human. Thus, the oil is not fit for consumption or any other applications in food industry. Hence, production of FAME from crude oil increases the economic value as well as productivity of the oil.

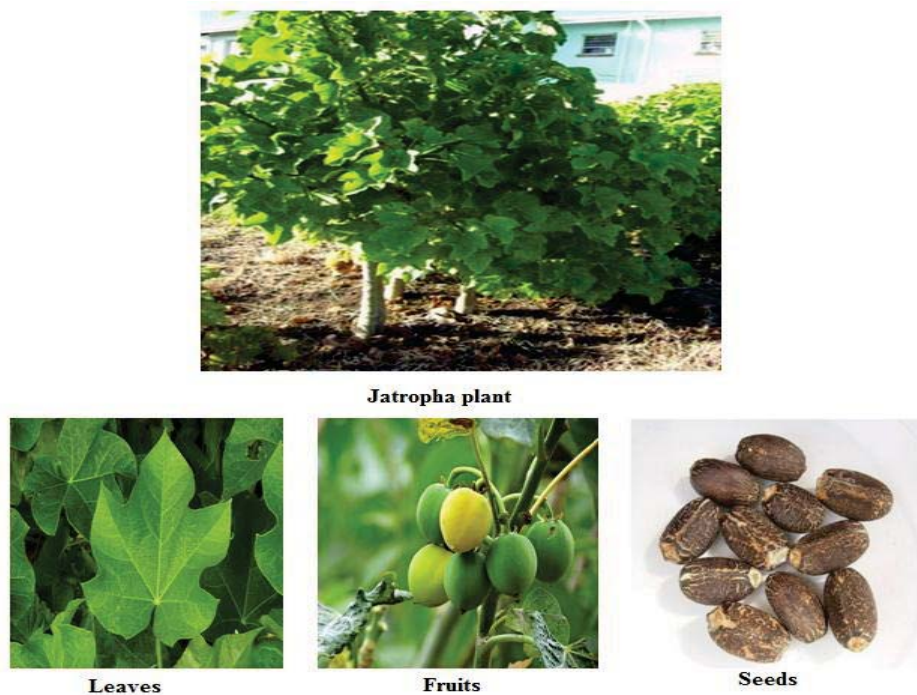


Figure 1.1: Different parts of Jatropha plants

In this paper, we report synthesis of bio-epoxides from FAME derived from crude Jatropha oil using the epoxidation method. The process was initiated by the production of methyl esters from crude Jatropha oil by employing transesterification method whereby acid and alkali were used as catalyst. Optimization of epoxidation was obtained using response surface methodology (RSM).

1.2 Problem Statements

Jatropha methyl esters (JME) have high iodine value which makes them suitable to be used as raw material in the production of bioepoxides. Epoxidized Jatropha methyl esters (EJME) has high oxirane value, therefore has an excellent potential to be used as bio-epoxy resins due to high reactivity of oxirane ring. Previous works has synthesized bio-epoxides from JME using conventional epoxidation methods (Mushtaq et al., 2013; Campanella et. al., 2008). Other works by Borugadda & Goud, (2014) also produces bio epoxides from Castor oil methyl esters using heterogeneous catalyst like ion acidic exchange resin (AIER). Epoxidation method using AIER is an effective method because it minimizes side reaction, high selectivity to epoxidized product and it is a clean and environmental- friendly catalyst. Optimization of production bio epoxy resin from JME is important to find out the optimum operating conditions to maximize production of bio-epoxides. Current epoxy resins are synthesized from petroleum resources. The depletion

of the resources urges the need to find alternative resources that available in abundant. Moreover, the usage of synthetic epoxy resin derives from petroleum raises many issues in terms of safety of use towards health and environmental impact. Bioresources derived from plant oil is an excellent substitutes because besides being available in abundant, they are also environmental friendly. No work has ben done to synthesize bio-epoxides from JME using AIER method. Therefore, this work was conducted to optimize the production of bio-epoxides from JME using AIER epoxidation method and spcetroscopically characterize it. Bio-epoxides obtained from epoxidation process was blended with synthetic epoxy resins and subjected to tensile and flexural test. This is important to asses the properties of bio-epoxides in comparison to synthetic epoxy for further applications. Bio-epoxides produced through epoxidation of JME have potential as plasticizer and stabilizer in PVC, biolubricants and as a polymeric coating.

1.3 Research Objectives

The main purpose of this study was to investigate the synthesis of Jatropha methyl ester using acidic ion exchange resin (AIER) as catalyst.

The objectives of this research are:

- To investigate various factors affecting production of bio-epoxides from JME through epoxidation method and optimize the production of bio-epoxides using response surface methodology (RSM).
- To characterize bio-epoxides in term of physicochemical and spectroscopic characterization

1.4 Scope of works

- i. This study focus on production of bio-epoxides from JME through epoxidation method. During preliminary studies, five reaction parameters were investigated namely, reaction temperature, time, molar ratio of hydrogen peroxide to unsaturated carbon, molar ratio of acetic acid to unsaturated carbon and percentage weight of catalyst loading. The range of investigated parameters were; temperature (30-85°C) molar ratio of hydrogen peroxide to unsaturated carbon (0.8-2.5 mol), molar ratio of acetic acid to unsaturated carbon (0.3-1.0 mol), catalyst loading (5-20%) and time (1-10 hours).
- ii. Different from previous works, this work focused on epoxidation of JME using combination of peroxyacetic acid generated *in-situ* and Amberlite-120 catalyst with the purpose to accelarate the formation of epoxides and reduce the usage of hydrogen peroxide. Optimization study was conducted to investigate the optimum reaction parameters and Response Surface Methodology (RSM) method was used. Central composite desing (CCD) was adopted and four reaction parameters were studied which were temperature (30-85°C), molar ratio of hydrogen peroxide to unsaturated carbon (1.1-2.5 mol), molar ratio of

acetic acid to unsaturated carbon (0.5-0.8mol) and reaction time (2-7 hours).The results were analysed using ANOVA.

- iii. Physicochemical JME and epoxidized Jatropha methyl esters (EJME) such as iodine value, acid value, free fatty acid, saponification value, density, viscosity and specific gravity were identified. GC-MS analysis were done to evaluate the fatty acid compositions of JME. Spectroscopic characterization, FTIR and NMR were used to identified molecular structure in both JME and EJME. Hence, to confirm formation of bio-epoxides. Evaluation of mechanical properties; tensile and flexural strength of bio-epoxides and synthetics epoxy resins blends were conducted to evaluate the suitability of bio-epoxides as an alternative to synthetic bio-resin.



REFERENCES

- Abduh, M. Y., Iqbal, M., Picchioni, F., Manurung, R., & Heeres, H. J. (2015). Synthesis and properties of cross-linked polymers from epoxidized rubber seed oil and triethylenetetramine. *Journal of Applied Polymer Science*, 42591, 1–12.
- Abdullah, B. M., Salih, N., & Salimon, J. (2014). Optimization of the chemoenzymatic mono-epoxidation of linoleic acid using D-optimal design. *Journal of Saudi Chemical Society*, 18, 276–287.
- Abdullah, B. M., Yusop, R. M., Salimon, J., Derawi, D., & Ahmed, W. A. (2016). Epoxidation Synthesis of Linoleic Acid for Renewable Energy Applications. *Malaysian Journal of Analytical Science*, 20(1), 131–141.
- Abidin, Z. Z., Ismail, N., Yunus, R., Ahamad, I. S., & Idris, A. (2011). A preliminary study on *Jatropha curcas* as coagulant in wastewater treatment. *Environmental Technology*, 32(9–10), 971–977.
- Abidin, Z. Z., Mohd Shamsudin, N. S., Madehi, N., & Sobri, S. (2013). Optimisation of a method to extract the active coagulant agent from *Jatropha curcas* seeds for use in turbidity removal. *Industrial Crops and Products*, 41(1), 319–323.
- Ahmed, W., Nazar, M. F., Ali, S. D., Rana, U. A., & Khan, S. U. D. (2015). Detailed investigation of optimized alkali catalyzed transesterification of *Jatropha* oil for biodiesel production. *Journal of Energy Chemistry*, 24(3), 331–336.
- Akbar, E., Yaakob, Z., Kamarudin, S. K., Ismail, M., & Salimon, J. (2009). Characteristic and Composition of *Jatropha Curcas* Oil Seed from Malaysia and its Potential as Biodiesel Feedstock. *European Journal of Scientific Research*, 29(3), 396–403.
- Al-Namie, I., Ibrahim, A. A., & Hassan, M. F. (2011). Study the mechanical properties of epoxy resin reinforced with silica (quartz) and alumina particles. *The Iraqi Journal For Mechanical And Material Engineering*, 11(3), 486–506.
- Alam, M., Akram, D., Sharmin, E., Zafar, F., & Ahmad, S. (2014). Vegetable oil based eco-friendly coating materials: A review article. *Arabian Journal of Chemistry*, 7(4), 469–479.
- Aouf, C., Nouailhas, H., Fache, M., Caillol, S., Boutevin, B., & Fulcrand, H. (2013). Multi-functionalization of gallic acid. Synthesis of a novel bio-based epoxy resin. *European Polymer Journal*, 49(6), 1185–1195.
- Archana, J., Pankaj, S., & Bachheti, R. K. (2011). Physicochemical Characterization of Seed Oil of *Jatropha Curcas* L. Collected From Dehradun (Uttarakhand). *International Journal of Applied Biology and Pharmaceutical Technology*, 2(2), 123–127.

- Aung, M. M., Yaakob, Z., Kamarudin, S., & Abdullah, L. C. (2014). Synthesis and characterization of Jatropha (*Jatropha curcas* L.) oil-based polyurethane wood adhesive. *Industrial Crops and Products*, *60*, 177–185.
- Ays, H. (2002). Immobilized *Candida antarctica* lipase-catalyzed alcoholysis of cotton seed oil in a solvent-free medium, *83*, 125–129.
- Bajwa, A. S., Sathaye, S., Kulkarni, V. M., & Patwardhan, A. V. (2016). Chemoenzymatic epoxidation of Karanja oil : an alternative to chemical epoxidation *Asia-Pacific Journal of Chemical Engineering*, *11*(March), 314–322.
- Benaniba, M. T., Belhaneche-Bensemra, N., & Gelbard, G. (2007). Kinetics of tungsten-catalyzed sunflower oil epoxidation studied by ¹H NMR. *European Journal of Lipid Science and Technology*, *109*, 1186–1193.
- Bobade, S. N., Kumbhar, R. R., & Khyade, V. B. (2013). Preparation of Methyl Ester (Biodiesel) from *Jatropha Curcas* Linn Oil. *Research Journal of Agriculture and Forestry Sciences*, *1*(2), 12–19.
- Boonmee, K., Chuntranuluck, S., Punsuvon, V., & Silayoi, P. (2010). Optimization of Biodiesel Production from *Jatropha* Oil (*Jatropha curcas* L.) using Response Surface Methodology. *Kasetsart J. (Nat. Sci.)*, *44*, 290–299.
- Bora, M. M., Deka, R., Ahmed, N., & Kakati, D. K. (2014). Karanja (*Millettia pinnata* (L.) Panigrahi) seed oil as a renewable raw material for the synthesis of alkyd resin. *Industrial Crops and Products*, *61*, 106–114.
- Boruah, M., Gogoi, P., Adhikari, B., & Dolui, S. K. (2012). Preparation and characterization of *Jatropha Curcas* oil based alkyd resin suitable for surface coating. *Progress in Organic Coatings*, *74*(3), 596–602.
- Borugadda, V. B., & Goud, V. V. (2014). Epoxidation of Castor Oil Fatty Acid Methyl Esters (COFAME) as a Lubricant base Stock Using Heterogeneous Ion-exchange Resin (IR-120) as a Catalyst. *Energy Procedia*, *54*(361), 75–84.
- Borugadda, V. B., & Goud, V. V. (2015a). Improved thermo-oxidative stability of structurally modified waste cooking oil methyl esters for bio-lubricant application. *Journal of Cleaner Production*, *112*, 4515–4524.
- Borugadda, V. B., & Goud, V. V. (2015b). Response surface methodology for optimization of bio-lubricant basestock synthesis from high free fatty acids castor oil. *Energy Science & Engineering*, *3*(4), 371–383.
- Cai, C., Dai, H., Chen, R., Su, C., Xu, X., Zhang, S., & Yang, L. (2008). Studies on the kinetics of in situ epoxidation of vegetable oils. *European Journal of Lipid Science and Technology*, *110*, 341–346.
- Cai, S., & Wang, L. (2011). Epoxidation of Unsaturated Fatty Acid Methyl Esters in the

Presence of SO₃H-functional Brønsted Acidic Ionic Liquid as Catalyst. *Chinese Journal of Chemical Engineering*, 19(1), 57–63.

Campanella, A., Fontanini, C., & Baltanás, M. A. (2008). High yield epoxidation of fatty acid methyl esters with performic acid generated in situ. *Chemical Engineering Journal*, 144(3), 466–475.

Carbonell-Verdu, A., Bernardi, L., Garcia-Garcia, D., Sanchez-Nacher, L., & Balart, R. (2015). Development of environmentally friendly composite matrices from epoxidized cottonseed oil. *European Polymer Journal*, 63, 1–10.

Chaudhari, A., Gite, V., Rajput, S., Mahulikar, P., & Kulkarni, R. (2013). Development of eco-friendly polyurethane coatings based on neem oil polyetheramide. *Industrial Crops and Products*, 50, 550–556.

Chen, R., Zhang, C., & Kessler, M. R. (2015). Polyols and Polyurethanes Prepared from Epoxidized Soybean Oil Ring-Opened by Polyhydroxy Fatty Acids with Varying OH Numbers, 41213, 1–10.

Chen, Y.H., Chen, J.H., Luo, Y.-M., Shang, N.C., Chang, C.H., Chang, C.-Y., ... Shie, J.L. (2011). Property modification of Jatropha oil biodiesel by blending with other biodiesels or adding antioxidants. *Energy*, 36(7), 4415–4421.

Cheng, W., Liu, G., Wang, X., Liu, X., & Jing, L. (2015). Kinetics of the epoxidation of soybean oil with H₂O₂ catalyzed by phosphotungstic heteropoly acid in the presence of polyethylene glycol, 1185–1191.

Chua, S.-C., Xu, X., & Guo, Z. (2012). Emerging sustainable technology for epoxidation directed toward plant oil-based plasticizers. *Process Biochemistry*, 47(10), 1439–1451.

Cooney, T. I., Cardona, F., & Tran-Cong, T. (2011). Kinetics of in Situ Epoxidation of Hemp Oil Under Heterogenous Reaction Conditions: an Overview With Preliminary Results. *Energy, Environment and Sustainability*, 106–111.

Das, G., & Karak, N. (2009). Epoxidized Mesua ferrea L. seed oil-based reactive diluent for BPA epoxy resin and their green nanocomposites. *Progress in Organic Coatings*, 66(1), 59–64.

De Silva, S. H. U. I., Amarasinghe, A. D. U. S., Premachandra, B.A. J. K., & Prashantha, M. A. B. (2012). Effect of karawila (*Momordica charantia*) seed oil on synthesizing the alkyd resins based on soya bean (*Glycine max*) oil. *Progress in Organic Coatings*, 74(1), 228–232.

De Torres, M., Arends, I. W. C. E., Mayoral, J.A., Pires, E., & Jiménez-Osés, G. (2012). A highly efficient, green and recoverable catalytic system for the epoxidation of fatty esters and biodiesel with H₂O₂. *Applied Catalysis A: General*, 425–426, 91–96.

- Deng, X., Fang, Z., & Liu, Y. (2010). Ultrasonic transesterification of *Jatropha curcas* L. oil to biodiesel by a two-step process. *Energy Conversion and Management*, 51(12), 2802–2807.
- Derawi, D., & Salimon, J. (2010). Optimization on Epoxidation of Palm Olein by Using Performic Acid. *E-Journal of Chemistry*, 7(4), 1440–1448.
- Dinda, S., Patwardhan, A. V., Goud, V. V., & Pradhan, N. C. (2008). Epoxidation of cottonseed oil by aqueous hydrogen peroxide catalysed by liquid inorganic acids. *Bioresource Technology*, 99, 3737–3744.
- Dutta, N., Karak, N., & Dolui, S. K. (2006). Alkyd–epoxy blends as multipurpose coatings. *Journal of Applied Polymer Science*, 100(1), 516–521.
- Farias, M., Martinelli, M., & Bottega, D. P. (2010). Epoxidation of soybean oil using a homogeneous catalytic system based on a molybdenum (VI) complex. *Applied Catalysis A: General*, 384(1–2), 213–219.
- Francucci, G., Cardona, F., & Manthey, N. W. (2012). Cure kinetics of an acrylated epoxidized hemp oil-based bioresin system. *Journal of Applied Polymer Science*, 2030–2037.
- Galià, M., de Espinosa, L. M., Ronda, J. C., Lligadas, G., & Cádiz, V. (2010). Vegetable oil-based thermosetting polymers. *European Journal of Lipid Science and Technology*, 112(1), 87–96.
- Gan, L. H., Goh, S. H., & Ooi, K. S. (1992). Kinetic studies of epoxidation and oxirane cleavage of palm olein methyl esters. *Journal of the American Oil Chemists' Society*, 69(4), 347–351.
- Gan, L. H., Ooi, K. S., Goh, S. H., Gan, L. M., & Leong, Y. C. (1995). Epoxidized esters of palm olein as plasticizers for poly(vinyl chloride). *European Polymer Journal*, 31(8), 719–724.
- Ghiron, C., Nannetti, L., & Taddei, M. (2005). Alkene epoxidation with urea-hydrogen peroxide complex and PS-DVB supported phthalic anhydride. *Tetrahedron Letters*, 46, 1643–1645.
- Goud, V. V., Dinda, S., Patwardhan, A. V., & Pradhan, N. C. (2010). Epoxidation of *Jatropha* (*Jatropha curcas*) oil by peroxyacids. *Asia-Pacific Journal of Chemical Engineering*, 5(May 2009), 346–354.
- Goud, V. V., Patwardhan, A. V., Dinda, S., & Pradhan, N. C. (2007). Kinetics of epoxidation of *Jatropha* oil with peroxyacetic and peroxyformic acid catalysed by acidic ion exchange resin. *Chemical Engineering Science*, 62, 4065–4076.
- Goud, V. V., Pradhan, N. C., & Patwardhan, A. V. (2006). Epoxidation of karanja (*Pongamia glabra*) oil by H₂O₂. *Journal of the American Oil Chemists' Society*,

83(7), 635–640.

Goud, V. V., Patwardhan, A. V., & Pradhan, N. C. (2006). Studies on the epoxidation of mahua oil (*Madhumica indica*) by hydrogen peroxide. *Bioresource Technology*, 97(12), 1365–71.

Hilker, I., Bothe, D., Pru, J., & Warnecke, H. (2001). Chemo-enzymatic epoxidation of unsaturated plant oils. *Chemical Engineering Science*, 56, 427–432.

Hong, L. K., Yusop, R. M., Salih, N., & Salimon, J. (2015). Optimization of the in situ epoxidation of linoleic acid of *Jatropha curcas* oil with performic acid. *The Malaysian Journal of Analytical Sciences*, 19(1), 144–154.

Hosseini, N., Webster, D. C., & Ulven, C. (2016). Advanced biocomposite from highly functional Methacrylated Epoxidized Sucrose Soyate (MAESS) resin derived from vegetable oil and fiberglass fabric for composite applications. *European Polymer Journal*.

Hwang, H.-S., & Erhan, S. Z. (2001). Modification of epoxidized soybean oil for lubricant formulations with improved oxidative stability and low pour point. *Journal of the American Oil Chemists' Society*, 78(12), 1179–1184.

Ikuhoria, E. U., Maliki, M., Okieimen, F. E., Aigbodion, A. I., Obaze, E. O., & Bakare, I. O. (2007). Synthesis and characterisation of chlorinated rubber seed oil alkyd resins. *Progress in Organic Coatings*, 59(2), 134–137.

Ikuhoria, E. U., Obuleke, R. O., & Okieimen, F. E. (2007). Studies on the Kinetics of Epoxidation of the Methyl Esters of *Parkia Biglobosa* Seed Oil. *Journal of Macromolecular Science, Part A*, 44(2), 235–238.

Ikwuagwu, O. E., Ononogbu, I. C., & Njoku, O. U. (2000). Production of biodiesel using rubber [*He 6 ea brasiliensis* (Kunth . Muell .)] seed oil. *Industrial Crops and Products*, 12, 57–62.

Insanu, M., Dimaki, C., Wilkins, R., Brooker, J., Van Der Linde, P., & Kayser, O. (2013). Rational use of *Jatropha curcas* L. in food and medicine: From toxicity problems to safe applications. *Phytochemistry Reviews*, 12(1), 107–119.

İşeri-Çağlar, D., Baştürk, E., Oktay, B., & Kahraman, M. V. (2014). Preparation and evaluation of linseed oil based alkyd paints. *Progress in Organic Coatings*, 77(1), 81–86.

Issariyakul, T., & Dalai, A. K. (2014). Biodiesel from vegetable oils. *Renewable and Sustainable Energy Reviews*, 31, 446–471.

Jain, S., & Sharma, M. P. (2010). Kinetics of acid base catalyzed transesterification of *Jatropha curcas* oil. *Bioresource Technology*, 101(20), 7701–6.

- Jankovic, M. R., Sinadinovic, V., & Govedarica, O. M. (2014). Kinetics of the Epoxidation of Castor Oil with Peracetic Acid Formed in Situ in the Presence of an Ion-Exchange Resin. *Industrial and Engineering Chemistry Research*, 53, 9357–9364.
- Jebrane, M., Cai, S., Panov, D., Yang, X., & Terziev, N. (2015). Synthesis and characterization of new vinyl acetate grafting onto epoxidized linseed oil in aqueous media. *Journal of Applied Polymer Science*, 132(24), 1–9.
- Jiang, J., Zhang, Y., Yan, L., & Jiang, P. (2012). Epoxidation of soybean oil catalyzed by peroxy phosphotungstic acid supported on modified halloysite nanotubes. *Applied Surface Science*, 258(17), 6637–6642.
- Jin, F. L., Li, X., & Park, S. J. (2015). Synthesis and application of epoxy resins: A review. *Journal of Industrial and Engineering Chemistry*, 29, 1–11.
- Kadam, A., Pawar, M., Yemul, O., Thamke, V., & Kodam, K. (2015). Biodegradable biobased epoxy resin from karanja oil. *Polymer*, 72, 82–92.
- Kay, K. H., & Yasir, S. M. (2012). Biodiesel Production from Low Quality Crude Jatropha Oil Using Heterogeneous Catalyst. *APCBEE Procedia*, 3(May), 23–27.
- Khalid, K., & Khalid, K. (2011). Transesterification of Palm Oil for the Production of Biodiesel. *American Journal of Applied Sciences*, 8(8), 804–809.
- Khalil, H. P. S. A., Aprilia, N. A. S., Bhat, A. H., Jawaid, M., Paridah, M. T., & Rudi, D. (2013). A Jatropha biomass as renewable materials for biocomposites and its applications. *Renewable and Sustainable Energy Reviews*, 22, 667–685.
- Kouame, S.-D. B., Perez, J., Eser, S., & Benesi, A. (2012). ¹H-NMR Monitoring of the transesterification process of Jatropha oil. *Fuel Processing Technology*, 97, 60–64.
- Kumar, G., Kumar, D., Poonam, Johari, R., & Singh, C. P. (2011). Enzymatic transesterification of Jatropha curcas oil assisted by ultrasonication. *Ultrasonics Sonochemistry*, 18(5), 923–7.
- Lathi, P., & Mattiasson, B. (2007). Green approach for the preparation of biodegradable lubricant base stock from epoxidized vegetable oil. *Applied Catalysis B: Environmental*, 69(3–4), 207–212.
- Liew, K. H., Yusop, R. M., Salih, N., & Salimon, J. (2015). Optimization of the in situ epoxidation of linoleic acid of Jatropha curcas oil with performic acid. *The Malaysian Journal of Analytical Sciences*, 19(1), 144–154.
- Lim, B. Y., Shamsudin, R., Baharudin, B. T. H. T., & Yunus, R. (2015). A review of processing and machinery for Jatropha curcas L. fruits and seeds in biodiesel production: Harvesting, shelling, pretreatment and storage. *Renewable and Sustainable Energy Reviews*, 52, 991–1002.

- Lligadas, G., Ronda, J. C., Galià, M., Biermann, U., & Metzger, J. O. (2006). Synthesis and characterization of polyurethanes from epoxidized methyl oleate based polyether polyols as renewable resources. *Journal of Polymer Science, Part A: Polymer Chemistry*, 44(1), 634–645.
- Lligadas, G., Ronda, J. C., Galià, M., & Cádiz, V. (2013). Renewable polymeric materials from vegetable oils: a perspective. *Materials Today*, 16(9), 337–343.
- Lu, H., Liu, Y., Zhou, H., Yang, Y., Chen, M., & Liang, B. (2009). Production of biodiesel from *Jatropha curcas* L. oil. *Computers & Chemical Engineering*, 33, 1091–1096.
- Lu, H., Sun, S., Bi, Y., & Yang, G. (2012). Enzymatic epoxidation of biodiesel optimized by response surface methodology. *African Journal of Biotechnology*, 11(59), 12356–12363.
- M. Rusch gen. Klaas, & Warwel, S. (1996). Chemoenzymatic Epoxidation of Unsaturated Fatty Acid Esters and Plant Oils. *Biocatalysis Articles*, 73(11), 9–13.
- Manthey, N. W., Cardona, F., & Aravinthan, T. (2012). Cure kinetic study of epoxidized hemp oil cured with a multiple catalytic system. *Journal of Applied Polymer Science*, 125(S2), E511–E517.
- Manthey, N. W., Cardona, F., Aravinthan, T., & Cooney, T. (2011). Cure kinetics of an epoxidized hemp oil based bioresin system. *Journal of Applied Polymer Science*, 122(1), 444–451.
- Manthey, N. W., Cardona, F., Aravinthan, T., Wang, H., & Cooney, T. (2003). Natural fibre composites with QLD based fibres and vegetable oils.
- Manthey, N. W., Cardona, F., Francucci, G., & Aravinthan, T. (2013). Thermo-mechanical properties of epoxidized hemp oil-based bioresins and biocomposites. *Journal of Reinforced Plastics and Composites*, 32(19), 1444–1456.
- May, C. A. (1973). *Epoxy Resins: Chemistry and Technology*. Marcel Dekker, New York.
- McNutt, J., & He, Q. S. (2016). Journal of Industrial and Engineering Chemistry Development of biolubricants from vegetable oils via chemical modification. *Journal of Industrial and Engineering Chemistry*.
- Meier, M. A R., Metzger, J. O., & Schubert, U. S. (2007). Plant oil renewable resources as green alternatives in polymer science. *Chemical Society Reviews*, 36, 1788–1802.
- Mofijur, M., Masjuki, H. H., Kalam, M. A., & Atabani, A. E. (2013). Evaluation of biodiesel blending, engine performance and emissions characteristics of *Jatropha curcas* methyl ester: Malaysian perspective. *Energy*, 55, 879–887.

- Mohanty, A. K., Misra, M., & Drzal, L. T. (2002). Sustainable Bio-Composites from Renewable Resources: Opportunities and Challenges in the Green Materials World, *10*(April), 19–26.
- Monteavaro, L. L., Da Silva, E. O., Costa, A. P. O., Samios, D., Gerbase, A. E., & Petzhold, C. L. (2005). Polyurethane networks from formiated soy polyols: Synthesis and mechanical characterization. *JAOCS, Journal of the American Oil Chemists' Society*, *82*(5), 365–371.
- Mungroo, R., Pradhan, N. C., Goud, V. V., & Dalai, A. K. (2008). Epoxidation of canola oil with hydrogen peroxide catalyzed by acidic ion exchange resin. *JAOCS, Journal of the American Oil Chemists' Society*, *85*, 887–896.
- Murillo, E. a., Vallejo, P. P., & López, B. L. (2010). Synthesis and characterization of hyperbranched alkyd resins based on tall oil fatty acids. *Progress in Organic Coatings*, *69*(3), 235–240.
- Mushtaq, M., Tan, I. M., Nadeem, M., Devi, C., Lee, S. Y. C., Sagir, M., & Rashid, U. (2013). Epoxidation of methyl esters derived from Jatropha oil: An optimization study. *Grasas Y Aceites*, *64*(1), 103–114.
- Mustata, F., Nita, T., & Bicu, I. (2014). The curing reaction of epoxidized methyl esters of corn oil with Diels–Alder adducts of resin acids. The kinetic study and thermal characterization of crosslinked products. *Journal of Analytical and Applied Pyrolysis*, *108*, 254–264.
- Muturi, P., Wang, D., & Dirlikov, S. (1994). Epoxidized vegetable oils as reactive diluents I. Comparison of vernonia, epoxidized soybean and epoxidized linseed oils. *Progress in Organic Coatings*, *25*(1), 85–94.
- Nakpong, P., & Wootthikanokkhan, S. (2010). Optimization of Biodiesel Production from Jatropha Oil (*Jatropha curcas* L .) using Response Surface Methodology. *Journal of Sustainable Energy & Environment*, *299*, 290–299.
- Nayak, B. S., & Patel, K. N. (2010). Physicochemical characterization of seed and seed oil of *Jatropha curcas* L. Collected from bardoli (South Gujarat). *Sains Malaysiana*, *39*(6), 951–955.
- Ni, M., Fong, F., & Salimon, J. (2012). Epoxidation of Palm Kernel Oil Fatty Acids. *Journal of Science and Technology*, *4*(12), 87–98.
- Ni, Y., & Jumat, L. (2015). Synthesis and Physicochemical Properties of Partially and Fully Epoxidized Methyl Linoleate Derived from *Jatropha curcas* Oil, 257–266.
- Nzikou, J. M., Matos, L., Mbemba, F., Ndangui, C. B., Pambou-Tobi, N. P. G., Kimbonguila, A., ... Desobry, S. (2009). Characteristics and composition of *Jatropha curcas* oils, variety Congo-Brazzaville. *Research Journal of Applied Sciences, Engineering and Technology*, *1*(3), 154–159.

- Odetoeye, T. E., Ogunniyi, D. S., & Olatunji, G. A. (2010). Preparation and evaluation of *Jatropha curcas* Linneaus seed oil alkyd resins. *Industrial Crops and Products*, 32(3), 225–230.
- Ogunniyi, D. S., & Odetoeye, T. E. (2008). Preparation and evaluation of tobacco seed oil-modified alkyd resins. *Bioresource Technology*, 99(5), 1300–4.
- Okieimen, F. ., Bakare, O. ., & Okieimen, C. . (2002). Studies on the epoxidation of rubber seed oil. *Industrial Crops and Products*, 15(2), 139–144.
- Okieimen, F. E., Pavithran, C., & Bakare, I. O. (2005). Epoxidation and hydroxlation of rubber seed oil: one-pot multi-step reactions. *European Journal of Lipid Science and Technology*, 107(5), 330–336.
- Paquot, C. (1979). *Standard Methods for the Analysis of Oils, Fats and Derivatives Part 1* (6th ed.). United Kingdom: Pergamon, Oxford.
- Parajuli, R. (2009). *Jatropha Curcas and Its Potential Applications; A Compilation Paper on Plantation and Application of Jatropha Curcas*. *Renewable and Sustainable Energy Reviews*, 15, 3733–3756.
- Pawar, M., Kadam, A., Yemul, O., Thamke, V., & Kodam, K. (2016). Biodegradable bioepoxy resins based on epoxidized natural oil (cottonseed & algae) cured with citric and tartaric acids through solution polymerization: A renewable approach. *Industrial Crops and Products*, 89, 434–447.
- Petrovic, Z. S., Zlatanic, A., Lava, C., Polymer, K., & Sad, N. (2002). Epoxidation of soybean oil in toluene with peroxyacetic and peroxyformic acids – kinetics and side reactions. *Eur. J. Lipid Sci. Technol.*, 104, 293–299.
- Piazza, G. J., Nuñez, A., & Foglia, T. A. (2003). Epoxidation of fatty acids , fatty methyl esters , and alkenes by immobilized oat seed peroxygenase . *Journal of Molecular Catalysis B: Enzymatic* 21, 21, 143–151.
- Pin, J. M., Sbirrazzuoli, N., & Mija, A. (2015). From epoxidized linseed oil to bioresin: An overall approach of epoxy/anhydride cross-linking. *ChemSusChem*, 8(7), 1232–1243.
- Pradhan, S., Naik, S. N., Khan, M. A. I., & Sahoo, P. K. (2012). Experimental assessment of toxic phytochemicals in *Jatropha curcas*: Oil, cake, bio-diesel and glycerol. *Journal of the Science of Food and Agriculture*, 92(July 2011), 511–519.
- Rabiah Nizah, M. F., Taufiq-Yap, Y. H., Rashid, U., Teo, S. H., Shajaratun Nur, Z. A., & Islam, A. (2014). Production of biodiesel from non-edible *Jatropha curcas* oil via transesterification using Bi₂O₃–La₂O₃ catalyst. *Energy Conversion and Management*, 88, 1257–1262.
- Rafiee-Moghaddam, R., Salimon, J., Haron, M. D. J., Jahangirian, H., Ismail, M. H. S.,

- Hosseini, S., ... Unit, C. (2014). Lipase epoxidation of *Jatropha curcas* oil using perlauric acid. *Digest Journal of Nanomaterials and Biostructures*, 9(3), 1159–1169.
- Raghavachar, R., Sarnecki, G., Baghdachi, J., & Massingill, J. L. (2000). Cationic, Thermally Cured Coating Using Epoxidized Soybean Oil. *Journal of Coatings Technology*, 72(909), 125–133.
- Rangarajan, B., Havey, A., Grulke, E. A., & Culnan, P. D. (1995). Kinetic parameters of a two-phase model for in situ epoxidation of soybean oil. *Journal of the American Oil Chemists' Society*, 72(10), 1161–1169.
- Rashid, U., & Anwar, F. (2008). Production of biodiesel through optimized alkaline-catalyzed transesterification of rapeseed oil. *Fuel*, 87, 265–273.
- Rashid, U., Ibrahim, M., Ali, S., Adil, M., Hina, S., Bukhari, I. H., & Yunus, R. (2012). Comparative study of the methanolysis and ethanolysis of maize oils using alkaline catalysts. *Grasas Y Aceites*, 63(1), 35–43.
- Rios, L. A., Echeverri, D. A., & Franco, A. (2011). Epoxidation of *Jatropha* oil using heterogeneous catalysts suitable for the Prileschajew reaction: Acidic resins and immobilized lipase. *Applied Catalysis A: General*, 394(1–2), 132–137.
- Saithai, P., Lecomte, J., Dubreucq, E., & Tanrattanakul, V. (2013). Effects of different epoxidation methods of soybean oil on the characteristics of acrylated epoxidized soybean oil-co-poly (methyl methacrylate) copolymer. *Express Polymer Letters*, 7(11), 910–924.
- Salimon, J., Abdullah, B. M., Yusop, R. M., & Salih, N. (2014). Synthesis, reactivity and application studies for different biolubricants. *Chemistry Central Journal*, 8(1), 16.
- Sammaiah, A., Padmaja, K. V., Badari, R., & Prasad, N. (2014). Synthesis of Epoxy *Jatropha* Oil and its Evaluation for Lubricant Properties. *Journal of Oleo Science*, 63(6), 637–643.
- Saremi, K., Tabarsa, T., Shakeri, A., & Babanalbandi, A. (2012). Epoxidation of Soybean Oil. *Annals of Biological Research*, 3(9), 4254–4258.
- Satheesh Kumar, M. N., Yaakob, Z., Maimunah, S., & Abdullah, S. R. S. (2010). Synthesis of Alkyd Resin from Non-Edible *Jatropha* Seed Oil. *Journal of Polymers and the Environment*, 18(4), 539–544.
- Satyanarayana, M., & Muraleedharan, C. (2011). Comparative Studies of Biodiesel Production from Rubber Seed Oil, Coconut Oil, and Palm Oil Including Thermogravimetric Analysis. *Energy Sources, Part A: Recovery, Utilization, and Environmental Effects*, 33(10), 925–937.
- Saurabh, T., Patnaik, M., Bhagat, S. L., & Renge, V. C. (2011). Epoxidation of vegetable

- oil: A review. *International Journal of Advanced Engineering Technology*, 2(4), 491–501.
- Schneider, R. D. C. S., Lara, L. R. S., Bitencourt, T. B., da Graça Nascimento, M., & dos Santos Nunes, M. R. (2009). Chemo-enzymatic epoxidation of sunflower oil methyl esters. *Journal of the Brazilian Chemical Society*, 20(8), 1473–1477.
- Shah, S. N., Joshi, A., Patel, A., & Brahmkhatri, V. P. (2013). Synthesis of Jatropha Oil based Biodiesel using Environmentally Friendly Catalyst and their Blending Studies with Diesel. *Energy and Power*, 3(1), 7–11.
- Shikha, K., & Rita, C. Y. (2012). Review Article Biodiesel production from non edible-oils : A Review. *Journal of Chemical and Pharmaceutical Research*, 4(9), 4219–4230.
- Shrestha, K., Ghimire, J., & Gewali, M. (2013). Biodiesel Production From Jatropha Curcas (L .) Oil Of Nepal By Transesterification Process. *International Journal of Pharmaceutical, Chemical and Biological Sciences*, 3(3), 603–609.
- Silitonga, A. S., Masjuki, H. H., Mahlia, T. M. I., Ong, H. C., Atabani, A. E., & Chong, W. T. (2013). A global comparative review of biodiesel production from jatropha curcas using different homogeneous acid and alkaline catalysts: Study of physical and chemical properties. *Renewable and Sustainable Energy Reviews*, 24, 514–533.
- Sinadinović-Fišer, S., Janković, M., & Borota, O. (2012). Epoxidation of castor oil with peracetic acid formed in situ in the presence of an ion exchange resin. *Chemical Engineering and Processing: Process Intensification*, 62, 106–113.
- Sinadinović-Fišer, S., Janković, M., & Petrović, Z. S. (2001). Kinetics of in situ epoxidation of soybean oil in bulk catalyzed by ion exchange resin. *Journal of the American Oil Chemists' Society*, 78(7), 725–731.
- Singh, R. K., & Padhi, S. K. (2009). Characterization of jatropha oil for the preparation of biodiesel. *National Product Radiance*, 8(2), 127–132.
- Soucek, M. D., Johnson, A. H., & Wegner, J. M. (2004). Ternary evaluation of UV-curable seed oil inorganic/organic hybrid coatings using experimental design. *Progress in Organic Coatings*, 51(4), 300–311.
- Susana, M., Luiz, E., Martins, S., Neuma, T., Dantas, D. C., Avelino, A., & Neto, D. (2015). New hydraulic biolubricants based on passion fruit and moringa oils and their epoxy. *Industrial Crops and Products Journal*, 69, 362–370.
- Tan, S. G., & Chow, W. S. (2010). Biobased Epoxidized Vegetable Oils and Its Greener Epoxy Blends: A Review. *Polymer-Plastics Technology and Engineering*, 49(15), 1581–1590.

- Taufiq-Yap, Y. H., Teo, S. H., Rashid, U., Islam, A., Hussien, M. Z., & Lee, K. T. (2014). Transesterification of *Jatropha curcas* crude oil to biodiesel on calcium lanthanum mixed oxide catalyst: Effect of stoichiometric composition. *Energy Conversion and Management*, 88, 1290–1296.
- Thames, S. F., & Yu, H. (1999). Cationic UV-cured coatings of epoxide-containing vegetable oils. *Surface and Coatings Technology*, 115(2–3), 208–214.
- Tippayawong, N., & Sittisun, P. (2012). Continuous-flow transesterification of crude jatropha oil with microwave irradiation. *Scientia Iranica*, 19, 1324–1328.
- Törnvall, U., Orellana-Coca, C., Hatti-Kaul, R., & Adlercreutz, D. (2007). Stability of immobilized *Candida antarctica* lipase B during chemo-enzymatic epoxidation of fatty acids. *Enzyme and Microbial Technology*, 40(3), 447–451.
- Uzoh, C. F., Onukwuli, O. D., Odera, R. S., & Ofochebe, S. (2013). Optimization of polyesterification process for production of palm oil modified alkyd resin using response surface methodology. *Journal of Environmental Chemical Engineering*, 1(4), 777–785.
- Wan Rosli, W. D., Kumar, R. N., Mek Zah, S., & Hilmi, M. M. (2003). UV radiation curing of epoxidized palm oil-cycloaliphatic diepoxide system induced by cationic photoinitiators for surface coatings. *European Polymer Journal*, 39(3), 593–600.
- Wang, R. (2014). Manufacturing of vegetable oils-based epoxy and composites for structural applications.
- Wang, R., & Schuman, T. P. (2012). Vegetable oil-derived epoxy monomers and polymer blends: A comparative study with review. *Express Polymer Letters*, 7(3), 272–292.
- Witnauer, L. E. E. P., Knight, H. B., Palm, W. E., Koos, R. E., Ault, W. C., & Swern, D. (1955). Epoxy Esters as Plasticizers and Stabilizers for Vinyl Chloride Polymers. *Industrial and Engineering Chemistry*, 47(11).
- Xia, W., Budge, S. M., & Lumsden, M. D. (2016). ¹H - NMR Characterization of Epoxides Derived from Polyunsaturated Fatty Acids. *Journal of the American Oil Chemists' Society*, 93(4), 467–478.
- Yee, K. F., Kandedo, J., & Lee, K. T. (2010). Biodiesel Production From Palm Oil Via Heterogeneous Transesterification: Optimization Study. *Chemical Engineering Communications*, 197(12), 1597–1611.
- Yee, K. F., Wu, J. C. S., & Lee, K. T. (2011). A green catalyst for biodiesel production from jatropha oil: Optimization study. *Biomass and Bioenergy*, 35, 1739–1746.
- Yunus, R., & Syam, A. M. (2010). Kinetics of transesterification of *Jatropha curcas*-based triglycerides with an alcohol in the presence of alkaline catalyst. *2010 1st*

International Nuclear and Renewable Energy Conference, INREC'10, (June 2015), 37–41.

Zhang, W., Jiang, P., Wu, J., Zhang, P., & Jiang, K. (2014). Catalytic epoxidation of fatty acid methyl esters by modified metalloporphyrins with variable metals and electron-donating substituents. *Reaction Kinetics, Mechanisms and Catalysis*, 112(1), 147–158.

Zlatanovic, A., Lavan, C., Zhang, W., & Petrovic, Z. S. (2004). Effect of Structure on Properties of Polyols and Polyurethanes Based on Different Vegetable Oils. *Journal of Polymer Science: Part B: Polymer Physics*, 42, 809–819.

