



UNIVERSITI PUTRA MALAYSIA

**MEASUREMENT OF THERMAL DIFFUSIVITY AND
THERMAL EFFUSIVITY OF SOLID AND LIQUID USING
PHOTOACOUSTIC TECHNIQUE**

TEH EE PHING

FSAS 2001 3

**MEASUREMENT OF THERMAL DIFFUSIVITY AND THERMAL EFFUSIVITY
OF SOLID AND LIQUID USING PHOTOACOUSTIC TECHNIQUE**

By

TEH EE PHING

**Thesis Submitted in Fulfilment of the Requirement of the
Degree of Master of Science in the Faculty of Science and Environmental Study
Universiti Putra Malaysia**

June 2001



To my parents
and Lee Lee



Abstract of thesis presented to the Senate of Universiti Putra Malaysia in fulfilment
of the requirement for the degree of Master of Science

**MEASUREMENT OF THERMAL DIFFUSIVITY AND THERMAL EFFUSIVITY
OF SOLID AND LIQUID USING PHOTOACOUSTIC TECHNIQUE**

By

TEH EE PHING

June 2001

Chairman: Associate Professor W. Mahmood Mat Yunus, Ph.D.

Faculty: Science and Environmental Studies

The capability of photoacoustic technique in thermal diffusivity measurement has attracted a lot of interest lately. In the experiment, the open photoacoustic cell (OPC) technique was applied for thermal diffusivity measurement on solid materials such as metal, superconductors and soft ferrites. The photoacoustic signal amplitude was captured as a function of modulated frequency and the characteristic frequency, f_c , of each sample is computed. Thermal diffusivity was calculated based on the f_c and the sample thickness. The way that thermal diffusivity value behaves towards the change of dopant concentration were then investigated. Generally, the thermal diffusivity value measured were between 0.19 to 0.99 cm²/s.

The second part of the work concentrated on liquid materials. By applying the basic theoretical approach and redesigning the OPC sample cell, the thermal effusivity value of liquid samples were able to be determined. The samples chosen were distilled water,

engine oil, lubricant, edible oil and creamy consumer products. The measured value was in a good agreement with the reported values previously published. The technique was feasible in obtaining thermal effusivity ranged from 0.042 to 0.159 $\text{Ws}^{1/2}/(\text{cm}^2\text{°C})$.

Thirdly, for liquid samples with low boiling point such as acetone, methanol and ethanol solvents, the PA technique was used to monitor its evaporation time. The sample of interest was placed in a 13.57 mm^3 container heated by a 30 mW He-Ne laser beam. As expected, the evaporation time were found to be inversely proportional to the respective boiling points.

The fourth part of the work focused on investigation on the protonation process in polyanilines, a kind of conducting polymer. The photoacoustic spectroscopy was obtained where the optical absorption spectrum was plotted against photon energy. Other than this, the Fourier Transform Infrared (FTIR) spectra, thermal diffusivity and scanning electron microscope (SEM) diagram were also examined. Generally, it was found that the formula structures before and after protonation were almost similar except the protonated polyaniline exhibited higher thermal diffusivity value.

The final part of the work was mainly on application of the phase shift approach against chopping frequency of the PA technique. The behavior of phase change with sample thickness was investigated. Later, the carrier transport properties of silicon wafer was measured based on the approach. The parameters examined were the surface recombination velocity and diffusion coefficient.

Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia
sebagai memenuhi keperluan untuk ijazah Master Sains

**PENGUKURAN PEKALI RESAPAN TERMA DAN EFFUSIVITI TERMA
UNTUK PEPEJAL DAN CECAIR DENGAN TEKNIK FOTOACOUSTIK**

Oleh

TEH EE PHING

Jun 2001

Pengerusi: Prof. Madya W. Mahmood Mat Yunus, Ph. D.

Fakulti: Sains dan Pengajian Alam Sekitar

Kebolehan teknik fotoakustik dalam pengukuran pekali resapan terma telah menarik minat para penyelidik kebelakangan ini. Dalam kajian ini, teknik fotoakustik sel terbuka (OPC) digunakan untuk pengukuran pekali resapan terma pada bahan pepejal seperti logam, superkonduktor and ferit. Magnitud isyarat fotoakustik telah diukur sebagai fungsi frekuensi termodulasi dan frekuensi kritikal, f_c , setiap sampel dikira. Pekali resapan terma kemudian dapat diperolehi berasaskan pada f_c dan ketebalan sampel. Perubahan nilai pekali resapan terma dengan perubahan ketumpatan pendopan telah pun diselidik. Secara amnya, pekali resapan terma yang dikaji berada dalam julat 0.19 hingga 0.99 cm²/s.

Bahagian kedua dalam kajian ini bertumpu pada bahan cecair. Dengan menggunakan teori asas fotoakustik dan merekabentuk semula sel sampel OPC, nilai effusiviti terma untuk sampel cecair ditentukan. Antara sampel yang dipilih adalah air suling, minyak enjin dan bahan pengguna berbentuk krim. Nilai yang diukur didapati amat mendekati

nilai yang dilaporkan oleh penyelidik sebelum ini. Teknik ini berkemampuan untuk memperoleh effusiviti terma dalam julat 0.042 ke 0.159 $Ws^{1/2}/(cm^2\text{°C})$.

Ketiga, untuk sampel cecair dengan takat pengewapan rendah seperti acetone, metanol dan etanol, teknik PA telah dieksplotasikan untuk pemantauan masa pengewapan. Sampel cecair dimasukkan dalam suatu sel dengan isipadu 13.57 mm^3 dan dipanaskan dengan alur laser 30 mW. Masa pengewapan didapati berkadar songsang dengan takat pengewapan cecair masing-masing.

Bahagian keempat kajian ini bertumpu pada proses pemprotonan sejenis polimer konduktor iaitu *polyanilines*. Spektroskopi fotoakustik telah diperolehi di mana spektrum penyerapan optik telah diplotkan melawan tenaga foton. Selain daripada ini, spectra Infra Merah Fourier Transform (FTIR), pekali resapan terma dan mikroskop pengimbas elektron (SEM) telah juga dikaji. Amnya, telah didapati bahawa struktur formula sebelum dan selepas *protonation* adalah hampir sama melainkan *polyaniline* selepas *protonation* mempunyai pekali resapan terma yang lebih tinggi.

Bahagian terakhir kajian ini mengkaji pendekatan fasa melawan frekuensi dalam teknik PA. Sifat perubahan fasa dengan penukaran ketebalan sampel telah dikaji. Kemudian, sifat angkutan pembawa pada kepingan silikon diukur berdasarkan pendekatan tersebut. Antara parameter yang diselidik termasuklah halaju penyantuman permukaan dan pekali resapan.

ACKNOWLEDGEMENTS

My supervisor, Assoc. Prof. Dr. W. Mahmood Mat Yunus certainly is the first and most important person whom I would like to acknowledge. Thank you for your guidance, help, suggestion and patience throughout the duration of this project. My sincere appreciation also goes to my co-supervisor Prof. Dr. Abdul Halim Shaari and Dr. Zaidan Abdul Wahab for their fruitful discussion and support during my study.

I would like to have this opportunity to acknowledge Dr. Mohd. Maarof Moxsin, Dr. IV Grozescu and Dr. Azmi Zakaria for their advice. I would also like to thank Dr. Senin Hamdan for his help on the DSA usage. Special thanks are also given to Mr. Roslim in the Physics Department for the construction of apparatus.

Along the way, I have been assisted by my seniors and friends who share their knowledge with me. I would particularly like to thank C.Y.J. Fanny, Noorhana Yahya, Tan Thian Khoon, Ling Yoke Ting and lots more to mention.

I gratefully acknowledge the award of the PASCA Scholarship from the Universiti Putra Malaysia, which enable me to undertake this work.

Last but not least is the support and encouragement from my beloved parents and Lee Lee. Their belief and patience have brought this study into success.

TABLE OF CONTENTS

		Page
DEDICATION.....		ii
ABSTRACT.....		iii
ABSTRAK.....		v
ACKNOWLEDGEMENTS.....		vii
APPROVAL.....		viii
DECLARATION.....		x
LIST OF TABLES.....		xiii
LIST OF FIGURES.....		xiv
CHAPTER		
1	INTRODUCTION	
	The Brief Historical Background.....	1
	The Basic Concept of Photoacoustic Effect.....	2
	The Present Work.....	5
2	LITERATURE REVIEW	
	Thermal Diffusivity.....	7
	Thermal Effusivity and Evaporation Time Monitoring of Liquids.....	10
	Photoacoustic Spectroscopy and Polyanilines.....	12
	Semiconductors Phase Behavior.....	15
3	THEORY	
	Introduction.....	18
	Rosencwaig-Gersho Theory.....	18
	The Generation of Photoacoustic Signal.....	22
	The Special Cases.....	24
	Optically Transparent Solids.....	24
	Optically Opaque Solids.....	26
	Modification of the R-G Model.....	28
	Open Photoacoustic Cell.....	29
	Liquid Layer Thickness Effect.....	33
	Application on Thermal Effusivity Measurement.....	35
	Brief Discussion to Conducting Polymer.....	37
	Photoacoustic Spectroscopy.....	38
	Brief Investigation on Semiconductor Transport Properties.....	39
	PA Technique in Transport Properties Measurement of Semiconductor Material.....	41
4	METHODOLOGY	
	Photoacoustic Spectroscopy.....	43
	Optical Source.....	44



	Modulation System.....	46
	Close Photoacoustic Cell.....	47
	Open Photoacoustic Cell.....	48
	The Signal Processing System.....	51
	Experimental Procedure.....	53
	Thermal Diffusivity.....	53
	Thermal Effusivity.....	60
	Data Analysis.....	62
	Evaporation Time Monitoring.....	65
	Photoacoustic Spectroscopy.....	65
	Open Cell Photoacoustic Phase Analysis.....	68
5	RESULTS AND DISCUSSION	
	Introduction.....	70
	Thermal Diffusivity Measurement of Solid by OPC Technique.....	71
	Thermal Diffusivity of Superconductor Ceramic.....	72
	Thermal Diffusivity of Soft Ferrites.....	78
	Thermal Effusivity Measurement on Liquid Samples by PA Technique.....	81
	Evaporation Time Monitoring by PA Technique.....	91
	Investigation on Polyaniline Protonation Effect.....	95
	Brief Discussion on the Polyaniline Protonation Process.....	95
	PAS Investigation.....	96
	Fourier Transform Infrared Spectroscopy Study.....	97
	Thermal Diffusivity Measurement with OPC.....	98
	Silicon Carrier Transport Parameter Analysis with Phase Behavior Approach by OPC Technique.....	105
	Some Simple Theoretical Approach.....	105
	Application in Determining Carrier Transport Parameters.....	106
	The Effect of Sample Thickness.....	107
	Error Analysis.....	110
6	CONCLUSION	
	Thermal Diffusivity Measurement of Solid by OPC Technique.....	111
	Thermal Effusivity Measurement of Liquid Sample by PA Technique.....	112
	Evaporation Time Monitoring by PA Technique.....	112
	Investigation of Polyaniline Protonation Effect by PAS Technique...	112
	Silicon Carrier Transport Parameter Analysis by OPC Technique.....	113
	Suggestion.....	113
	BIBLIOGRAPHY	114
	APPENDICES	119
	VITA	123



LIST OF TABLES

Table		Page
5.1	Thermal diffusivity of $\text{Bi}_2\text{Pb}_{0.6}\text{Sr}_2\text{Ca}_{2-x}\text{M}_x\text{Cu}_3\text{O}_8$ superconductor system ceramic with Sn, V and Y dopants.....	80
5.2	Thermal diffusivity of soft ferrites.....	80
5.3	Thermal effusivity values of liquid samples.....	88
5.4	Solvent evaporation time compared to the boiling point of each sample.....	94
5.5	FTIR spectra of PANI and PANI-HCl.....	98



LIST OF FIGURES

Figure	Page
1.1 Transformation of Photon Energy into Heat and Photoacoustic Signal.....	3
3.1 Schematic Diagram of a Cylindrical Photoacoustic Cell and Sample.....	19
3.2 Schematic Representation of Special Cases for the Photoacoustic Effect in Solids.....	27
3.3 Phenomenon Occuring after Light Absorption in Solid Samples. (a) Thermal Expansion and (b) Thermoelastic Bending.....	28
3.4 Schematic Diagram of the Open Photoacoustic Cell Setup.....	30
3.5 Geometry of Surface Strain due to Thermoelastic Bending.....	32
3.6 Schematic Geometry of the PA Cell.....	35
3.7 General Formula of Emeraldine Base.....	37
3.8 Protonation Process of Emeraldine Base.....	38
3.9 Indirect Generation–recombination Process at Thermal Equilibrium.....	39
4.1 Components of Photoacoustic Spectroscopy.....	43
4.2 Three Basic Components in the Argon Laser System.....	44
4.3 Basic Structure of the Laser Head.....	45
4.4 Mechanical Chopper SR540.....	46
4.5 Monochromator.....	47
4.6 Close Photoacoustic Cell.....	49
4.7 Open Photoacoustic Cell.....	50
4.8 Low-noise Preamplifier SR560.....	51



4.9	Lock-in Amplifier SR530.....	52
4.10	OPC Schematic Experimental Setup.....	54
4.11	Plot of PA Signal Versus Chopping Frequency for Al Sample.....	57
4.12	Plot of ln(PA Signal) Versus ln <i>f</i> for Al Sampel.....	58
4.13	Plot of Chopping Frequency, <i>f_c</i> , Versus $1/(l_s)^2$ for $\text{Bi}_2\text{Pb}_{0.6}\text{Sr}_2\text{Ca}_{2-x}\text{Sn}_x\text{Cu}_3\text{O}_8$	59
4.14	Experimental Setup for Thermal Effusivity Measurement in Liquids.....	61
4.15	PA Cell with the Liquid Sample Holder Attached.....	61
4.16	Plot of PA Siganl Versus Chopping Frequency When the Sample Holder is Empty and Filled with Distilled Water.....	63
4.17	Plot of ln (PA Signal) Versus ln <i>f</i> While the Sample Holder is Empty.....	64
4.18	Plot of ϕ as a Function of 1/ <i>x</i> of Distilled Water Sample.....	64
4.19	The Photoacoustic Spectroscopy (PAS) Schematic Setup.....	66
4.20	8 mm Diameter Pellet Mould.....	67
4.21	Pressing Machine.....	68
5.1	The Plot of PA Signal (Arbitrary Unit) as a Function of Chopping Frequency for Superconductors $\text{Bi}_2\text{Pb}_{0.6}\text{Sr}_2\text{Ca}_{2-x}\text{M}_x\text{Cu}_3\text{O}_8$ (where M=Sn, V, Y;x=0.10).....	72
5.2	Plot of ln(PA signal) Versus ln <i>f</i> for $\text{Bi}_2\text{Pb}_{0.6}\text{Sr}_2\text{Ca}_{2-x}\text{Y}_x\text{Cu}_3\text{O}_8$ (x=0.07).....	73
5.3	Plot of ln(PA Siganl) Versus ln <i>f</i> for $\text{MgO}_{0.30-x}\text{CuO}_{0.20}\text{ZnO}_x\text{Fe}_2\text{O}_3(0.5)$ (x=0.01).....	73
5.4	Thermal Diffusivity as a Function of Composition Parameter x for $\text{Bi}_2\text{Pb}_{0.6}\text{Sr}_2\text{Ca}_{2-x}\text{Sn}_x\text{Cu}_3\text{O}_8$ (x=0.05-0.10).....	76
5.5	Thermal Diffusivity as a Function of Composition Parameter x for $\text{Bi}_2\text{Pb}_{0.6}\text{Sr}_2\text{Ca}_{2-x}\text{V}_x\text{Cu}_3\text{O}_8$ (x=0.05-0.10).....	76



5.6	Thermal Diffusivity as a Function of Composition Parameter x for $\text{Bi}_2\text{Pb}_{0.6}\text{Sr}_2\text{Ca}_{2-x}\text{Y}_x\text{Cu}_3\text{O}_8$ ($x=0.02-0.10$).....	77
5.7	Thermal Diffusivity Versus Mole Fraction x for 3 Series of Superconductors.....	77
5.8	Thermal Diffusivity as a Function of Mole Fraction x for $\text{MgO}_{0.30-x}\text{CuO}_{0.20}\text{ZnO}_x\text{Fe}_2\text{O}_3(0.5-5)$ ($x=0.01-0.08$).....	79
5.9	Thermal Diffusivity as a Function of Mole Fraction x for $\text{MgO}_x\text{ZnO}_{0.5-x}\text{Fe}_2\text{O}_3(0.5-5)$ ($x=0.05-0.40$).....	79
5.10	PA Signal as a Function of Chopper Frequency for Glycerol.....	83
5.11	PA Signal as a Function of Chopper Frequency for Engine Oil.....	83
5.12	PA Signal as a Function of Chopper Frequency for Canola Oil.....	84
5.13	Plot of $\ln(\text{PA Signal})$ as a Function of $\ln(\text{Frequency})$ for Glycerol....	84
5.14	Plot of $\ln(\text{PA Signal})$ as a Function of $\ln(\text{Frequency})$ for Engine Oil.....	85
5.15	Plot of $\ln(\text{PA Signal})$ as a Function of $\ln(\text{Frequency})$ for Canola Oil.....	85
5.16	ϕ as a Function of $1/x$ for Glycerol.....	86
5.17	ϕ as a Function of $1/x$ for Engine Oil.....	86
5.18	ϕ as a Function of $1/x$ for Canola Oil.....	87
5.19	ϕ as a Function of $1/x$ for Various Edible Oil.....	87
5.20	ϕ as a Function of $1/x$ for Various Creamy Samples.....	88
5.21	Thermal Effusivity & Density of Selected Edible Oil.....	90
5.22	Time Dependence of the PA Signal for Acetone Recorded at a 40-Hz Modulation Frequency.....	93
5.23	Time Dependence of the PA Signal for Methanol Recorded at a 40-Hz Modulation Frequency.....	93



5.24	Time Dependence of the PA Signal for Ethanol Recorded at a 40-Hz Modulation Frequency.....	94
5.25	PA Signal as a Function of Wavelength for Emeraldine Base at 60 Hz Chopping Frequency.....	99
5.26	PA Signal as a Function of Wavelength for Carbon Black at 60 Hz Chopping Frequency.....	99
5.27	Normalized PA Signal as a Function of Wavelength for Emeraldine Base at 60 Hz Chopping Frequency.....	100
5.28	PA Signal Intensity as a Function of Photon Energy for Emeraldine Base.....	100
5.29	PA Signal Intensity as a Function of Photon Energy at Different Chopping Frequency for Emeraldine Base.....	101
5.30	PA Signal Intensity as a Function of Photon Energy at Different Chopping Frequency for Emeraldine Salt.....	101
5.31	Infrared Transmission of Emeraldine Base as a Function of Wavenumber.....	102
5.32	Infrared Transmission of Emeraldine Salt as a Function of Wavenumber.....	102
5.33	ln(PA Signal) Versus ln(Frequency) for Emeraldine Base Sample with Thickness 0.190 mm.....	103
5.34	ln(PA Signal) Versus ln(Frequency) for Emeraldine Base Sample with Thickness 0.235 mm.....	103
5.35	ln(PA Signal) Versus ln(Frequency) for Emeraldine Base Sample with Thickness (a) 0.400 mm; (b) 0.450 mm; (c) 0.500 mm.....	104
5.36	Theoretical PA Phase Angle Versus Chopping Frequency at Different Recombination Velocity.....	108
5.37	Breaking Frequency Versus Recombination Velocity at Different Recombination Lifetime.....	108
5.38	Phase Angle Versus Chopping Frequency for Si Wafer. Solid Line Represents the Fitted Curve.....	109



5.39	Phase Angle as a Function of Chopping Frequency for PS-RS Finishing Si Wafer with Different Thickness.....	109
5.40	Phase Angle as a Function of Chopping Frequency for PS-PS Finishing Si Wafer with Different Thickness.....	110



CHAPTER 1

INTRODUCTION

The Brief Historical Background

The photoacoustic effect and spectroscopy concept as cited by Wood (1992) were based on the first reported publication by the Alexander Graham Bell in the year of 1880. He placed a sample in an air filled cell and he observed that when a beam of modulated sunlight shinning onto a sample surface, a sound could be heard through a hearing tube attached to the cell. After Bell, no significant progress was found in the photoacoustic field until 1970, the photoacoustic and photothermal research again gained interest due to the invention of some advanced scientific apparatus. Improvement in such apparatus enabled detection with higher signal-to-noise ratio and therefore increased the sensitivity of the experiments. Three major improvement were:

1. The development of intense light sources; such as lasers, dye lasers and high pressure arc lamps, such as xenon lamps.
2. The development of sensitive detection equipment; such as condenser and electret microphones and piezoelectric detectors.
3. The development of more sensitive signal processing equipment; such as filters, phase sensitive detectors and lock-in amplifiers.

The first known use of a laser to be the light source in photoacoustic as cited by Wood. (1992) was in 1968, by Kerr and Attwood. They applied it in a gas photoacoustic

system. This system was later developed by other research groups. Kreuzer and Patel (1971) and Goldan and Goto (1974) improved the signal to noise ratio obtained from a gas phase PA cell by developing a multi-pass cell. Later, Kreuzer et al. (1972) applied this system into practical problem such as the detection of atmospheric pollutants. One of the most renowned theory for photoacoustic spectra for solid sample was then published by Rosencwaig in 1973. Three years later, Rosencwaig and Gersho (1976) published the famous 1-dimentional theory, known as the R-G theory which has served as the basis of most of other theories on microphonic photoacoustic detection for a solid sample.

The Basic Concept of Photoacoustic Effect

The basic concept of the photoacoustic effect is that a sample is placed in an enclosed cell which is filled with a gas. The sample is then heated with a periodically modulated heating source. A microphone placed in the cell detects the pressure variations in the gas which are caused by periodic heat flow from the sample to the gas.

By examining the effect in detail, the absorption of photons by the molecules of a gas sample may induce a large variety of effects. The excited level may lose its energy by radiation processes, such as spontaneous or stimulated emission, and by radiationless collisional deactivation, which always channels at least part of the absorbed energy into the translational degrees of freedom. If the excitation energy is high enough, direct photochemical decomposition of the excited molecule can be achieved. In the case of fundamental vibration excitation, radiative emission and chemical reactions do not play

an important role, because the radiative lifetime of vibrational levels is long compared with the time needed for collisional deactivation at ordinary pressures and the photon energy is too small to induce reactions. However, in the case of multiphoton and electronic excitation, chemical reaction processes may compete efficiently with collisional deactivation. This may also be true for the emission of radiation from electronic levels. These competing processes are illustrated in Figure 1.1.

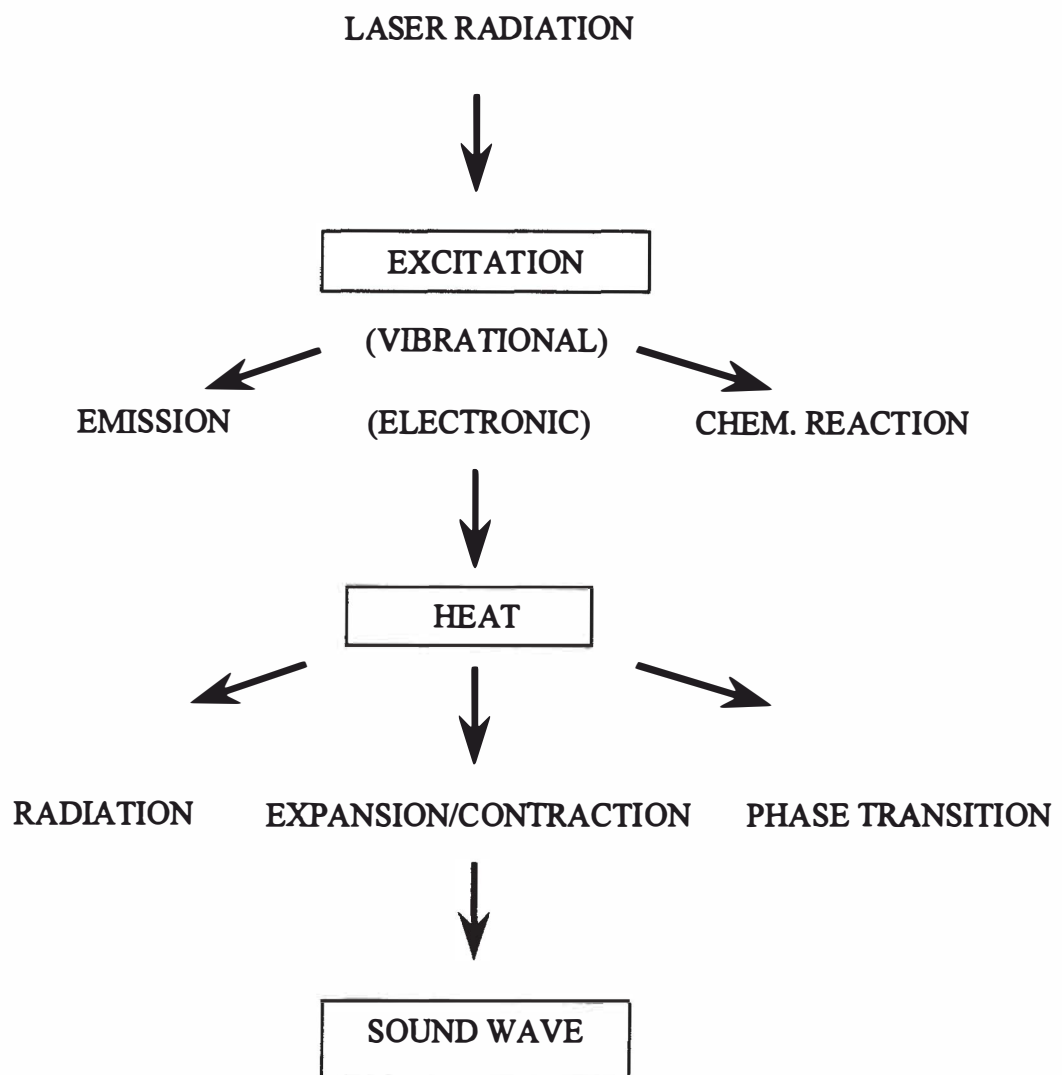


Figure 1.1: Transformation of Photon Energy into Heat and Photoacoustic Signal.

The photoacoustic spectroscopy or PAS is different than the conventional techniques in the sense that the earlier technique measured the energy absorbed by the material as a result of its interaction with the photon beam. There are several advantages of photoacoustics as a form of spectroscopy. Since absorption of modulated optical and electromagnetic radiation is required before a photoacoustic signal can be generated, light that is transmitted or elastically scattered by the sample is not detected and therefore does not interfere with the inherently absorptive PAS measurements. The insensitivity to scattered radiation also permits investigation on optical absorption data on highly light-scattering materials such as powders, amorphous solids and gels. Secondly, it is capable on obtaining optical absorption spectra on completely opaque to light-transmitted materials since the technique does not depend on the detection of the photons. Thirdly, it is capable in performing nondestructive depth-profile analysis of absorption as a function of depth into a material. As the result, photoacoustic has already found many important applications in the research and characterization of the materials. Photoacoustic studies are performed on all types of materials, inorganic, organic and biological on all the three matter states which includes gas, liquid, and solid. Listed below are some other attractive features of the photoacoustic spectroscopy:

1. Requires minimal sample preparation.
2. Application on broad range of material such as gases, liquids, solids, powders, gel, thin film and etc.
3. Application on wide range of photothermal detection methods.
4. It is always a non-destructive method.

The Present Work

For the present work, two different photothermal techniques i.e. open photoacoustic cell and closed photoacoustic cell were used to investigate the thermal properties of solid and liquid materials. Other than thermal characterization, application on optical absorption spectra for conducting polymer and carrier transport parameter of semiconductor was also done. The objective of each different experiment is summarized as below:

1. To measure the thermal diffusivity value of various solid samples by using the open photoacoustic cell (OPC) technique. The thermal diffusivity, α , is defined as $\alpha = \frac{k}{\rho c}$, where k is the thermal conductivity, ρ is the density and c is the specific heat at a constant pressure. The measurement were performed on aluminium, superconductor materials($\text{Bi}_2\text{Pb}_{0.6}\text{Sr}_2\text{Ca}_{2-x}\text{M}_x\text{Cu}_3\text{O}_8$; $M= \text{Sn}, \text{V}$ and Y) and soft ferrites ($\text{MgO}_{0.30-x}\text{CuO}_{0.20}\text{ZnO}_x\text{Fe}_2\text{O}_{3(0.5)}$ and $\text{MgO}_x\text{ZnO}_{0.5-x}\text{Fe}_2\text{O}_{3(0.5-\delta)}$).
2. To measure thermal effusivity values of various liquid samples by photoacoustic technique. Thermal effusivity is an important thermophysical property, defined as $e=(k\rho c)^{1/2}$. It could also be related with the thermal diffusivity with the expression $e = k/\sqrt{\alpha}$. It measures the sample's ability to exchange heat with the environment. The samples measured including distilled water, glycerol, engine oil, lubricant, various edible oil and creamy samples.

3. To monitor liquid evaporation time by photoacoustic technique. The samples used were solvent such as acetone, methanol and ethanol.

4. To investigate optical absorption spectra of polyanilines. The spectra before and after the process of protonation were captured applying photoacoustic spectroscopy (PAS). The FTIR spectroscopy spectrum and the thermal diffusivity values were also analyzed.

5. To obtain carrier transport parameters of Si semiconductor using OPC technique. The surface recombination velocity and diffusion coefficient of silicon wafer were obtained using this technique.