



UNIVERSITI PUTRA MALAYSIA

**SYNTHESIS AND CHARACTERISATION OF VANADIUM ANTIMONY
OXIDE CATALYSTS**

ITA JONG YEE PING

FSAS 2002 13

**SYNTHESIS AND CHARACTERISATION OF VANADIUM ANTIMONY
OXIDE CATALYSTS**

By

ITA JONG YEE PING

**Thesis Submitted to the School of Graduate Studies, Universiti Putra Malaysia, in
Fulfilment of the Requirement for the Degree of Master of Science**

March 2002



Dedicated to my beloved family and friends.



Abstract of thesis presented to the Senate of Universiti Putra Malaysia in fulfilment of the requirement for the degree of Master of Science

SYNTHESIS AND CHARACTERISATION OF VANADIUM ANTIMONY OXIDE CATALYSTS

By

ITA JONG YEE PING

March 2002

Chairman: Taufiq Yap Yun Hin, Ph.D.

Faculty: Science and Environmental Studies

V-Sb-oxide catalysts are commercially viable catalysts for the ammoxidation of propane to acrylonitrile, a novel and considerable cost saving route compared to the current industrial method which utilizes the ammoxidation of propene. The characteristic of V-Sb-oxide catalysts were studied and analyzed in relation to their structural/composition features using X-ray diffraction (XRD), Fourier Transform Infrared (FTIR), Brunauer-Emmett-Teller (BET) surface area, Scanning Electron Micrograph (SEM), Energy Dispersive X-ray (EDX) microanalysis and Thermogravimetric Analysis (TGA). Results showed significant difference in presence of crystalline phases, surface area, porosity and morphologies in the samples prepared according to three different methods, i.e. solid state (SS) reaction, sol-gel (GS) and deposition on antimonite acid (DAA) methods, as a function of the Sb:V ratio and heat treatment. XRD and FTIR studies revealed that the calcination temperature at 500 °C is not suitable for the V-Sb-oxide catalysts as there is little or no VSbO₄ formed in some samples. Sb/V ratio of 2 or more is recommended for the GS method as there is hardly any Sb species formed for samples



with Sb/V ratio = 1. For the SS method, sample calcined at 700 °C with Sb/V ratio = 1 would be deemed the best as it has the highest amount of VSbO₄. Raising of calcination temperature had a detrimental effect on the surface area of the GS and DAA catalysts but bore no significant effect on SS catalysts. The EDX microanalysis showed antimony enrichment on the surface the catalysts. The study of TPD revealed the evolution of lattice oxygen from the catalysts. In TPR, the amount of oxygen desorbed from the catalysts prepared by SS method is found to be much higher compared to the other methods, i.e. about 16.7 times higher than GS method and 6.3 times higher than DAA method (for Sb/V = 1) whilst for ratio 3, it is 21.3 times higher than GS method and 14.5 times higher than DAA method.



Abstrak tesis yang dikemukakan kepada Senat Universiti Putra Malaysia sebagai memenuhi keperluan untuk ijazah Master Sains

SINTESIS DAN PENCIRIAN MANGKIN VANADIUM ANTIMONI OKSIDA

Oleh

ITA JONG YEE PING

Mac 2002

Pengerusi: Taufiq Yap Yun Hin, Ph.D.

Fakulti: Sains and Pengajian Alam Sekitar

Mangkin V-Sb-oksida adalah mangkin yang mempunyai potensi yang baik dalam pasaran untuk proses pengammoksidan propena kepada akrilonitril. Ia adalah lebih ekonomi berbanding dengan penggunaan propena dalam proses tersebut. Ciri-ciri mangkin V-Sb-oksida dikaji and dianalisis struktur dan komposisinya dengan menggunakan teknik seperti pembelauan sinaran-X, spektroskopi inframerah, teknik Brunauer-Emmett-Teller, mikroskopi elektron pengimbas, mikroanalisis tenaga penyebaran sinaran-X dan analisis termogravimetri. Hasil kajian menunjukkan perbezaan dalam fasa kristal, luas permukaan, keliangan dan morfologi dalam mangkin-mangkin tersebut yang disediakan berdasarkan tiga cara berlainan, iaitu, tindakbalas keadaan pepejal (SS), sol-gel (GS) dan pemendakan ke atas asid antimonik (DAA), dengan pembedaan dalam fungsi Sb:V and tindakan haba. Daripada kajian menggunakan teknik pembelauan sinaran-X serta spektroskopi inframerah, didapati tindakan haba pada 500 °C tidak sesuai untuk mangkin V-Sb-oksida kerana sedikit atau tiada $VSbO_4$ terbentuk dalam sampel-sampel. Sb/V sama atau lebih besar daripada 2 adalah baik untuk teknik GS kerana hampir tiada Sb yang terbentuk dalam sampel untuk Sb/V = 1. Untuk teknik SS,

sampel yang ditindakkan haba pada 700 °C dengan $Sb/V = 1$ dijangka terbaik kerana terdapat jumlah terbesar $VSbO_4$. Peningkatan dalam suhu tindakan haba memberi kesan negatif ke atas luas permukaan mangkin tetapi tidak memberi kesan yang ketara ke atas mangkin SS. Mikroanalisis tenaga penyebaran sinaran-X pula menunjukkan perkayaan unsur antimoni pada permukaan mangkin. Kajian Penyaherapan berprogram suhu (TPD) untuk oksigen menunjukkan pembebasan oksigen kekisi dari mangkin. Dalam kajian Penurunan berprogram suhu (TPR) dalam hydrogen, jumlah oksigen yang ternyaherap dari mangkin yang disediakan melalui teknik SS adalah lebih besar berbanding mangkin-mangkin teknik lain, iaitu hampir 16.7 kali lebih besar berbanding mangkin teknik GS dan 6.3 kali lebih besar berbanding mangkin teknik DAA (untuk $Sb/V = 1$) manakala untuk $Sb/V = 3$, ia adalah 21.3 kali lebih besar daripada mangkin teknik GS dan 14.5 kali lebih besar berbanding mangkin teknik DAA.

ACKNOWLEDGEMENTS

The author would like to express her gratitude towards those who had helped her throughout the project especially her supervisor, Dr. Taufiq Yap Yun Hin, for his guidance, technical advice, tremendous patience and unlimited help. She would also like to thank her co-supervisors Associate Professor Dr. Mohd. Zobir Hussein and Associate Professor Dr. Zulkarnain Zainal.

She is grateful for the help and invaluable advice given by Dr. Rusnah Samsuddin on her project and to a host of people who had helped her through this study: Dr. Amir Khadum (GC, UKM), Encik Zaimi Naim (ASAP and catalytic test, Petronas), Cik Shamsina (Petronas), Puan Mona (GC, Petronas), Mr. Siew (GC, UM), Encik Kamal (TGA), Puan Rosnah (FTIR), Encik Azhari (XRD, UKM), Cik Suleika (SEM), Cik Azilah (SEM), Mr. Ho (SEM), Puan Siti Selina (SEM and EDX), Encik Narzari (chemicals), Dr. Luca Lucarelli (TPD and TPR, ThermoFinnigan, Italy) and laboratory mates (Kak Feez, Rodhy, Suhaimi, Ming Hong, Won Ying, Tian Hai, Kim Nee, Chee Kheong, Leong, Kian Peng, Wooi Keat, Poh Li and Ei Bee).

Last but not least, she would like to dedicate this project to her family members and friends for their prayers, love and moral support.



DECLARATION

I hereby declare that the thesis is based on my original work except for quotations and citations which have been duly acknowledged. I also declare that it has not been previously or concurrently submitted for any other degree at UPM or other institutions.

ITA JONG YEE PING

Date: 9 March 2002

TABLE OF CONTENTS

	Page
DEDICATION	ii
ABSTRACT	iii
ABSTRAK	v
ACKNOWLEDGEMENTS	vii
APPROVAL SHEETS	viii
LIST OF TABLES	xiii
LIST OF FIGURES	xiv
LIST OF ABBREVIATIONS	xvi
CHAPTER	
1 INTRODUCTION	1
Acrylonitrile	4
Production of Acrylonitrile	6
What about Propane as Feedstock?	7
Acrylonitrile Production via Propane Ammoxidation Route	7
Vanadium Antimony Oxide (V-Sb-O) Catalyst	8
The Catalytic Pathway of the Ammoxidation of Propane	10
Literature Review	12
Preparation Methods	12
Non-stoichiometry of Rutile-type Vanadium Antimonate	16
Role of Vanadium Species	17
Role of Antimony Species	20
Role of Non-stoichiometry of Vanadium Antimonate	20
Objectives of the Study	22
2 METHODOLOGY	23
Materials	23
Synthesis of the precursors	23
Deposition on Antimonic Acid (DAA) Method	24
Gel-Solid (GS) Method	25
Solid State Reaction (SS) Method	25
Calcination of the catalysts	25
Catalyst Characterisation	27
Powder X-Ray Diffraction (XRD) Analysis	27
Fourier Transform Infra-Red (FTIR)	27
Surface Area and Porosity Analysis (ASAP)	28
Scanning Electron Micrograph (SEM)	28
Energy Dispersive X-ray Microanalysis	28
Thermogravimetric Analysis (TGA)	29
Temperature-Programmed Desorption (TPD) of Oxygen	29



	Temperature-Programmed Reduction (TPR) in Hydrogen	30
3	RESULTS AND DISCUSSION	32
	X-Ray Diffraction (XRD) and Fourier Transform Infra-Red (FTIR) Analysis	32
	SS Method	32
	DAA Method	33
	GS Method	34
	Effect of Calcination Temperature	35
	Effect of Sb/V Ratio	36
	Surface Area and Porosity	43
	Surface Area	43
	Adsorption-desorption Hysteresis	49
	Scanning Electron Micrograph (SEM)	52
	Energy Dispersive X-ray Microanalysis	58
	SS Method	58
	DAA Method	58
	GS Method	58
	Thermogravimetric Analysis (TGA)	64
	SS Method	64
	DAA Method	66
	GS Method	68
	Temperature-Programmed Desorption (TPD) of Oxygen	71
	Temperature-Programmed Reduction (TPR) in Hydrogen	77
4	CONCLUSION	83
	REFERENCES/BIBLIOGRAPHY	85
	APPENDICES	90
	VITA	106



LIST OF TABLES

Table		Page
1	Common oxide-catalyzed selective oxidation reactions	3
2	A summary of usage of acrylonitrile	5
3	Phases detected by XRD and FTIR analysis on the V-Sb-Oxide catalysts	35
4	BET surface area and average pore diameter of VSbO catalysts prepared by various methods	44
5	Comparison with some surface area values from Centi <i>et al.</i> 's work	45
6	Sb/V ratio on surface of VSbO catalysts obtained by energy dispersive x-ray microanalysis	60
7	Summary of Percentage Weight Gain/Loss for the SS catalysts	65
8	Summary of Percentage Weight Gain/Loss for the DAA catalysts	67
9	Summary of Percentage Weight Gain/Loss for the GS catalysts	69
10	Amount of Oxygen Desorbed and Desorption Activation Energies Obtained by Temperature-Programmed Desorption from V-Sb-Oxide catalysts	73
11	Total Number of Oxygen Atoms Removed from the V-Sb-Oxide Catalyst by Reduction in H ₂ /Ar	79



LIST OF FIGURES

Figure		Page
1	Kinetic reaction network for propane ammoxidation	11
2	XRD patterns of VSbO catalysts prepared by using SS method	37
3	XRD patterns of VSbO catalysts prepared by using DAA method	38
4	XRD patterns of VSbO catalysts prepared by using GS method	39
5	FTIR spectra of the V-Sb-Oxide catalysts prepared by using the SS method	40
6	FTIR spectra of the V-Sb-Oxide catalysts prepared by using the DAA method	41
7	FTIR spectra of the V-Sb-Oxide catalysts prepared by using the GS method	42
8	Surface areas of the VSbO catalysts prepared by the SS method at calcination temperatures of (a) 500 °C, (b) 600 °C and (c) 700 °C	47
9	Surface areas of the VSbO catalysts prepared by the DAA method at calcination temperatures of (a) 500 °C, (b) 600 °C and (c) 700 °C	48
10	Surface areas of the VSbO catalysts prepared by the GS method at calcination temperatures of (a) 500 °C, (b) 600 °C and (c) 700 °C	49
11	G16 (GS method, Sb/V ratio 1, 600 °C calcination temperature) × 450 magnification	54
12	G16 (GS method, Sb/V ratio 1, 600 °C calcination temperature) × 20,000 magnification	55
13	D27 (DAA method, Sb/V ratio 2, 700 °C calcination temperature) × 12,000 magnification	55
14	S26 (SS method, Sb/V ratio 2, 600 °C calcination temperature) × 12,000 magnification	56



15	G36 (GS method, Sb/V ratio 3, 600 °C calcination temperature) ×200 magnification	56
16	G35 (GS method, Sb/V ratio 3, 500 °C calcination temperature) ×6,000 magnification	57
17	G37 (GS method, Sb/V ratio 3, 700 °C calcination temperature) ×5,000 magnification	57
18	Bar graph of EDX microanalysis results showing Sb/V ratio on surface of VSbO catalysts prepared by SS method	61
19	Bar graph of EDX microanalysis results showing Sb/V ratio on surface of VSbO catalysts prepared by DAA method	62
20	Bar graph of EDX microanalysis results showing Sb/V ratio on surface of VSbO catalysts prepared by GS method	63
21	TGA curves showing common stages of weight loss for SS catalysts, i.e. at (a) 545-625 °C, (b) 660-845 °C and (c) 845 °C onwards	66
22	TGA curves showing common stages of weight loss of DAA catalysts, i.e. at (a) 750-800 °C for Sb/V ratio 3 and (b) <i>ca</i> 825 °C onwards for all samples, and onset temperatures (--) of the first sharp drop in weight	68
23	TGA curves showing common stages of weight loss for GS catalysts, i.e. at (a) 575-765 °C, (b) 765-855 °C, (c) 855 °C onwards and (d) 430-765 °C	70
24	Oxygen TPD spectra of the VSbO catalysts	74
25	Bar graph showing amount of oxygen desorbed from the VSbO catalysts	75
26	Oxygen TPR spectra of the VSbO catalysts	80
27	Bar graph showing amount of oxygen desorbed from the VSbO catalysts	81



LIST OF ABBREVIATIONS

ASAP	Analysis of Surface Area and Porosity
DAA	Deposition on Antimonic Acid Method
E_d	Desorption activation energy
EDX	Energy Dispersive X-ray Microanalysis
E_r	Reduction activation energy
FID	Flame ionization detector
FTIR	Fourier Transform Infra-Red
GS	Gel-Solid Method
JCPDS	Joint Committee on Powder Diffraction Standards
MS	Mass spectroscopy
OFN	Oxygen free nitrogen
SEM	Scanning Electron Micrograph
SS	Solid State Reaction Method
STP	Standard temperature and pressure
TCD	Thermal conductivity detector
TGA	Thermogravimetric Analysis
TPD	Temperature-Programmed Desorption of Oxygen
TPR	Temperature-Programmed Reduction in Hydrogen
VSbO	Vanadium Antimony Oxide
XRD	Powder X-Ray Diffraction Analysis



CHAPTER 1

INTRODUCTION

Selective catalytic oxidation and ammoxidation processes of hydrocarbons comprise approximately one quarter of the value produced by all catalytic processes worldwide. They contribute hence significantly to the gross national product of industrial countries and afford future opportunities for developing countries [1]. Oxidation processes are defined as conversions of compounds under the influence of various oxidizing agents. There are two types of oxidation, i.e. complete and partial oxidation. Complete oxidation is an undesirable side process in organic synthesis which leads to the formation of CO, CO₂ and H₂O, whereas partial oxidation processes involves usage of air or oxygen in the manufacture of chemicals [2].

Oxidation reactions are made much more selective in nature by means of a catalyst that lowers the activation energy for the selected process and provides a facile path by which useful products can form. There are three categories of catalysts for oxidation reactions, i.e. transition metal oxides in which oxygen is readily transferred to and from the structure, metals onto which oxygen is chemisorbed, and metal oxides in which the active species is chemisorbed oxygen, as molecules or atoms [2].

There are two types of selective oxidation reactions. Firstly, the dehydrogenation reactions, in which a hydrocarbon molecule is converted into a more unsaturated




hydrocarbon by the breaking of C-H bonds and forming of C=C bonds. Secondly, the dehydrogenation and oxygen insertion, in which oxygen is needed as an oxidant for the incorporation into the hydrocarbon molecules and in the formation of water in the dehydrogenation steps. In general, the C-H bonds are broken and C-O bonds are formed [3].

Selective oxidation often requires catalysts of a more complex nature. Theoretically, a metal could be used for the catalysis process but it would not be favourable if high temperature is needed as the hydrocarbon is often unstable and might decompose completely. A successful process can only result if the thermodynamics allow the use of a somewhat lower temperature for favourable reaction to take place. It is of paramount importance to find catalysts that can conduct the catalysis reaction selectively, i.e. without giving deep oxidation at the same time. In the oxidation of hydrocarbons by incorporation of one or more oxygen atoms, it is usually important to preserve the original unsaturation, and to activate one of the carbon-hydrogen bonds instead [4].

The first major breakthrough in the search for an acceptable catalyst for selective oxidation occurred in the late 1950s when it was discovered in the Sohio laboratories that a compound oxide, namely bismuth molybdate, showed an acceptably high selectivity in the oxidation of propene to acrolein [4]:



This was soon followed by an even more important finding that propene could be oxidized in the presence of ammonia in a one-step ammoxidation to give acrylonitrile:



Some of the common oxide-catalyzed selective oxidation reactions can be seen in Table 1 [3]:

Table 1: Common oxide-catalyzed selective oxidation reactions

Reactions	Catalysts
1. Dehydrogenation	
ethylbenzene → styrene	V-Ti-O
isopentane, isopentene → isoprene	Sn-Sb-O
Butane, butene → butadiene	Bi-Mo-O, promoted Fe-O, promoted V-O
Methanol → formaldehyde	Fe-Mo-O, MoO ₃
2. Dehydrogenation and Oxygen Insertion	
Butane, butene → maleic anhydride	V-P-O
Propene → acrolein (Propene and NH ₃ → acetonitrile)	Bi-Mo-O Bi-Mo-O, U-Sb-O, Fe-Sb-O, Bi-Sb-Mo-O
methane → methanol, formaldehyde	Mo-O, V-O
ethylene → ethylene oxide	Fe-Mo-O
methyl ethyl ketone → acetaldehyde, acetic acid	V-Mo-O

Due to the global abundance of liquefied petroleum gas (LPG), interest in the potential of light alkanes as sources in selective oxidation to their corresponding useful products is increasing. Among these is the partial oxidation and ammoxidation of propane to acrylonitrile.

Acrylonitrile

Acrylonitrile is commodity chemical used throughout the world to make acrylic fibers for shirts, socks, sweaters, carpets, blankets; plastics for computers, telephones, refrigerators, food packaging and cars; nitrile rubber for automotive tyres, hoses and belts; and a variety of specialty products. About 95 % of the world's production of acrylonitrile uses the BP Amoco Chemicals process [5]. Fabrics account for the large percentage of acrylonitrile end uses (Table 2). Acrylic fibers are a popular substitute for cotton and wool and are used to make carpeting, blankets and especially clothing. Rugged, durable acrylonitrile-butadiene-styrene (ABS) plastics, derived from acrylonitrile, are chosen for telephones, computer and television, housings, sports equipment and molded automobile parts. Oil resistant nitrile rubber, made from acrylonitrile, is used for hoses at gasoline service stations and in automobiles, trucks and buses. BP Amoco Chemical's scientists recover co-products generated by the acrylo process. These co-products, previously treated as unusable wastes, are now used by manufacturers to make household detergents and shampoos, dyes, plastics and pharmaceuticals, including life-saving insulin for diabetics and many other products [5].



Table 2: A summary of usage of acrylonitrile [5]

Usage	Percentage
Co-monomer for acrylic and modacrylic fibers	51 %
Co-monomer for acrylonitrile-butadiene-styrene resins	18 %
Chemical intermediate for adiponitrile	13 %
Chemical intermediate for acrylamide	6 %
Co-monomer for nitrile elastomers	3 %
Co-monomer for Styrene-Acrylonitrile resins	2 %
Other uses	7 %


Acrylonitrile capacity amounted to 10.0 billion pounds as of 1st January, 1995 [7]. The growth of its demand was 2.2 % per year. The expectant growth was projected to be 2 % per year through 2001 [8].

World acrylonitrile consumption is largely dependent on demand for acrylic fibers, especially in Asia and Europe, where acrylic fibers account for 50 % of consumption. In contrast, acrylic fibers account only for 25 % of acrylonitrile demand in the United States. Combined, acrylonitrile-butadiene-styrene (ABS) and styrene-acrylonitrile (SAN) resins account for 24 % of world consumption of acrylonitrile, although in Asia they account for 34 % of demand. Acrylamide accounts for most of the growth in the 'other' category. Future demand growth for acrylonitrile will come mainly from acrylic fibers (Asia and Eastern Europe), ABS/SAN (Asia) and acrylamide (all regions) [9].

In the long term, developing Asian countries possess the best conditions for continued growth of acrylonitrile consumption. Taiwan, China and India will continue to be short of acrylonitrile requirements for at least the next 5 years and will continue to rely on imports to satisfy demand, mainly for acrylic fiber production. Additionally, as production of ABS/SAN resins continues its shift to Asia, demand for acrylonitrile for this application will grow at robust rates. Demand for acrylonitrile in Eastern Europe is forecasted to grow aggressively, due mainly to healthier utilization rates at existing acrylic fiber plants after years of negative growth and low utilization rates [9].

Production of Acrylonitrile

Over 90 % of world acrylonitrile is produced by using the SOHIO Acrylonitrile Process [7]. This process is based on vapour phase catalytic air oxidation of propene and ammonia, known as ammoxidation, in a fluid bed reactor [10].

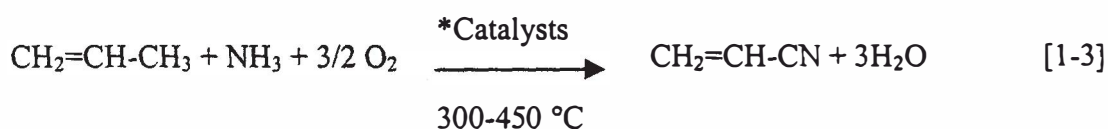

*Catalysts: $\text{BiO}_2 \cdot n\text{MoO}_3$ ($n = 1, 2, 3$)
 $\text{USb}_3\text{O}_{10}$
 $\text{Fe}_2\text{O}_3/\text{Sb}_2\text{O}_4$
 $\text{Bi}/\text{Mo}/\text{O}_x$ multicomponent systems



What about Propane as Feedstock?

The difference between propane and propene prices, i.e. 3 - 15 cents a pound, is the reason behind the interest in developing technology to use propane instead of propene as feedstock. The use of this technology appears to be most promising in the Far East where propane is more readily available than propene [11].

Acrylonitrile Production via Propane Ammoxidation Route

When considering the selective catalytic oxidation of propane into oxygenates, two main difficulties arise. The first one is, as for the partial oxidation of other light alkanes, the lower reactivity of the reactant as compared to that of the formed products. Activation of the reactant needs operating conditions (temperature as high as 500 °C for example) which are detrimental to the stability of the product. Therefore, the considered reaction requires catalysts with specific properties: activation of propane partial oxidation and decrease or inhibition of the product oxidation. The second difficulty is to design suitable catalysts because little is known about the involved reaction mechanisms [12].



It was found that two main classes of catalysts give the best results:

- Systems based on antimonate rutile structure and containing V as the key element [13, 14];
- Systems based on the Bi-Mo-V scheelite structure [15].

Fe-antimonate containing excess Sb-oxide and $\text{SnO}_2\text{-Sn}_2\text{O}_x$ are known system for propene ammoxidation [16] but they show poor activity/selectivity for propane ammoxidation [17]. Other catalysts studied included Ga antimonate [18], Ag-doped bismuth vanadomolybdate [19], V-silicate and V-aluminium phosphate [20] and vanadyl pyrophosphate [17]. Best performance is obtained using V-antimonate systems which contain excess Sb-oxide [21]. The first patent reports selectivity in acrylonitrile of approximately 60 % [22].

In 1988, Standard Oil (now BP America) published 5 key patents on V-Sb-O based catalyst, reporting much better yields and productivities in acrylonitrile from propane. In 1996, BP Amoco started off a demo unit for production of acrylonitrile using propane in its plant in Green Lake, USA. The process is said to cut cost by at least 20 % [23].

Vanadium Antimony Oxide (V-Sb-O) Catalyst

The phase composition of V-Sb-oxide catalysts depends on four main factors: (i) method of preparation, (ii) temperature, (iii) gas phase composition during the thermal treatment, (iv) Sb/V atomic ratio [24].

